

## Author Manuscript

**Title:** Multimetal-Substituted Epsilon-Iron Oxide  $\epsilon$ -Ga<sub>0.31</sub>Ti<sub>0.05</sub>Co<sub>0.05</sub>Fe<sub>1.59</sub>O<sub>3</sub> for Next Generation Magnetic Recording Tape in the Big Data Era

**Authors:** Shin-ichi Ohkoshi; Asuka Namai; Marie Yoshikiyo; Kenta Imoto; Kazunori Tamazaki; Koji Matsuno; Osamu Inoue; Tsutomu Ide; Kenji Masada; Masahiro Goto; Takashi Goto; Takayuki Yoshida; Tatsuro Miyazaki

This is the author manuscript accepted for publication and has undergone full peer review but has not been through the copyediting, typesetting, pagination and proofreading process, which may lead to differences between this version and the Version of Record.

**To be cited as:** 10.1002/anie.201604647

**Link to VoR:** <http://dx.doi.org/10.1002/anie.201604647>

# Multimetal-Substituted Epsilon-Iron Oxide $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$ for Next Generation Magnetic Recording Tape in the Big Data Era

Shin-ichi Ohkoshi,<sup>\*[a]</sup> Asuka Namai,<sup>[a]</sup> Marie Yoshikiyo,<sup>[a]</sup> Kenta Imoto,<sup>[a]</sup> Kazunori Tamazaki,<sup>[b]</sup> Koji Matsuno,<sup>[b]</sup> Osamu Inoue,<sup>[b]</sup> Tsutomu Ide,<sup>[b]</sup> Kenji Masada,<sup>[c]</sup> Masahiro Goto,<sup>[c]</sup> Takashi Goto,<sup>[c]</sup> Takayuki Yoshida,<sup>[c]</sup> and Tatsuro Miyazaki<sup>[c]</sup>

**Abstract:** From the viewpoints of large capacity, long-term guarantee, and low cost, magnetic recording tapes have drawn revival attention as archive storage media for big data. In fact, they are used in data centers for insurance, broadcasting, and cloud. In the present work, we prepared a new series of metal-substituted  $\epsilon\text{-Fe}_2\text{O}_3$ ,  $\epsilon\text{-Ga}_{0.31}^{\text{III}}\text{Ti}_{0.05}^{\text{IV}}\text{Co}_{0.05}^{\text{II}}\text{Fe}_{1.59}^{\text{III}}\text{O}_3$ , with an average size of 18 nm. Ga, Ti, and Co cations tune the magnetic properties of  $\epsilon\text{-Fe}_2\text{O}_3$  to the demanded specifications for a magnetic recording tape. The coercive field was tuned to 2.7 kOe by introduction of single-ion anisotropy on  $\text{Co}^{\text{II}}$  ( $S = 3/2$ ) along the  $c$ -axis. The saturation magnetization was increased by 44% with  $\text{Ga}^{\text{III}}$  ( $S = 0$ ) and  $\text{Ti}^{\text{IV}}$  ( $S = 0$ ) substitution through the enhancement of positive sublattice magnetizations. The magnetic tape media was also fabricated using the actual production line. This magnetic tape showed a very sharp signal response and a remarkably high signal-to-noise ratio compared to the presently used magnetic tape, and therefore, this series of material is useful for magnetic tape storage in the next generation.

To achieve high-density magnetic recording media, the magnetic particles must be downsized.<sup>[1–5]</sup> Magnetic recording tapes are expected to play an important role in the big data era due to their long-term guarantee and low cost.<sup>[6–8]</sup> Magnetic recording tapes are now used for data archiving in insurance companies, banks, broadcasters, and web services. In the current market, spindle-shaped cobalt-iron alloy nanoparticle is the main magnetic material in recording tapes, but downsizing this alloy is difficult due to its pyrophoric character and the disappearance of its magnetic ordering. Recently, barium ferrite has also started to be used. In 2004, a single phase of  $\epsilon\text{-Fe}_2\text{O}_3$  was first prepared by combining the reverse-micelle and sol–gel methods. This material exhibits a large coercive field ( $H_c$ ) over 20 kOe at room temperature.<sup>[9]</sup> Since then, various studies have been reported.<sup>[10–22]</sup> In such a high  $H_c$  ferrite magnet, the particle size can be downsized because the superparamagnetic limitation

size ( $d_s$ ) is very small (i.e.,  $d_s$  is 7.5 nm).<sup>[22]</sup> To adjust the performance of the magnetic material for magnetic recording systems, the  $H_c$  value must be tuned to 3 kOe. In the present study, we synthesized multimetal-substituted  $\epsilon\text{-Fe}_2\text{O}_3$  containing  $\text{Ga}^{3+}$ ,  $\text{Ti}^{4+}$ , and  $\text{Co}^{2+}$  ions,  $\epsilon\text{-Ga}_{0.31}^{\text{III}}\text{Ti}_{0.05}^{\text{IV}}\text{Co}_{0.05}^{\text{II}}\text{Fe}_{1.59}^{\text{III}}\text{O}_3$ . The synthesized sample is composed of spherical nanoparticles with an average particle size of 18 nm, and its  $H_c$  value was tuned to 2.9 kOe, which is suitable for a high-density magnetic memory. Using this material, we manufactured a practical magnetic recording tape, and demonstrated its performance as a next-generation magnetic recording material.

The target material  $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  was synthesized using the sol–gel method, where an aqueous solution of  $\text{Fe}(\text{NO}_3)_3$ ,  $\text{Ga}(\text{NO}_3)_3$ ,  $\text{Co}(\text{NO}_3)_2$ , and  $\text{Ti}(\text{SO}_4)_2$  was mixed with  $\text{NH}_3$  aqueous solution to obtain metal hydroxide nanoparticles. Then the metal hydroxide nanoparticles were covered with  $\text{SiO}_2$  matrix, and subsequently sintered at 1075 °C for 4 hours in air. The  $\text{SiO}_2$  matrices were etched by a NaOH solution, and the sample was obtained as brown powder (see Experimental section for details). The formula was determined to be  $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  according to the X-ray fluorescence (XRF) measurement.

The X-ray powder diffraction (XRPD) measurement shows that  $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  has an isomorphic crystal structure with  $\epsilon\text{-Fe}_2\text{O}_3$ . From the Rietveld analysis, the crystal structure is refined with an orthorhombic structure in the  $Pna2_1$  space group with lattice constants of  $a = 5.0928(2)$  Å,  $b = 8.7775(4)$  Å,  $c = 9.4484(4)$  Å, and  $V = 422.36(3)$  Å<sup>3</sup> (Figure 1). The crystal structure has four nonequivalent Fe sites (A–D) (i.e., the coordination geometries of the A and B sites are distorted octahedral, the C site is regular octahedral, and the D site is tetrahedral).  $\text{Ga}^{3+}$ ,  $\text{Ti}^{4+}$ , and  $\text{Co}^{2+}$  ions predominantly occupy the D sites followed by the C sites;  $\text{Ga}^{3+}$  occupies 48% of the D sites and 14% of the C sites,  $\text{Ti}^{4+}$  occupies 10% of the D sites, and  $\text{Co}^{2+}$  occupies 10% of the D sites. The transmission electron microscopy (TEM) images show that the obtained sample is composed of spherical nanoparticles with a particle size of  $18.3 \pm 8.8$  nm (Figure 1b, inset).

The magnetization versus magnetic field curve shows a magnetization value of  $23.4 \text{ emu g}^{-1}$  at 7 tesla (Figure 2), while that of the original  $\epsilon\text{-Fe}_2\text{O}_3$  is  $16.2 \text{ emu g}^{-1}$ , resulting in a 44% increase upon metal-substitution. This magnetization increase can be explained by the reduction in the sublattice magnetization at the D sites due to the substitution of the  $\text{Fe}^{3+}$  ions ( $S = 5/2$ ) as 48%, 10%, and 10% are replaced by  $\text{Ga}^{3+}$  ( $S = 0$ ),  $\text{Ti}^{4+}$  ( $S = 0$ ), and  $\text{Co}^{2+}$  ( $S = 3/2$ ), respectively. The magnetism of  $\epsilon\text{-Fe}_2\text{O}_3$  can be understood by collinear

[a] Prof. S. Ohkoshi, Dr. A. Namai, M. Yoshikiyo, Dr. K. Imoto  
 Department of Chemistry, School of Science, The University of  
 Tokyo

7-3-1, Hongo, Bunkyo-ku, Tokyo 113-0033 (Japan)  
 E-mail: ohkoshi@chem.s.u-tokyo.ac.jp


[b] K. Tamazaki, K. Matsuno, O. Inoue, T. Ide  
 TDK Corporation

2-15-7 Higashi-owada, Ichikawa, Chiba 272-8558 (Japan)

[c] K. Masada, M. Goto, T. Goto, T. Yoshida, T. Miyazaki  
 Dowa Electronics Materials, Co., Ltd.

1-3-1 Kaigandori, Minami-ku, Okayama 702-8506 (Japan)

ferrimagnetism with a positive sublattice magnetization at the B and C sites ( $M_B, M_C > 0$ ) and a negative sublattice magnetization at the A and D sites ( $M_A, M_D < 0$ ) (Figure 3a).<sup>[18]</sup> Therefore, the reduction of the negative sublattice magnetization at the D sites by metal-substitution should contribute to the increased total magnetization (Figure 3b).

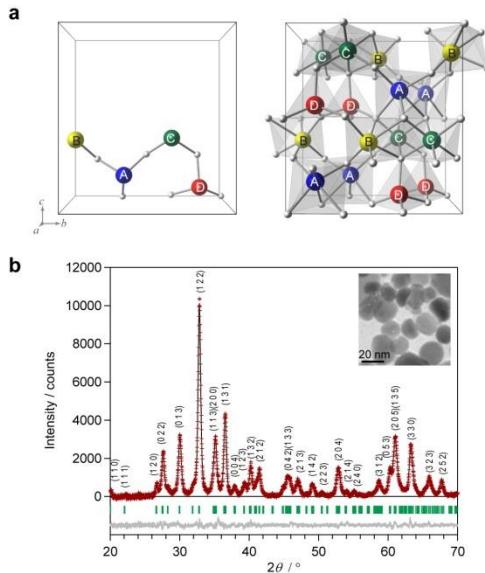


**Figure 1.** a) Asymmetric unit (left) and unit cell (right) of the  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  crystal structure shown from the  $a$ -axis direction. b) XRPD pattern and Rietveld analysis. Red crosses, black line, and grey line are the observed pattern, calculated pattern, and their difference, respectively. Green bars represent the calculated positions of the Bragg reflections of the  $\epsilon$ -phase (orthorhombic,  $Pna2_1$ ). Inset is the TEM image.


The magnetic hysteresis loop shows that the  $H_c$  value can be tuned below 3 kOe,  $H_c = 2.69$  kOe, which is one order smaller than the  $H_c$  value of the original  $\epsilon$ - $\text{Fe}_2\text{O}_3$ . This reduction in the  $H_c$  value can be explained by the compensation of single-ion anisotropies of  $\text{Fe}^{3+}$  and the additional  $\text{Co}^{2+}$ . In the case of  $\epsilon$ - $\text{Fe}_2\text{O}_3$ , the first-principles calculation indicates that the large magnetic anisotropy of  $\epsilon$ - $\text{Fe}_2\text{O}_3$  along the  $a$ -axis at room temperature is due to the orbital angular momentum of  $\text{Fe}^{3+}$  at the B site, which originates from the hybridization between  $\text{Fe}^{3+}$  ion and  $\text{O}^{2-}$  ion (Figure 3b).<sup>[15]</sup> In  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$ , the magnetic anisotropy of the  $\text{Co}^{2+}$  ion at the D site is considered to be directed along the  $c$ -axis. Hence, the magnetic anisotropy of  $\text{Fe}^{3+}$  ion at the B site along the  $a$ -axis is compensated by that of  $\text{Co}^{2+}$  ion, resulting in the tuning of  $H_c$  below 3 kOe.

One of the requirements of a magnetic recording tape is an  $H_c$  value of ca. 3 kOe. Since the  $H_c$  value of  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  is suitable for magnetic recordings, we synthesized a large amount of this sample (5 kg), and manufactured a trial magnetic tape in an actual factory. The dispersion solution of  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  in a resin was coated onto a non-magnetic layer film under an external magnetic field of 7 kOe (Figure 4a) (see Experimental section for details). The layered structure of the  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$


magnetic tape is schematically illustrated in Figure 4b, and the cross section scanning electron microscopy (SEM) image of the manufactured magnetic tape is shown in Figure 4c. The magnetic layer is  $110 \pm 5$  nm thick and the surface roughness of the magnetic layer is a very low value of 2.7 nm. The magnetic measurement shows that the nanoparticles are crystallographically oriented due to the applied magnetic field during the tape preparation. The squareness ratio of the magnetic hysteresis loop, which is defined as the residual magnetic flux density over maximum magnetic flux density, is 0.68, and the  $H_c$  value is 2.91 kOe in the longitudinal direction of the magnetic tape.

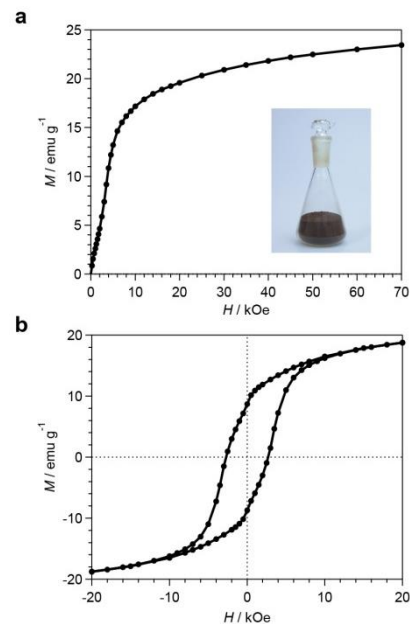

**Figure 2.** a) Initial magnetization curve and b) magnetic hysteresis loop of  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  measured at 300 K. Inset of (a) is a picture of the powder sample.

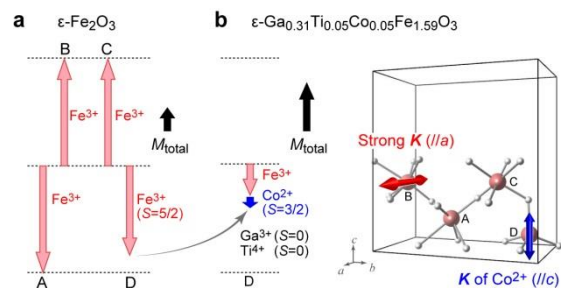

**Figure 3.** Magnetic structure of  $\epsilon$ - $\text{Fe}_2\text{O}_3$  (a)  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  (b, left). Red and blue arrows denote the sublattice magnetizations of  $\text{Fe}^{3+}$  and  $\text{Co}^{2+}$ , respectively. Upward (downward) arrows denote the positive (negative) sublattice magnetization. Black arrows show the total magnetization. Right figure in (b) shows the asymmetric unit in the unit cell denoting the direction of the single ion anisotropies ( $K$ , red and blue arrows) for  $\text{Fe}^{3+}$  at the B site along  $a$ -axis and  $\text{Co}^{2+}$  at the D site along  $c$ -axis.

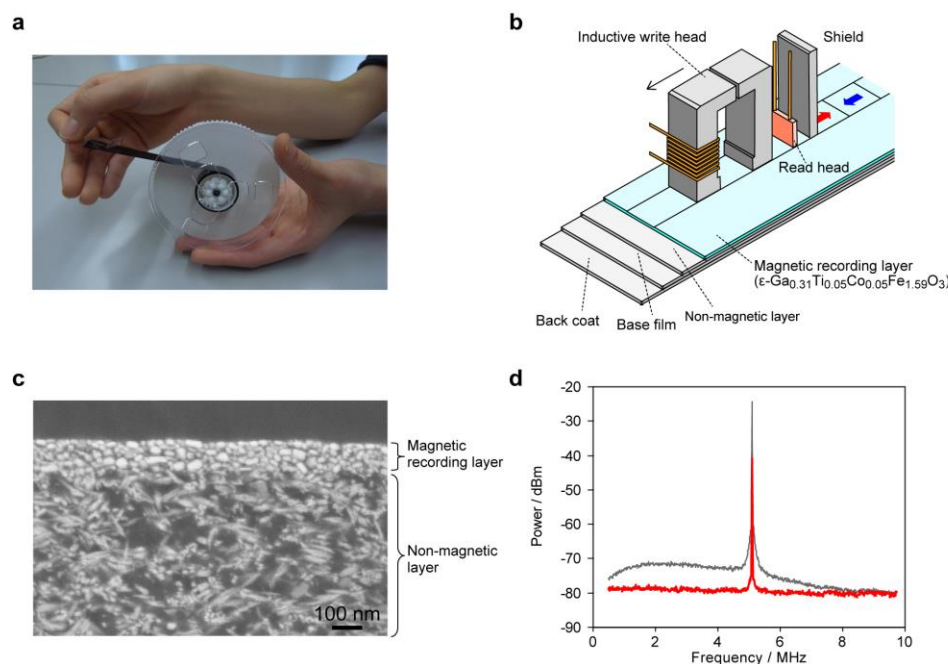

**Figure 4.** a) Picture of the manufactured magnetic recording tape composed of  $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$ . b) Schematic illustration of the LTO-3 AMR head composed of an inductive write head, a read head, and a shield. c) Cross section SEM image of the manufactured magnetic tape. d) Power spectrum of the signal of the  $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  tape (red line) and cobalt-iron alloy tape (grey line) measured with the LTO-3 AMR head.

The performance of the magnetic recording tape was evaluated using a 3rd-generation linear tape-open (LTO-3) anisotropic magnetoresistive (AMR) head (Figure 4b). The recording performance of the  $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  magnetic recording tape was investigated using a spectrum analyser, and the results were compared to those of a cobalt-iron metal alloy (MP1, DOWA Electronics Materials) magnetic tape. As shown in Figure 4d, the  $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  tape gives a very sharp signal peak. The foot of the signal peak is remarkably narrower compared to the MP1 magnetic tape, and the baseline is perfectly flat. These features indicate that the  $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  magnetic tape has a high signal-to-noise ratio (S/N). Such a remarkably high S/N performance indicates that the present magnetic material has potential in future magnetic tape recording applications.

In summary, we prepared a new series of metal-substituted  $\epsilon\text{-Fe}_2\text{O}_3$ ,  $\epsilon\text{-Ga}^{\text{III}}_{0.31}\text{Ti}^{\text{IV}}_{0.05}\text{Co}^{\text{II}}_{0.05}\text{Fe}^{\text{III}}_{1.59}\text{O}_3$ , with an average size of 18 nm.  $\text{Ga}^{3+}$ ,  $\text{Ti}^{4+}$ , and  $\text{Co}^{2+}$  cations tune the magnetic properties of  $\epsilon\text{-Fe}_2\text{O}_3$  to the demanded specifications for a magnetic recording tape, and we demonstrated that it is useful for the magnetic recording storage system. This series of materials should be applicable for data storage in the big data era as it should realize high-density economical and long-guarantee magnetic recording media.

## Experimental Section

**Material characterization and magnetic measurement.** Elemental analyses of the prepared samples were performed using an XRF spectrometer, Rigaku ZSX Primus II. Calcd: Ga, 13.4%; Ti, 1.4%; Co, 1.7%; and Fe, 54.2%. Found: Ga, 13.1%; Ti, 1.4%; Co, 1.7%; and Fe, 53.4%. The TEM measurements were conducted using a JEOL JEM-

2000EXII and 100CX-Mark II, while the X-ray powder diffraction (XRPD) measurements were conducted by a Rigaku Ultima IV with Cu K $\alpha$  radiation ( $\lambda = 1.5418 \text{ \AA}$ ). Rietveld analysis was performed by the RIETAN-FP program. The magnetic properties were measured using a superconducting quantum interference device (SQUID) magnetometer (Quantum Design, MPMS 7) and a Quantum Design 6000 physical property measurement system (PPMS).

**Preparation of the magnetic tape:**  $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  powder sample was mixed into a resin solution composed of polyurethane and polyvinylchloride dissolved in methylethylketone, toluene, and cyclohexane. The dispersion was coated on a non-magnetic layer on a base film. The non-magnetic layer was composed of spindle-shaped hematite, carbon, and an  $\text{Al}_2\text{O}_3$ . PEN film of Teijin DuPont was used for the base film. The  $\epsilon\text{-Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  particles were oriented in the resin under an external magnetic field of 7 kOe along the longitudinal direction of the tape. TEM and SEM images of the magnetic recording tapes were acquired using JEOL 3010 and HITACHI S4700, respectively.

## Acknowledgements

The present research was supported in part by JSPS Grant-in-Aid for Specially Promoted Research (Grant Number 15H05697), JSPS Grant-in-Aid for Young Scientists (B), ACCEL-FS project of JST, and DOWA Technofund. We also recognize the Cryogenic Research Center, the University of Tokyo, APSA, and Nanotechnology Platform, which are supported by MEXT.

**Keywords:** Epsilon-iron oxide • Hard Magnetic Ferrite • Magnetic Properties • Magnetic Recording Tape • Nanoparticles


- [1] M. L. Plumer, J. van Ek & D. Weller, *The Physics of Ultra-High Density Magnetic Recording*, Springer, Berlin, Germany 2001.

- [2] W. A. Challener, C. Peng, A. V. Itagi, D. Karns, W. Peng, Y. Peng, X. M. Yang, X. Zhu, N. J. Gokemeijer, Y.-T. Hsia, G. Ju, R. E. Rottmayer, M. A. Seigler, E. C. Gage, *Nature Photon.* **2009**, *3*, 220.
- [3] T. Hayashi, S. Hirono, M. Tomita, S. Umemura, *Nature* **1996**, *381*, 772.
- [4] I. Tudosă, C. Stamm, A. B. Kashuba, F. King, H. C. Siegmann, J. Stöhr, G. Ju, B. Lu, D. Weller, *Nature* **2004**, *428*, 831.
- [5] D. Alloeyau, C. Ricolleau, C. Mottet, T. Oikawa, C. Langlois, Y. Le Bouar, N. Braidy, A. Loiseau, *Nature Mater.* **2009**, *8*, 940.
- [6] G. Cherubini, C. C. Chung, W. C. Messner, S. O. R. Moheimani, *IEEE Trans. Contr. Syst. Tech.* **2012**, *20*, 296.
- [7] H. Nishio, H. Yamamoto, *IEEE Trans. Magn.* **2010**, *46*, 3747.
- [8] R. E. Fontana Jr., G. M. Decad, S. R. Hetzler, *J. Appl. Phys.* **2015**, *117*, 17E301.
- [9] J. Jin, S. Ohkoshi, K. Hashimoto, *Adv. Mater.* **2004**, *16*, 48.
- [10] E. Tronc, C. Chanéac, J. P. Jolivet, J. M. Grenèche, *J. Appl. Phys.* **2005**, *98*, 053901.
- [11] S. Ohkoshi, S. Kuroki, S. Sakurai, K. Matsumoto, K. Sato, S. Sasaki, *Angew. Chem. Int. Ed.* **2007**, *46*, 8392.
- [12] Y. -C. Tseng, N. M. Souza-Neto, D. Haskel, M. Gich, C. Fontera, A. Roig, M. van Veenendaal, J. Nogués *et al.*, *Phys. Rev. B* **2009**, *79*, 094404.
- [13] A. Namai, S. Sakurai, T. Suemoto, M. Nakajima, K. Matsumoto, M. Goto, S. Sasaki, S. Ohkoshi, *J. Am. Chem. Soc.* **2009**, *131*, 1170.
- [14] J. Tuček, R. Zbořil, A. Namai, S. Ohkoshi, *Chem. Mater.* **2010**, *22*, 6483.
- [15] A. Namai, M. Yoshikiyo, K. Yamada, S. Sakurai, T. Goto, T. Yoshida, T. Miyazaki, M. Nakajima, T. Suemoto, H. Tokoro, S. Ohkoshi, *Nature Commun.* **2012**, *3*, 1035.
- [16] M. Gich, I. Fina, A. Morelli, F. Sánchez, M. Alexe, J. Gàzquez, J. Fontcuberta, A. Roig, *Adv. Mater.* **2014**, *26*, 4645.
- [17] P. Brázda, E. Večerníková, E. Pližingrová, A. Lančok, D. Nižňanský, *J. Therm. Anal. Calorim.* **2014**, *117*, 85.
- [18] S. Ohkoshi, H. Tokoro, *Bull. Chem. Soc. Jpn.* **2013**, *86*, 897.
- [19] D. A. Balaev, I. S. Poperechny, A. A. Krasikov, K. A. Shaikhutdinov, A. A. Dubrovskiy, S. I. Popkov, A. D. Balaev, S. S. Yakushkin, G. A. Bukhtiyarova, O. N. Martyanov, Yu. L. Raikher, *J. Appl. Phys.* **2015**, *117*, 063908.
- [20] J. Kohout, P. Brázda, K. Závěta, D. Kubániová, T. Kmječ, L. Kubičková, M. Klementová, E. Šantavá, A. Lančok, *J. Appl. Phys.* **2015**, *117*, 17D505.
- [21] A. A. Dubrovskiy, D. A. Balaev, K. A. Shaykhutdinov, O. A. Bayukov, O. N. Pletnev, S. S. Yakushkin, G. A. Bukhtiyarova, O. N. Martyanov, *J. Appl. Phys.* **2015**, *118*, 213901.
- [22] S. Ohkoshi, A. Namai, K. Imoto, M. Yoshikiyo, W. Tarora, K. Nakagawa, M. Komine, Y. Miyamoto, T. Nasu, S. Oka, H. Tokoro, *Sci. Rep.* **2015**, *5*, 14414.

## Entry for the Table of Contents

## COMMUNICATION

A new series of metal-substituted  $\epsilon$ - $\text{Fe}_2\text{O}_3$ ,  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$ , with an average size of 18 nm was prepared. Ga, Ti, and Co cations tune the magnetic properties of  $\epsilon$ - $\text{Fe}_2\text{O}_3$  to the demanded specifications for a magnetic recording tape, e.g., coercive field= 3 kOe. The fabricated magnetic tape showed a remarkably high signal-to-noise ratio. This series of materials should be applicable for data storage in the big data era.

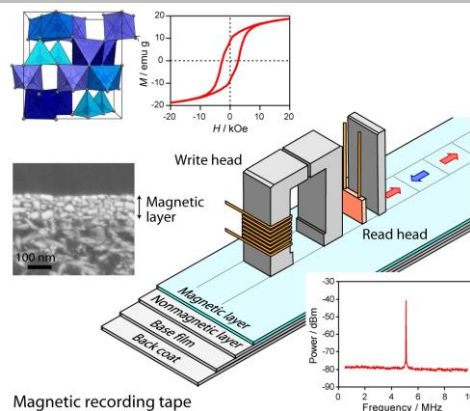

*Shin-ichi Ohkoshi,\* Asuka Namai, Marie Yoshikiyo, Kenta Imoto, Kazunori Tamasaki, Koji Matsuno, Osamu Inoue, Tsutomu Ide, Kenji Masada, Masahiro Goto, Takashi Goto, Takayuki Yoshida, and Tatsuro Miyazaki*

**Page No. – Page No.**

**Multimetal-Substituted Epsilon-Iron Oxide  $\epsilon$ - $\text{Ga}_{0.31}\text{Ti}_{0.05}\text{Co}_{0.05}\text{Fe}_{1.59}\text{O}_3$  for Next Generation Magnetic Recording Tape in the Big Data Era**