

Author Manuscript

Title: Nano/micro-Structured Si/C Anodes with High Initial Coulombic Efficiency in Li-Ion Batteries

Authors: Yu-Guo Guo

This is the author manuscript accepted for publication and has undergone full peer review but has not been through the copyediting, typesetting, pagination and proofreading process, which may lead to differences between this version and the Version of Record.

To be cited as: Chem. Asian J. 10.1002/asia.201600067

Link to VoR: <http://dx.doi.org/10.1002/asia.201600067>

Nano/micro-Structured Si/C Anodes with High Initial Coulombic Efficiency in Li-Ion Batteries

Quan Xu,^[a,b] Jin-Yi Li,^[a,b] Ya-Xia Yin,^[a] Yi-Ming Kong,^[a] Yu-Guo Guo^{*[a,b]}, Li-Jun Wan^[a]

^a CAS Key Laboratory of Molecular Nanostructure and Nanotechnology, and Beijing National Laboratory for Molecular Sciences, Institute of Chemistry, Chinese Academy of Sciences (CAS), Beijing 100190, P.R. China.

^b University of Chinese Academy of Sciences, Beijing 100049, P.R. China

Abstract: One of the major challenges for designing high capacity anode materials is to combine both coulombic efficiency and cycling stability. Herein, nano/micro-structured Si/C composites are designed and synthesized to address this challenge by decreasing the specific surface and improving the tap density of Si/C materials. An ultrahigh initial coulombic efficiency of 91.2% could be achieved due to the proper particle size, low specific surface area and optimized structure. The nano/micro-structured Si/C anodes exhibit excellent cycling stability with 96.5% capacity retention after 100 cycles under a current density of 0.2 A g⁻¹.

Lithium-ion batteries (LIBs) have become the most important energy storage system for portable devices and electrical vehicles due to its high energy density and long cycle life.^[1-3] Growing demands for high energy LIBs have aroused extensive interests in developing high capacity electrode materials.^[4-6] Silicon, known for its high lithium storage capacity, was proposed as the most attractive materials for high energy LIBs.^[7-9] The primary challenge of Si anodes was the huge volume change (~300%) during (de)lithiation process, which caused the pulverization of electrodes and instability of solid-electrolyte interface.^[10,11] Decreasing the size of Si to nanoscale was an effective approach to prevent the pulverization of Si.^[12,13] However, nano-materials also presented some disadvantages, including surface side reactions, large surface area and electrochemical agglomeration, which led to low coulombic efficiency (CE) and severe capacity fading.^[14-16]

To address these problems, various Si/C composites were fabricated to enhance the electrochemical performance of Si-based anodes.^[17-20] However, it was difficult to combine both coulombic efficiency and cycling stability.^[14] The lower CE, especially initial CE (less than 85%) was often presented in

recent reports in which the Si-based composites demonstrated proper electrochemical performance.^[21-23] In this case, a large amount of Li-ions, provided by the cathode, would be consumed in practical applications.^[20] In addition, scalable fabrication process of Si/C composites was still a significant challenge.^[4,13] Therefore, successful implementation of Si/C as commercial anode materials has been impeded. Spray drying was a effective transformation of materials from the slurry into dried particulate by spraying the materials into a hot drying medium.^[24] Recently, Si/C composites have been fabricated by open-air drying system.^[25-27] However, nano-Si was easily oxidized, which could lead to poor electrochemical performance. Therefore, the closed cycle system was used to fabricate Si/C composite under N₂ atmosphere and ethanol solvent in this work. The spray drying process was beneficial to mix materials uniformly and obtain porous structure due to the solvent evaporation.^[27] Furthermore, the use of closed cycle system enabled gas and solvent recovery.

In this study, we synthesized nano/micro-structured Si/C composites by closed cycle drying system to improve the CE, especially for the first cycle. With this optimized structure, the surface area of compact Si/C composites decreased to 10.5 m² g⁻¹, corresponding to the high tap density. The nano/micro-structured Si/C anode also demonstrated proper reversible capacity and excellent capacity retention after 200 cycles.

The fracture of Si particles and SEI layer concurrently has been identified as the main reasons for the poor electrochemical performance of Si-based materials.^[6] It was effective to mitigate mechanical degradation by decreasing the particle size to nanoscale.^[4] Therefore, nano-Si (Figure 1a) was used as starting materials in the precursor solution. However, the significant increase of surface area could seriously influence the CE of nano-Si electrodes due to the formation of unstable SEI layer.^[20] Although, pioneering works demonstrated that porous Si/C composite microspheres would be the desirable solution to overcome the limitations of nano-Si electrodes, the uniform dispersion of nano-Si and the appropriate surface area of porous Si/C were challenging.^[3,27-29] Herein, the nano-Si and flake graphite with different size were utilized to construct nano/micro-structured Si/C composites (Figure 1). The PSD curves (Figure 2a) showed that the raw materials possessed proper particle size distribution, which was essential to establish engineered structure.

[a] Prof. Y.-G. Guo, Q. Xu, J.-Y. Li, Dr. Y.-X. Yin, Y.-M. Kong, Prof. L.J. Wan
CAS Key Laboratory of Molecular Nanostructure and Nanotechnology, and Beijing National Laboratory for Molecular Sciences
Institute of Chemistry, Chinese Academy of Sciences (CAS)
Beijing, 100190 (P. R. China)
E-mail: ygguo@iccas.ac.cn

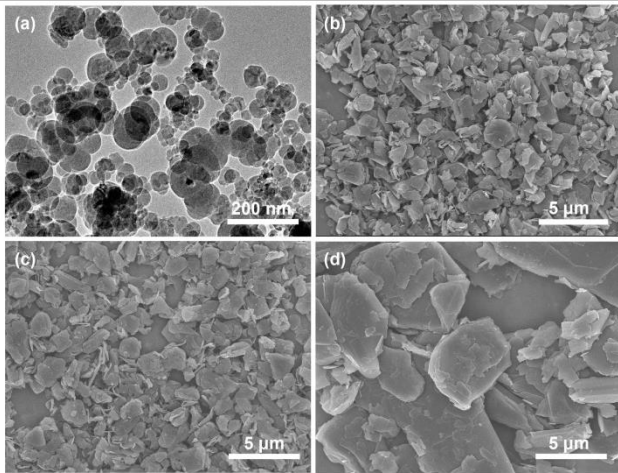


Figure 1. (a) TEM image of nano-Si. SEM images of (b) flake graphite (average diameter=1 μm), (c) flake graphite (average diameter=5 μm) and (d) flake graphite (average diameter=10 μm).

The nano/micro-structured Si/C composites were prepared by closed cycle drying system, which was the high-efficiency method to fabricate porous materials.^[24] The existing pores could accommodate the huge volume expansion of nano-Si and allow for the rapid infiltration of electrolyte (Figure S1 and S3). As shown in Figure 2b, the PSD curves of obtained Si/C composites presented distinct size distribution due to the various flake graphite, consistent with the following SEM images in Figure 3. The size distribution of Si/C-3 was wider than other Si/C materials due to the flake graphite (average diameter=10 μm) which was difficult to fabricate composites by closed cycle drying system. Furthermore, the Si/C-3 (Figure 3b) was fragile because of the loose structure, leading to high specific surface area (SSA) up to 98.2 $\text{m}^2 \text{g}^{-1}$. Commercial LIBs were mainly based on micro-sized electrodes materials, which was limited by their structural stability, kinetics

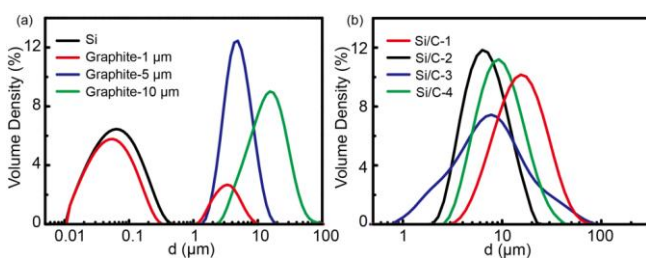


Figure 2. The PSD curves of (a) original materials and (b) obtained various Si/C composites by closed cycle drying system.

and Li-ion intercalation capacities.^[2] The Si/C-1 (Figure 3d) showed the proper size which was commonly used in the production of commercial anode materials. It was noted that the average diameter of Si/C composites increased when larger-size flake graphite was used in slurry. As shown in Figure 3a and 3b, the average diameter of Si/C-2 was only 6.69 μm , but the surface of Si/C-2 was smooth and compact, compared with Si/C-3. The hybrid Si/C-4 (Figure 3c) displayed suitable sphericity and size distribution. Therefore, the optimal Si/C-1 was fabricated by the combination of three different flake graphite. Diverse size was

conductive to efficiently occupy space by filling interstitial with smaller particles, rather than packing uniform Si/C materials which would leave large interstitial volume.^[13] The obtained Si/C-1 presented smooth surface, compact structure and superior size distribution, which were beneficial to enhance the electrochemical performance of Si/C anodes with high mass loading.

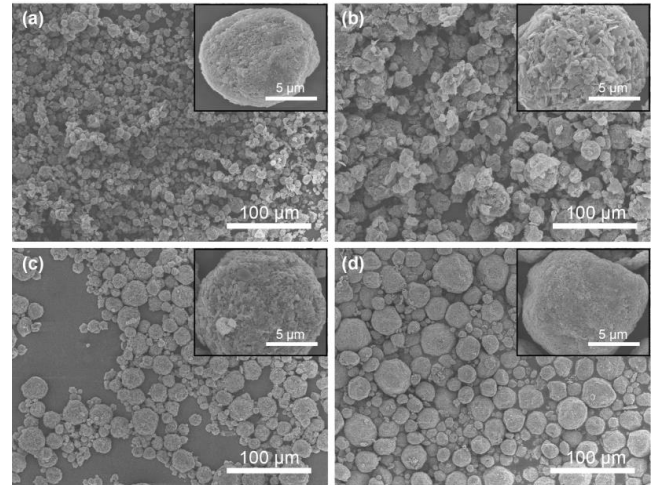


Figure 3. SEM images of (a) Si/C-2, (b) Si/C-3, (c) Si/C-4 and (d) Si/C-1 composites.

The structure of Si/C composites was further characterized by XRD patterns and Raman spectra (Figure 4). The Si/C composites were composed of crystalline Si, graphitic carbon and disordered carbon, no other impurities which could be ascribed to the protection of inactive atmosphere during spray drying and calcination process. According to the TG analysis (Figure S3), the carbon content of Si/C-1 is approximately 84.5%. Raman spectrum demonstrated a sharp adsorption peak at around 515 cm^{-1} and two small adsorption peaks at 295 and 950 cm^{-1} , indicating the crystalline Si.^[19] The other two primary peaks at 1351 and 1601 cm^{-1} are the D and G band, respectively. The ratio of the integrated area of the D and G band reflected the graphitization degree of the Si/C composites.^[21] The lower I_D/I_G suggested that Si/C composites had superior electrical conductivity. The conductive framework, composed of flake graphite, not only functioned as the electrical highway and mechanical backbone to maintain the structural integrity during cycling, but also promoted the formation of stable SEI layer.

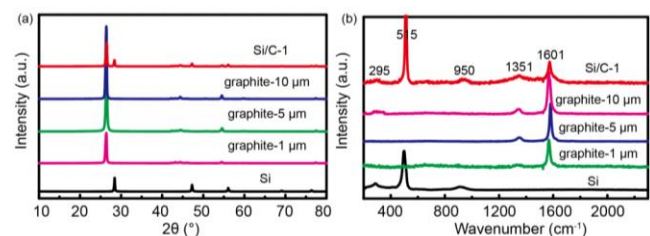


Figure 4. (a) XRD patterns and (b) Raman spectra of various samples.

In nano-Si electrodes, the enormously exposed surface resulted in forming more interparticle space and severe side reactions which lowered CE and tap density.^[13] As shown in

Table 1, the Si/C-1 anode exhibited an ultrahigh initial CE up to 91.2% which could be attributed to the following aspects: (1) most SEI layer formed on the outer surface of Si/C composites instead of nano-Si due to the disordered carbon layer (Figure S2),^[17] (2) the nano/micro-structure is favorable for electrolyte penetration and all nano-Si could participate into the electrochemical reactions;^[16] (3) the lower specific surface area and higher tap density were beneficial to decrease the thickness of electrodes and the distance of electron pathway under the same mass loading.^[4] The average CE of Si/C-1 from 2nd to 200th cycle was 99.65% at a relatively slow rate of 0.2 A g⁻¹. However, when the Si/C-1 anode is measured under a constant current of 0.5 A g⁻¹, the average CE of Si/C-1 from 2nd to 200th cycle could be increased to 99.8% (Figure S5).

Table 1. Comparison of the properties of Si/C composites

Samples	Average diameter (μm)	SSA (m ² g ⁻¹)	Tap density (g cm ⁻³)	Initial CE (%)
Si/C-2	6.69	40.8	0.65	80.3
Si/C-3	8.47	98.2	0.53	76.9
Si/C-4	9.42	22.8	0.72	86.9
Si/C-1	15.3	10.5	0.81	91.2

With well-established Si/C composites built from optimized nano/micro-structure, excellent electrochemical performance could be achieved. Figure 5a exhibited the first charge and discharge profiles of Si/C anodes at 0.1 A g⁻¹ between 1 V and 0.005 V. The Si/C-1 anode demonstrated the highest reversible capacity due to the ultrahigh initial CE, indicating that the novel nano/micro-structure enable the formation of stable SEI layer during the first cycle.^[21] The mass loading of all Si/C anodes were around 3.1 mg cm⁻² excluding super-P and binder. As shown in Figure 5b, stable cycling of Si/C-1 anode for 100 cycles with 96.5% capacity retention was displayed under a current density of 0.2 A g⁻¹. Furthermore, it should be noted that the reversible areal capacity reached 2.25 mA h cm⁻² in Figure 5d. Even after 200 cycles, the areal capacity was still more than 2 mA h cm⁻².

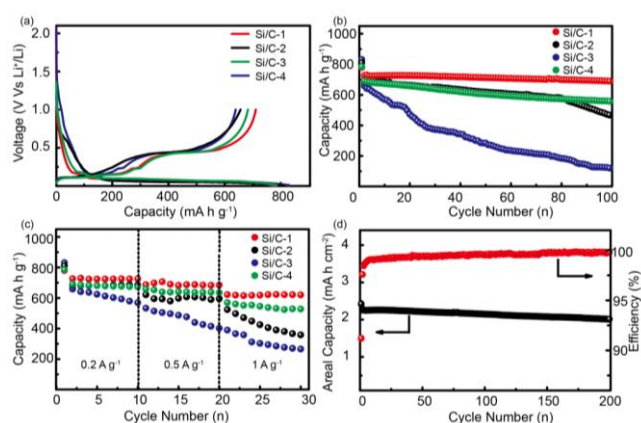


Figure 5. (a) The first charge and discharge profiles. (b) The cycling stability of different Si/C anodes. (c) Rate capability of different Si/C anodes. (d) High areal mass loading test and coulombic efficiency of Si/C-1 anode.

Si/C-1 anode also presented superior rate capability under the same charge/discharge current density (Figure 5c). 85.5% of the original capacity was maintained when the current density was

increased from 0.2 A g⁻¹ to 1 A g⁻¹. In Figure S5, the Si/C-1 anodes also presented proper capacity retention: 88.5% of the second discharge capacity after 200 cycles under the current density of 0.5 A g⁻¹ (0.7 C). The high CE, associated with the stable SEI layer, contributes to the superior cycling stability. The stable cycling of a high mass loading battery is another advantage of the nano/micro-structured Si/C anodes. There are two interdependent characteristics of the nano/micro-structured design to ensure the excellent performance at high areal capacity. The first is the sufficient and well-established internal void space which is essential to maintain the structural integrity of the Si/C anodes. The second is the carbon framework. It is beneficial to form stable SEI layer and remain electrically connected of the Si/C materials.

In summary, we synthesized nano/micro-structured Si/C composites by the closed cycle drying system which exhibited an ultrahigh initial CE of 91.2% under the current density of 0.1 A g⁻¹. 88.9% capacity retention was achieved under a current density of 0.2 A g⁻¹ after 200 cycles, even when the reversible areal capacity was up to 2.25 mA h cm⁻². Furthermore, scalability and manufacturing efficiency of Si/C anodes met the requirements of practical application. The facile fabrication process and superior performance will make Si/C anodes the promising alternative to graphite for high energy density LIBs.

Experimental Section

Synthesis

Firstly, 10 g nano-Si, 10 g polyvinyl pyrrolidone and 10 g phenolic resin were stirred in ethanol solution under sonication. Then, 10 g flake graphite (average diameter=10 μm), 15 g flake graphite (average diameter=5 μm) and 20 g flake graphite (average diameter=1 μm) were added to the above solution, followed by vigorous stirring for 12 h to form a homogeneous slurry. The resulting solution was used to prepare Si/C composites by closed cycle drying system under N₂ atmosphere. The obtained Si/C composites were pyrolysed at 1000 °C for 3 h at a heating rate of 5 °C min⁻¹ under argon atmosphere. The obtained Si/C composites were denoted as Si/C-1. For comparison, Si/C-2, Si/C-3 and Si/C-4 were prepared by the same process. However, the flake graphite was different. The slurry of Si/C-2 was composed of 45 g flake graphite (average diameter=1 μm). The slurry of Si/C-3 contained 45 g flake graphite (average diameter=10 μm), 19 g flake graphite (average diameter=5 μm) and 26 g flake graphite (average diameter=1 μm) were used in the slurry for the fabrication of Si/C-4.

Characterization

The morphologies of all materials were investigated by the SEM (JEOL 6701F) and TEM (JEM-2100F). X-ray diffraction patterns (XRD) were obtained by a Rigaku D/max 2500 diffractometer using Cu Kα radiation. Particle size distribution (PSD) was measured using a laser particle size distribution. Raman spectra was obtained using a Digilab FTS3500. CR2032-type coin cells were assembled to measure electrochemical performance in an Ar-filled glove box. The half cells were composed of the Li foil as the counter electrode, a celgard 2500 as separator, electrolyte and the working electrode. The electrolyte was 1M LiPF₆ in a mixture of EC/DMC/DEC (1:1:1, by volume, 70 μl) containing 5% FEC and 2% VC additives. Si/C composites were mixed with super P, CMC and SBR in the mass ratio of 90 : 5 : 2.5 : 2.5 to form a homogeneous slurry in deionized water. The obtained slurry was pasted onto the carbon coated copper and then dried in a vacuum oven at 60 °C for 12 h. The loading of active materials was around 3.1 mg cm⁻². The charge and discharge measurements of batteries were carried out in a voltage range of 0.005-1.0 V vs. Li⁺/Li under a constant current of 0.1 A g⁻¹ for the first cycle and 0.2 A g⁻¹ for later cycles.

Acknowledgements

This work was supported by the National Basic Research Program of China (Grant No. 2012CB932900), the National Natural Science Foundation of China (Grant Nos. 51225204, and 21127901), and the “Strategic Priority Research Program” of the Chinese Academy of Sciences (Grant No. XDA09010000) and CAS.


Keywords: lithium-ion batteries • anode • Si/C • Coulombic efficiency • nano/micro-structures

- [1] H. Li, Z. Wang, L. Chen, X. Huang, *Adv. Mater.* **2009**, 21, 4593-4607.
- [2] Y. G. Guo, J. S. Hu, L. J. Wan, *Adv. Mater.* **2008**, 20, 2878-2887.
- [3] A. Magasinski, P. Dixon, B. Hertzberg, A. Kvit, J. Ayala, G. Yushin, *Nat. Mater.* **2010**, 9, 353-258.
- [4] X. Li, M. Gu, S. Hu, R. Kennard, P. Yan, X. Chen, C. Wang, M. J. Sailor, J. G. Zhang, J. Liu, *Nat. Commun.* **2014**, 5, 4105.
- [5] X. L. Wu, Y. G. Guo, L. J. Wan, *Chem. Asian J.* **2013**, 8, 1948-1958.
- [6] Q. Zhang, X. Xiao, W. Zhou, Y. T. Cheng, M. W. Verbrugge, *Adv. Energy Mater.* **2015**, 5, 1401398.
- [7] X. Chang, X. Huang, G. Zhou, S. Cui, P. B. Hallac, J. Jiang, P. T. Hurley, J. Chen, *Adv. Mater.* **2014**, 26, 758-764.
- [8] Y. Du, G. Zhu, K. Wang, Y. Wang, C. Wang, Y. Xia, *Electrochem. Commun.* **2013**, 36, 107-110.
- [9] C. K. Chan, H. Peng, G. Liu, K. McIlwrath, X. F. Zhang, R. A. Huggins, Y. Cui, *Nat. Nanotechnol.* **2008**, 3, 31-35.
- [10] X. Xiao, W. Zhou, Y. Kim, I. Ryu, M. Gu, C. Wang, G. Liu, Z. Liu, H. Gao, *Adv. Funct. Mater.* **2015**, 25, 1426-1433.
- [11] J. S. Kim, W. Pfleging, R. Kohler, H. J. Seifert, T. Y. Kim, D. Byun, H. G. Jung, W. Choi, J. K. Lee, *J. Power Sources* **2015**, 279, 13-20.
- [12] J. Song, S. Chen, M. Zhou, T. Xu, D. Lv, M. L. Gordin, T. Long, M. Melnyk, D. H. Wang, *J. Mater. Chem. A* **2014**, 2, 1257-1262.
- [13] D. Lin, Z. Lu, P.-C. Hsu, H.R. Lee, N. Liu, J. Zhao, H. Wang, C. Liu, Y. Cui, *Energy Environ. Sci.* **2015**, 8, 2371-2376.
- [14] S. H. Ng, J. Wang, D. Wexler, K. Konstantinov, Z. P. Guo, H. K. Liu, *Angew. Chem. Int. Ed.* **2006**, 45, 6896-6899.
- [15] S. J. Kim, M. Naguib, M. Zhao, C. Zhang, H. T. Jung, M. W. Barsoum, Y. Gogotsi, *Electrochim. Acta* **2015**, 163, 246-251.
- [16] C. Zhang, Z. Lin, Z. Yang, D. Xiao, P. Hu, H. Xu, Y. Duan, S. Pang, L. Gu, G. Cui, *Chem. Mater.* **2015**, 6, 2189-2194.
- [17] N. Liu, Z. Lu, J. Zhao, M. T. McDowell, H. W. Lee, W. Zhao, Y. Cui, *Nat. Nanotechnol.* **2014**, 9, 187-192.
- [18] X. Gao, J. Li, Y. Xie, D. Guan, C. Yuan, *ACS Appl. Mater. Interfaces* **2015**, 7, 7855-7862.
- [19] S. O. Kim, A. Manthiram, *J. Mater. Chem. A* **2015**, 3, 2399-2406.
- [20] Y. He, X. Yu, Y. Wang, H. Li, X. Huang, *Adv. Mater.* **2011**, 23, 4938-4941.
- [21] M. Li, X. Hou, Y. Sha, J. Wang, S. Hu, X. Liu, Z. Shao, *J. Power Sources* **2014**, 248, 721-728.
- [22] H. Zhang, X. Qin, J. Wu, Y. B. He, H. Du, B. Li, F. Kang, *J. Mater. Chem. A* **2015**, 3, 7112-7120.
- [23] X. Zhou, Y. G. Guo, *J. Mater. Chem. A* **2013**, 1, 9019-9023.
- [24] K. Cal, K. Solloway, *J. Phram. Sci.* **2010**, 2, 575-586.
- [25] S. Li, X. Qin, H. Zhang, J. Wu, Y. B. He, B. Li, F. Kang, *Electrochem. Commun.* **2014**, 49, 98-102.
- [26] W. Ren, Z. Zhang, Y. Wang, Q. Tan, Z. Zhong, F. Su, *J. Mater. Chem. A* **2015**, 3, 5859-5865.
- [27] D. S. Jung, T. H. Hwang, S. B. Park, J. W. Choi, *Nano Lett.* **2013**, 13, 2092-2097.
- [28] R. Yi, J. Zai, F. Dai, M. L. Gordin, D. H. Wang, *Nano energy*, **2014**, 6, 211-218.
- [29] R. Yi, F. Dai, M. L. Gordin, S. Chen, D. H. Wang, *Adv. Mater.* **2013**, 3, 285-300.

Author Manuscript

COMMUNICATION

Naon/micro-structured Si/C materials were designed and synthesized in large scale. The as-obtained Si/C anodes exhibit excellent electrochemical properties in terms of specific capacity, Coulombic efficiency, and cycling stability.

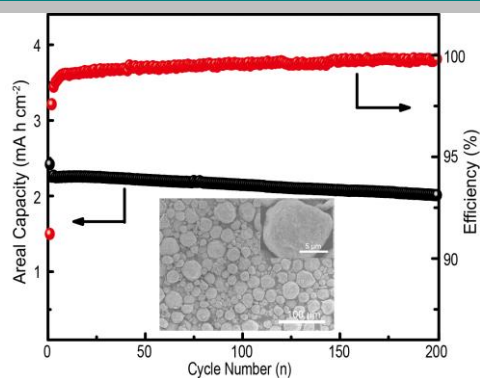

Quan Xu, Jin-Yi Li, Ya-Xia Yin,
Yi-Ming Kong, Yu-Guo Guo*, Li-Jun
Wan

Page No. – Page No.

Title: Nano/micro-Structured Si/C
Anodes with High Initial Coulombic
Efficiency in Li-Ion Batteries

Author Manuscript