

Article type: Full Paper

Layer-By-Layer Assembly Fabrication of Porous Boron Nitride Coated Multifunctional Materials for Water Cleaning

Dan Liu,[†] Mingwen Zhang,[†] Li He,^{#,‡} Ying Chen,^{*,†} and Weiwei Lei^{*,†}

Dr. Dan Liu, Dr. Mingwen Zhang, Prof. Ying Chen, Dr. Weiwei Lei

[†] Institute for Frontier Materials, Deakin University, Waurn Ponds Campus, Locked Bag 20000, Victoria 3220, Australia.

E-mail: ian.chen@deakin.edu.au; weiwei.lei@deakin.edu.au.

Dr. Li He

[#] Department of Chemical Engineering, University of Michigan, Ann Arbor, Michigan 48109-2136, USA.

Dr. Li He

[‡] School of Chemistry and Environment, Beihang University, Beijing 100191, P.R. China.

Keywords: Boron nitride nanosheet, layer-by-layer, oil absorption, melamine sponge, flame-retardant

Clean-up of oil spills and industrial discharge of organic solvents is a global challenge. However, development of the ideal materials for water remediation with a high separation efficiency and low risk of fire is still rather sparse because the material needs to be superhydrophobic/superoleophilic and

This is the author manuscript accepted for publication and has undergone full peer review but has not been through the copyediting, typesetting, pagination and proofreading process, which may lead to differences between this version and the [Version of Record](#). Please cite this article as [doi: 10.1002/adma.201700392](#).

also flame-retardant. Here, we report a novel coating material of porous boron nitride nanosheets (BNNSs) and a layer-by-layer (LBL) assembly technology for tailoring inexpensive cotton fabric and melamine sponge with these desired properties. The BNNS-coated cotton fabric and melamine sponge exhibit high oil/water separation efficiency, selective absorption capacity of oil and organic solvents, and excellent recyclability. Furthermore, the coated materials show an efficient flame-retardant effect which completely stops melamine sponge melt dripping upon exposure to the direct flame from a butane blowtorch within 52s. The integrated advantages of the high porosity, low water adhesion, compressibility, strong fire-resistance, simple operation, and commercial availability enable the porous BNNS-coated cotton fabric and melamine sponge to satisfy various practical oil/water separation requirements.

1. Introduction

Oil pollution is one of the major global issues because of the large amounts of oily wastewater generated from petrochemical, textiles, food, leathers, and metal industries, as well as frequent offshore oil-spill events during exploration and transportation.^[1,2] It has long-term adverse effects on natural environment, ecological balance and human health.^[3,4] Recently, it has been proposed that an ideal absorbent material should possess excellent flame retardant properties to reduce the risk of fire and explosion because the crude oil and some organic solvents are highly flammable and extremely dangerous once ignited.^[5,6] As a result, it is still an arduous challenge on oil/water separation with a technology of high efficiency, good stability, excellent recyclability, simply operation, flame retardancy and commercially available world widely. There is an extremely urgent and strong demand for multifunctional materials with high absorption capacity and selectivity, thermal stability, lightweight, chemical inertness, low cost and environmental friendliness for effectively separating oil from water.

Currently, one of the most efficient oil/water separation techniques is using oil-absorbing materials, such as textiles and polyurethane foams at the sites where a large amount of oil spill, e.g. Gulf of Mexico.^[7] Although textiles and polyurethane foams have some merits, such as high absorption capability, flexibility, low cost and density, as well as high mechanical stability under harsh practical conditions, both of them absorbing water and oil simultaneously lead to a low efficiency of oil absorption.^[9-10] Recently, research on fabricating novel two-dimensional (2D) nanomaterials to possess simultaneous superhydrophobicity and superoleophilicity has attracted considerable interests in the field of oil/water separation.^[11,12] Based on that, many effective 2D absorbent materials, including graphene and boron nitride nanosheets (BNNSs), have been exhibited superior absorption capacity and excellent recyclability for organic pollutant adsorption and clean-up of oil spillage.^[13-15] Although extensively implemented in research, these materials often have limitations for practical application under different situations because some technical challenges such as the tiny materials are difficult for practical operation and collection completely after usage. Further effort has been made to synthesise three-dimensional (3D) materials with interconnected structure and hydrophobic surface through the rational control of surface structures and chemical compositions, such as graphene-based sponges^[16], superhydrophobic conjugated microporous polymers,^[17] and carbon aerogels.^[18] Although these materials have high processing capacity and excellent separation efficiency, the difficulty of large-scale fabrication, multistep processes, and high-cost limits their commercial applications.

Inspired by the previous achievements, we hypothesise that if the surface of commercially available and low-cost textiles and polyurethane foams could be modified to be superhydrophobic and superoleophilic, the 2D membranes and 3D foams would be fabricated for practical applications in both ocean oil spillage and industry. In our previous paper.¹³ We have reported that the porous BNNSs have some advantages over existing technologies for clean-up of oil spillage due to the superhydrophobicity, ultralight, high resistance to oxidation, good chemical inertness, and easy

recyclability.^[19-24] Importantly, this nanostructured material exhibited a high absorption capacity up to 33 times its own weight in oils and organic solvents while repelling water.

Here we develop a new fabrication strategy of flexible and multifunctional porous BNNS based membranes and sponges with superhydrophobic and excellent flame retardant properties through an easy and versatile LBL assembly process. Both of 2D fabric membrane and 3D melamine sponge with low water adhesion, light weight, high porosity and robustness were used as a framework for porous BNNS coating, which overcome many fundamental limitations due to their commercial availabilities and low-cost. The new BNNS coated membranes and sponge exhibit ultrafast oil/water separation and simple operation. More importantly, as-fabricated BNNS-coated fabric membrane and melamine sponge absorb a broad range of oils and organic solvents with high selectivity, good recyclability, and excellent absorption capacities approaching 112 times its own weight as well as low risk of fire and explosion. The current study will contribute to the development of advanced oil-water separation materials, promising for water remediation. To our knowledge, these features are novel and have not been reported in the research literature.

2. Results and discussion

Figure 1a shows the chemical structures of the coating materials and the procedures to prepare superhydrophobic fabrics. In this study, a simple and effective LBL building blocks method^[25-27] was employed for coating treatment of fabrics and melamine sponge as described in Figure 1a. The assembly of BNNS and soft base materials is based on electrostatic interaction as driving force and it is easy for BNNS adsorbing on the modified surface of cotton fabric or melamine sponge by cationic polyelectrolyte as the first layer due to hydrogen bonding force. The base material was dipped into the solutions, alternating between the cationic polyelectrolyte and BNNS, with each cycle corresponding to one bilayer. A typical scanning electron microscope (SEM) images of the superhydrophobic fabric

and melamine sponge before and after coating treatment were shown in Figure 1b-f. Before the coating, both the fabric and melamine sponge had a smooth surface of a network framework. After LBL coating, a rough surface formed on both the fabric and melamine sponge, indicating that porous BNNSs were assembled on the frameworks of both fabric and melamine sponge. FTIR measurements provide a further evidence for the porous BNNSs coating existed, as shown in Figure S1. Compared with uncoated fabric and melamine sponge, the FTIR spectra of the porous BNNSs coated fabric and melamine sponge exhibited strong absorption peaks at 1371 and 791 cm^{-1} assigned to the B–N stretching (in-plane ring vibration) and B–N bending (out of plane vibration) (in Figure S1).¹³ Figure 1d and 1g display the wetting behaviors of water and oil on the surface of the cotton fabric and melamine sponge with and without coating, respectively. It can be seen that the uncoated fabric and melamine sponge can be easily wetted by both water (dyed pink colour) and oil (dyed blue colour) with a water CA of 0° and 115° , respectively. After LBL coating, drops of oil completely spread out and was infused into the pores of the fabric and melamine sponge, whereas several stationary water droplets rest on the surface of both fabric and melamine sponge with a water CA of 151° and 159° , respectively, resulting from the wettability property changed from hydrophobic to superhydrophobic. Moreover, the water adhesion test was carried out by using a water droplet as a probe water to contact and leave the surface of porous BNNSs coated 3D melamine sponge. As shown in Figure 1h, the water droplet can completely detach from the surface of porous BNNSs coated 3D melamine sponge without leaving any residue, indicating an extremely low water adhesion.

Since most oils and organic solvents are flammable liquid and could be extremely dangerous when ignited, high thermal stability and flame-retardant properties are another important criterion for practical applications. The combustion behaviour of both the porous BNNSs coated 2D fabric membrane and 3D melamine sponge were investigated by using butane blowtorch, as shown in Figure 2 and Movie S1 and S2. For comparison, the same sizes of uncoated fabric membrane and melamine

sponge were tested under the same condition. As shown in Figure 2a, a rapid and vigorous combustion was showed on the uncoated fabric membrane once being ignited, it completely burned out within only 5s. In contrast, the burning time took 9s after the flame on the porous BNNSs coated 2D fabric membrane (Figure 2b). Different from fabric, melamine sponge has an intrinsic flame-retardant property reported by Ruan et al.⁵ The flame on the uncoated melamine sponge is weak and finished within 9s, leaving one third of residue (Figure 2c). In contrast, there is no flame on the porous BNNSs coated 3D melamine sponge within the first 11s after being ignited (Figure 2d). Then, a weak flame occurs and was completely went out after 52s, leaving behind a shrinkage framework of porous BNNSs coated 3D melamine sponge, in Figure S2. The improvement of flame-retardant behavior in porous BNNSs coated sponges is at least 6 times more than uncoated melamine sponge, indicating its great potential of reducing the risk of fire and explosion due to the strong resistance to oxidation and excellent thermal stability of BN material. Therefore, the porous BNNSs coated fabric and 3D melamine sponge are ideal flame-retardant candidates for inflammable oils and organic solvents.

The compression experiments were performed to evaluate the mechanical performances of porous BNNSs coated 3D melamine sponge. As shown in Figure 3a, the coated sponge exhibit excellent elasticity and flexibility after the compressions even as high as 80%. Figure 3b shows the stress-strain curves of the porous BNNSs coated melamine sponge at a maximum strain of 20%, 40%, 60% and 80%, respectively. The coated sponge can easily recover without losing porous BNNSs compared to the original morphology after the compressions. Importantly, the stress-strain curve of the 1000th cycle is identical to that of the first cycle from 50% of compression strain, with the exception that the compressive stress decreases slightly to 88% of the original value (Figure 3c). The compressive durability endows the porous BNNSs coated melamine sponge with highly stable and robust against various harsh conditions, which is of great significance for practical applications.

Having demonstrated the peculiar wettability toward water and oil, porous BNNSs coated 2D fabric membrane is expected to efficiently separate or absorb insoluble oil from water. As a proof of concept, an oil/water separation experiment using the porous BNNSs coated 2D fabric as the separation membrane was setup as shown in Figure 4 and Figure S3. The porous BNNSs coated 2D fabric membrane was sandwiched between two glass tubes of the filter apparatus (Figure 4a). The floating pump oil (dyed by red colour)/water mixture of 75 mL ($V_{\text{oil}}/V_{\text{water}}: 1/2$) is added to the upper tube (Figure 4b). During the whole separation process, the 25 mL pump oil continuously permeates through the porous BNNSs coated 2D fabric membrane and drops into the beaker by gravity while the water is retained above the membrane due to the excellent superhydrophobicity and low water-adhesion features of the porous BNNSs coated 2D fabric membrane. More importantly, no water is observed in the oil or vice versa after separation, indicating the highly effective separation of the oil from water. The performance of the coated 2D fabric membrane for the underwater dichloromethane separation was also tested (in Figure S3). Once the dichloromethane (dyed by blue colour) contacts the membrane, the surface starts to reconfigure (Figure S3c). Within just 5 seconds, 50 mL dichloromethane quickly permeated through the membrane while the water was blocked. Moreover, after usage, the coated 2D fabric membrane can be easily regenerated by squeezing or solvent (e.g., acetone) washing and drying. No obvious change in filtration capacity was found after five cycles (Figure S4). The above results indicate that the porous BNNSs coated 2D fabric membrane has a great potential in the industrial application of oil-polluted water treatments.

The porous BNNSs coated 3D melamine sponge is another potential ideal absorbent for highly efficient separation of oil contaminants from water due to its surface superhydrophobicity, excellent absorption, light weight, high porosity, robustness, and good flame retardancy. The evolution of absorbing oil is shown in a series of photos in Figure 5. The underwater dichloromethane droplet dyed with blue colour was completely adsorbed by a piece of porous BNNSs coated 3D melamine sponge

within a few seconds, as shown in Figure 5a. When a piece of porous BNNSs coated 3D melamine sponge meets pump oil, which floats in water dyed with blue colour, the oil was sucked up into the sponge immediately, resulting in the clean water originally contaminated by the pump oil (in Figure 5b). The saturated sponge still floats on clean water surface due to its low density and superhydrophobic nature, which makes them easy to be collected, thereby indicating a facile and useful route for cleaning up oil spillage. As a comprehensive sorbent in practical requirements, it should not only effectively separate oil from water, but also possess excellent recyclability and recoverability of the absorbed oil simultaneously. The regeneration of the absorbed oil by porous BNNSs coated 3D melamine sponge was evaluated in this study (in Figure 5c). The pump oil can be easily recovered by simply squeezing an oil-absorbed porous BNNSs coated 3D melamine sponge due to its excellent robustness. Most importantly, the coated 3D melamine sponge almost unchanged after 10 cycles of the absorption/squeezing tests, which indicates a strong adherence of porous BNNSs to the 3D melamine sponge even after multiple extrusions. In addition, the porous BNNSs coated 3D melamine sponge also exhibits excellent absorption capacity towards a wide range of other organic solvents and oils (Figure 5d), such as ethanol and toluene, hexane, which are common oily pollutants in daily life or industry. The efficiency of absorption can be referred to weight gain (wt%) defined as the weight of absorbed substances per unit weight of porous BNNSs coated 3D melamine sponge. It was revealed that the porous BNNSs coated 3D melamine sponge exhibited excellent absorption capacity in the range 58–112 times its own. For instance, the absorption capacity towards pump oil, white oil and chloroform is close to 58×, 91× and 112×, respectively, which is much higher than porous sponge materials, including porous poly (dimethylsiloxane),^[28] polyurethane and iron oxide composites,^[26] graphene hydrogels,^[30] and nanocellulose aerogels,^[31] validating its great potential in water remediation. Importantly, it shows a similar absorption capacity (51×) of pump oil using the coated sponge after 1000 compressions cycles at 50% strain, which not only indicates the strong

adhesion between BNNS and the base material but also a promising materials with long cycle availability for oil-spill cleanup (Figure S5).

3. Conclusion

We reported a facile LBL assembled method to coat porous BNNSs onto the commercial cotton fabric and melamine sponge, changing the surface of fabric and melamine sponge framework to be superhydrophobicity and superoleophilicity. Meanwhile, the coated porous BNNSs membrane and sponge show improved flame-retardant upon exposure to flame due to the intrinsic high resistance to oxidation and flame retardancy of BNNSs. Moreover, the oil/water separation tests have been performed, indicating some outstanding features of coated materials: high separation efficiency (superhydrophobic), self-clean (low water adhesion), good adsorption capability (58–112 times its own weight), excellent recyclability (> 10 cycles), and simple recycling routes (robustness). We believe that such a simple, low cost, easily scale up, and effective assembly protocol will provide a new pathway for applications in oil-water separators and clean-up of large-area oil spills.

4. Experimental Section

Materials and chemicals: Poly dimethyl diallyl ammonium chloride (PDDA, 20 wt%, Mw ca. 100,000-200,000), chitosan, tetrahydrofuran, dichloromethane, pump oil, white oil, toluene, hexane and ethanol were obtained from Sigma-Aldrich (Australia). Sylgard 186 silicone elastomer base and Sylgard 186 silicone elastomer curing agent were purchased from Dow Corning (United States). All chemicals were used as received. Deionised water was used during all the experiments. Cotton fabric and melamine sponge were purchased from local stores.

Fabrication of super hydrophobic coating (Layer-by-Layer assemble): The cotton fabric was cut into $5 \times 5 \text{ cm}^2$ and followed by washing repeatedly with water and ethanol for three times and dried overnight at room temperature. The as-cleaned cotton fabric was then immersed in aqueous PDDA solution (10 mg/mL) for 30 min to render its surface positively charged, followed by rinsing with water and drying at room temperature.

For BNNS preparation, boron trioxide and guanidine hydrochloride in a 1:5 molar ratio were mixed in methanol (20 mL) to form a clear, colourless solution.[13] After 24 h under vigorous stirring, a white crystalline powder constituting a complex between boron trioxide and urea had formed. The resulting porous BNNS powder was placed in a quartz boat and heated up to $1100 \text{ }^\circ\text{C}$ at a rate of $10 \text{ }^\circ\text{C}/\text{min}$ and held for 2 h under a gas flow of mixture of 15% hydrogen in nitrogen. Finally, the as-synthesized BNNSs were used to prepare a 0.5 mg/mL porous BNNS aqueous suspension using probe ultrasonic treatment for 2 h at room temperature.

As-above modified cotton fabric was first soaked in 50 mL as-prepared BN aqueous suspension for 30 min under slowly stirring, ensuring the negatively charged porous BNNSs transferred onto the surface of the cotton fabric. The cotton fabric was removed from suspension when the electrostatic absorption completed, and hang-dried at room temperature. 1.25 mL of PDDA aqueous solution (10 mg/mL) was subsequently spread on the cotton fabric and also hang-dried at room temperature. Repeating the above 16 steps, positive PDDA and negative BNNSs with different layers alternatively formed on the surface of the cotton fabric. The PDDA layer provided a uniformly charged surface and facilitate subsequent electrostatic absorption of BNNSs, therefore the outermost surface layer was always BNNSs.

The surface coating of polydimethylsiloxane (PDMS) was carried out by a dip-coating method. The solution contained 0.909% on weight of bath (o.w.b.) of Sylgard 186 silicone elastomer base and

0.091% o.w.b. of Sylgard 186 silicone elastomer curing agent in tetrahydrofuran. Fabrics were squeezed by a Rapid PA0 pad mangle (Rapid Labortex Co. Ltd., Taiwan) after each bath to remove excess liquor. After padding the solution retained in the fabrics was around 100% w/w to ensure the loading amount of polydimethylsiloxane close to 1% on weight of fabric (o.w.f.). Finally, the treated fabric samples were cured at 65 °C for 5 h.

The porous BNNS-coated melamine sponge was fabricated in a similar way as cotton fabric with minor modification. To further enhance the positive charge of the surface, the melamine sponge was firstly modified by a cationic solution rather than PDDA. The cationic solution was prepared by adjusting the pH value of deionized water to 4 with acetic acid and then dissolving 0.2 wt% chitosan. This aqueous solution was magnetically stirred overnight as the chitosan was completely dissolved. The cleaned melamine sponge ($3 \times 3 \times 3 \text{ cm}^3$) was immersed into 20 mL above cationic solution for 30 min. Followed by rinsing with water and drying at room temperature, the sponge immersed into 20 mL porous BNNS aqueous suspension (0.5 mg/mL) for 30 min and then dried. The assembly of porous BNNSs and chitosan based on electrostatic interaction as a driving force was carried on repeatedly as the cotton fabric, and the outermost surface layer was also BNNSs. After coating the desired number of layers, sponge samples were coated by PDMS using the dip-coating method.

Characterizations: Scanning electron microscopy (SEM) was conducted on a Zeiss Supra 55V operating at 110 kV. Fourier transform infrared (FTIR) spectra were recorded on a Bruker Lumos FTIR Microscope (Billerica, MA, USA) in ATR mode, with an accumulation of 64 scans at 4 cm⁻¹ resolution. The contact angle was measured using a contact angle measurement system (CAM101, KSV Instruments Ltd). Fabric and foam flammability was evaluated through exposure to direct flame from a butane microtorch (Tradeflame, the approximate blue flame temperature is 2400 °F).

Supporting Information

This article is protected by copyright. All rights reserved.

Supporting Information is available from the Wiley Online Library or from the author.

Acknowledgements

Financial support from the Australian Research Council Discovery Program, the Australian Research Council Discovery Early Career Researcher Award scheme (DE150101617 and DE140100716), and Central Research Grant Scheme at Deakin University are acknowledged.

Received: ((will be filled in by the editorial staff))

Revised: ((will be filled in by the editorial staff))

Published online: ((will be filled in by the editorial staff))

References

- [1] T. Dalton, D. Jin, Extent and frequency of vessel oil spills in US marineprotected areas. *Mar. Pollut. Bull.* **2010**, *60*, 1939–1945.
- [2] J. Aurell, B. K. Gullet, Aerostat sampling of PCDD/PCDF emissions from thegulf oil spill in situ burns. *Environ. Sci. Technol.* **2010**, *44*, 9431–9437.
- [3] J. W. Doerffer, Oil spill response in the marine environment, *Pergamon Press*. New York, **1992**.
- [4] C. Wu, C. Maurer, Y. Wang, S. Xue, D. L. Davis, Water pollution and human health in China. *Environ. Health Perspect.* **1999**, *107*, 251-256.

This article is protected by copyright. All rights reserved.

- [5] C. P. Ruan, K. Ai, X. V. Li, L. H. Lu, A superhydrophobic sponge with excellent absorbency and flame retardancy. *Angew. Chem. Int. Ed.* **2014**, *53*, 5556–5560.
- [6] J. C. Gu, P. Xiao, Y. J. Huang, J. W. Zhang, T. Chen, Controlled functionalization of carbon nanotubes as superhydrophobic material for adjustable oil/water separation. *J. Mater. Chem. A* **2015**, *3*, 4124-4128.
- [7] <http://oilguard.org/thesolution/>, (accessed April 2011).
- [8] <http://www.youtube.com/watch?v=4KDo1I1M9Zk>, (accessed April 2011).
- [9] T. Shimizu, S. Koshiro, Y. Yamada, K. Tada, Effect of cell structure on oil absorption of highly oil absorptive polyurethane foam for on-site use. *J. Appl. Polymer Sci.* **1997**, *65*, 179-186.
- [10] Y. S. Oh, J. Maeng, S. J. Kim, Use of microorganism-immobilized polyurethane foams to absorb and degrade oil on water surface. *Appl Microbiol Biotechnol.* **2000**, *54*, 418-423.
- [11] D. Liu, W. W. Lei, Y. Chen, Scalable production of wrinkled and few-layered graphene sheets and their use for oil and organic solvents absorption. *Phys. Chem. Chem. Phys.* **2015**, *17*, 6913-6918.
- [12] D. Liu, L. He, W. W. Lei, K. D. Klika, L. X. Kong, Y. Chen, Multifunctional polymer/porous boron nitride nanosheets membranes for superior trapping emulsified oils and organic molecules. *Advanced. Materials. Interfaces* **2015**, *2*, 1500228.
- [13] W. W. Lei, D. Portehault, D. Liu, S. Qin, Y. Chen, Porous boron nitride nanosheets for effective water cleaning. *Nat. Comm.* **2013**, *4*, 1777.

- [14] W. Xie, M. Zhang, D. Liu, W. Lei, L. Sun, X. Wang, Photocatalytic TiO₂/porous BNNSs composites for simultaneous LR2B and Cr (VI) removal in wool dyeing bath. *J. Photochem. Photobiol. A: Chem.* **2017**, *333*, 165-173.
- [15] D. Liu, M. W. Zhang, W. J. Xie, L. Sun, Y. Chen, W. W. Lei, Efficient photocatalytic reduction of aqueous Cr (VI) over porous BNNSs/TiO₂ nanocomposites under visible light irradiation. *Catalysis Sci. & Tech.* **2016**, *6*, 8309-8313.
- [16] D. D. Nguyen, N. H. Tai, S. B. Lee, W. S. Kuo, Superhydrophobic and superoleophilic properties of graphene-based sponges fabricated using a facile dip coating method. *Energy Environ. Sci.* **2012**, *5*, 7908–7912.
- [17] A. Li, H. X. Sun, D. Z. Tan, W. J. Fan, S. H. Wen, X. J. Qing, G. X. Li, S. Y. Li, W. Q. Deng, Superhydrophobic conjugated microporous polymers for separation and adsorption. *Energy Environ. Sci.* **2011**, *4*, 2062-2065.
- [18] X. C. Gui, J. Q. Wei, K. L. Wang, A. Y. Cao, H. W. Zhu, Y. Jia, Q. K. Shu, D. H. Wu, Carbon nanotube sponges. *Adv. Mater.* **2010**, *22*, 617-621.
- [19] Z. G. Chen, J. Zou, G. Liu, F. Li, Y. Wang, L. Wang, X. L. Yuan, T. Sekiguchi, H. M. Cheng, G. Q. Lu, Novel boron nitride hollow nanoribbons. *ACS Nano.* **2008**, *2*, 2183–2191.
- [20] L. Song, L. J. Ci, H. Lu, P. B. Sorokin, C. H. Jin, J. Ni, A. G. Kvashnin, D. G. Kvashnin, J. Lou, B. I. Yakobson, P.M. Ajayan, Large scale growth and characterization of atomic hexagonal boron nitride layers. *Nano Lett.* **2010**, *10*, 3209–3215.

- [21] C. Y. Zhi, Y. Bando, C. C. Tang, H. Kuwahara, Golberg, D. Large-scale fabrication of boron nitride nanosheets and their utilization in polymeric composites with improved thermal and mechanical properties. *Adv. Mater.* **2009**, *21*, 2889-2893.
- [22] R. Gao, L. W. Yin, C. X. Wang, Y. X. Qi, N. Lun, L. Y. Zhang, Y. X. Liu, L. Kang, X. F. Wang, High-yield synthesis of boron nitride nanosheets with strong ultraviolet cathodoluminescence emission. *J. Phys. Chem. C.* **2009**, *113*, 15160–15165.
- [23] X. L. Meng, X. L. Meng, N. Lun, Y. Q. Qi, J. Q. Bi, Y. X. Qi, H. L. Zhu, F. D. Han, Y. J. Bai, L. W. Yin, R.H. Fan, Low-temperature synthesis of meshy boron nitride with a large surface area. *Eur. J. Inorg. Chem.* **2010**, *2010*, 3174–3178.
- [24] W. W. Lei, V. Mochalin, D. Liu, S. Qin, Y. Gogotsi, Y. Chen, One-step exfoliation and functionalization of boron nitride: colloidal solutions, ultralight aerogels and freestanding membranes, *Nat. Comm.* **2015**, *6*, 8849.
- [25] J. C. Yang, Z. J. Cao, Y. Z. Wang, D. A. Schiraldi, Ammonium polyphosphate-based nanocoating for melamine foam towards high flame retardancy and anti-shrinkage in fire. *Polymer*, **2015**, *66*, 86-93.
- [26] Y. Kim, J. Zhu, B. Yeom, M. D. Prima, X. Su, J. G. Kim, S. J. Yoo, C. Uher, N. A. Kotov, Stretchable nanoparticle conductors with self-organized conductive pathways. *Nature*, **2013**, *500*, 59-63.
- [27] J. Zhu, H. Zhang, N. A. Kotov, Thermodynamic and structural insights into nanocomposites engineering by comparing two materials assembly techniques for graphene. *ACS Nano* **2013**, *7*, 4818-4829.

- [28] A. J. Zhang, M. J. Chen, C. Du, H. Z. Guo, H. Bai, L. Li, Poly (dimethylsiloxane) oil absorbent with a three-dimensionally interconnected porous structure and swellable skeleton. *ACS Appl. Mater. Interfaces*, **2013**, *5*, 10201-10206.
- [29] P. Calcagnile, D. Fragouli, I. S. Bayer, G. C. Anyfantis, L. Martiradonna, P. D. Cozzoli, R. Cingolani, A. Athanassiou, Magnetically driven floating foams for the removal of oil contaminants from water. *ACS Nano* **2012**, *6*, 5413-5419.
- [30] H. C. Bi, X. Xie, K. B. Yin, Y. L. Zhou, S. Wan, L. B. He, F. Xu, F. Banhart, L. T. Sun, R. S. Ruoff, Spongy graphene as a highly efficient and recyclable sorbent for oils and organic solvents. *Adv. Funct. Mater* **2012**, *22*, 4421-4425.
- [31] J. T. Korhonen, M. Kettunen, R. H. A. Ras, Ikkala, O. Hydrophobic nanocellulose aerogels as floating, sustainable, reusable, and recyclable oil absorbents. *ACS Appl. Mater. Interfaces*, **2011**, *3*, 1813-1816.

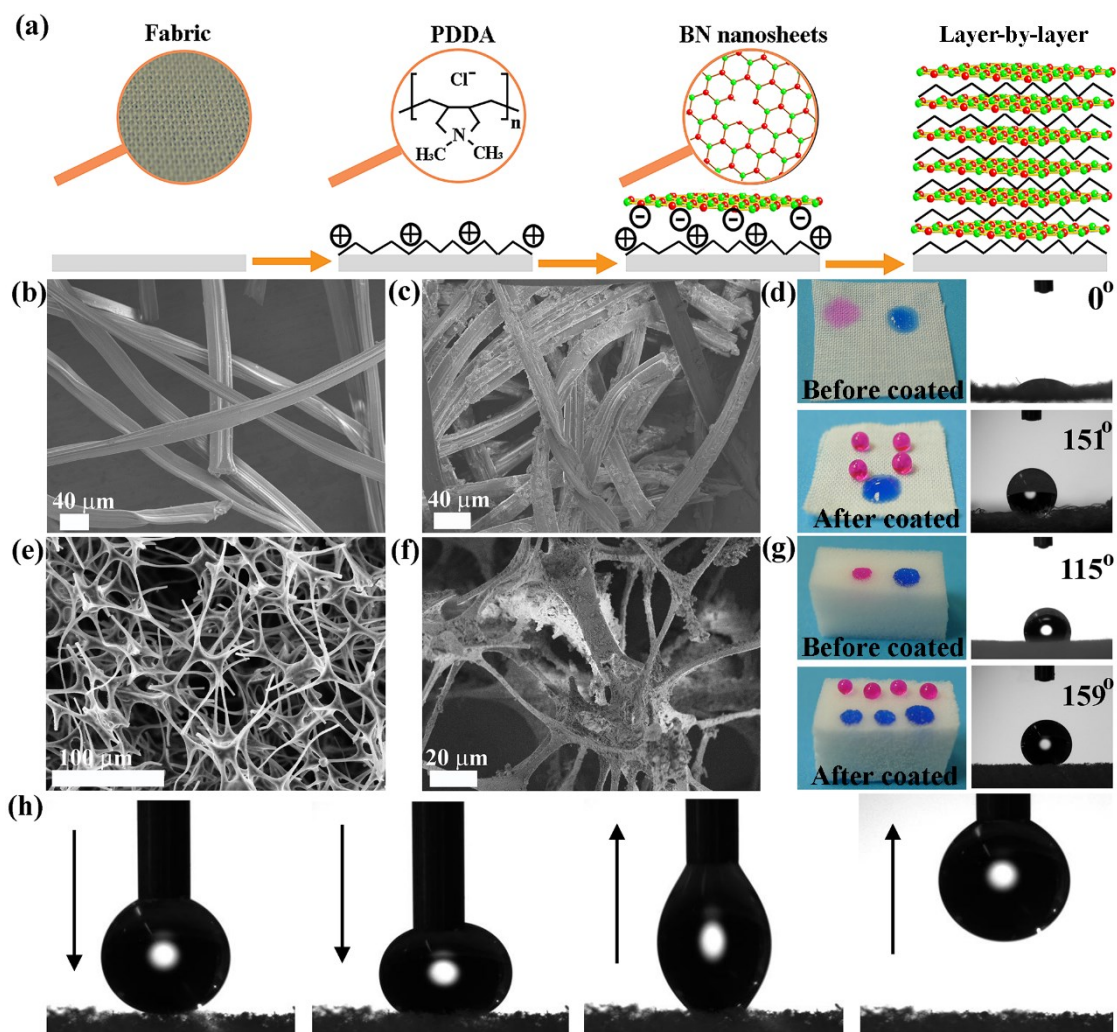


Figure 1. (a) Chemical structures of layer-by-layer materials and procedure for LBL treatment, (b) and (c) SEM images of cotton fabrics before and after PDDA and porous BNNSs LBL coating, (d) images of dyes water (red) and oil drops (blue) on the uncoated (upper) and coated (under) fabric, and their water contact-angle images. (e, f) SEM images of melamine sponge before and after PDDA and porous BNNSs LBL coating. (g) Photographs of dyed water (red) and oil drops (blue) on the uncoated (upper) and coated (under) melamine sponge, and their water contact-angle images. (h) Photographs of the dynamic water-adhesion measurements on the coated melamine sponge. A water

droplet was used as the detecting probe to contact the surface and then leave. The coated melamine sponge exhibits excellent low affinity to the water droplet.

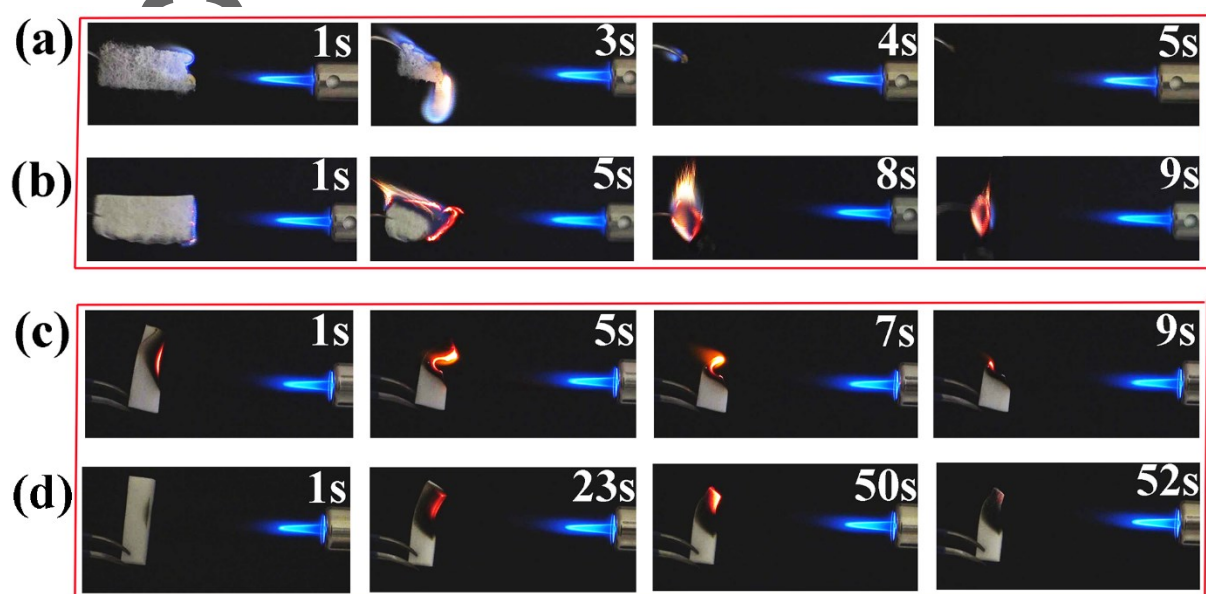


Figure 2. The combustion process of (a) uncoated 2D fabric membrane, (b) porous BNNSs coated 2D fabric membrane, (c) uncoated 3D melamine sponge, (d) porous BNNSs coated 3D melamine sponge using a blowtorch.

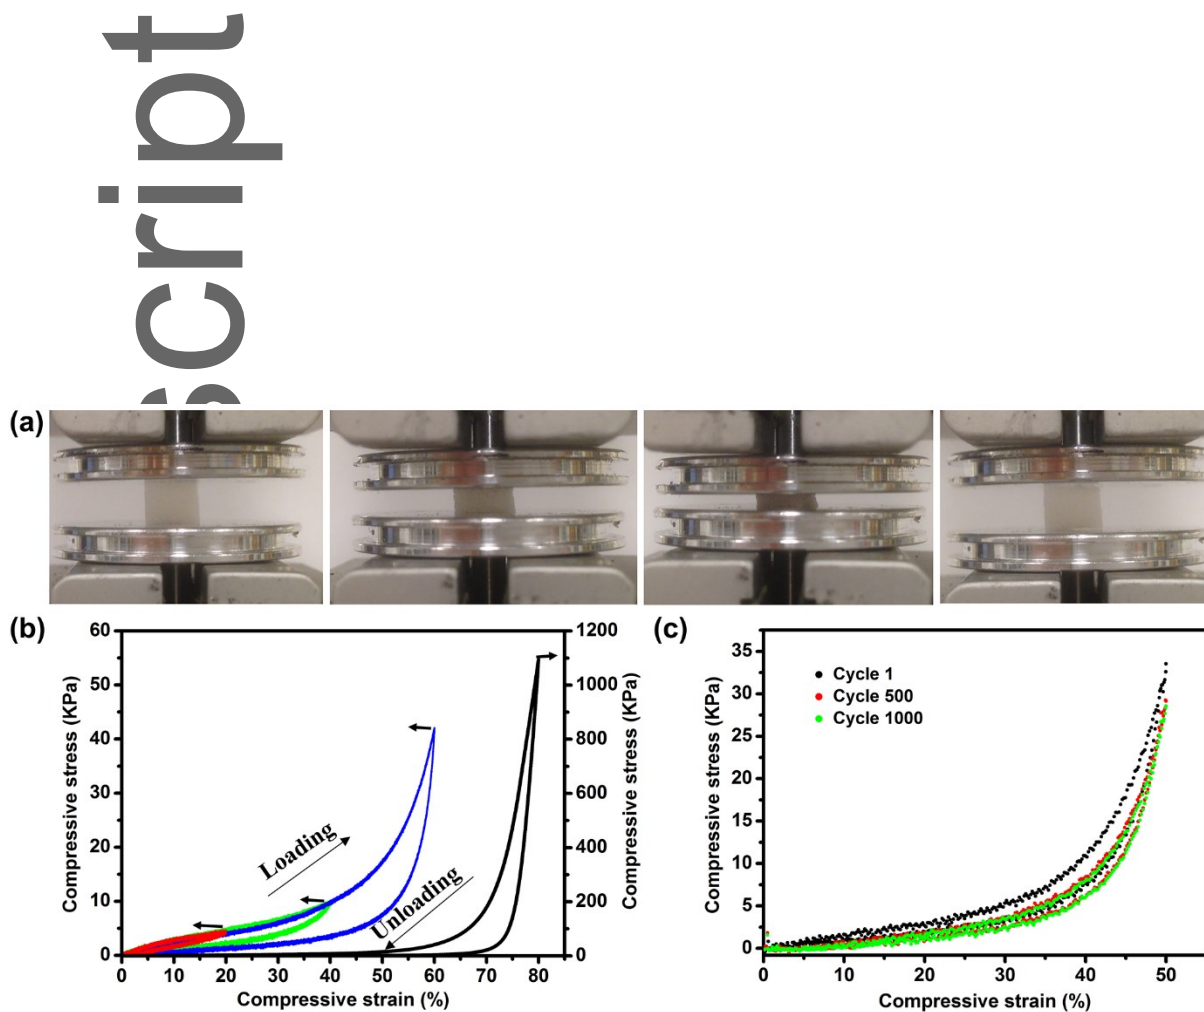


Figure 3. (a) The compression-recovery process showing that the porous BNNSs coated 3D melamine sponge recovers their original shape after compression by more than 80%. (b) Stress-strain curves of porous BNNSs coated 3D melamine sponge with a different set strain of 20, 40, 60 and 80%, respectively. (c) The compressive stress-strain curves of the porous BNNSs coated 3D melamine sponge over 1000 cycles at 50% strain.

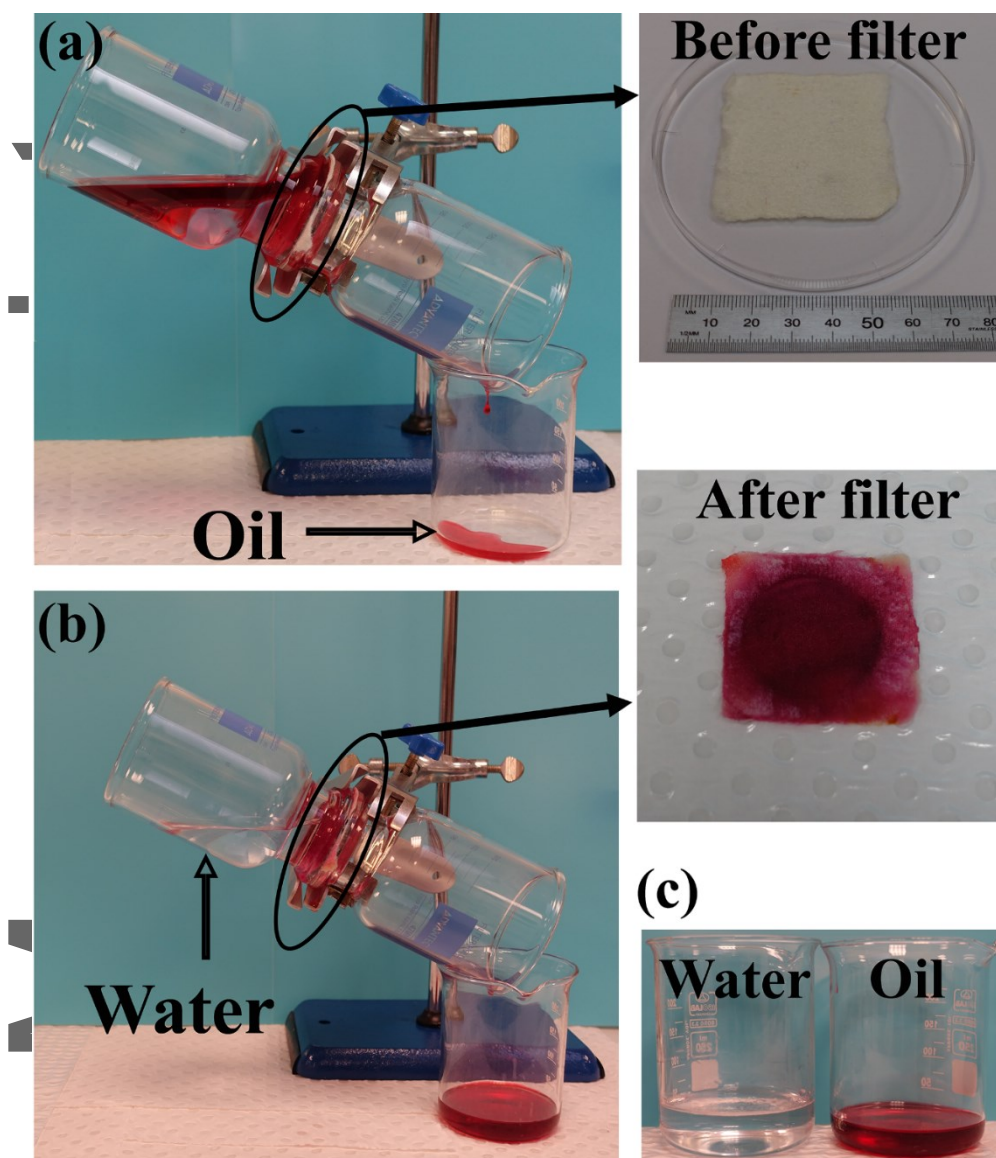


Figure 4. Oil/water separation studies of the porous BNNSs coated 2D fabric membrane. (a) the mixture of pump oil (dyed by red colour) and water was put into the upper glass tube, the zoom in shows the coated membrane was fixed between two glass tubes, (b) pump oil permeated through the coated membrane, while the water was repelled and kept in the upper glass tube, the zoom in shows the coated membrane after oil/water separation, (c) Photograph shows collected water and pump oil after the separation.

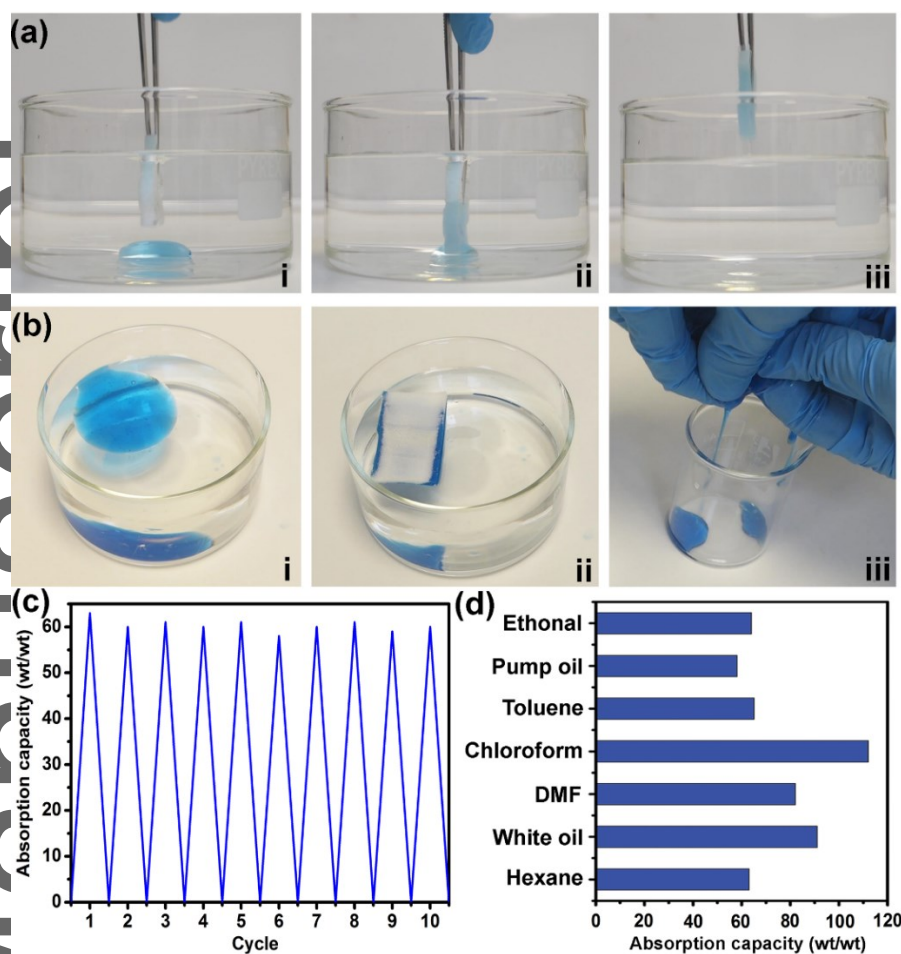



Figure 5. (a) Photographs showing the underwater adsorption of dichloromethane (dyed by blue colour) by a piece of porous BNNSs coated 3D melamine sponge. (b) Photographs showing the absorption/squeezing process of pump oil (dyed by blue colour). (c) The pump oil absorption capacity of the porous BNNSs coated 3D melamine sponge recycled via squeezing methods. (d) The adsorption capacity of porous BNNSs coated 3D melamine sponge towards a variety of organic solvents and oils.

Porous Boron Nitride Coated Multifunctional Materials are synthesized via a layer-by-layer assemble method. The multifunctional materials exhibit high oil/water separation efficiency, selective absorption capacity of oil and organic solvents, excellent recyclability, and efficient flame-retardant effect, which enable the materials to satisfy various practical water cleaning applications.

Keyword: Boron nitride nanosheet, layer-by-layer, oil absorption, melamine sponge, flame-retardant

D. Liu, M. W. Zhang, L. He, Y. Chen, and W. W. Lei**

Layer-By-Layer Assembly Fabrication of Porous Boron Nitride Coated Multifunctional Materials for Water Cleaning

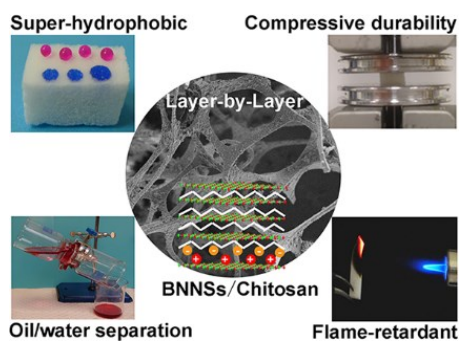

This article is protected by copyright. All rights reserved.