

Author Manuscript

Title: Achieving Balanced Energetics Through Cocrystallization

Authors: Michael Kevin Bellas; Adam J. Matzger, Dr.

This is the author manuscript accepted for publication and has undergone full peer review but has not been through the copyediting, typesetting, pagination and proofreading process, which may lead to differences between this version and the Version of Record.

To be cited as: 10.1002/anie.201908709

Link to VoR: <https://doi.org/10.1002/anie.201908709>

Achieving Balanced Energetics Through Cocrystallization

Michael K. Bellas and Adam J. Matzger*

Abstract: Achieving energetic materials with a balanced ratio of oxidant to fuel is a challenge that has been difficult to meet through molecular synthesis. The alternative approach, composite formulation, fails to achieve intimate association of the components to the detriment of performance. Herein, the energetic oxidizer ammonium dinitramide (ADN) is combined with fuel-rich pyrazine-1,4-dioxide via cocrystallization. The result is a material with a balanced oxidant/fuel ratio in which the components maintain intimate association. The material exhibits desirable physical and energetic properties which are much improved over ADN and comparable to contemporary energetics.

The development of novel energetic materials (EMs) traditionally progresses via two pathways: the synthetic combination of fuel (hydrocarbon component) and oxidizing organic functional groups (NO₂, ONO₂, etc.) on a molecular scaffold, or composite formulation whereby separate oxidizer and fuel components are combined in a physical mixture.^[1] The ratio of oxidant to fuel is quantified as oxygen balance (*OB*). *OB* describes the excess (+), or deficiency (-), of oxidant, relative to fuel, in a system, and is the ratio of oxygen present to that required for the complete conversion of the material to neutral gaseous molecules (e.g. H₂O, CO₂, CO, etc.) expressed as %.^[1] Ideally an EM would be balanced (*OB* = 0) and the oxidizing and fuel components would be in intimate association ensuring optimal detonation/combustion processes. Achieving balanced molecular EMs is rare and the necessarily heterogeneous nature of physical mixtures precludes intimate contact between oxidizing and fuel moieties. Cocrystallization, which is the combination within a crystal lattice of two or more compounds that are solid at ambient in a defined stoichiometry, affords the opportunity to address this need in the field.^[2]

Although fuel rich EMs are common, there are relatively fewer oxidant-rich molecules to choose from in cocrystal design. Ammonium dinitramide (ADN), *OB* = +26%, was selected as the oxidizing cofomer because it has demonstrated promise as a replacement for ammonium perchlorate (AP), *OB* = +34%, in contemporary composite propellant formulations.^[3] ADN has failed to see wide-spread implementation due to issues with processing, hygroscopicity, and thermal stability.^[4] As cocrystallization has proved effective at modulating bulk materials properties in various fields including drug delivery,^[5] non-linear optics,^[6] organic electronics,^[7] and EMs^[8] this presents a promising route to balanced EMs while concomitantly redressing ADNs undesirable properties. However, whereas cocrystallization is now widely studied, cocrystallization between neutral and ionic cofomers has yet to significantly impact areas

outside of pharmaceuticals.^[5] This may be due to the difficulties in a priori cocrystal design or the added influence of strong coulombic forces arising from ion-ion interactions. These issues are compounded in EMs by the general lack of supramolecular synthons typically employed in cocrystal design.^[9] Few examples exist outside of energetic salt:crown ether complexes^[10] and the very recent report of an hexanitrohexaazaisowurtzitane (CL-20):1-amino-3-methyl-1,2,3-triazolium nitrate cocrystal.^[11] The lack of progress in this area is indicative of the need to develop new cocrystal design strategies applicable to energetic salt systems.

Developing a design strategy began with identifying those interactions in ADN that could be perturbed, and therefore exploited, by the introduction of a cofomer. In doing so, we identified the ammonium ion (NH₄⁺), with its relatively localized charge and hydrogen bond (H-bond) donating ability, as an attractive target. Cofomer selection was confined to those compounds bearing strong H-bond accepting functionalities. Among these, *N*-oxides, displaying formal charge separation, were noted for their lack of basicity (protonated pyridine-*N*-oxide pK_a = 0.79)^[12] and a search of the Cambridge Structural Database (CSD) revealed two *N*-oxide:NH₄⁺ salt cocrystals.^[13] These cocrystals both utilize pyridyl-*N*-oxide acceptors, bipyridine dioxide (BPDO) and trans-bis(4-pyridyl)ethylenedioxide (BPED); the use of a bis-accepting cofomer represents a second element of our design strategy. A cofomer capable of participating in H-bonding interactions with two NH₄⁺ could yield a cocrystal with a 2:1 stoichiometry (ADN:cofomer) allowing consideration of more fuel-rich cofomers. The final design requirement was that the *OB* of the cofomer be complimentary to ADN such that an oxygen-balanced EM may be attained. In discussing *OB* it is important to note that experimental conditions affect the ratio of product gases; as such, for explosives it is customary to consider all carbon as being converted to CO₂ whereas the *OB* of propellants is often discussed in terms of CO as this is the favored product under relevant conditions.^[14] This final requirement excludes BPDO and BPED from consideration as large, carbon rich backbones would deleteriously affect the *OB* of any ADN cocrystal. Thus, cofomer selection focused on small, strong bis-acceptors. With these design principles in place, pyrazine-1,4-dioxide (PDO) was identified as a potential cofomer. There were, however, initial concerns given that PDO is expected to be a weaker H-bond acceptor than either BPDO or BPED. This is evident through comparison of electrostatic potential maps (EPMs) for the bis-acceptors (Figure 1). EPMs are visual representations of charge distribution upon an

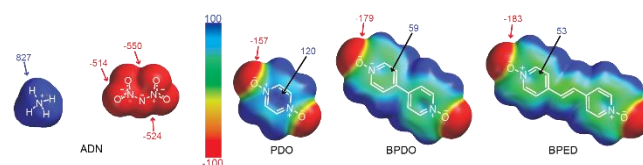


Figure 1. Structures and EPMs of ADN and bis-acceptors. Values given are in kJ/mol and represent local electrostatic minima, $V_{s,min}$, (in red), and maxima, $V_{s,max}$, (in blue); calculated using B3LYP/6-31+G**.

Prof. A. J. Matzger
Department of Chemistry, University of Michigan
930 North University Avenue, Ann Arbor, MI 48109-1055 (USA)
E-mail: matzger@umich.edu

Supporting information for this article is given via a link at the end of the document.

isodensity surface and using EPMs to rank or, in some cases, predict intermolecular interactions in cocrystals is meeting with success for a variety of systems.^[15] Beyond the difference in electrostatic potential at the *N*-oxide functionalities of the bis-acceptors, we also note the significant differences among the electron deficient π systems. Despite these differences, PDO proved effective at competing with the dinitramide ion for H-bonding interactions with NH_4^+ and a balanced **ADN-PDO** cocrystal was obtained.

ADN-PDO is accessible via solution methods or liquid assisted grinding. **ADN-PDO** is distinguished from the pure cocomers by Raman spectroscopy and bulk phase purity was verified using PXRD, which also allowed for the exclusion of false-positives resulting from polymorphism (see SI).^[16] The Raman spectra show differences in the signals arising from all modes for both ADN and PDO (see SI). Additionally, the N-H stretch of NH_4^+ shifts from 3163 to 3178 cm^{-1} , suggesting a stronger covalent N-H bond in NH_4^+ contained in **ADN-PDO** than in single-component ADN. This change in the covalent bond strength is significant as the first step in the decomposition of ADN is believed to be a proton transfer from NH_4^+ to the dinitramide ion.^[4]

Single crystal X-ray diffraction of **ADN-PDO** reveals 0.5 PDO and 1 ADN unit in the asymmetric unit. **ADN-PDO** exhibits a room temperature (RT) crystallographic density of 1.778 g/cm^3 , compared to 1.808 and 1.597 g/cm^3 for ADN and PDO, respectively. The RT structure of ADN was determined here as only a low temperature structure is available in the CSD.^[17] The packing of the ADN and PDO units involves two unique H-bonding interactions between *N*-oxide oxygen atoms and NH_4^+ , the shortest of which at an $^+\text{N}-\text{O}\cdots\text{NH}_4^+$ contact distance of 2.830 Å (Figure 2). This is comparable to the shortest $\text{NO}_2\cdots\text{NH}_4^+$ interaction distance in the crystal structure of ADN at 2.888 Å. NH_4^+ also participates in a bifurcated H-bonding interaction with one nitro group of the closest dinitramide ion at $\text{NO}_2\cdots\text{NH}_4^+$ distances of 3.110 and 3.007 Å. The second nitro group of the dinitramide ion participates in a nitro- π interaction at $\text{NO}_2\cdots\pi$ (oxygen to centroid) distances of 3.251 and 3.253 Å. This establishes the central repeating motif of the structure (blue shaded region, Figure 2a). The PDO molecule participates in two nitro- π and two $^+\text{N}-\text{O}\cdots\text{NH}_4^+$ interactions (orange shaded region, Figure 2a). This arrangement results in a 2D sheet where each NH_4^+ sits in an oxygen rich pocket (red shaded region, Figure 2a). In this pocket, six oxygen atoms are directed towards NH_4^+ which sits only 0.700 Å off-center (centroid $\cdots\text{NH}_4^+$) within this cavity- in the direction of the $^+\text{N}-\text{O}\cdots\text{NH}_4^+$ interaction. Additionally, NH_4^+ sits 0.292 Å above a mean plane connecting these six oxygen atoms with three hydrogen atoms directed towards this mean plane. The 2D sheets (Figure 2a) stack (Figure 2b,c) via H-bonding interactions between NH_4^+ and *N*-oxide oxygens in adjacent sheets at an $^+\text{N}-\text{O}\cdots\text{NH}_4^+$ distance of 2.919 Å.

As internal order gives rise to external features, cocrystallization results in unique morphology. The morphology

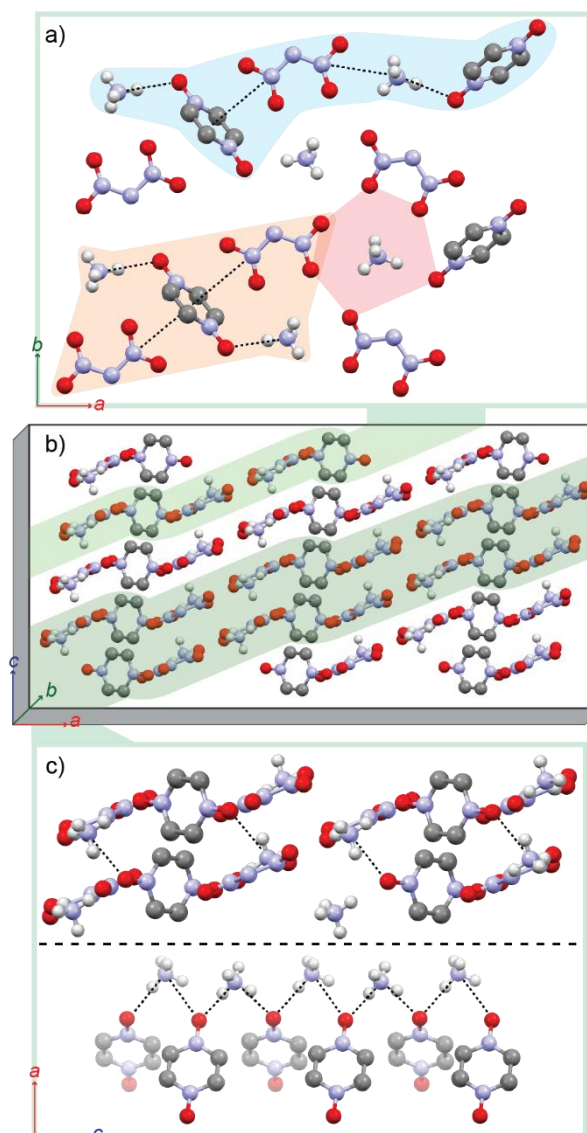


Figure 2. Crystal packing of **ADN-PDO**. a) intermolecular/ionic interactions in two dimensions (2D), b) stacking of the 2D sheets formed from the interactions displayed in panel (a), c) interactions between 2D sheets.

of ADN is either needle-like or rod-like, presenting processing challenges which can compromise performance.^[18] These issues are commonly addressed by morphology altering processes post-synthesis to produce ADN with an aspect ratio approaching one.^[18] The morphology of **ADN-PDO** (Figure 3) much improved relative to ADN, displaying an aspect ratio closer to unity without additional post-synthesis processing and would lend itself well to dense packing in application.

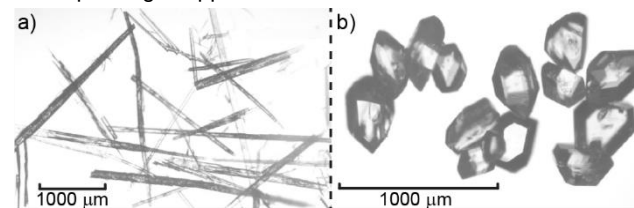


Figure 3. a) Needle-like ADN, b) **ADN-PDO** crystals.

Thermal stability of EMs is an important consideration, often affecting processing and application. Thermal analysis of **ADN-PDO** was conducted by differential scanning calorimetry (DSC) and thermogravimetric analysis (TGA) (Figure 4). By DSC, **ADN-PDO** begins melting at 114 °C an increase of >20 °C relative to ADN (91.4 °C). With continued heating the decomposition of **ADN-PDO** commences at 176 °C, a 16 °C higher value than ADN (160 °C).

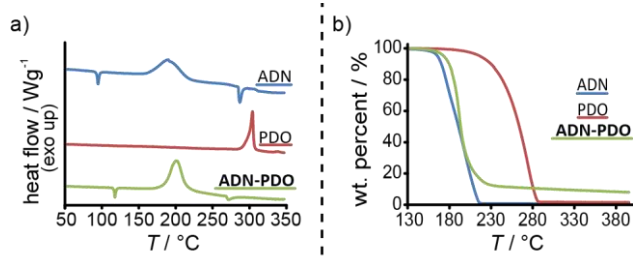


Figure 4. DSC thermograms and TGA traces, a) and b) respectively, for ADN (blue), PDO (red), and **ADN-PDO** (green).

An additional barrier to application of ADN is hygroscopicity. The effect of cocrystallization on the hygroscopicity of ADN was evaluated by determining the critical relative humidity (CRH) for **ADN-PDO**. The CRH is the minimum relative humidity at which a salt will deliquesce (Figure 5). ADN has a CRH of 53.5% at 25 °C and is more hygroscopic than AP (see SI). Attempts to address this issue in the past have involved coating ADN in inert polymer binder, or the addition of chemical stabilizers; neither method, however, addresses the fundamental thermodynamic issue of affinity for water. Cocrystallization directly addresses the affinity of ADN for water by introducing intermolecular/ionic hydrogen bonding interactions to stabilize the material. **ADN-PDO** exhibits a much improved CRH of 79.5% at 25 °C.

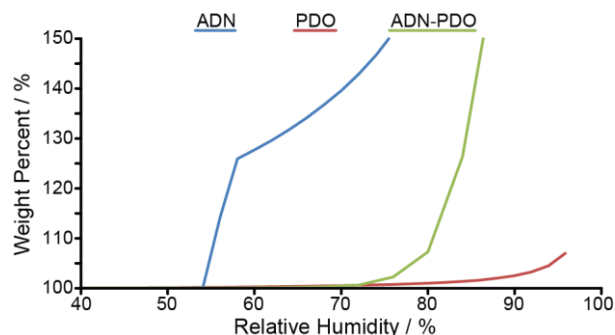


Figure 5. Dynamic vapor sorption traces for ADN (blue), PDO (red), and **ADN-PDO** (green).

Our design strategy emphasizes the need to obtain balanced EMs and several criteria are used to describe/quantify energetic performance. Important considerations for EMs, in general, include detonation velocity (D_v) and detonation pressure (P_{cj}) while specific impulse (I_{sp}) is an important metric used in evaluating propellant performance. **ADN-PDO** is expected to exhibit superior D_v and P_{cj} , relative to both AP and ADN, and approach that of the high explosives triaminotrinitrobenzene (TATB) and cyclotrimethylenetrinitramine (RDX)- a balanced EM (Table 1). The I_{sp} of **ADN-PDO** is dramatically increased

(+27.6%) relative to ADN, and **ADN-PDO** based composite propellant systems are comparable to AP based systems used in the space shuttle and Ariane-5 rocket systems as well as similarly oxygen balanced systems based on RDX (see SI). This represents, to our knowledge, a unique synergy achieved by cocrystallizing a positive *OB* EM with a negative *OB* cofomer.

Table 1: Energetic performance criteria of contemporary EMs and **ADN-PDO**; values calculated using the thermochemical code *CHEETAH.7.0* (see SI).

EM	I_{sp} / s	P_{cj} / GPa	D_v / kms^{-1}	$OB_{(CO)}$	$OB_{(CO_2)}$
AP	157	17.7	6.43	+34%	+34
ADN	202	28.9	8.17	+26%	+26
ADN-PDO	259	33.3	8.94	0%	-18
TATB	200	34.6	8.46	-19%	-56
RDX	266	35.8	8.84	0%	-58

A design strategy utilizing cocrystallization has been developed and successfully applied to produce an oxygen-balanced EM based on ADN. This affords a synthetic method to achieve oxygen balanced energetic materials which redresses some of the shortcomings of both composite formulation and molecular synthesis approaches while achieving their desirable characteristics. **ADN-PDO** shows promise as an EM and may find application as an explosive, or in aluminized propellant formulations. Cocrystallization has successfully redressed many of the barriers to the implementation of ADN in energetic systems and **ADN-PDO** represents, to our knowledge, the first ADN cocrystal to accomplish this while preserving performance. This methodology will be applied to the broader class of energetic ammonium salts in efforts to achieve EMs that can act as energetic oxidizers.

Acknowledgements

Initial support for this work was provided by the Army Research Office via a Multidisciplinary University Research Initiative (grant number: W911NF-13-1-0387); This material is based upon research supported by, or in part by, the U. S. Office of Naval Research under award number N00014-19-1-2086. We thank Ren Wiscons for help with crystal structure determination.

Keywords: ammonium dinitramide • cocrystal • crystal engineering • energetics • noncovalent interactions

- [1] T. M. Klapötke, *Chemistry of High-Energy Materials*, 2 ed., de Gruyter, Berlin, **2012**.
- [2] J. Zhang, J. M. Shreeve, *Cryst. Eng. Comm.* **2016**, *18*, 6124.
- [3] M. B. Talawar, R. Sivabalan, T. Mukundan, H. Muthurajan, A. K. Sikder, B. R. Gandhe, A. Subhananda Rao, *J. Hazard. Mater.* **2009**, *161*, 589.
- [4] S. Löbbbecke, H. H. Krause, A. Pfeil, *Propellants Explos. Pyrotech.* **1997**, *22*, 184.
- [5] D. J. Berry, J. W. Steed, *Adv. Drug. Deliv. Rev.* **2017**, *117*, 3.
- [6] W. Zhu, L. Zhu, L. Sun, Y. Zhen, H. Dong, Z. Wei, W. Hu, *Angew. Chem. Int. Ed.* **2016**, *55*, 14023.
- [7] a) R. A. Wiscons, N. R. Goud, J. T. Damron, A. J. Matzger, *Angew. Chem. Int. Ed.* **2018**, *57*, 9044; b) Y. Huang, Z. Wang, Z. Chen, Q. Zhang, *Angew. Chem. Int. Ed.* **2019**, *58*, 2.
- [8] O. Bolton, A. J. Matzger, *Angew. Chem. Int. Ed.* **2011**, *50*, 8960.

- [9] a) G. R. Desiraju, *Angew. Chem. Int. Ed.* **1995**, *34*, 2311; b) C. B. Aakeröy, A. M. Beatty, B. A. Helfrich, *Angew. Chem. Int. Ed.* **2001**, *40*, 3240.
- [10] a) T. Lee, J. W. Chen, H. L. Lee, T. Y. Lin, Y. C. Tsai, S. Cheng, S. Lee, J. Hu, C. L., *Chem Eng J.* **2013**, *225*, 809; b) Y. Wang, Y. Ma, H. Li, Y. Yu, Z. Yang, *Chin. J. Energ. Mater.* **2018**, *26*, 545; c) M. Cheng, X. Liu, Q. Luo, X. Duan, C. Pei, *Cryst. Eng. Comm.* **2016**, *18*, 8487.
- [11] X. Zhang, S. Chen, Y. Wu, S. Jin, X. Wang, Y. Wang, F. Shang, K. Chen, J. Du, Q. Shu, *Chem. Commun.* **2018**, *54*, 13268.
- [13] B. Ma, H. Sun, S. Goa, *Chem. Commun.* **2003**, *0*, 2164.
- [14] M. A. Kettner, T. M. Klapötke, in *Chemical Rocket Propulsion A Comprehensive Survey of Energetic Materials* (Ed.: L. T. DeLuca), Springer, web, **2017**.
- [15] a) D. Musumeci, C. A. Hunter, R. Prohens, S. Scuderi, J. F. McCabe, *Chem. Sci.* **2011**, *2*, 883; b) R. V. Kent, R. A. Wiscons, P. Sharon, D. Grinstein, A. A. Frimer, A. J. Matzger, *Cryst. Growth Des.* **2018**, *18*, 219.
- [16] R. A. Wiscons, A. J. Matzger, *Cryst. Growth Des.* **2017**, *17*, 901.
- [17] R. Gilardi, J. Flippen-Anderson, C. George, R. J. Butcher, *J. Am. Chem. Soc.* **1997**, *119*, 9411.
- [18] M. Y. Nagamachi, J. I. S. Oliveira, A. M. Kawamoto, R. C. L. Dutra, *J. Aerosp. Technol. Manag.* **2009**, *1*, 153.

Entry for the Table of Contents (Please choose one layout)


Layout 2:

COMMUNICATION

Michael K. Bellas and Adam J. Matzger*

Page No. – Page No.

Title

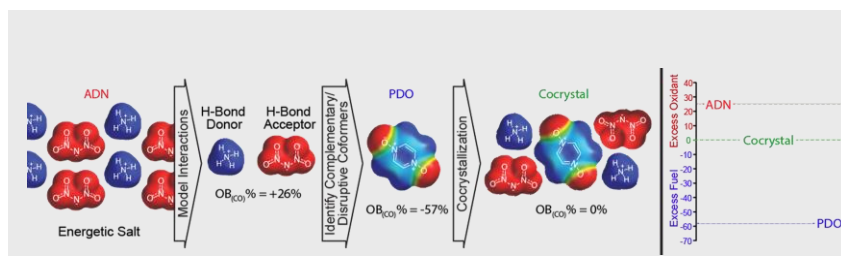

Balancing act: a method to achieve oxygen-balanced energetic materials (EMs) through cocrystallization is developed that avoids the risks inherent in molecular synthesis while achieving intimate association of oxidizing and fuel moieties. This method is applied to ammonium dinitramide yielding an EM with improved physical and energetic properties.