

UMTRI

71843

UM-HSRI-81-56

TRUCK TIRE TRACTION

Final Report
Sub-Contract S8101

R.D. Ervin
C.C. MacAdam

Highway Safety Research Institute
The University of Michigan

December 1981

Transportation
Research Institute

UMSRI

Technical Report Documentation Page

1. Report No.	2. Government Accession No.	3. Recipient's Catalog No.	71843
4. Title and Subtitle TRUCK TIRE TRACTION		5. Report Date December 1981	
		6. Performing Organization Code 019242	
7. Author(s) R. Ervin and C. MacAdam		8. Performing Organization Report No. UM-HSRI-81-56-2	
9. Performing Organization Name and Address Highway Safety Research Institute The University of Michigan Huron Parkway and Baxter Road Ann Arbor, Michigan 48109		10. Work Unit No.	
		11. Contract or Grant No. Sub-Cont. S8101	
12. Sponsoring Agency Name and Address Calspan Corporation* 4455 Genesee Street Buffalo, New York 14221		13. Type of Report and Period Covered Final 5-15-81/12-01-81	
14. Sponsoring Agency Code			
15. Supplementary Notes *Prime Contract No. DTNH-22-80-C-07093 National Highway Traffic Safety Administration U.S. Department of Transportation			
16. Abstract <p>The traction properties of heavy truck tires were measured using the HSRI Mobile Truck Tire Dynamometer on selected asphalt and concrete pavement sections at the Transportation Research Center of Ohio. A sample of eight test tires and five control tires were subjected to a sequence of longitudinal and lateral slip conditions on each of the two surfaces. Data were collected on analog magnetic tape during the field operations and later processed, in digital form, to produce condensed measures of traction behavior. The processed results are reported here without evaluation or discussion.</p>			
17. Key Words Truck Tires, Traction, Pavement Friction		18. Distribution Statement UNLIMITED	
19. Security Classif. (of this report) NONE	20. Security Classif. (of this page) NONE	21. No. of Pages 789	22. Price

TABLE OF CONTENTS

1. INTRODUCTION	1
2. METHODOLOGY	2
2.1 Mobile Traction Measurement Apparatus.	2
2.2 Test Procedure	11
2.3 Data Processing.	19
APPENDIX A - Processed Results of Longitudinal Traction Tests.	30
APPENDIX B - Processed Results from Lateral Traction Tests	203

1.0 INTRODUCTION

This document constitutes the final report on an experimental project entitled "Truck Tire Traction" conducted by the Highway Safety Research Institute of The University of Michigan under Subcontract Number S8101 to the Calspan Corporation. The project entailed the conduct of truck tire traction measurements using an over-the-road dynamometer as part of a round-robin testing program being directed by Calspan under their prime contract, Number DTNH-22-80-C-07093, with the National Highway Traffic Safety Administration of the U.S. Department of Transportation.

Tests were conducted using the HSRI Mobile Truck Tire Dynamometer on selected asphalt and concrete pavement sections at the Transportation Research Center of Ohio. A sample of eight test tires were subjected to a sequence of longitudinal and lateral slip conditions on each of the two surfaces. In addition to the eight-tire sample, five test sequences were performed on control tires at periodic points in the program. Data were collected on analog magnetic tape during the field operations and later processed, in digital form, to produce condensed measures of traction behavior.

The report contains a description of the test device, in Section 2.1, and outlines the data collection and processing procedures in Sections 2.2 and 2.3, respectively. The processed longitudinal traction data are presented in Appendix A and the lateral traction data are presented in Appendix B.

2.0 METHODOLOGY

Traction tests were conducted during June and July, 1981, according to a set of test procedures which duplicated those performed during a previous NHTSA-sponsored study.* The test program involved the exercise of longitudinal and lateral slip sequences on each of eight tire specimens, with five control tire tests being run in a pattern which meshed with the eight-tire sample. The test machine, the HSRI Mobile Truck Tire Dynamometer, was set up first in the configuration for making the longitudinal traction tests on the tire sample, and three weeks later, was operated in the lateral traction configuration for testing the sample. The test machine is described in Section 2.1 followed, in Section 2.2, by a description of the test procedure.

The data were collected in the field on FM analog tape and were later transcribed to digital format for processing. The data processing technique is described in Section 2.3.

2.1 Mobile Traction Measurement Apparatus

The HSRI mobile dynamometer in its current stage of development consists of a tractor-semitrailer vehicle which permits investigation of either longitudinal or lateral traction characteristics of heavy truck tires. The system permits measurement of longitudinal properties by way of the trailer-configured dynamometer as it is towed and serviced by the instrumented tractor. Mounted on the same tractor is a structure supporting a lateral traction measurement system, as diagrammed in the plan view of Figure 1. Each test system is basically designed to expose a truck tire specimen to a set of operating conditions which cover the full range of possible loads, velocities, longitudinal or angular slip, and pavements such as can be encountered under either normal or emergency situations on the highway.

The longitudinal traction dynamometer, shown in Figure 2, is a welded trailer structure of pipe and plate sections, designed for economy of construction and for stiffness. The test wheel is situated approximately at the trailer center-of-gravity position and is supported by a

*P.L. Boyd, A.H. Neill, Jr., and J.A. Hinch, "Truck Tire Cornering and Braking Traction Study," Final Rept., Contract No. NHTSA-9-6227, Rept. No. DOT HS-804 732, March 1979.


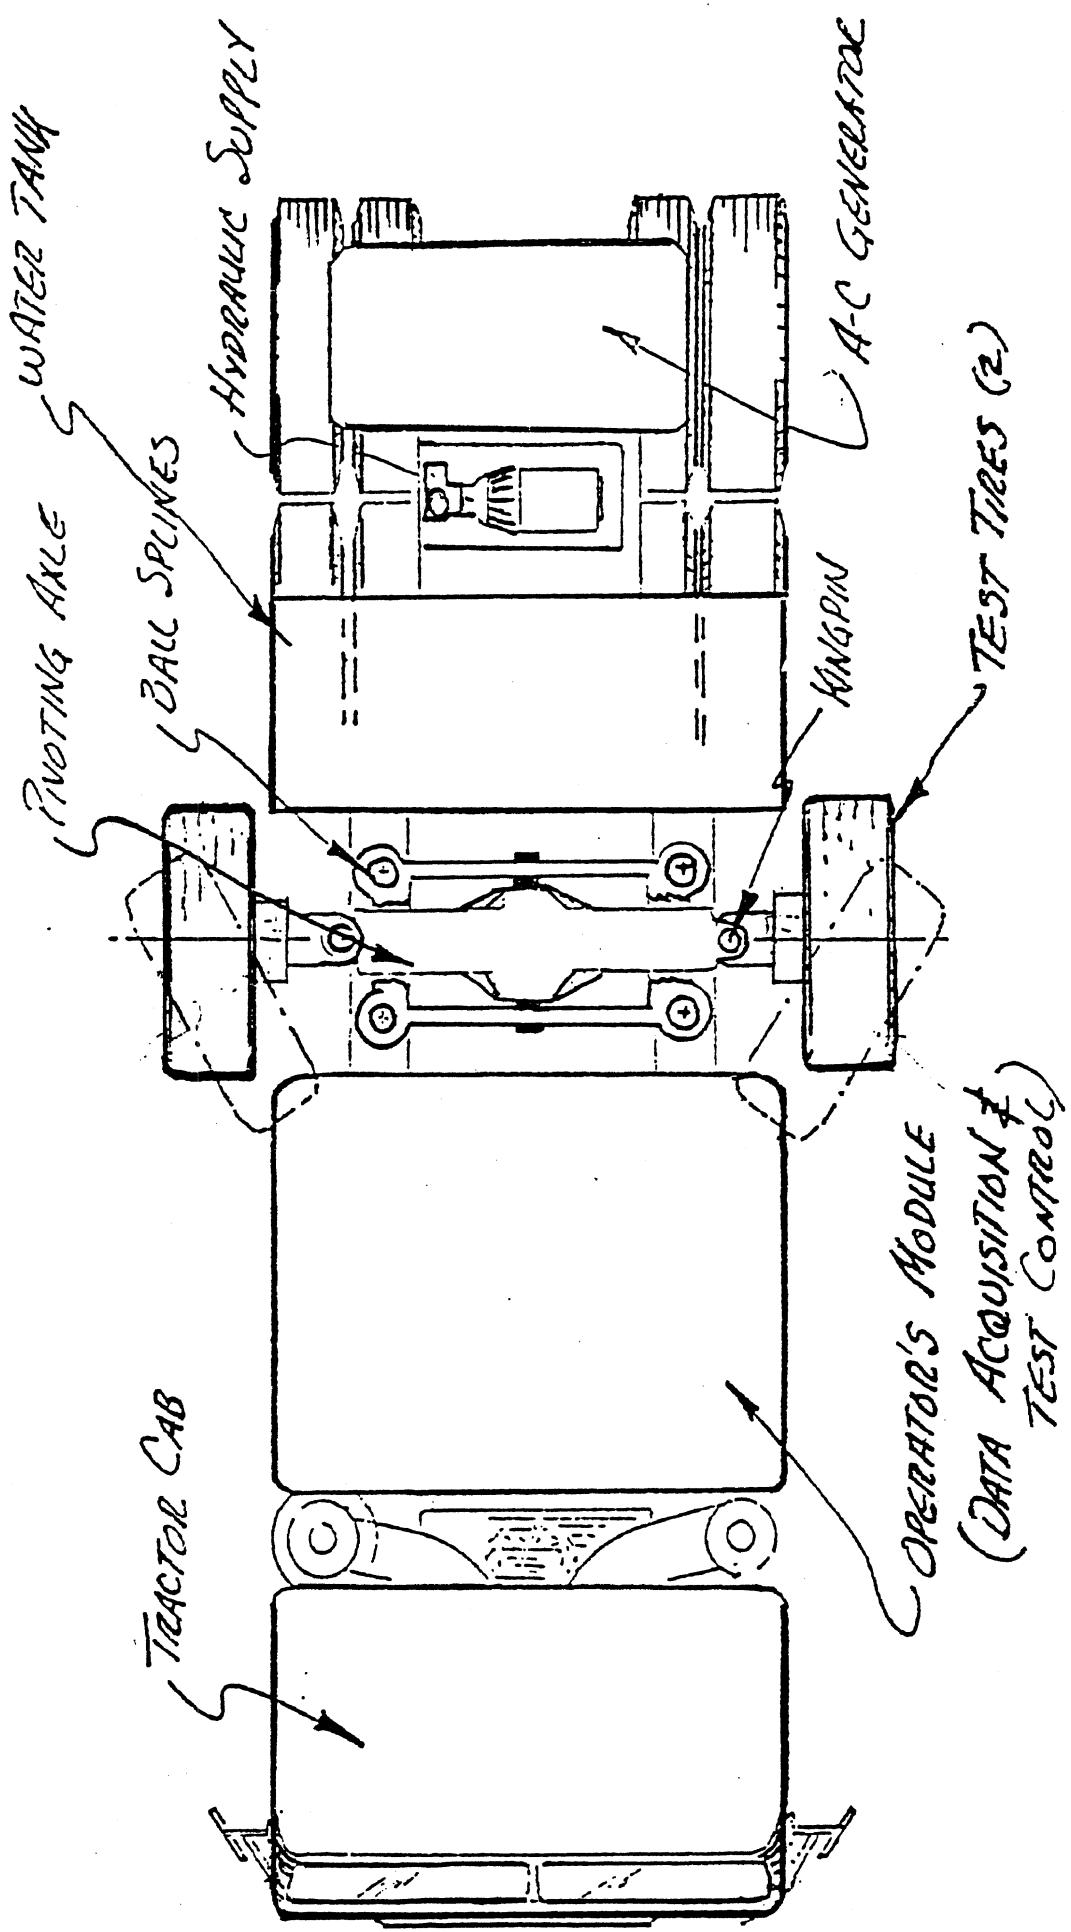


Figure 1. Plan view of Mobile Truck Tire Side Force Dynamometer.

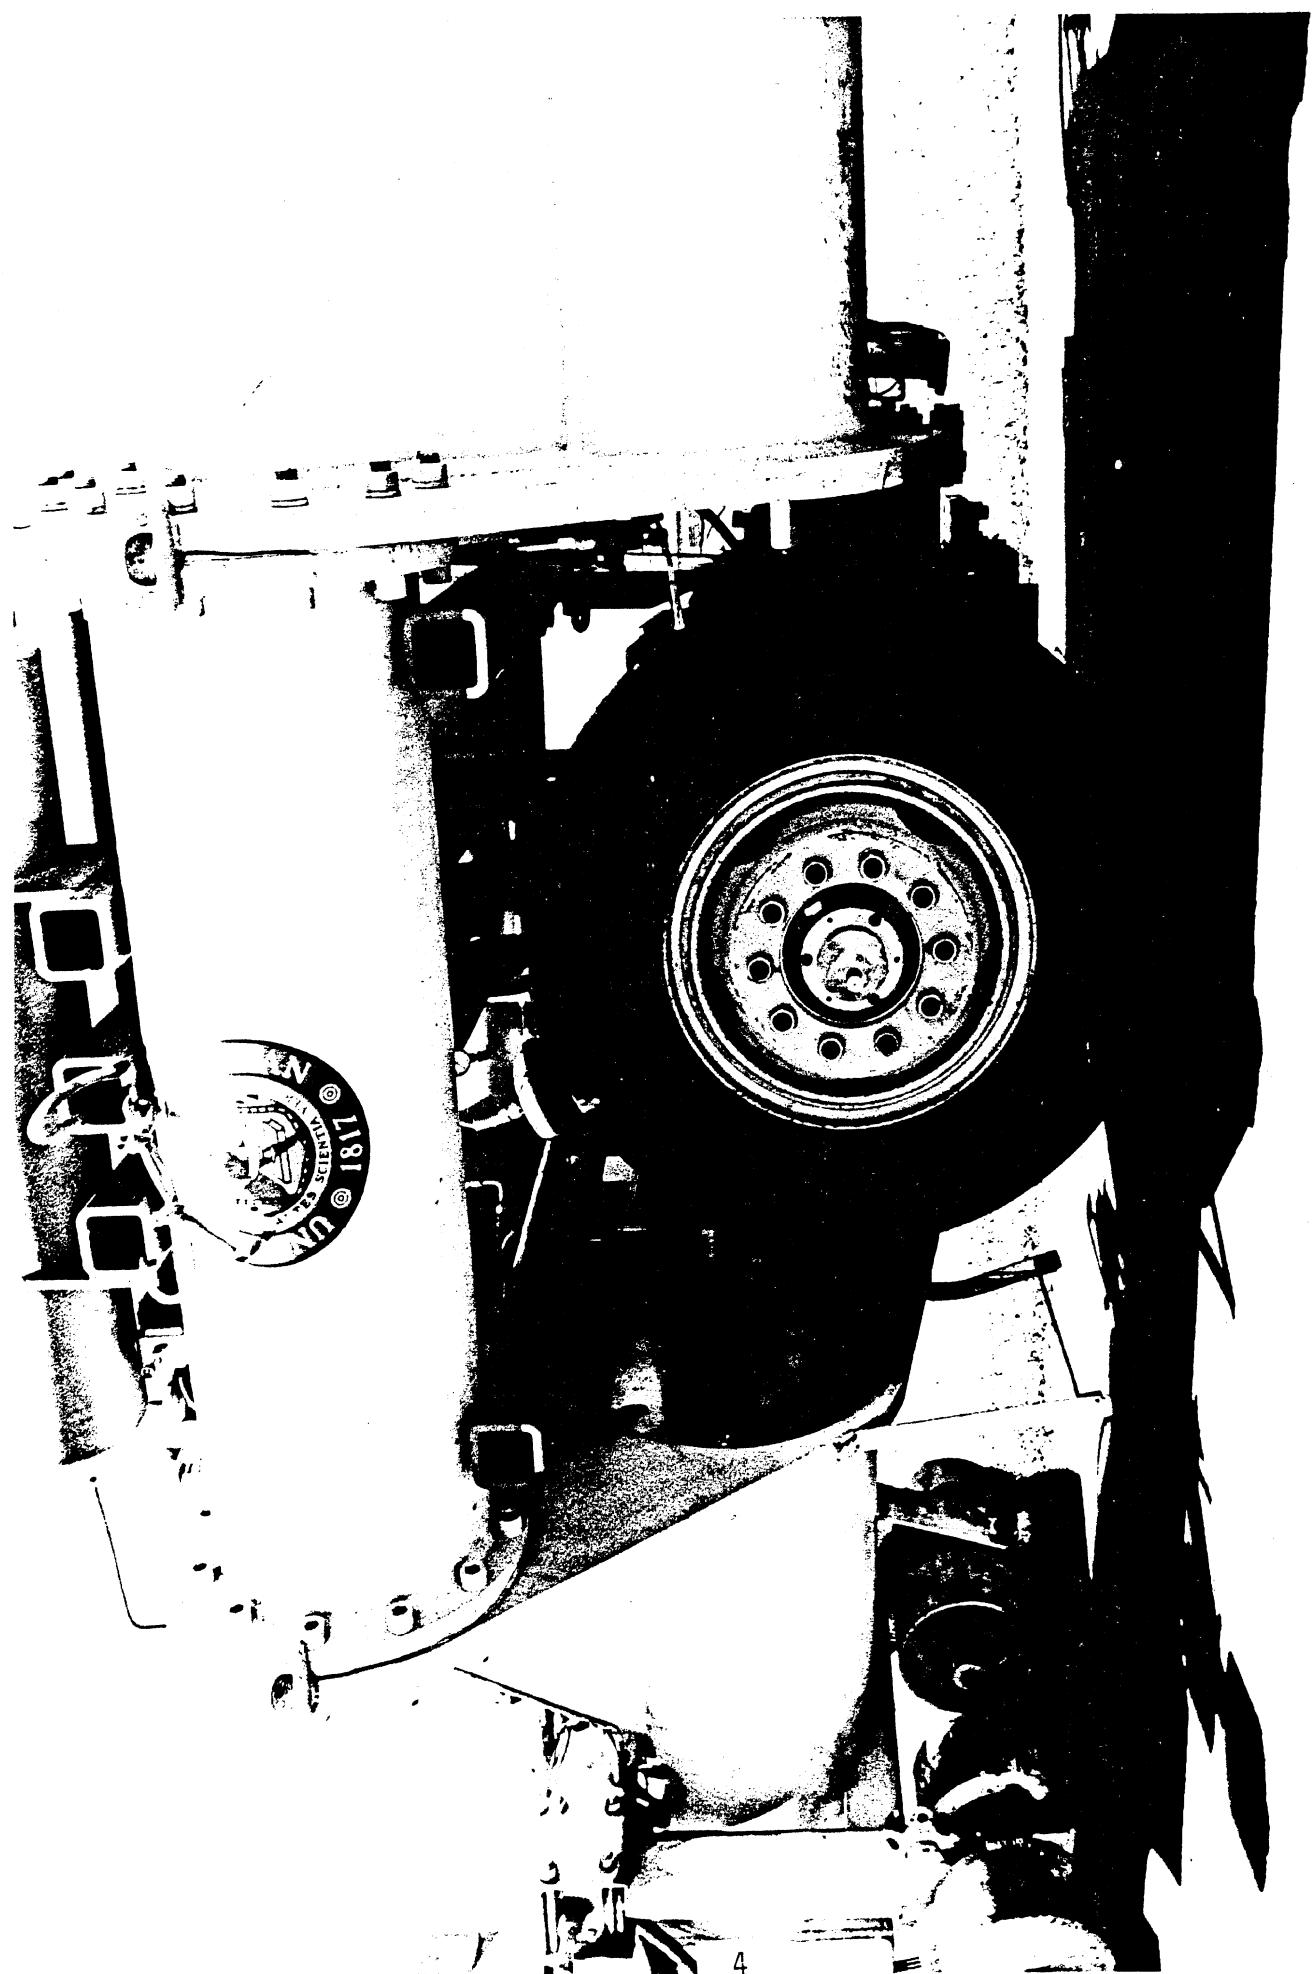

parallelogram suspension. This suspension configuration, shown in Figure 3, derives from attempts to achieve three fundamental qualities in a mobile traction measurement machine; namely,

- 1) the elimination of kinematic interactions between the loads applied to the test wheel and resulting shear forces and moments,
- 2) the employment of a low-spring rate loading mechanism (an air spring), to assure the attainment of the desired load levels while neither (a) sacrificing frequency response in the vertical degree of freedom of the test wheel, nor (b) imposing a significant through-coupling of the vibrations of the foundation vehicle to the test wheel, and
- 3) the minimization of the value of the "unsprung" mass, i.e., the mass which is displaced with the vertical motion of the test wheel spin axis.

The parallelogram linkage suspension is thus provided to assure kinematic isolation of forces while assuring a zero inclination (camber) of the test wheel plane.

The use of an air spring loading mechanism permits a controllable vertical load condition and, in the case of the HSRI machine, imposes a nominally 350 lb/in coupling between the trailer and the test wheel—while operating at a common mid-range load of 5000 lb, F_z . At higher loads, the spring rate rises to a maximum value of 1000 lb/in at a load of 20,000 lbs, while the spring rate, of course, diminishes to zero at zero inflation of the air spring. These spring rates contrast with corresponding leaf suspension rates of trucks which are five to thirty times stiffer at comparable rated wheel loads.

The basic design principle behind air spring loading, then, is that the machine incorporates a relatively "soft" loading member (which is also virtually frictionless) and thereby attains features which serve to enhance the quality of the vertical load condition which is imposed upon the test tire. With such a mechanism, it is then straightforward to

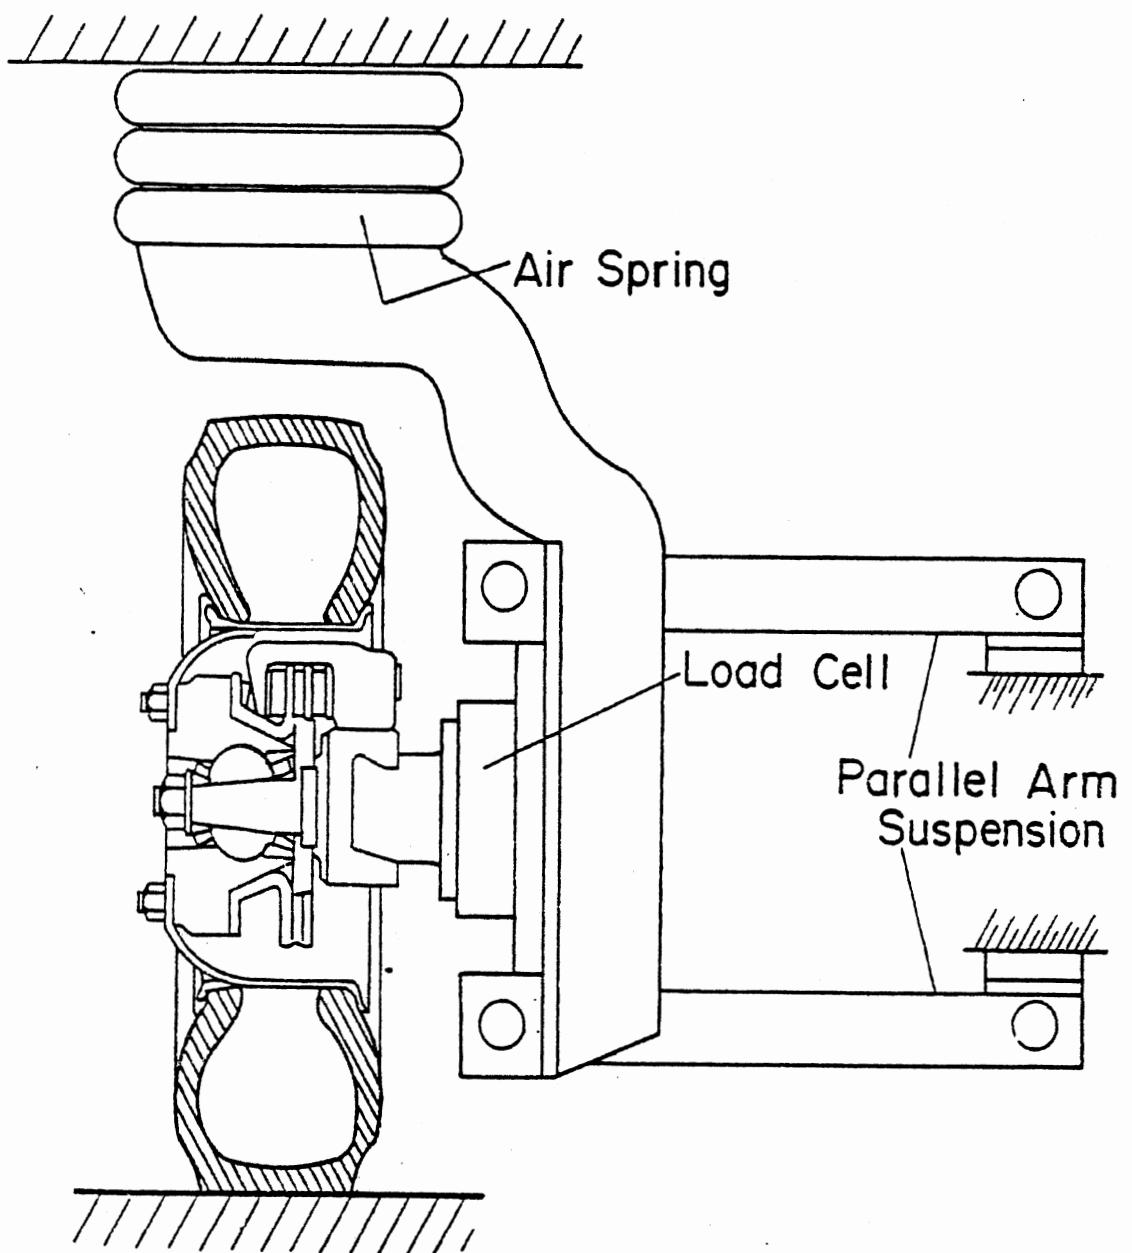


Figure 3. Test wheel suspension layout in the longitudinal traction measurement assembly.

obtain precision selections or vertical load through the use of commercially available precision regulators.

The unsprung mass which is associated with the vertical degree of freedom of the test wheel on the HSRI machine weighs 1850 lbs, when outfitted with a 10.00 x 20 load range F tire and the corresponding 20 x 7.50 disc wheel rim. By such a configuration, the "wheel hop" system indicates a natural frequency of approximately 5 Hz (for an effective radial spring rate of the tire of 5000 lb/in). In general, a high-frequency wheel hop system permits a minimal vertical load fluctuation as the tire follows the varying profile of the test surface. In the design of HSRI's longitudinal force dynamometer, the "quality" deriving from a reduced size of the unsprung mass was comprised with the obvious needs of strength, stiffness, and economy of construction of the wheel support assembly. The longitudinal force, F_x , vertical load, F_z , and brake torque, T_b , are transduced by way of a serial-mounted load cell. These signals, together with wheel angular velocity and vehicle velocity, constitute the primary data channels for the machine.

The nominal pitch and jounce trim of the HSRI trailer are controlled through the use of self-leveling air suspensions on both the trailer rear axle and the tractor rear tandem. Thus, as a given vertical load is transferred from the two respective axle sets to the test wheel, through inflation of the test wheel air spring, the tractor and trailer leveling systems adjust to a running equilibrium at which the trailer assumes its design trim attitude. The use of air suspensions on both ends of the trailer also contributes to attenuation of ride motions, thus further assuring quality in the vertical load condition.

The test trailer is capable of mounting any tire in the 20-inch rim size, and above, which is:

- a) less than 46 inches in free diameter, and
- b) 18 inches or less in maximum section width.

Tires can be loaded to a maximum level of 20,000 lbs, although, to date, brake torque limitations have prevented the lockup of tires on high friction surfaces at loads exceeding about 15,500 lbs.

The lateral traction dynamometer shown schematically in Figure 4 mounts two tire samples on opposing steerable spindles outboard of the tractor's wheel tracks. The two tires are "toed-in" together by an electrohydraulic servo system covering a slip angle range from -1° to +30°. The test wheel spindles are mounted upon a solid cross-axle which is constrained by a single longitudinal pivot pin.

The pin itself is fastened within a cage which can move only vertically, as constrained by a set of four ball-spline bearings. The vertically—"floating cage" is then loaded through inflation of a set of air springs. This machine thus incorporates a suspension designed to maximize the three "fundamental virtues" of mobile measurement described earlier—but for the more complicated case in which two tires are needed to achieve a side force equilibrium on the foundation vehicle. Clearly, the "pivot axle" arrangement provides for a load equalization between both tires while also providing a higher frequency response to road profile irregularities which are uncorrelated, side-to-side. The "floating cage" provides the needed kinematic isolation of the vertical load from forces in the ground plane by virtue of its rectilinear antifriction constraints. The air spring loading configuration again provides for precision load selection while incorporating a low spring rate coupling between the unsprung mass(es) and the foundation vehicle.

The two wheel spindles are "steered" to equal but opposing slip angles by an electrohydraulic servo system which incorporates two sets of actuating cylinders as shown in Figure 5. The linkage arrangement which mechanically couples both spindles together permits the use of a single control loop, operating on the feedback signal from the one instrumented wheel while assuring common slip angles, side-to-side, even in the event of a servo power failure.

The system permits mounting of any tire within the 30 to 48 inch range of free diameters and which is less than 18 inches in cross-section width. The measurement of tire force and moment conditions is achieved by way of a serial multicomponent load cell which transduces lateral and vertical force components as well as aligning moment.

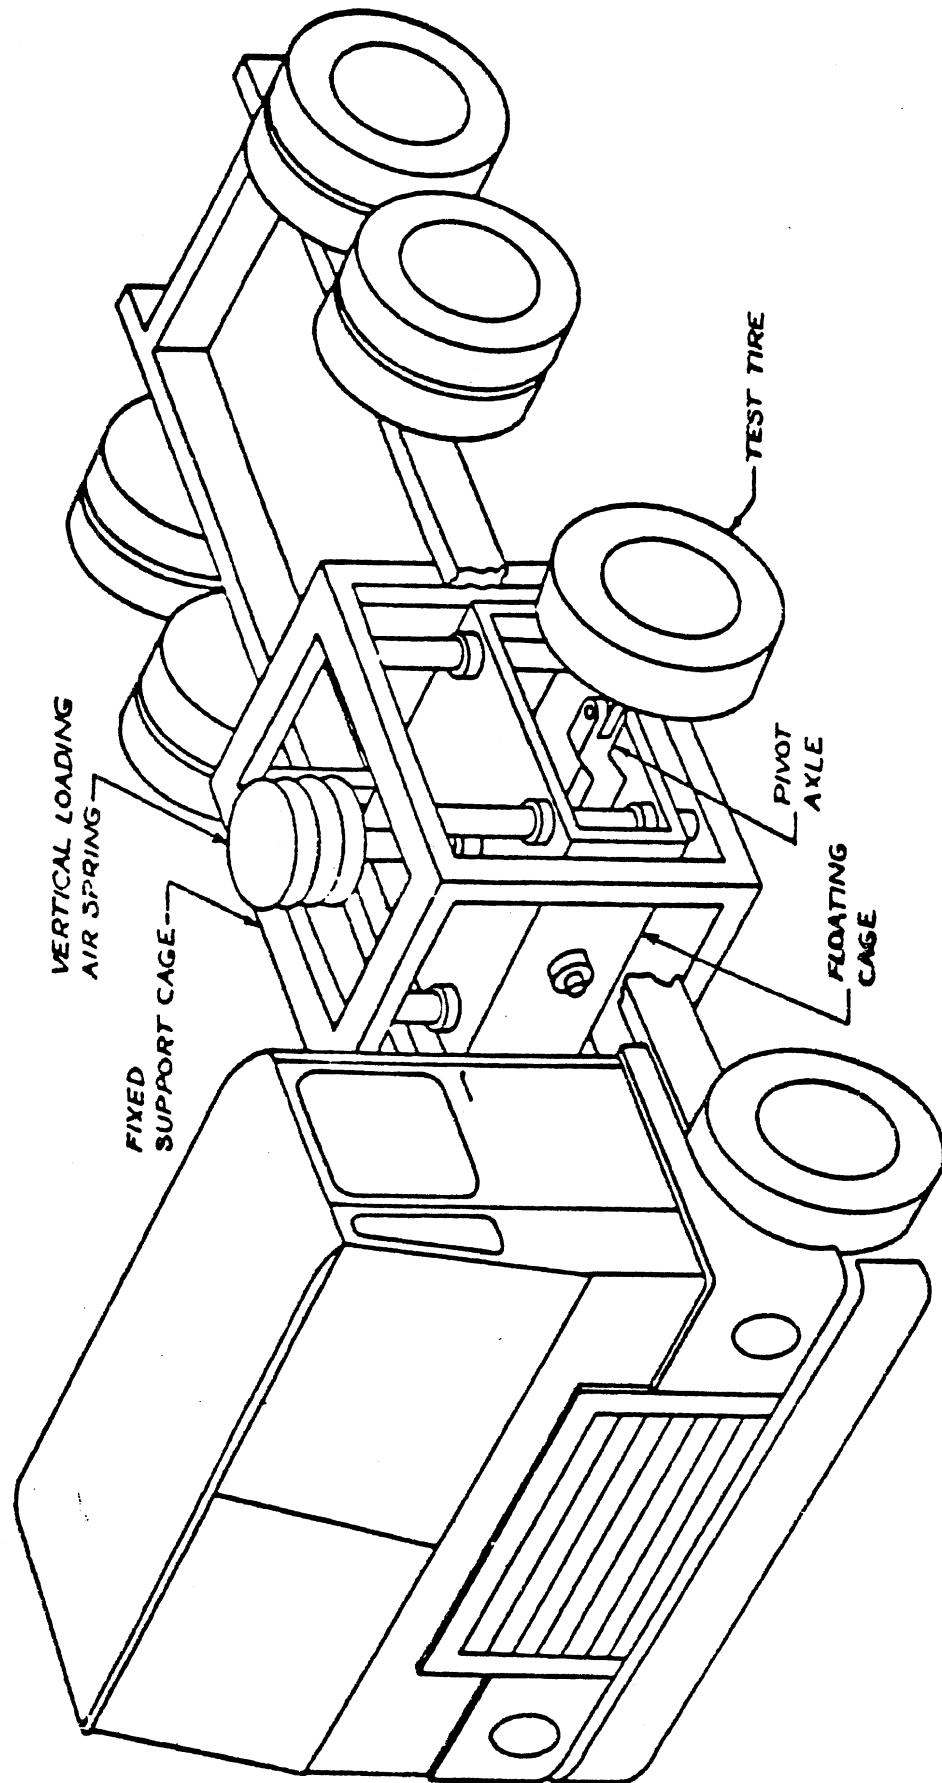


Figure 4. Major components of the side force dynamometer assembly.

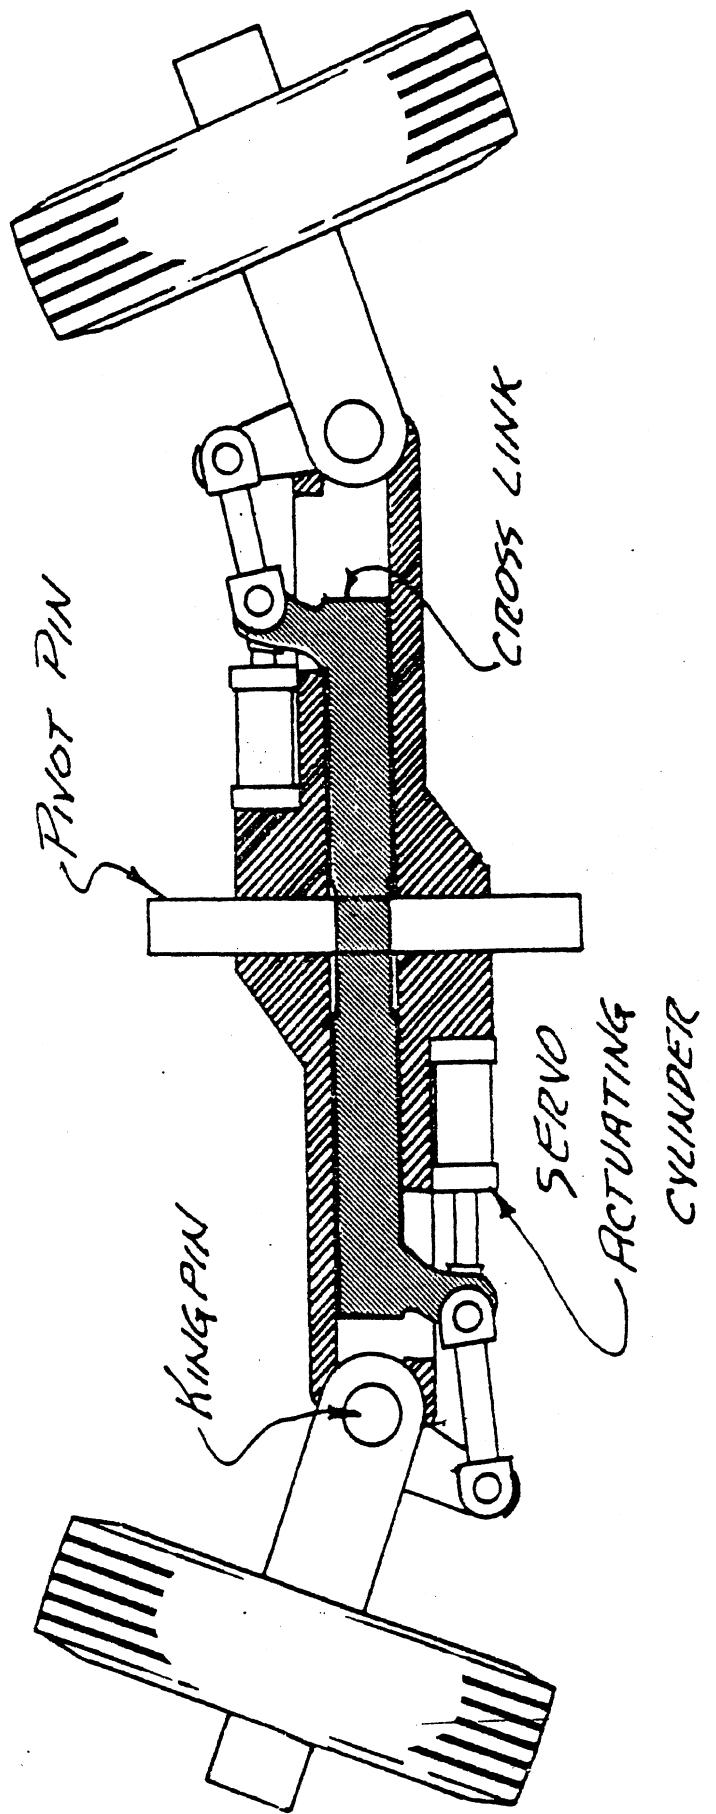


Figure 5. Section view of pivot axle with steering servo linkage.


Data signals from either the longitudinal or lateral test apparatuses are conditioned and recorded within a tractor-mounted module. The module serves as a self-contained data acquisition laboratory as well as the operator's station for selecting and initiating test control functions. As shown in Figure 6, the operator's module provides an array of hard-wired electrical controls in addition to certain pneumatic and hydraulic control elements.

2.2 Test Procedure

The mobile dynamometer exercised each tire in the longitudinal and lateral traction test series according to one basic matrix of conditions. The matrix included a single value of load, and the application of six sweeps of either longitudinal or lateral slip for each of two speeds and two surfaces. The overall test sequence required approximately 1-1/2 hours with each tire. In addition to traction measurements, certain test condition measurements were also made concurrently with the testing of each tire. The recorded data signals included the following:

- F_x longitudinal force
- F_y lateral force
- F_z vertical load
- V test vehicle velocity
- ω wheel angular velocity
- α slip angle

Data being recorded on FM magnetic tape were played back simultaneously and displayed to the test vehicle operator on a pen-chart recorder to provide for continuous assurance of nominal data quality. The traction measurements were made at the Transportation Research Center of Ohio. Shown in Figures 7a and 7b are diagrams of the Vehicle Dynamics Area at TRC, which provided an asphalt test surface, and the Skid Pad facility, which provided a polished concrete test surface. Tests were conducted on both surfaces using an on-board watering system for laying down an 18-inch-wide swath of water ahead of the test tire. The watering

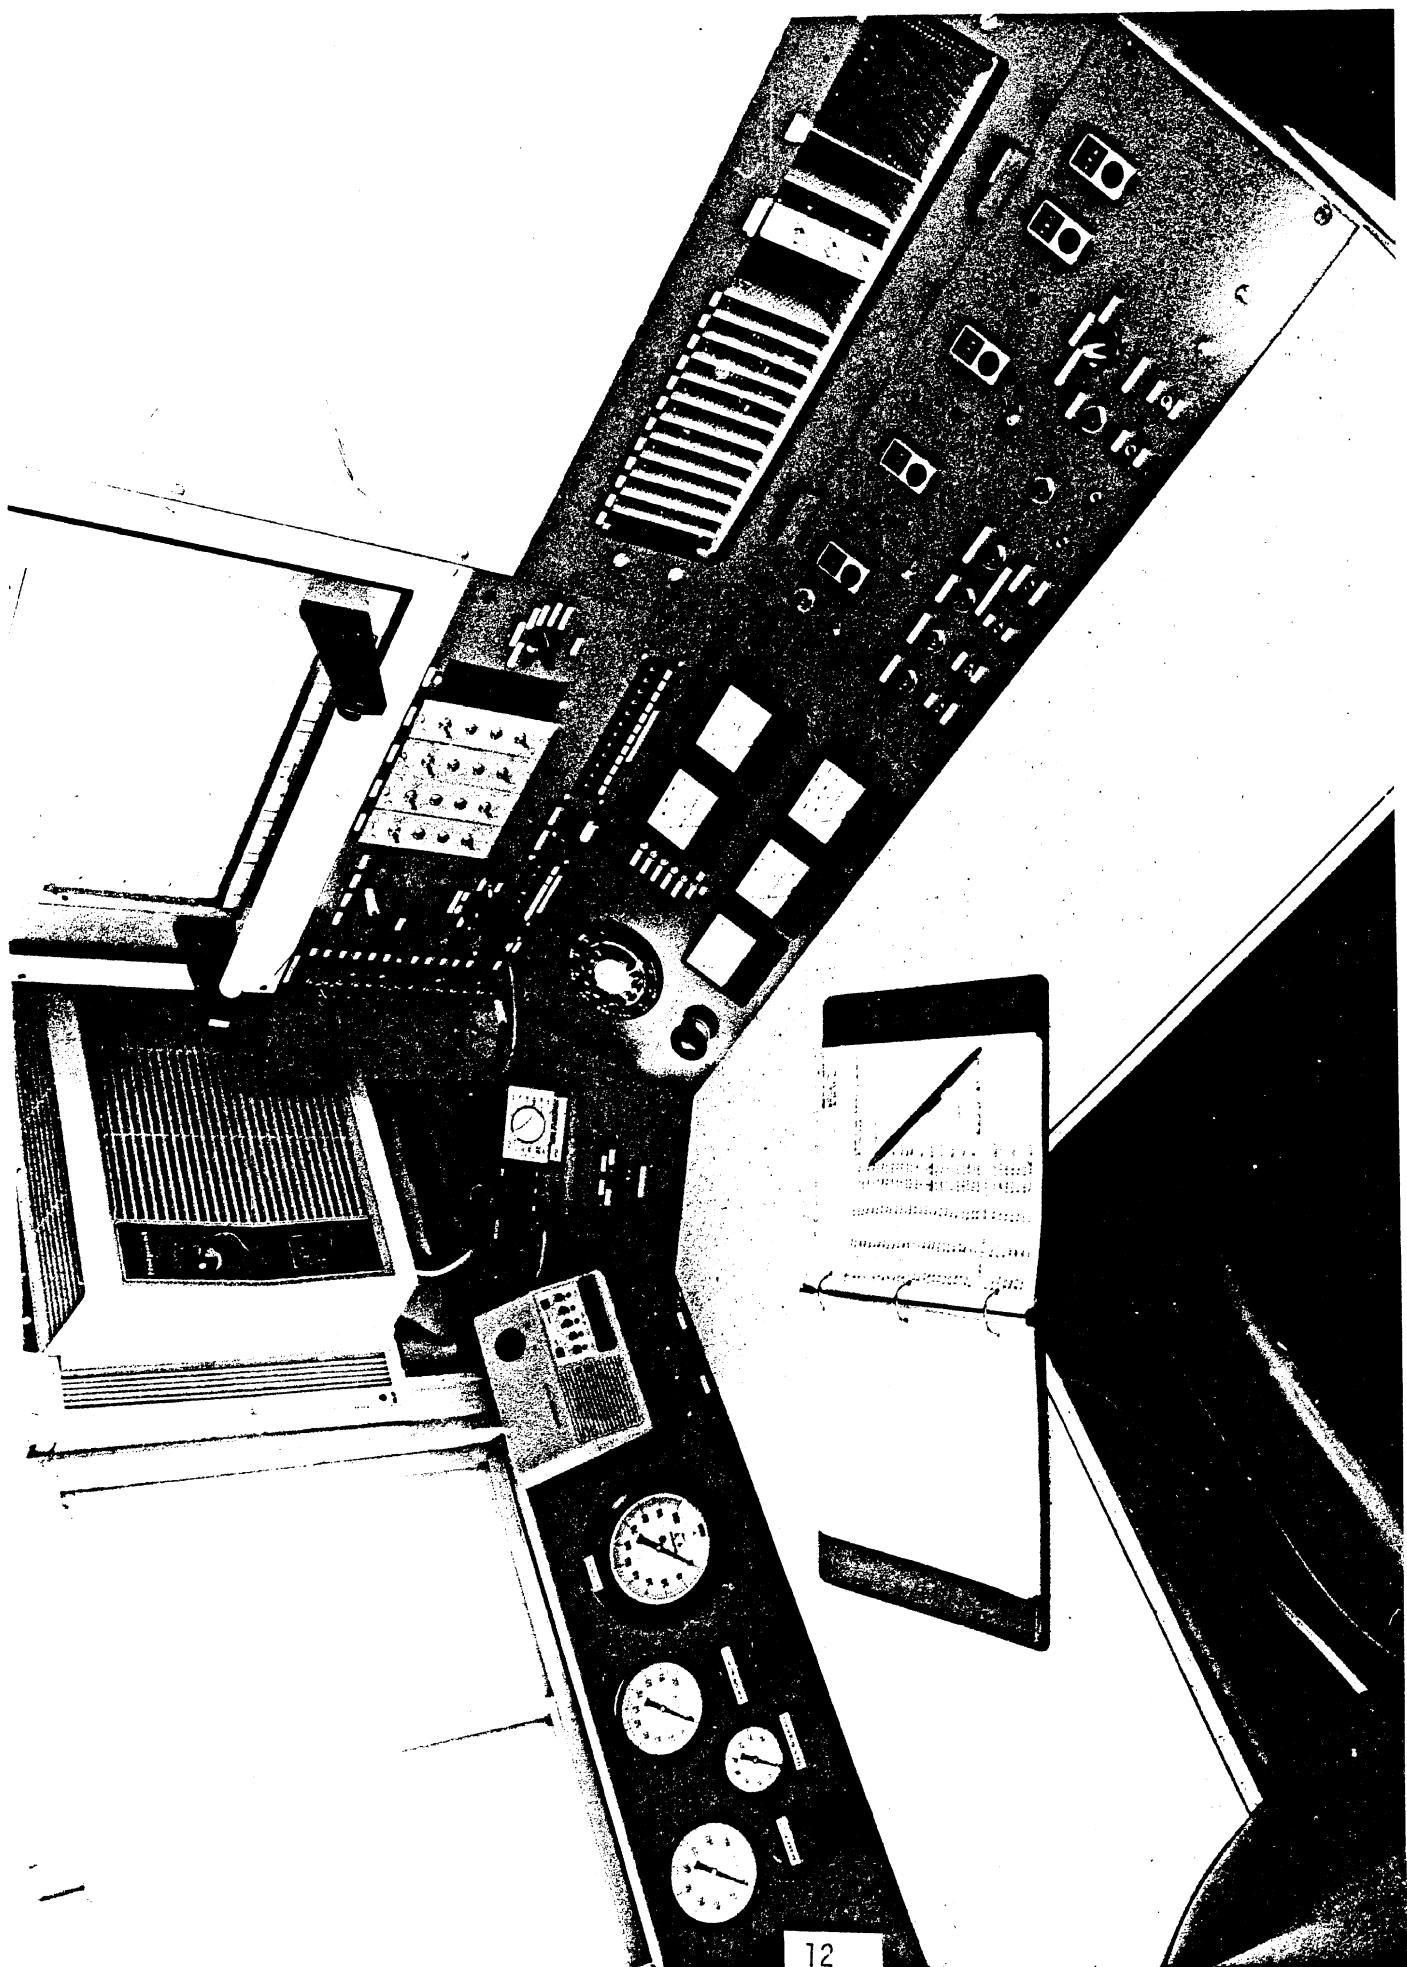

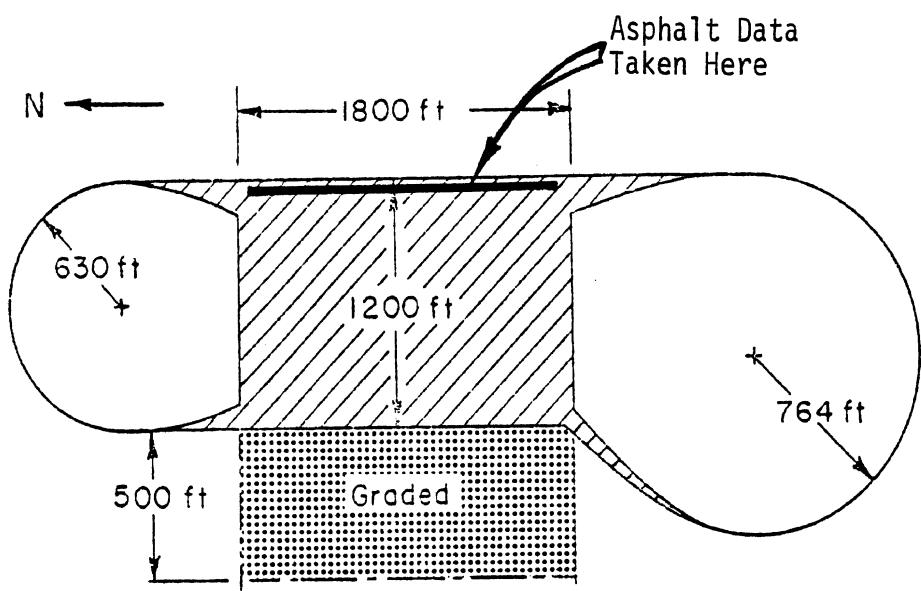


Figure 7a. Vehicle Dynamics Area at the Transportation Research Center of Ohio (TRC).

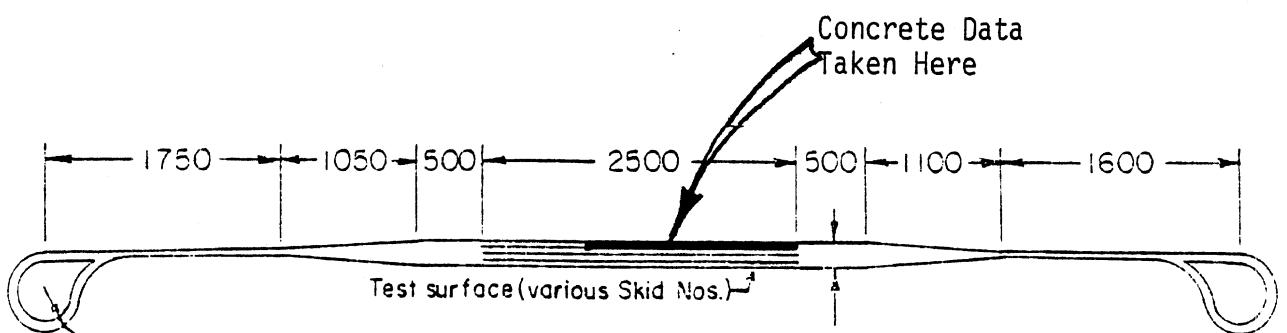


Figure 7b. Skid Pad at TRC.

system flow rate was adjusted in proportion to vehicle speed in order to establish a constant 0.020-inch nominal depth of the delivered water for the two test speeds, 40 and 50 mph. The following lists state the procedural steps by which were obtained the longitudinal and lateral traction measurements, respectively.

Longitudinal Traction Test Sequence

1. Initial measurement of the hardness of the tire's tread is made.
2. The tire is mounted on the test machine, loaded to 4,620 lbs, and is inflated (cold) to a pressure of 85 psi for bias tires and 90 psi for radial tires.
3. The machine is moved to the asphalt test track (VDA) with the tire raised and pretest calibration of instrumentation is performed. Measurements are made of the temperatures of the dry asphalt pavement surface and the temperature of the water in the on-board watering system tank. Weather conditions are logged, including ambient temperature, wind velocity and direction, and the general sky condition (sunny, overcast, etc.). The tire is lowered and loaded to 4,620 lbs.
4. Three warm-up laps* (\approx 5.7 miles) are performed on the asphalt track at a speed of 50-55 mph.
5. A pre-wet lap is made, delivering 0.020-inch depth of water at 40 mph and performing six brake applications (time to peak traction 0.3 sec + 0.1 sec) with the locked-wheel condition being sustained for 1 second and with a 1-second pause between the release of the brake at the end of one cycle and the reapplication of the brake at the initiation of the next.
6. Step 4 is repeated but test data are recorded throughout the braking sequences.
7. Step 6 is repeated, except at a speed of 50 mph.
8. The machine is stopped, the tire raised, and calibration of the instrumentation performed. The tire is inspected for damage.
9. The machine is moved to the polished concrete test track (skid pad), stopped, and the tire loaded to 4,620 lbs.

*All tests on the asphalt track are made with the test machine moving in one direction (south).

10. The test lane of the concrete surface is pre-wetted, heading south, at 40 mph.
11. Three brake applications* are made, heading north, at 40 mph delivering water and recording test data.
12. Step 11 is repeated (heading south).
13. Two brake applications are made, heading north, at 50 mph delivering water and recording data.
14. Step 13 is repeated (heading south).
15. Step 13 is repeated (heading north).
16. The machine is stopped, the tire raised, and a calibration of the instrumentation performed. The tire is inspected for damage. The temperature of the dry concrete surface is then measured.
17. A final measurement of the tread rubber hardness is performed after the tire has been dismounted and cooled to room temperature.

Lateral Traction Test Sequence

1. Initial measurement of the hardness of the tire's tread rubber is made.
2. The tire** is mounted on the test machine, loaded to 4,620 lbs and its cold inflation pressure set to 85 psi for bias tires and 90 psi for radial tires.
3. The machine is moved to the asphalt test track (VDA) with the tire raised and a pretest calibration of instrumentation is performed. Measurements are made of the temperatures of the dry asphalt pavement surface and the temperature of the water in the on-board watering system tank. Weather conditions are logged, including ambient temperature, wind velocity and direction, and the general sky condition (sunny, overcast, etc.). The tire is lowered and loaded to 4,620 lbs.
4. Three warm-up laps are performed (\approx 5.7 miles) on the asphalt track at a speed of 50-55 mph.

*More than one pass over the concrete surface is needed in order to fit the traction test cycles onto the available length of this low-friction surface. At 40 mph, three lockup cycles are conducted with each pass. At 50 mph, two lockup cycles are conducted per pass.

**A "dummy" tire must be installed in a complementary position to balance side forces on the test machine.

5. A pre-wet lap* is made, delivering 0.020-inch depth of water at 40 mph and performing the following linear slip-angle sweeps at a rate of 8 deg/sec: 0° to 20° to 0° to 20° to 0° (new tire only).
6. A data-recording run is made on the next lap while executing the slip angle sequence** shown in Figure 8a.
7. Step 6 is repeated, except at a speed of 50 mph.
8. The machine is stopped, the tire raised, and a calibration of the instrumentation performed. The tire is inspected for damage.
9. The machine is moved to the polished concrete test track (skid pad), stopped, and the tire lowered and loaded to 4,620 lbs.
10. The test lane of the concrete surface is pre-wetted, heading south, at 40 mph.
11. A data-recording run is made on the next lap, heading north, while executing the slip angle sequence shown in Figure 8b at 40 mph.
12. Step 11 is repeated (heading south).
13. Step 11 is repeated (heading north).
14. A data-recording run is made on the next lap, heading south, while executing the slip angle sequence shown in Figure 8c at 50 mph.
15. Step 14 is repeated (heading north).
16. Step 14 is repeated (heading south).
17. The vehicle is stopped, the tire lifted, and a calibration of the instrumentation performed. The tire is inspected for damage. The temperature of the dry concrete surface is measured.
18. A final measurement of the tread rubber hardness is performed after the tire has been dismounted and cooled to room temperature.

*All tests on the asphalt track are made with the test machine moving in one direction (south).

**The slip angle sequence is selected to provide six "legs" of swept slip angle—three upgoing and three downgoing. On the asphalt surface, the six "legs" are achieved in a continuous, three-cycle, triangular waveform. On the concrete surface, the six "legs" are achieved by means of individual (two-leg) triangles.

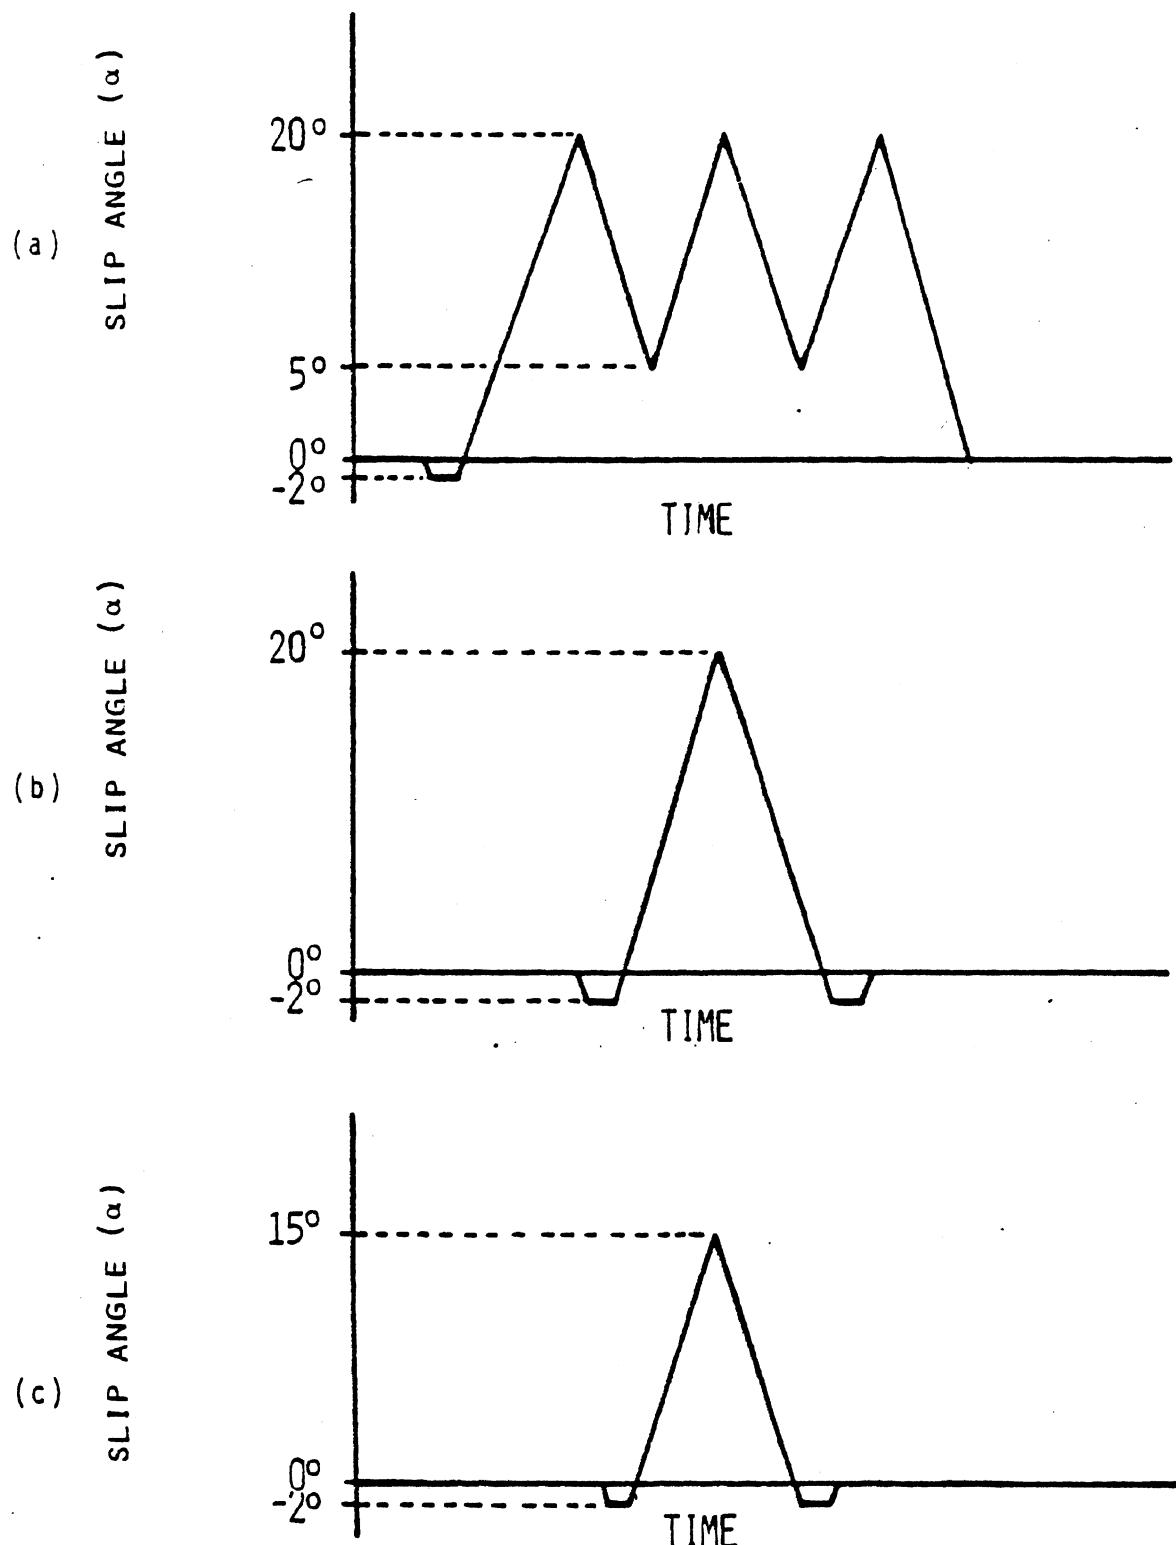


Figure 8. SLIP ANGLE TEST SEQUENCE FOR TESTS ON:
 (a) Asphalt Surface @ 40 & 50 MPH
 (b) Concrete Surface @ 40 MPH
 (c) Concrete Surface @ 50 MPH

In addition to traction measurements on truck tires, measurements of the ASTM skid number were also made by TRC on the asphalt and concrete surfaces before and after the test program.

The longitudinal and lateral test procedures were conducted over a 13-tire sequence. Listed in Table 1 are the sequences in which each of the coded tires was tested. The code letters indicate the following:

"C" represents a control tire

"RR and RL" represent Radial-ply carcass constructions with Rib-type and Lug-type tread patterns, respectively

"BR and BL" represent Bias-ply carcass constructions with Rib-type and Lug-type tread patterns, respectively

Table 1. Sequence in Which Tire Samples Were Tested.

Order	Tire Code Nos.:	Longitudinal Series		Lateral Series	
		Control Tires	Test Tires	Control Tires	Test Tires
1		C1		C9	
2			BR-1		BR-1
3			RR-1		RR-1
4		C2		C2	
5			BL-1		RL-1
6			RL-1		BL-1
7		C2		C9	
8			BR-2		RR-6
9			RR-2		BR-6
10		C1		C2	
11			BL-2		RL-6
12			RL-2		BL-6
13		C1		C9	

2.3 Data Processing

The block diagram shown in Figure 9 describes the different stages of data processing for both the longitudinal and lateral traction measurements. The initial steps in both processing sequences are nearly identical, differing only in the amount of analog filtering used and the rate at which data was digitized. The principal differences between lateral and longitudinal data processing occur following the analog-digital conversion, during the digital, "post-processing" calculations.

2.3.1 Longitudinal Tire Force Data Processing. The longitudinal tire force data were filtered at 10 Hz through single-pole filters and digitized at approximately 150 Hz. The variables digitized included longitudinal force (F_x), vertical load (F_z), brake torque (T_b), rotational velocity (ω), and wheel translational velocity (V).

The digital processing involved (a) calibration of each channel based on the zero, full-scale, and zero data signal levels which are recorded before and after each tire test sequence and based on the known load cell cross-talk sensitivities; (b) digital smoothing of each channel by a simple seven-point moving average calculation; (c) local least-squares curve fitting of each normalized traction (F_x/F_z) versus longitudinal slip data set in order to obtain normalized traction data at specific values of longitudinal slip for subsequent averaging; and (d) final averaging of all valid test repeats, at each slip level along the way toward lockup, for each loading/velocity condition in the test series.

The least-squares curve-fitting procedure referred to above involves performing a linear least-squares regression for four digitized pairs of ($F_x/F_z|_i$ vs $\text{slip}|_i$) and calculating new data pairs of ($F_x/F_z|_k$ vs $\text{slip}|_k$) at specified values of $\text{slip}|_k$ from the regression. This regression procedure is repeated for the entire range of data from 0 slip to 1.0, shifting by one point each time it is performed. The specific values of $\text{slip}|_k$ were in increments of 0.02 from 0 to 0.20 and in 0.05 increments from 0.20 to 1.0.

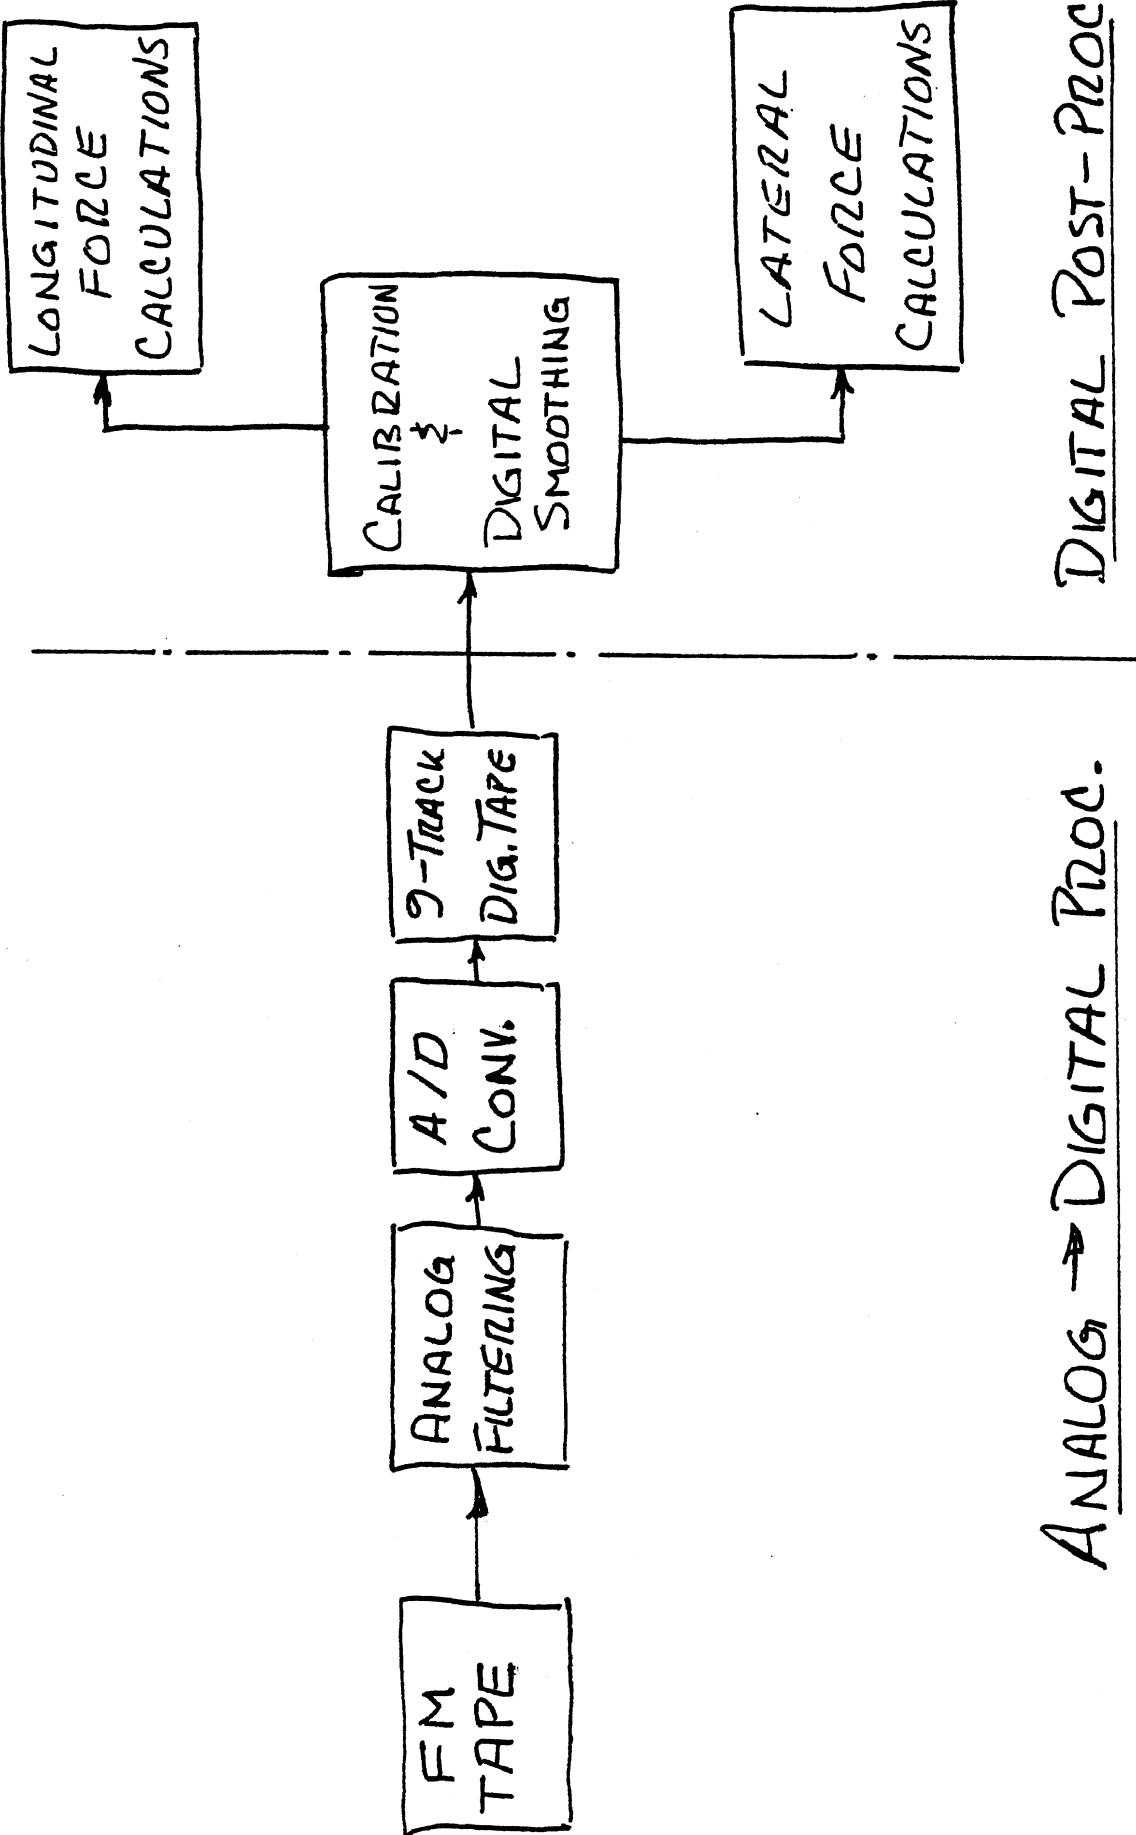


Figure 9. Tire force data processing.

A final average table was produced from a simple average of all the individual $F_x/F_z|_k$ vs slip $|_k$ tables. Each final average table appears in a printout of the form shown in Figure 10, with a tabulation of SLIP and MUX ($\triangleq F_x/F_z|_k$). Brake torque (TORQUE) and longitudinal tire force (FX) also are shown in Figure 10. The summary numerics appearing on the right-hand side of Figure 10 are defined as follows:

TQAV is the average brake torque at wheel lock ($= F_x \cdot \text{Loaded Radius}$) in lbs.

LOAD is the average vertical load prevailing just prior to a brake application, lbs.

VEL is the nominal velocity at which the test sequence was conducted, mph.

MUPEAK is the peak value of $F_x/F_z|_k$ from the final average table.

MULOCK is the locked-wheel value of $F_x/F_z|_k$ from the final average table.

RATIO is the ratio of MUPEAK to MULOCK.

Figure 11 shows the next page included in the printout which contains a plot of MUX VS SLIP. The above numerics are duplicated at the bottom of this page for convenience.

Figure 12 is an additional page from the printout showing values of $F_x/F_z|_k$ from each of the individual lockup cycles at the cited test conditions, along with the value of slip at which each peak occurred. These values are shown in the Figure 12 printout as MU-PEAK, SLIP@PEAK, and MU-LOCK. Average values and standard deviations for the individual MU-PEAK and MU-LOCK values are shown as the last two items on the Figure 12 listing.

TEST SAMPLE101 **

** A-D FILE 4

NEW FILE 1

TIRE C1 WET ASPHALT (TRC)

AVERAGE OF FILE 4 FOR 6 RECORDS.

SL IP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.18	17234.6	824.1
0.04	0.33	31689.8	1501.2
0.06	0.46	44608.5	2101.7
0.08	0.56	53717.7	2540.7
0.10	0.64	61685.2	2928.5
0.12	0.69	66962.0	3177.8
0.14	0.73	71218.4	3334.9
0.16	0.77	74371.2	3468.4
0.18	0.79	77488.5	3599.8
0.20	0.81	80002.0	3677.2
0.25	0.83	83781.1	3751.4
0.30	0.81	86109.9	3717.6
0.35	0.79	87595.6	3606.6
0.40	0.77	88869.8	3498.3
0.45	0.75	89882.9	3401.7
0.50	0.73	90735.7	3315.5
0.55	0.72	91590.9	3245.7
0.60	0.71	922394.2	3179.7
0.65	0.70	92695.3	3120.8
0.70	0.69	91759.1	3068.2
0.75	0.68	88461.8	3020.5
0.80	0.67	82093.6	2975.7
0.85	0.66	75686.7	2926.5
0.90	0.65	69772.4	2864.2
0.95	0.64	63954.6	2812.6
1.00	0.60	55958.3	2707.0

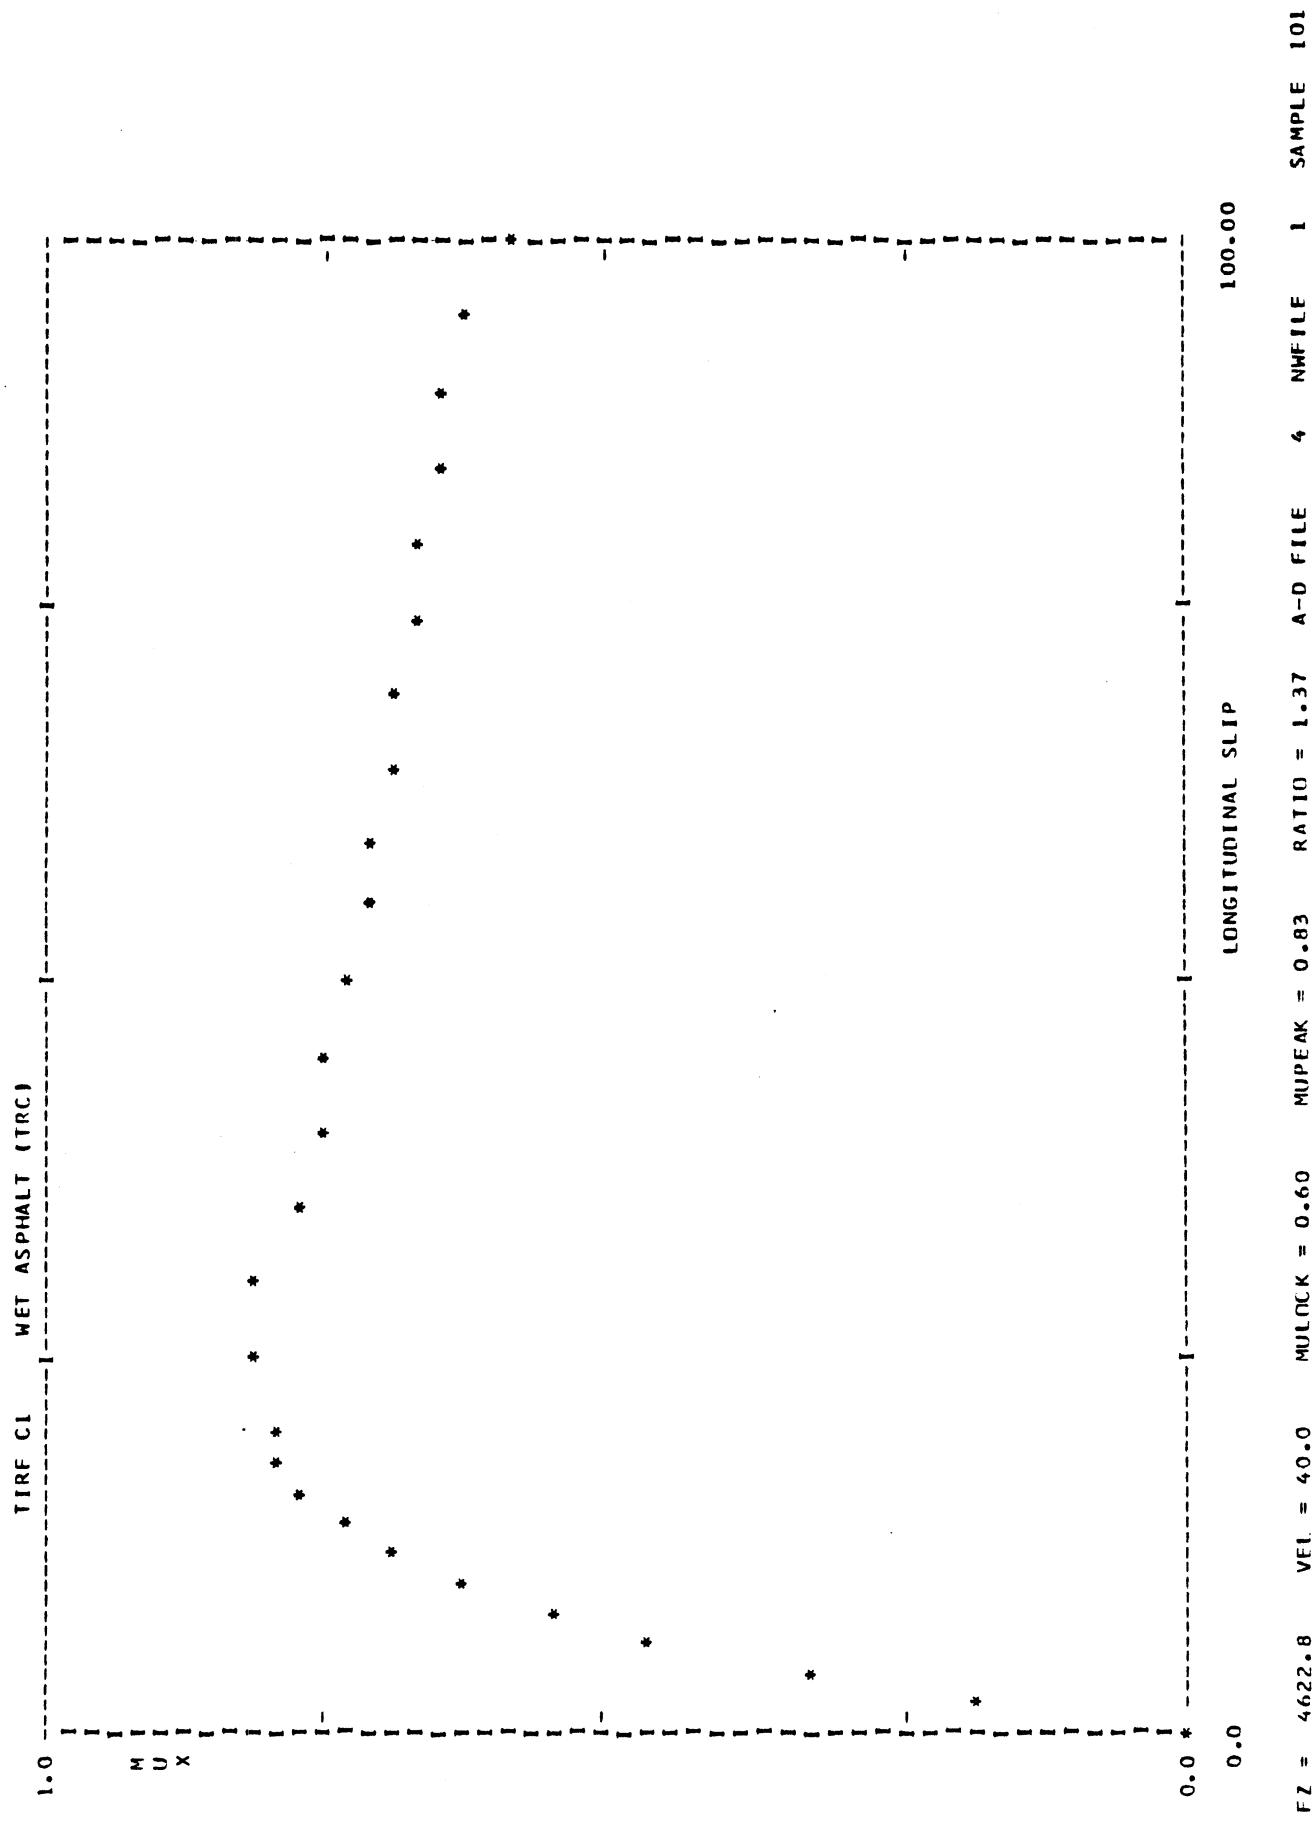


Figure 11. Sample page printer plot of normalized longitudinal force data.

MU-PEAK	SLIPPEAK	MU-LOCK
0.893	0.250	0.597
0.831	0.250	0.613
0.770	0.200	0.592
0.869	0.250	0.623
0.774	0.200	0.597
0.804	0.250	0.562

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.824 0.050
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.597 0.021

Figure 12. Sample printer output - normalized longitudinal force - individual peak and slide values.

2.3.2 Lateral Tire Force Data Processing. Lateral tire force data were filtered at 10 Hz through three-pole filters and digitized at 50 Hz. Four variables were digitized; namely, lateral force (F_y), vertical load (F_z), slip angle (α), and forward velocity (V).

As in the case of the longitudinal force data, the digital processing scheme involved (a) calibration of each channel based on the zero, full-scale, and zero data signal levels which were recorded before and after each tire test sequence and on the linear load cell cross-talk sensitivities; (b) digital smoothing of each channel by a simple nine-point moving average; (c) construction of individual normalized traction (F_y/F_z) versus slip angle (α) tables for each positive-going and negative-going "leg" of the triangular slip angle waveform; and (d) averaging of the individual (F_y/F_z) versus α tables into one final average table. The individual and average tables used a one-degree increment in slip angle to describe the (F_y/F_z) versus α characteristic.

The printed output from the lateral force processing includes (a) individual tables of F_y/F_z versus α (one for each "leg" of the triangular waveform of α), (b) the corresponding average table, and (c) a print-plot of the average F_y/F_z versus α data.

Figure 13 shows a sample printout of an individual table. The labels ALPHA, FY, FZ, and MUY correspond to slip angle (α), lateral tire force (F_y), vertical load (F_z), and the normalized traction coefficient (F_y/F_z), respectively. Figure 14 shows a sample printout of an average table. The same column heading definitions apply to this table, with the additional numerics defined as follows:

AVE. LOAD is the average vertical load prevailing just prior to the initial slip angle application.

PEAK MUY is the peak value of $(F_y/F_z) = MUY$ occurring in the average table.

@ALPHA is the slip angle value corresponding to the PEAK MUY value.

ALPHA	FY	FZ	MUY
0.0	0.0	0.0	0.0
0.0	0.0	0.0	0.0
0.9	575.5	4620.5	0.125
2.0	1046.4	4713.5	0.222
2.9	1339.3	4560.8	0.294
4.0	1695.4	4661.6	0.364
5.0	1907.8	4451.6	0.429
5.9	2183.5	4638.8	0.471
7.1	2384.5	4649.7	0.513
8.1	2528.1	4724.8	0.535
9.0	2528.1	4575.4	0.553
10.0	2614.2	4507.8	0.580
10.9	2717.6	4583.1	0.593
12.1	2832.4	4604.1	0.615
13.0	2820.9	4572.1	0.617
13.9	2775.0	4455.7	0.623
14.9	2775.0	4426.9	0.627
15.9	2987.5	4699.7	0.636
17.0	2941.5	4577.5	0.643
18.1	2901.3	4600.6	0.631
19.0	2683.1	4349.2	0.617
20.0	2740.5	4491.9	0.610

BLOCK 53

Figure 13. Sample printer output--lateral force individual table.

TIRE C9	WET ASPHALT	40 MPH	RUN 01					
AVERAGE TABLE:	ALPHA	MUY	FY	FZ	AVE. LOAD :	4563.	PEAK MUY : 0.649	@ ALPHA : 17.0
	-0.7	-0.042	-194.0	4655.6				
	0.0	0.013	58.7	4548.9				
	1.0	0.116	546.8	4727.3				
	2.0	0.205	974.7	4759.3				
	3.0	0.290	1350.8	4656.0				
	4.0	0.364	1695.4	4661.6				
	5.0	0.427	1979.6	4635.7				
	6.0	0.476	2168.2	4557.9				
	7.0	0.513	2337.6	4559.8				
	8.0	0.541	2502.2	4622.7				
	9.0	0.567	2596.0	4576.4				
	9.9	0.592	2663.0	4495.8				
	11.0	0.613	2735.8	4463.7				
	12.0	0.626	2810.4	4486.8				
	13.0	0.638	2896.6	4540.8				
	14.0	0.644	2916.7	4526.4				
	15.0	0.646	2865.9	4435.4				
	16.0	0.649	2918.6	4499.2				
	17.0	0.649	2925.3	4507.8				
	18.0	0.646	2909.0	4499.3				
	19.0	0.643	2890.8	4492.3				
	20.0	0.642	2871.7	4472.5				

AVE. PEAK MUY : 0.660 STD. DEV. : 0.029

Figure 14. Sample printer tabulated output--lateral force average table.

AVE. PEAK MUY is the average of the peak values of (F_y/F_z) shown on the individual (F_y/F_z) versus α tables.

STD. DEV. is the standard deviation of the AVE. PEAK MUY value.

Finally, Figure 15 shows the corresponding print-plot for F_y/F_z versus α from the average table.

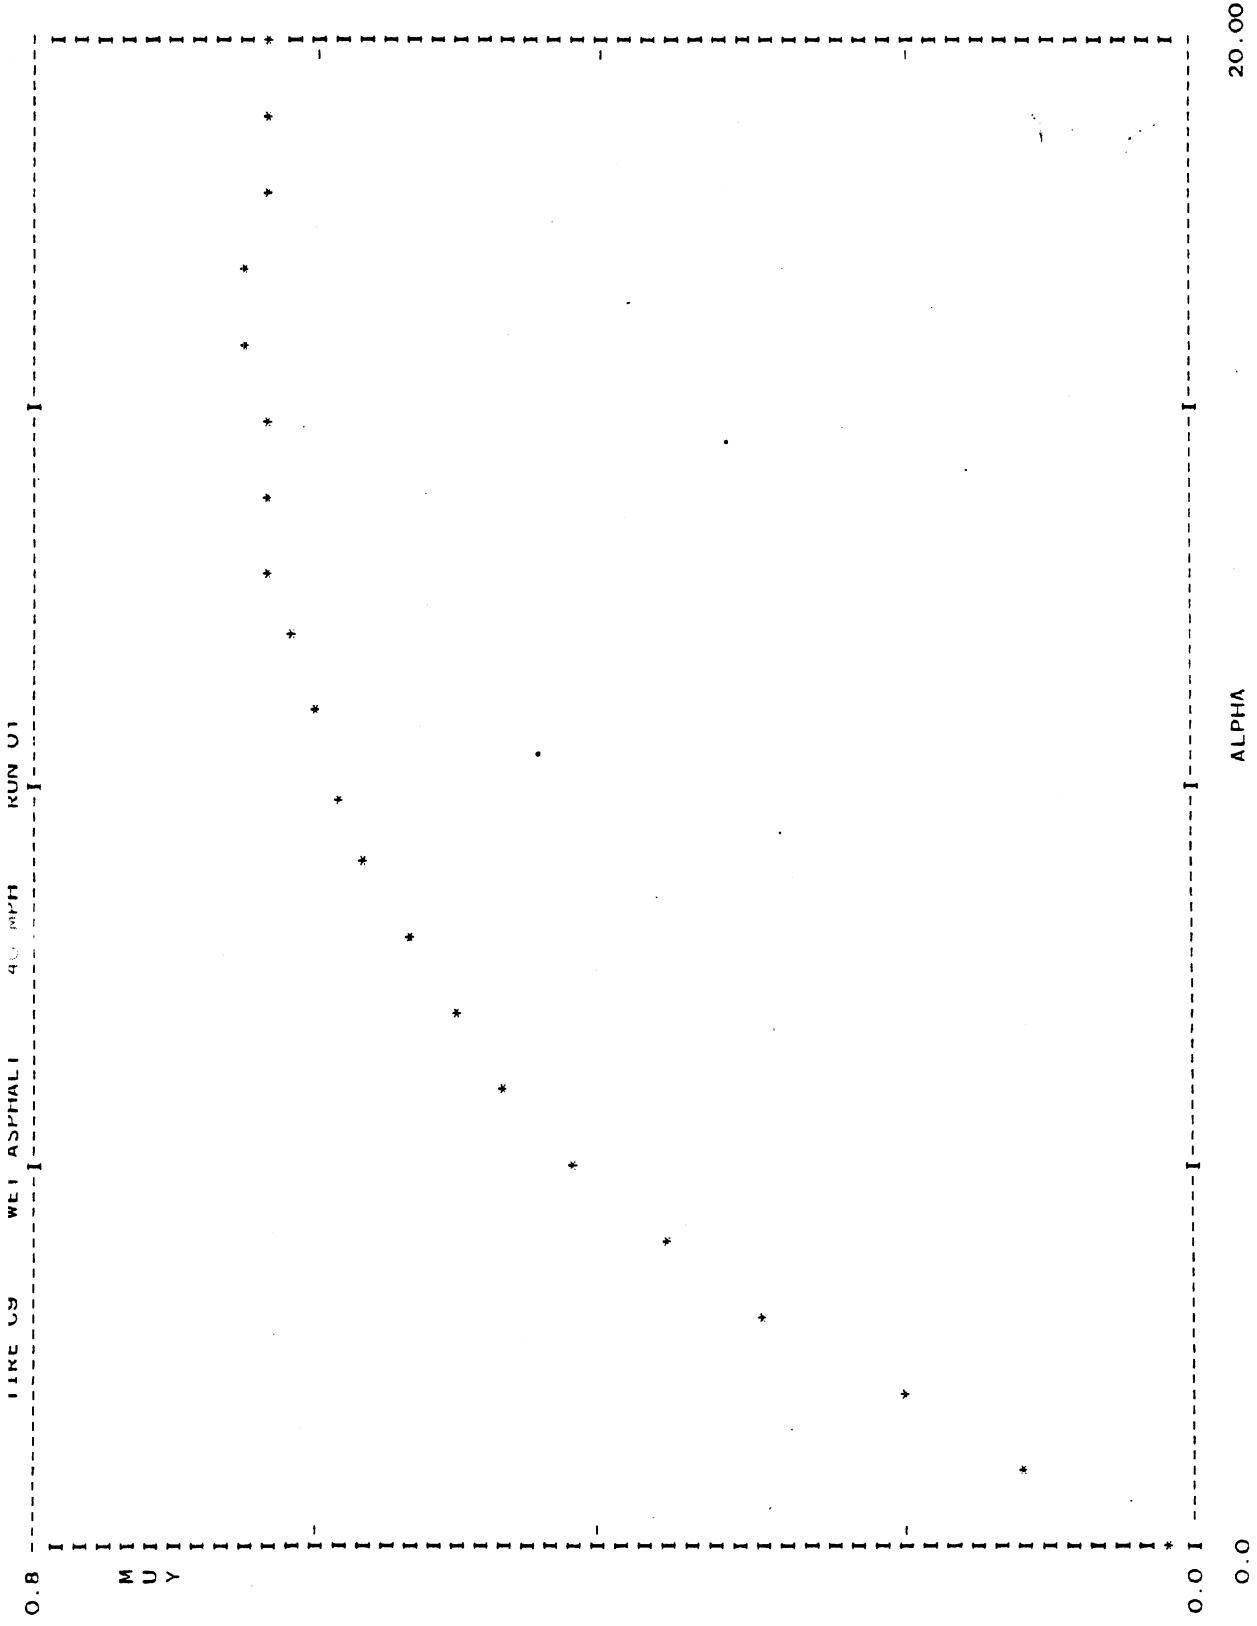


Figure 15. Sample page printer plot of normalized lateral force data.

APPENDIX A

PROCESSED RESULTS OF LONGITUDINAL TRACTION TESTS

In this section, computer-processed results from the longitudinal traction tests conducted on the eight test tires and five control tires are presented. Results appear in the following form:

- 1) A table of values representing the averaged normalized traction force, MUX, versus slip for the set of repeated lockup cycles.
- 2) A print-plot of the average MUX versus slip curve.
- 3) A listing of the values of certain numerics summarizing the traction measurements obtained in each of the individual repeat lockup cycles.

The presented numerics are defined in Section 2.3 of the technical report. Altogether, each tire is represented in the data listing by four sets of pages; that is, one set of pages for each of the four combinations of surface type and test speed. Each set of pages includes the three items cited above; that is, two tabular presentations and a plot of the average MUX versus slip curve.


The traction data presentation is preceded by a table summarizing the "condition data" pertaining to tire and weather conditions prevailing at the time of each test.

Date	Time	Tire Code No.	Inflation Pressure, psi		Shore A Rubber Hardness		Pavement Temp. °F		Water Temp. °F	Skies	Amb. Temp. °F	Relative Humidity %	Barometric Pressure in-Hg	Wind Comp. Direction Deg.	Wind Velocity mph
			Cold	Hot	Before	After	Asphalt	Concrete							
6/10/81	11:05A	C-1	85	94	49.8	50.8	68	71	55	Cloudy	67	78	28.6	315	10
6/10/81	12:52P	BR-1	85	94	58.0	59.0	84	79	65	Cloudy	68	68	28.6	350	5-10
6/10/81	4:10P	RR-1	90	97	54.8	60.7	87	85	55	Sunny	76	55	28.6	270	10-12
6/10/81	5:30P	C-2	85	94	50.0	50.8	87	86	62	Sunny	75	44	28.7	297	12-18
6/10/81	6:30P	BL-1	85	96	57.0	57.3	80	84	57	Sunny	75	46	28.7	270	10-18
31	6/11/81 5:30P	RL-1	90	104	62.1	59.6	78	76	55	Sunny	71	47	28.9	180	4-7
	6/11/81 7:28P	C-2	85	97	50.0	55.0	72	72	53	Cloudy	71	49	28.9	180	4-7
	6/11/81 8:45P	BR-2	85	96	57.6	60.6	71	70	54	Cloudy	70	50	28.9	180	3-5
	6/12/81 7:15A	RR-2	90	99	62.1	60.1	69	72	55	Pt. Sunny	67	61	28.9	151	6
	6/12/81 8:47A	C-1	85	98	49.8	50.8	74	71	56	Pt. Sunny	69	61	28.9	151	3-5
	6/12/81 10:00A	BL-2	85	98	57.6	56.2	79	76	55	Sunny	73	58	28.9	135	5-10
	6/12/81 11:30A	RL-2	90	103	61.7	58.2	82	82	61	Pt. Sunny	79	57	28.9	189	11-13
	6/12/81 12:35P	C-1	85	93	49.8	50.8	82	82	64	Cloudy	78	53	28.9	198	12-14

Longitudinal Traction - Condition Data

AVERAGE OF FILE		FOR 6 RECORDS		NEW FILE		TIRE C1		WET ASPHALT (TRC)		TEST SAMPLE 01 **	
SL IP	MUX	TORQUE	FX								
0.0	0.00	0.00	0.0								
0.02	C.18	17234.6	824.1								
0.04	0.33	31689.8	1501.2								
0.06	0.46	44608.5	2101.7								
0.08	0.56	53717.7	2540.7								
0.10	0.64	61685.2	2928.5								
0.12	0.69	66962.0	3177.8								
0.14	0.73	71218.4	3334.9								
0.16	0.77	74371.2	3468.4								
0.18	0.79	77488.5	3599.8	TQAV = 55958.3	LOAD = 4622.8	VEL = 40.0 MPH.					
0.20	0.81	80002.0	3677.2								
0.25	0.83	83781.1	3751.4	MUPEAK = 0.83	MULOCK = 0.60	RATIO = 1.37					
0.30	0.81	86109.9	3717.6								
0.35	0.79	87595.6	3606.6								
0.40	0.77	88869.8	3498.3								
0.45	0.75	89882.9	3401.7								
0.50	0.73	90735.7	3315.5								
0.55	0.72	91590.9	3245.7								
0.60	0.71	92394.2	3179.7								
0.65	0.70	92695.3	3120.8								
0.70	0.69	91759.1	3068.2								
0.75	0.68	88461.8	3020.5								
0.80	0.67	82093.6	2975.7								
0.85	0.66	75686.7	2926.5								
0.90	0.65	69772.4	2864.2								
0.95	0.64	63954.6	2812.6								
1.00	0.60	55958.3	2707.0								

000032

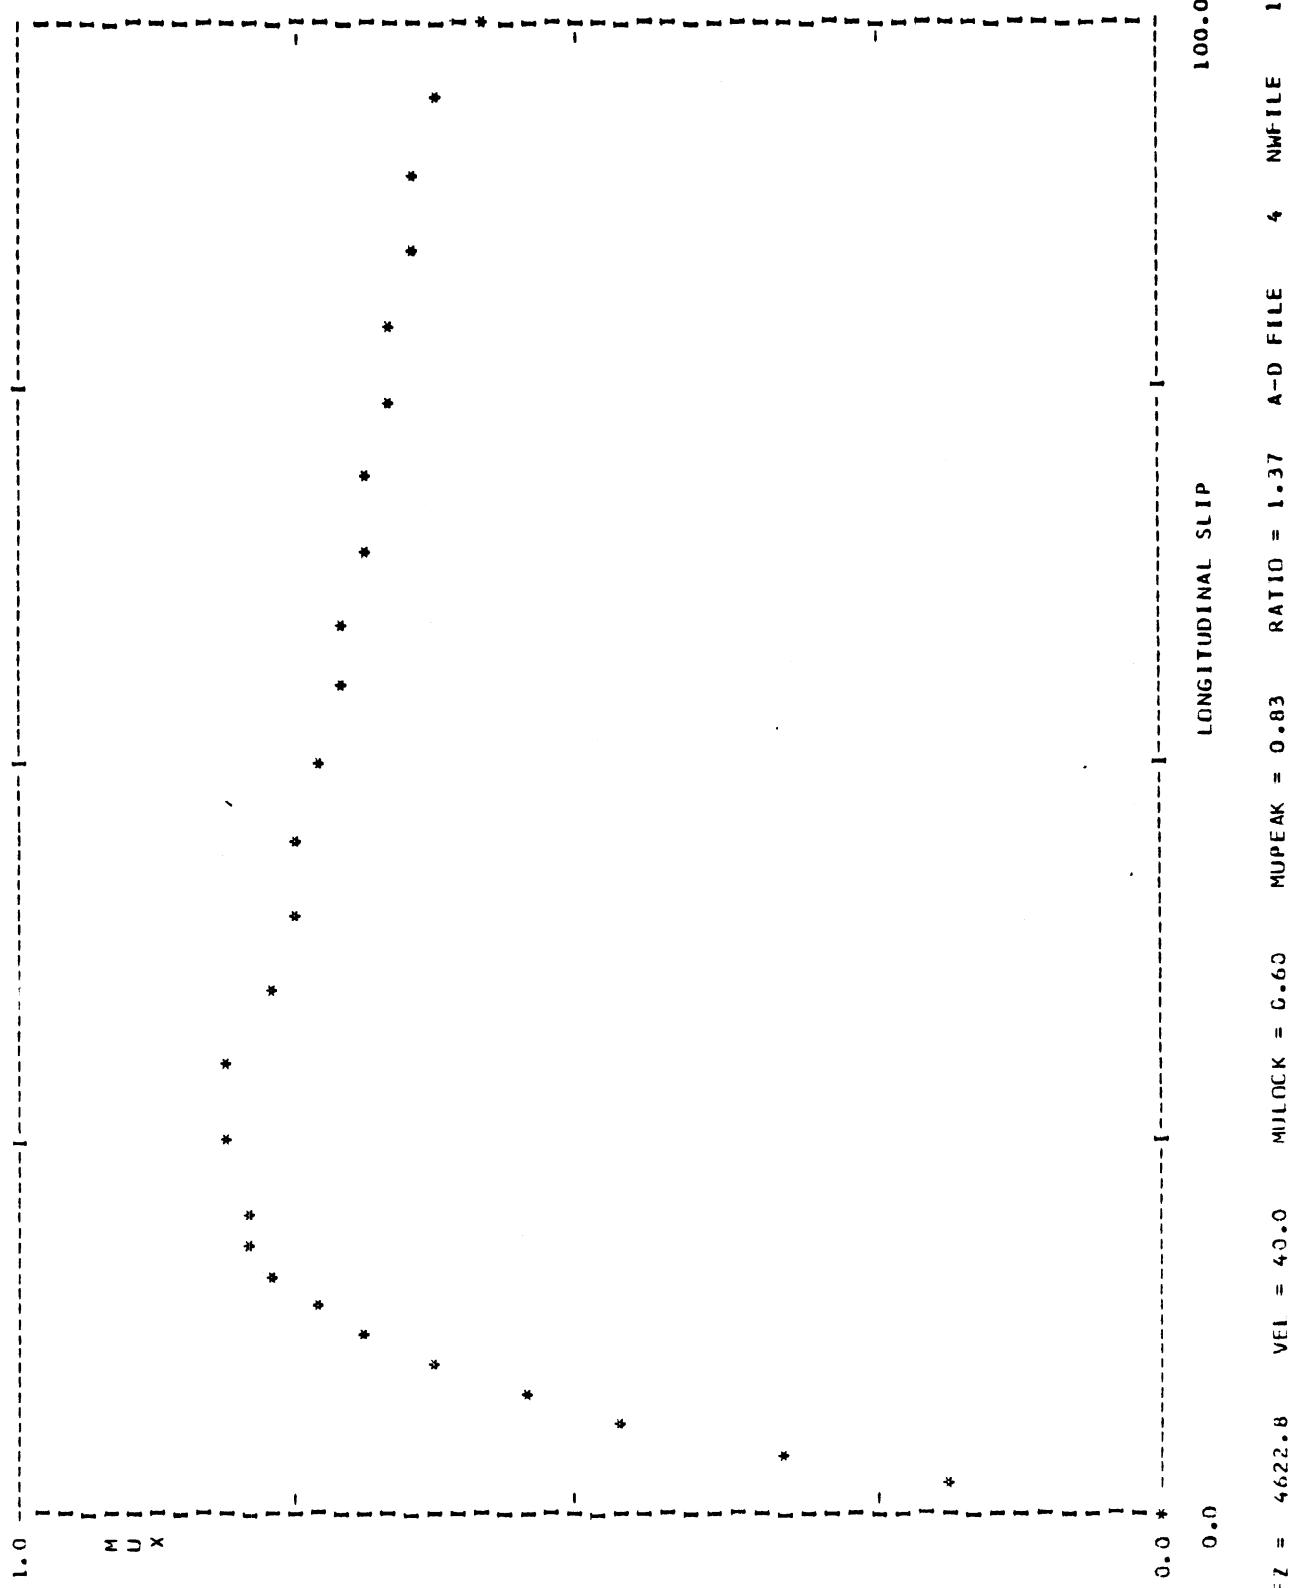

000033

F1 = 4622.8 VEL = 40.0 MULOCK = 6.60 MUPEAK = 0.83 RATIO = 1.37 A-D FILE 4 NMFILE 1 SAMPLE 101

MU-PEAK	SLIP@PEAK	MU-LICK
0.893	0.250	0.597
0.831	0.250	0.613
0.770	0.200	0.592
0.869	0.250	0.623
0.774	0.200	0.597
0.804	0.250	0.562

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.824 0.050
 MU-LICK AVERAGE VALUE AND STD. DEVIATION : 0.597 0.021


000034

AVERAGE OF FILE 5 FOR 5 RECORDS.

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.19	18276.5	828.5
0.04	0.33	32263.3	1507.9
0.06	0.44	43619.2	2014.2
0.08	0.53	52144.5	2414.5
0.10	0.58	57497.4	2639.0
0.12	0.62	61242.7	2805.0
0.14	0.66	65407.2	3004.5
0.16	0.68	69177.3	3118.5
0.18	0.69	72667.5	3204.5
0.20	0.69	74244.3	3184.9
0.25	0.69	76890.3	3121.2
0.30	0.68	79281.0	3056.1
0.35	0.67	81303.3	3002.4
0.40	0.66	83088.9	2955.9
0.45	0.65	84564.0	2908.5
0.50	0.64	85851.8	2864.5
0.55	0.63	87073.4	2813.3
0.60	0.62	88069.3	2759.3
0.65	0.60	88954.1	2695.9
0.70	0.59	89088.9	2630.4
0.75	0.57	86464.3	2567.8
0.80	0.56	78154.3	2510.0
0.85	0.55	70011.0	2449.5
0.90	0.53	62521.1	2372.5
0.95	0.52	55333.5	2330.5
1.00	0.46	44649.9	2140.2

000035

TIRE C1 WET ASPHALT (TRC)

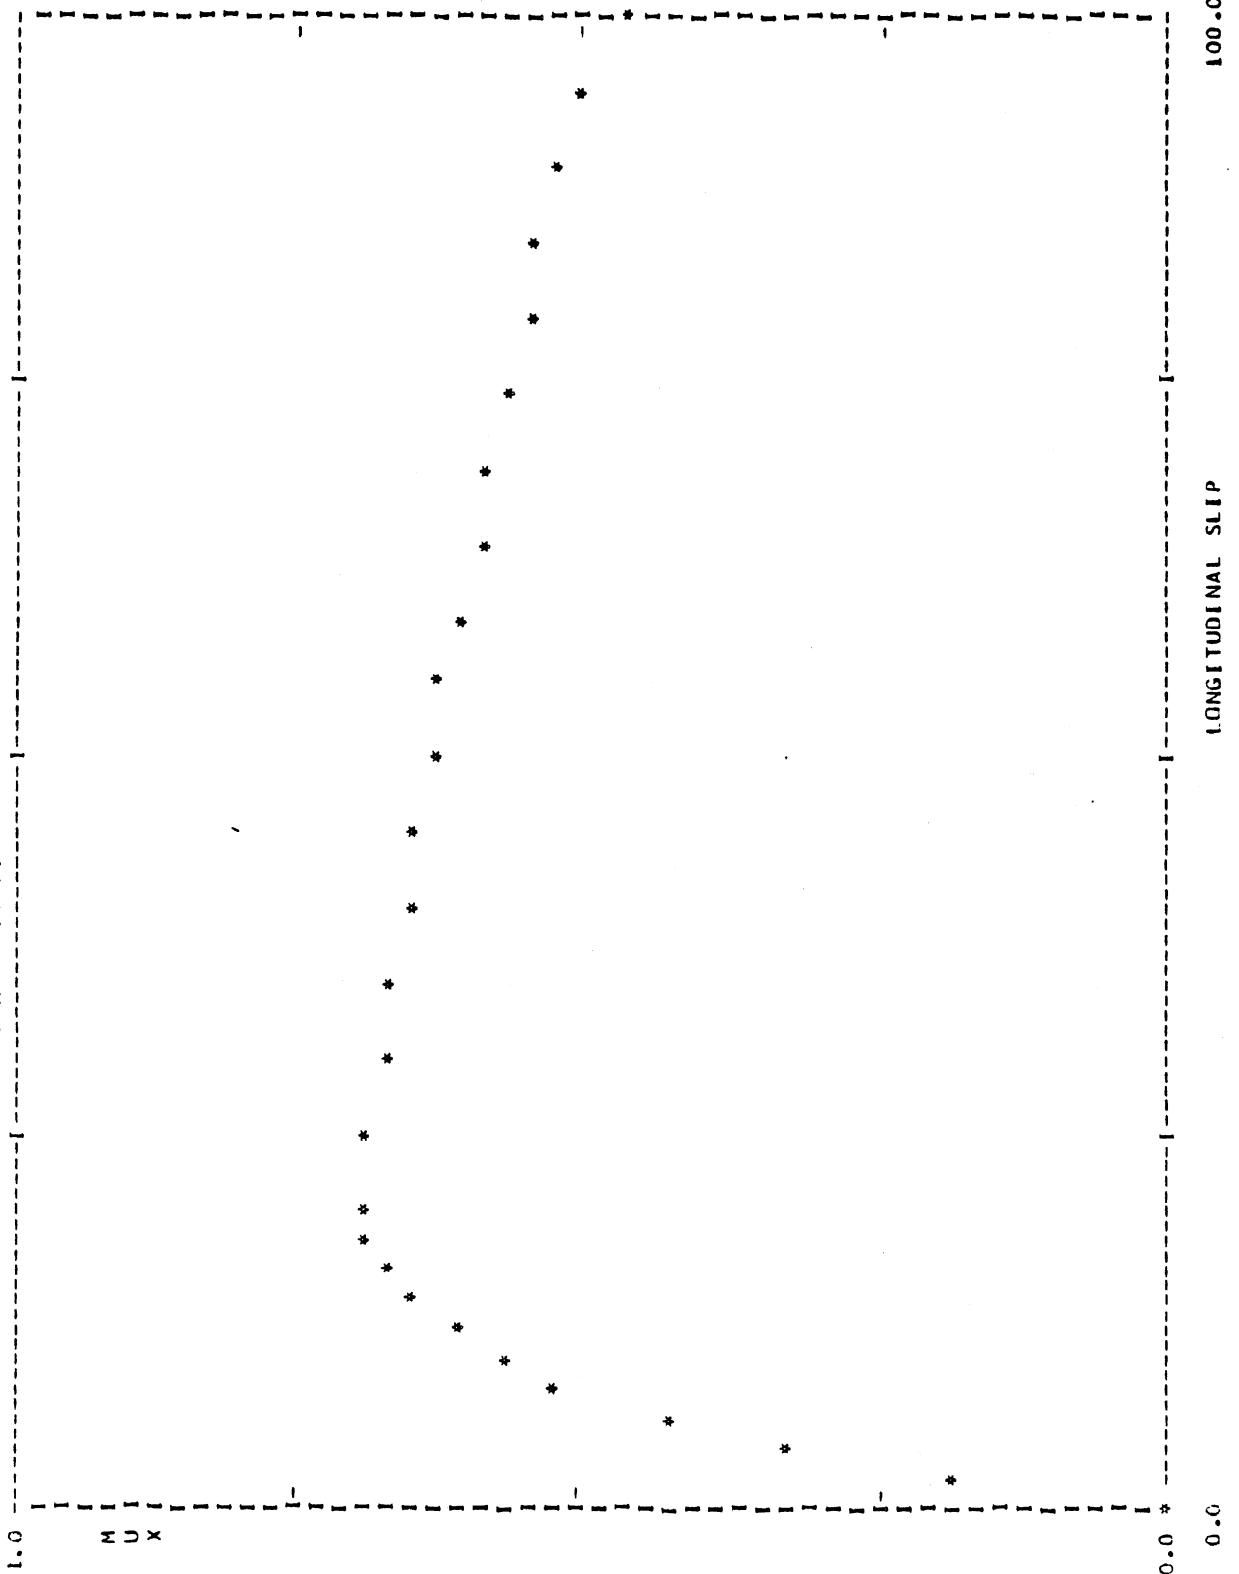

000036

FZ = 4668.8 VEL = 50.0 MULLOCK = 0.46 MUFAK = 0.69 RATIO = 1.50 A-D FILE S NWFILE 2 SAMPLE 102
LONGITUDINAL SLIP

MU-PEAK	STIPPEAK	MU-LOCK
0.816	0.186	0.495
0.698	0.160	0.468
0.671	0.250	0.437
0.671	0.200	0.426
0.619	0.300	0.466

MJ-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.695 0.074
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.459 0.027

00003

TEST SAMPLE 103 **

** A-D FILE 9


NEW FILE 3

AVERAGE OF FILE 9 FOR 6 RECORDS.

TIRE C1
WET CONCRETE (TRC)

SLIP	MU(X)	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.17	15664.4	781.0
0.04	0.25	24039.6	1119.5
0.06	0.31	29741.2	1358.9
0.08	0.35	34472.4	1550.5
0.10	0.37	37547.4	1663.8
0.12	0.39	40164.3	1749.9
0.14	0.40	42476.2	1810.0
0.16	0.41	44283.4	1850.1
0.18	0.42	45734.5	1873.0
0.20	0.42	47017.5	1889.6
0.25	0.42	49452.7	1901.4
0.30	0.42	51370.7	1888.1
0.35	0.42	52967.9	1865.9
0.40	0.41	54448.8	1839.7
0.45	0.41	55818.4	1819.0
0.50	0.41	57060.3	1798.4
0.55	0.40	58222.4	1773.5
0.60	0.40	59357.8	1742.1
0.65	0.39	60409.1	1701.0
0.70	0.38	60968.7	1652.0
0.75	0.37	58977.2	1600.9
0.80	0.36	53204.7	1551.8
0.85	0.34	46481.1	1498.5
0.90	0.33	40616.0	1431.3
0.95	0.31	34014.7	1361.3
1.00	0.24	22541.7	1094.5

0000033

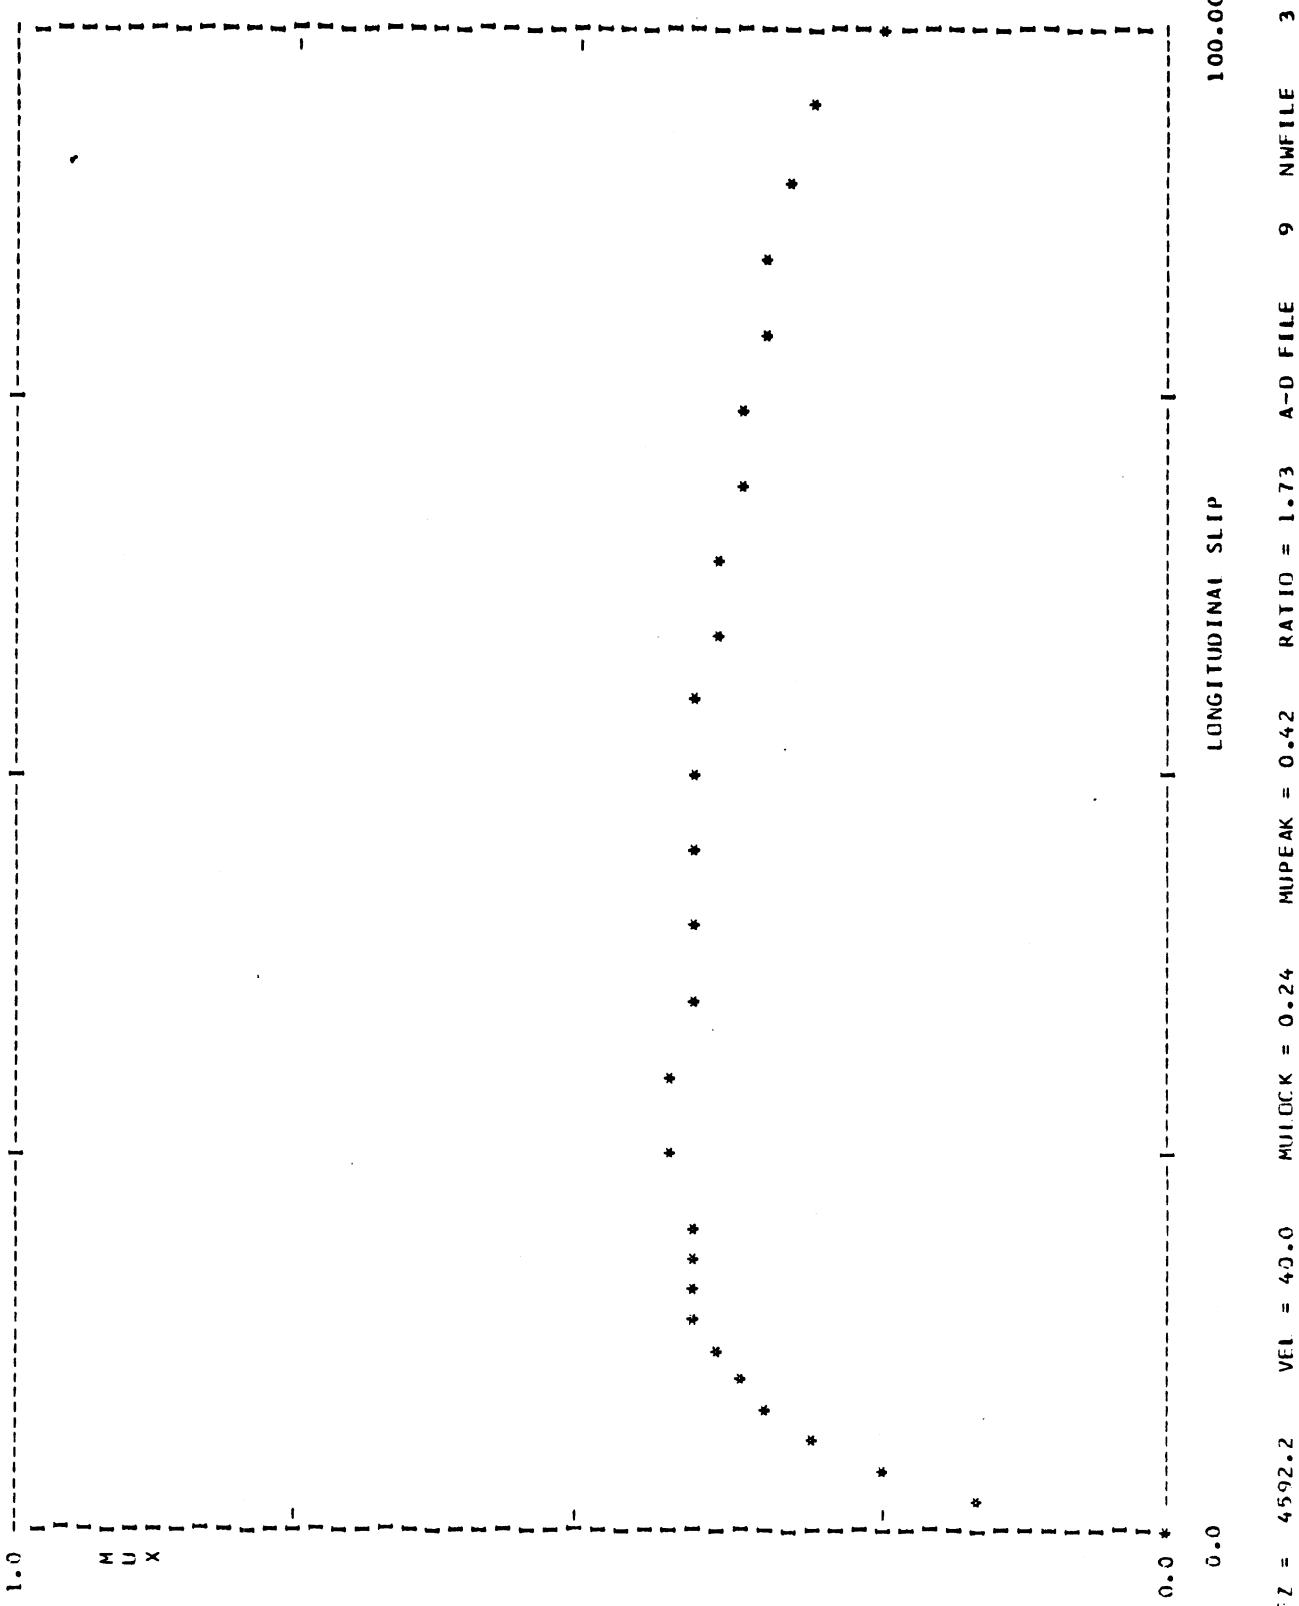

000039

MU-PEAK	S L I P P E A K	MU-LOCK
0.454	0.450	0.257
0.432	0.200	0.257
0.471	0.250	0.253
0.442	0.120	0.248
0.389	0.350	0.193
0.380	0.400	0.222


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.428 0.036
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.239 0.026

000040

SLIP	MU X	TURQUE	TIRE C1			WET CONCRETE (TRC)
			F X	M X	T QAV	
0.0	0.00	0.0	0.0	0.0	0.0	
0.02	0.15	14513.4	676.7			
0.04	0.22	21783.4	1004.2			
0.06	0.27	27971.4	1227.5			
0.08	0.29	31896.3	1346.0			
0.10	0.31	34968.4	1425.6			
0.12	0.32	37114.7	1464.1			
0.14	0.33	38722.1	1484.1			
0.16	0.33	40148.0	1495.2			
0.18	0.33	41443.8	1502.3			
0.20	0.34	42680.7	1510.5			
0.25	0.35	45405.8	1544.5			
0.30	0.35	47584.0	1571.8			
0.35	0.35	49693.6	1582.7			
0.40	0.35	51730.1	1574.5			
0.45	0.34	53608.1	1545.5			
0.50	0.33	55222.2	1502.8			
0.55	0.32	56562.3	1454.8			
0.60	0.31	57723.4	1403.3			
0.65	0.30	58707.5	1346.5			
0.70	0.29	59163.0	1283.3			
0.75	0.28	57419.1	1221.1			
0.80	0.26	50952.8	1165.6			
0.85	0.26	42432.0	1116.7			
0.90	0.24	34999.9	1052.4			
0.95	0.23	28028.2	988.6			
1.00	0.18	16708.3	805.0			

0000041

TIRE C1 WET CONCRETE (TRC)

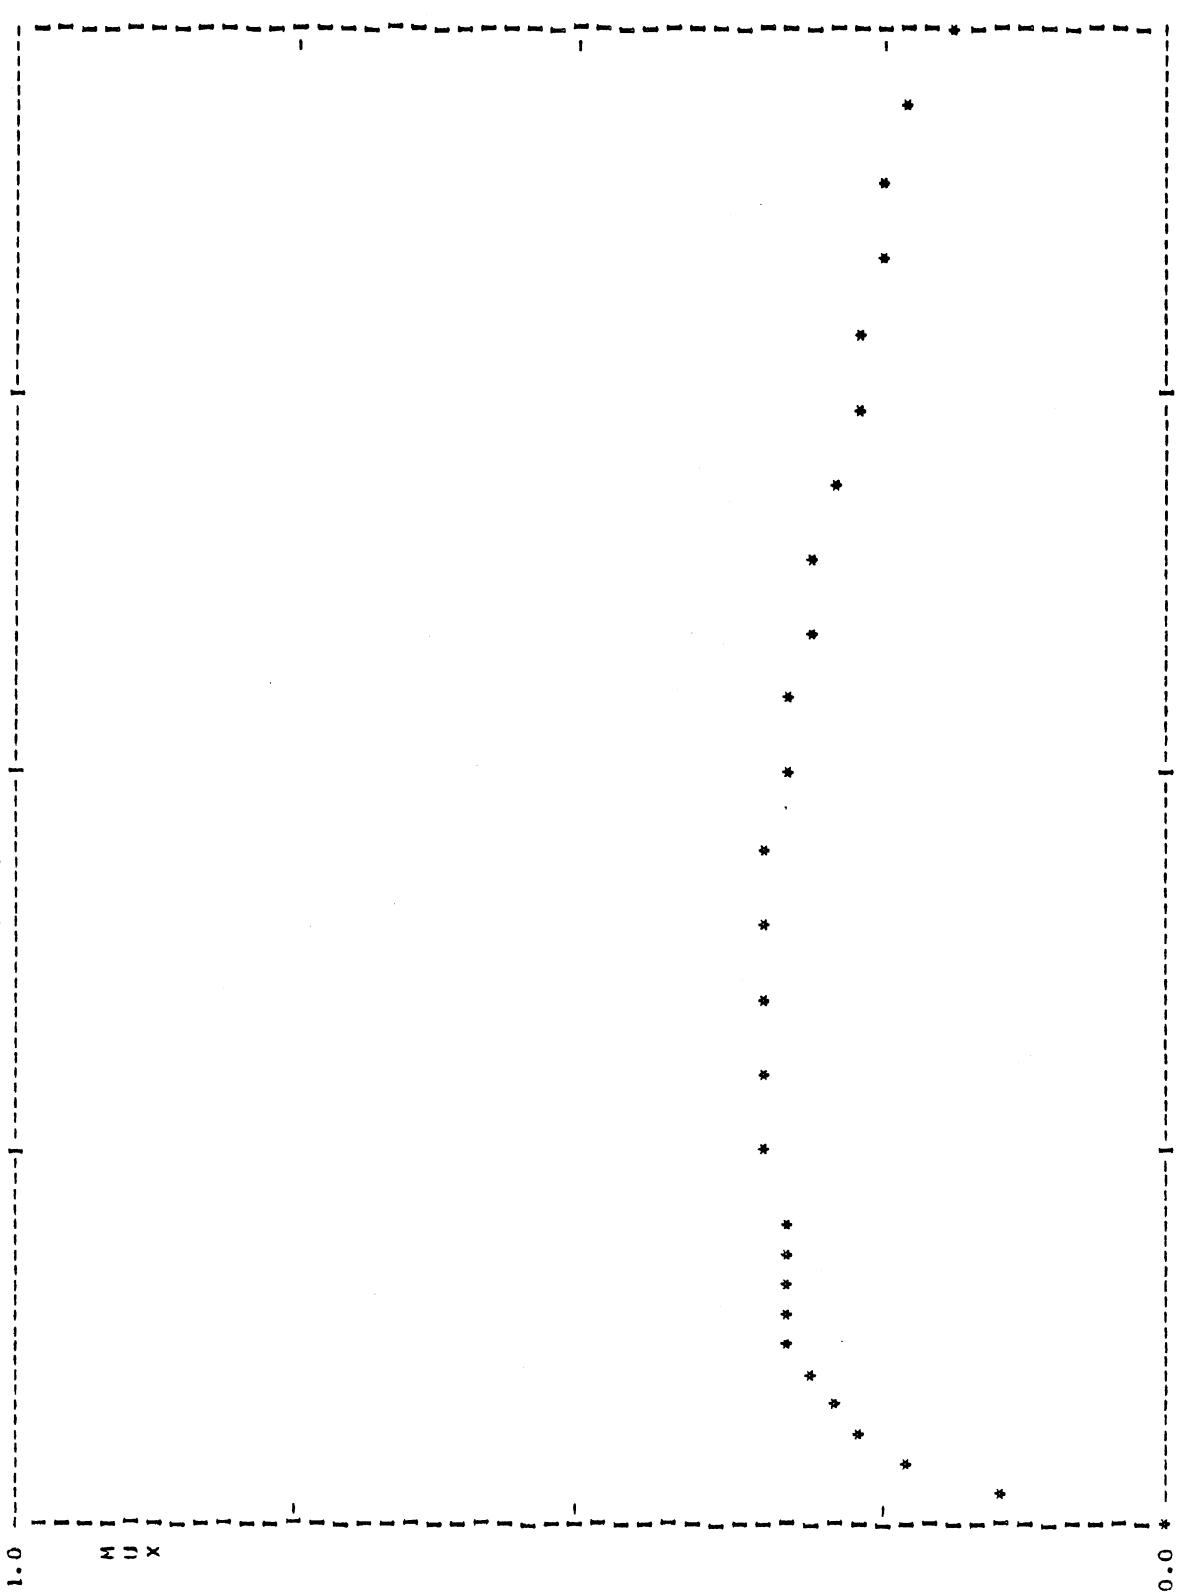

000042

FZ = 4596.5 VEL = 50.0 MULOCK = 0.18 MUPEAK = 0.35 RATIO = 1.91 A-D FILE 10 NMFILE 4 SAMPLE 104

MU-PEAK	SLIP@PEAK	MU-LICK
0.363	0.300	0.188
0.335	0.430	0.167
0.400	0.180	0.228
0.314	0.450	0.170
0.334	0.120	0.171
0.365	0.300	0.150


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.352 0.031
 MU-LICK AVERAGE VALUE AND STD. DEVIATION : 0.179 0.027

000043

** A-D FILE 21
AVERAGE OF FILE 21 FOR 5 RECORDS.

SLIP	MUx	TORQUE	FX	NEW FILE 5	TIRE BRI	WET ASPHALT (TRC)	TEST SAMPLE 105 **
0.0	0.30	0.0	0.0				
0.02	0.23	21257.5	1034.4				
0.04	0.41	36494.7	1848.2				
0.06	0.57	52901.8	2561.3				
0.08	0.67	63054.5	3032.1				
0.10	0.72	69200.5	3264.9				
0.12	0.78	73990.9	3488.7				
0.14	0.81	79805.4	3727.6				
0.16	0.82	82203.2	3766.9				
0.18	0.82	83194.6	3747.5	TQAV = 55199.9	LOAD = 4620.5	VEL = 40.0 MPH.	
0.20	0.81	84110.8	3716.4				
0.25	0.81	86115.9	36333.5	MUPEAK = 0.82	MULOCK = 0.60	RATIO = 1.36	
0.30	0.80	87810.2	3565.4				
0.35	0.79	89483.8	3501.9				
0.40	0.78	90834.5	3439.2				
0.45	0.76	91831.7	3372.2				
0.50	0.75	92840.3	3305.0				
0.55	0.73	93716.5	3237.6				
0.60	0.72	94518.4	3169.3				
0.65	0.70	94878.6	3105.2				
0.70	0.69	93462.2	3049.9				
0.75	0.68	89031.2	2999.8				
0.80	0.66	82735.1	2954.1				
0.85	0.65	76193.3	2905.8				
0.90	0.64	70177.1	2853.9				
0.95	0.62	64097.3	2797.9				
1.00	0.60	55199.9	2682.6				

000044

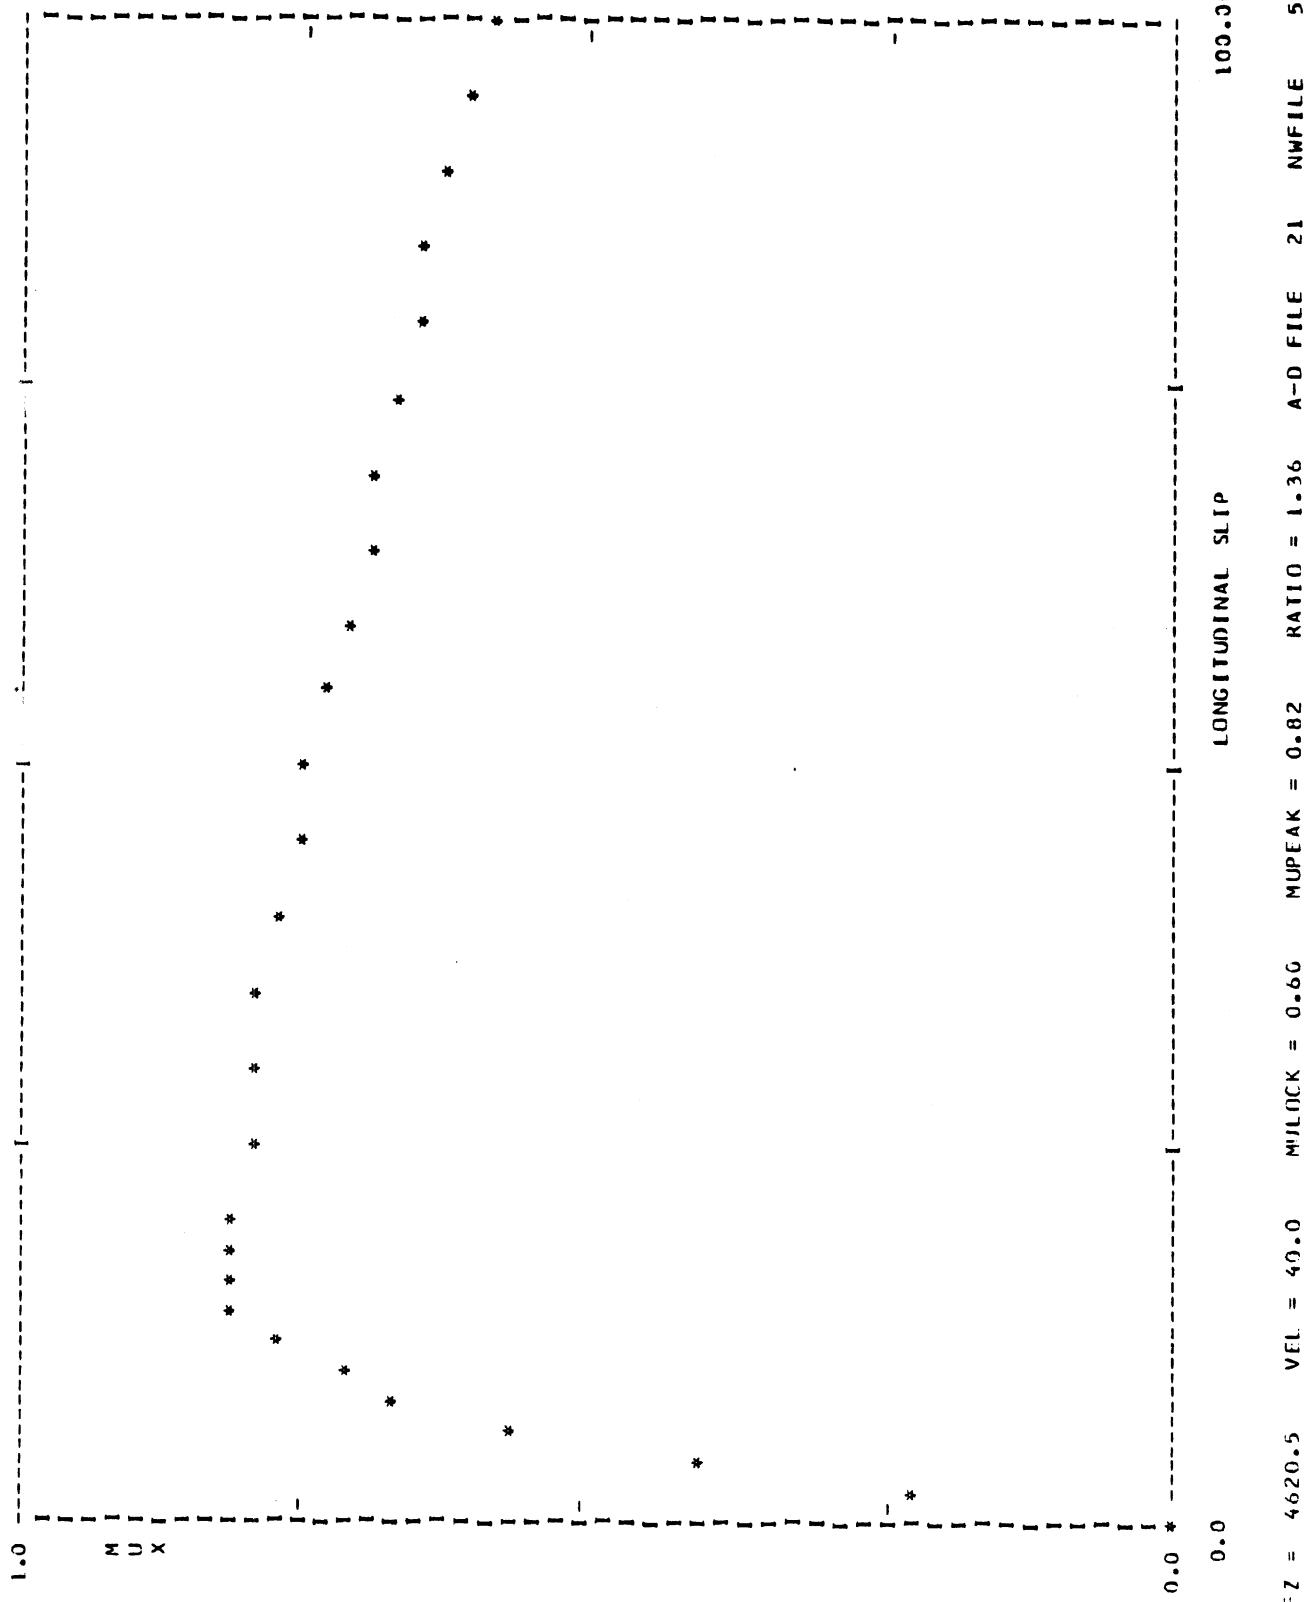

000045

MU-Peak	Slip Peak	MU-Lock
0.894	0.160	0.589
0.822	0.140	0.640
0.819	0.200	0.569
0.791	0.250	0.600
0.786	0.143	0.579


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.823 0.043
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.595 0.027

000046

SLIP	MUX	TORQUE	FX	
0.0	0.70	0.0	0.0	
0.02	0.22	21794.7	1921.1	
0.04	0.40	38052.1	1814.5	
0.06	0.54	52746.5	2471.6	
0.08	0.62	60223.0	2814.5	
0.10	0.70	66549.9	3102.0	
0.12	0.74	71196.6	3307.7	
0.14	0.76	75052.6	3424.9	
0.16	0.77	77285.6	3486.5	
0.18	0.77	79310.2	3504.5	
0.20	0.76	80616.2	3485.0	
0.25	0.74	82788.8	3400.7	
0.30	0.72	84451.3	3306.2	
0.35	0.70	86021.3	3221.0	
0.40	0.69	87267.6	3143.0	
0.45	0.68	88438.6	3073.4	
0.50	0.67	89499.1	3012.3	
0.55	0.66	90384.1	2955.0	
0.60	0.64	91188.3	2901.3	
0.65	0.63	91921.9	2841.9	
0.70	0.62	92147.0	2783.0	
0.75	0.61	90050.0	2728.8	
0.80	0.60	82172.1	2681.3	
0.85	0.59	74123.7	2632.9	
0.90	0.57	66614.0	2574.6	
0.95	0.56	59849.2	2532.6	
1.00	0.52	49249.9	2378.5	

000047

TIRE BR1 WET ASPHALT (TRC)

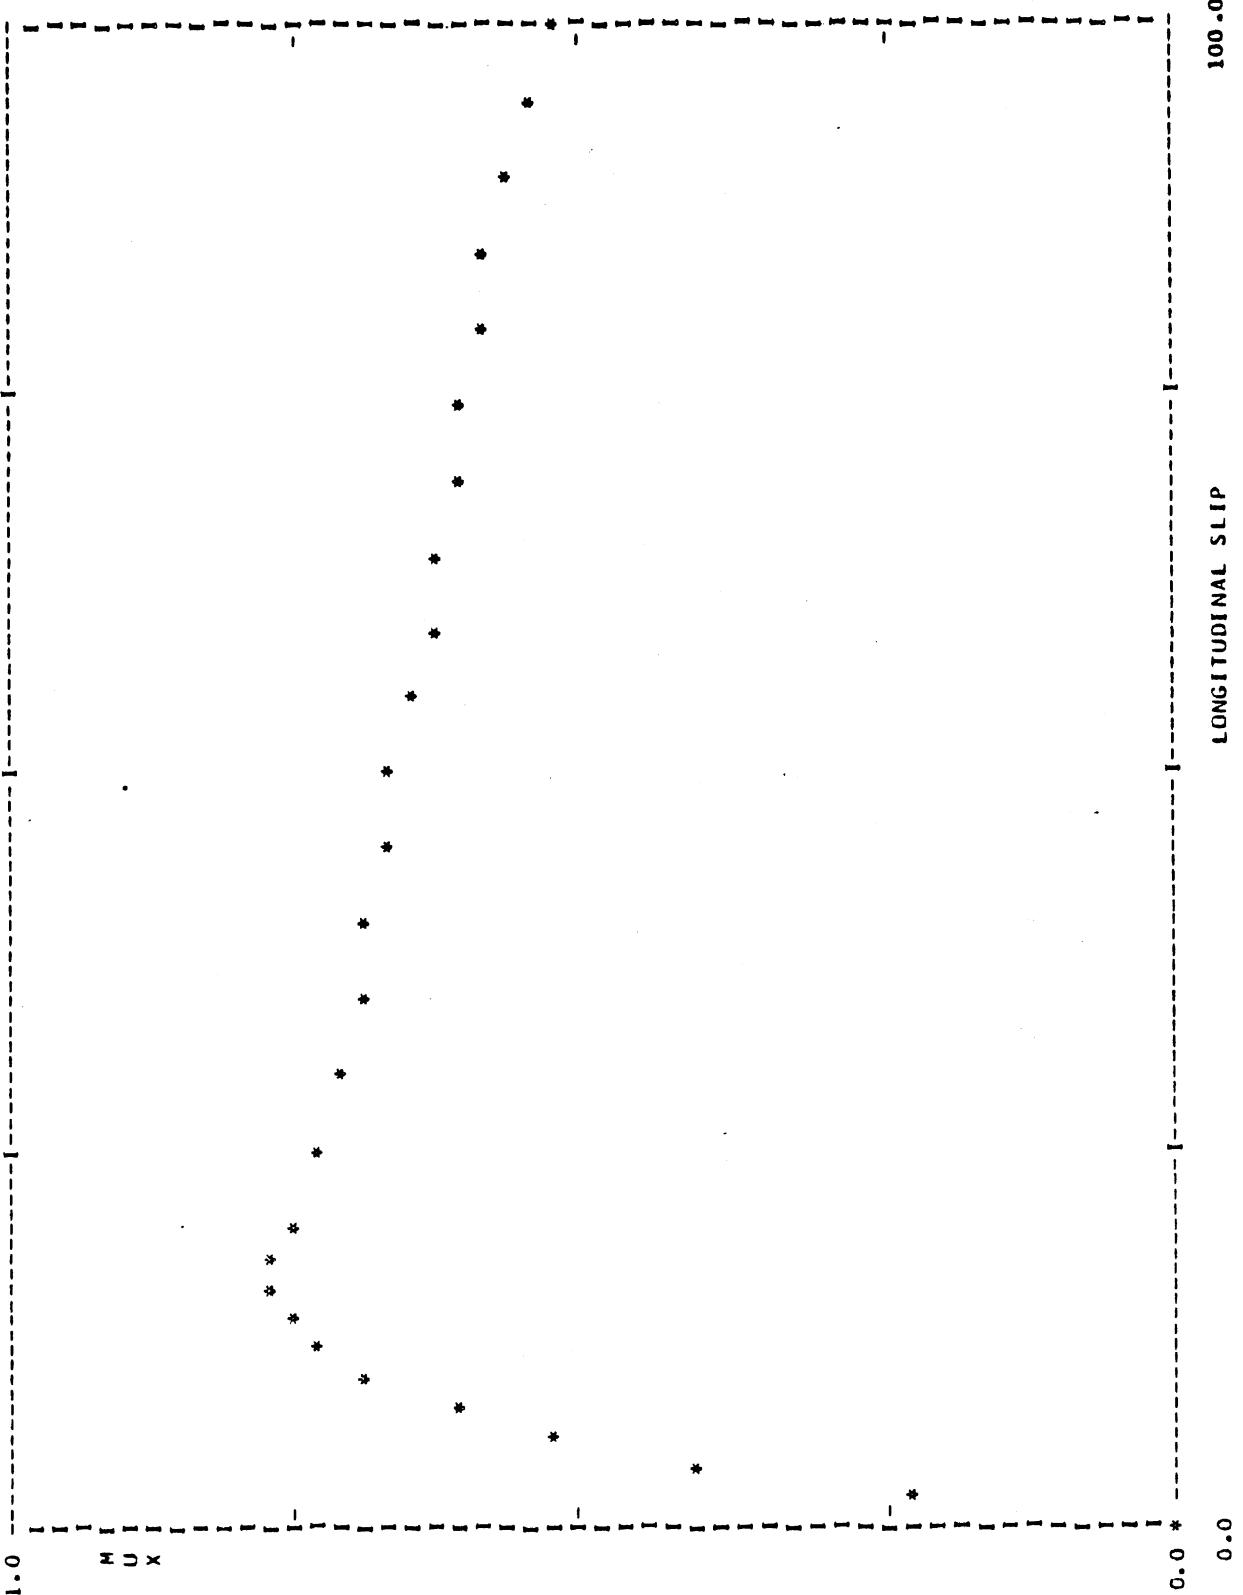

000048

FZ = 4672.9 VEL = 56.0 MULOCK = 0.52 MUPEAK = 0.77 RATIO = 1.47 A-D FILE 21 NWFILE 56 SAMPLE 106

MU-PEAK	SLIP@PEAK	MU-LOCK
0.859	0.200	0.523
0.781	0.140	0.511
0.784	0.180	0.516
0.683	0.120	0.517
0.753	0.160	0.535
0.748	0.160	0.505

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.768 0.057
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.518 0.010


000049

000050

** A-D FILE 25 NEW FILE 6 TEST SAMPLELOT **

AVERAGE OF FILE 25 FOR 6 RECORDS. TIRE BR1 WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.18	18260.1	839.2
0.04	0.26	26598.2	1176.8
0.06	0.31	31789.2	1391.1
0.08	0.34	36233.8	1509.5
0.10	0.35	39310.6	1582.3
0.12	0.36	41508.9	1625.3
0.14	0.37	43105.5	1657.0
0.16	0.37	44536.9	1682.1
0.18	0.37	45761.9	1699.5
0.20	0.38	46893.3	1716.2
0.25	0.39	49532.4	1755.8
0.30	0.40	51816.6	1799.0
0.35	0.41	53910.2	1809.1
0.40	0.41	55859.0	1800.1
0.45	0.40	57716.2	1774.3
0.50	0.40	59309.1	1744.5
0.55	0.39	60672.1	1715.1
0.60	0.39	61871.0	1688.6
0.65	0.38	62933.9	1664.2
0.70	0.38	63067.7	1644.2
0.75	0.37	61015.6	1630.8
0.80	0.37	55642.0	1617.9
0.85	0.36	49799.7	1601.8
0.90	0.35	43939.0	1566.3
0.95	0.34	37662.3	1508.3
1.00	0.31	29104.2	1386.0

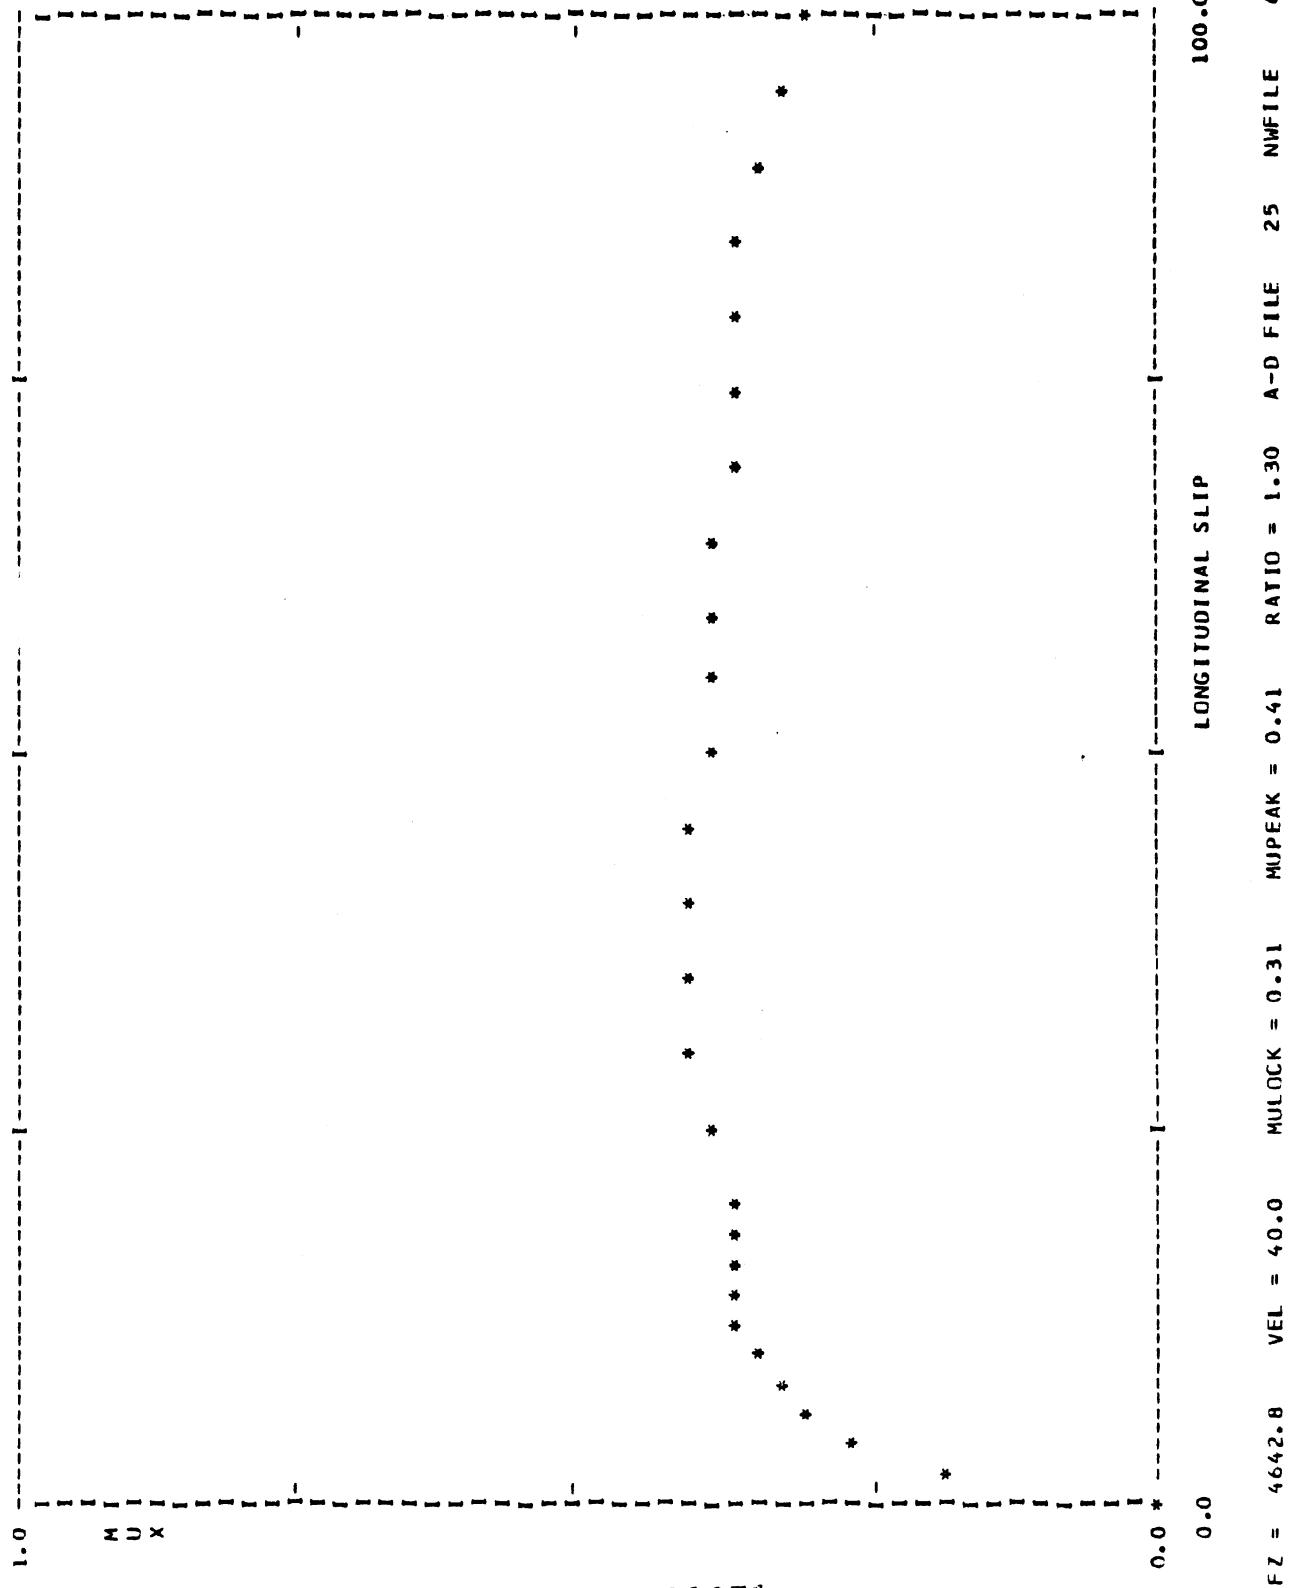

	MU-PEAK	SLIP-PEAK	MU-LOCK
	0.386	0.350	0.286
	0.369	0.550	0.305
	0.446	0.300	0.333
	0.451	0.160	0.329
	0.384	0.350	0.307
	0.390	0.400	0.285

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.404 0.035
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.308 0.020

000052

SLIP	AVERAGE OF FILE	FILE 26 FOR 6 RECORDS.	TORQUE	FX	FY	WET CONCRETE (TRC)
0.0	0.00	0.0	0.0	0.0	0.0	
0.02	0.17	16750.0	762.8			
0.04	0.25	24996.7	1109.5			
0.06	0.31	31366.8	1370.7			
0.08	0.32	35761.4	1471.7			
0.10	0.33	38548.3	1514.1			
0.12	0.34	40206.7	1534.8			
0.14	0.34	41547.5	1548.0			
0.16	0.34	42847.9	1556.5			
0.18	0.35	44087.3	1564.3	TQAV = 28229.2	LOAD = 4642.4	VEL = 50.0 MPH.
0.20	0.35	45440.9	1568.6			
0.25	0.35	48613.6	1580.8	MUPEAK = 0.37	MULOCK = 0.31	RATIO = 1.20
0.30	0.36	51154.9	1592.6			
0.35	0.36	53136.3	1590.2			
0.40	0.36	54882.1	1591.5			
0.45	0.36	56672.5	1602.0			
0.50	0.36	58295.8	1616.2			
0.55	0.37	59789.5	1633.4			
0.60	0.37	61162.4	1645.4			
0.65	0.37	62416.2	1649.5			
0.70	0.36	63450.6	1636.3			
0.75	0.35	63325.9	1610.3			
0.80	0.34	59367.5	1581.9			
0.85	0.34	51386.3	1552.2			
0.90	0.33	43877.6	1502.3			
0.95	0.31	36331.2	1434.0			
1.00	0.31	28229.2	1360.5			

000053

000054



FZ = 4642.4 VEL = 50.0 MULLOCK = 0.31 MUPEAK = 0.37 RATIO = 1.20 A-D FILE 26 NMFILE 7 SAMPLE 108


MU-PEAK	SLIP@PEAK	MU-LOCK
0.363	0.250	0.319
0.359	0.600	0.278
0.381	0.550	0.322
0.357	0.200	0.285
0.380	0.350	0.313
0.393	0.650	0.297

MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.372	0.014
MU-LOCK AVERAGE VALUE AND STD. DEVIATION :	0.302	0.018

000051

** A-D FILE		30	FOR 6 RECORDS.		NEW FILE	8	TEST SAMPLE109 **
SLIP	MUX	TORQUE		TIRE RRI	WET ASPHALT (TRC)		FX
0.0	0.00	0.0		0.0	0.0		
0.02	0.27	25668.1		1234.1			
0.04	0.47	46087.3		2185.0			
0.06	0.61	59860.7		2839.4			
0.08	0.67	65987.7		3094.5			
0.10	0.72	70209.4		3260.3			
0.12	0.75	73734.3		3378.9			
0.14	0.76	76486.0		3453.3			
0.16	0.77	78383.6		3465.1			
0.18	0.76	79915.3		3451.7			
0.20	0.76	81117.6		3424.8			
0.25	0.74	83055.7		3345.0			
0.30	0.73	84377.0		3259.7			
0.35	0.71	85449.8		3180.7			
0.40	0.69	86429.3		3106.3			
0.45	0.68	87388.8		3040.5			
0.50	0.67	88224.8		2978.3			
0.55	0.65	89044.6		2919.1			
0.60	0.64	89804.1		2859.8			
0.65	0.62	90308.7		2799.3			
0.70	0.61	89392.3		2740.5			
0.75	0.60	84935.1		2692.5			
0.80	0.58	76635.7		2649.2			
0.85	0.57	69286.1		2588.8			
0.90	0.55	64482.3		2499.7			
0.95	0.53	57008.1		2424.2			
1.00	0.49	46708.3		2240.5			

000056

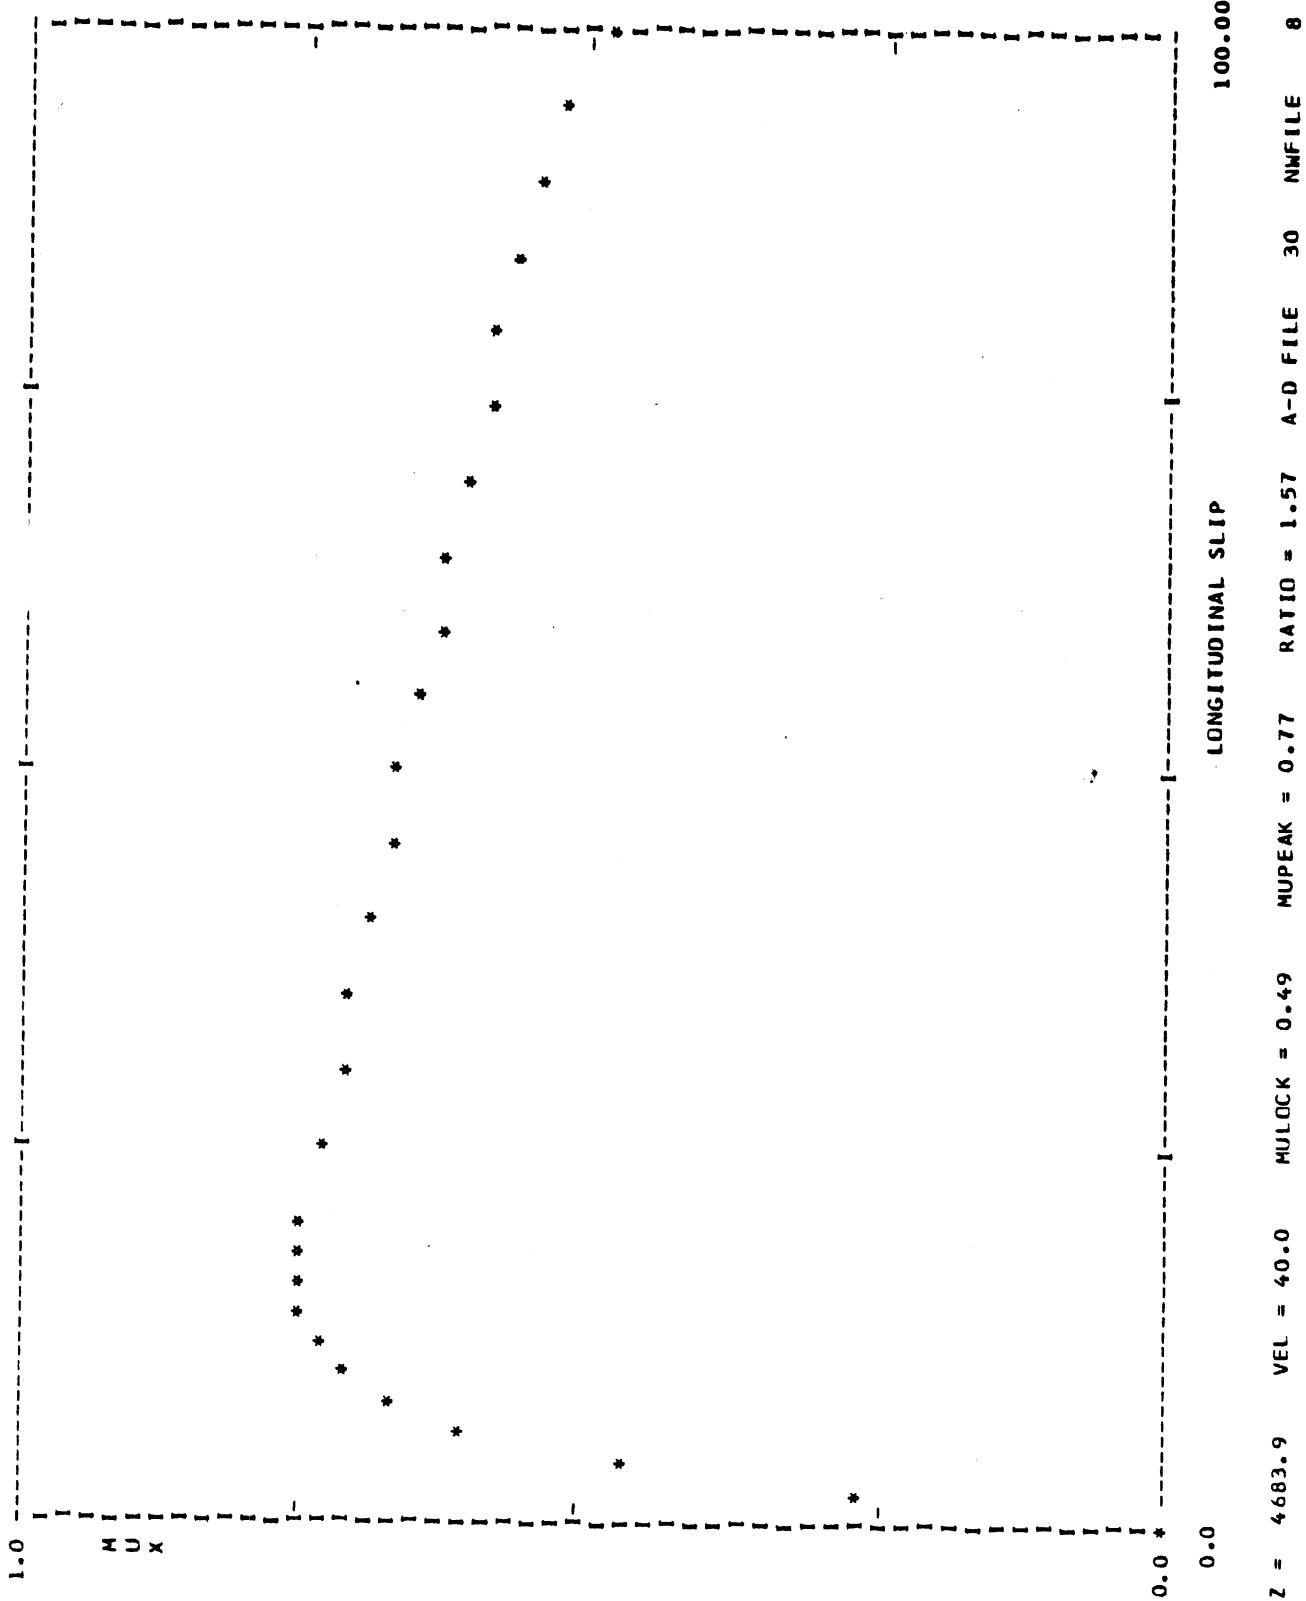

MU-PEAK	SLIP@PEAK	MU-LOCK
0.755	0.160	0.503
0.801	0.140	0.506
0.779	0.140	0.478
0.746	0.200	0.461
0.719	0.180	0.466
0.800	0.160	0.492


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.767 0.032
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.684 0.019

000058

AVERAGE OF FILE 31 FOR 5 RECORDS. TIRE RR1 WET ASPHALT (TRC)
 SLIP MU_X TORQUE FX
 0.0 0.00 0.0 0.0
 0.02 0.27 26795.1 1236.1
 0.04 0.47 45232.5 2151.3
 0.06 0.57 56786.3 2641.0
 0.08 0.61 61771.5 2774.9
 0.10 0.65 66070.9 2902.4
 0.12 0.69 69107.1 3032.9
 0.14 0.72 71155.4 3148.0
 0.16 0.73 73364.5 3213.8
 0.18 0.73 75366.3 3231.8 TQAV = 40349.9 LOAD = 4605.0 VEL = 50.0 MPH.
 0.20 0.73 77152.6 3226.7
 0.25 0.71 80557.9 3185.4 MUPEAK = 0.73 MULOCK = 0.43 RATIO = 1.72
 0.30 0.69 82593.3 3113.1
 0.35 0.66 84098.6 3020.7
 0.40 0.64 85173.1 2925.4
 0.45 0.62 86063.8 2832.5
 0.50 0.60 86660.8 2741.1
 0.55 0.57 87146.7 2649.8
 0.60 0.56 87611.9 2562.5
 0.65 0.54 88084.9 2475.2
 0.70 0.52 87913.5 2390.6
 0.75 0.50 84863.4 2316.1
 0.80 0.49 75990.1 2255.8
 0.85 0.48 65606.4 2194.0
 0.90 0.46 59306.0 2104.0
 0.95 0.45 50956.4 2040.1
 1.00 0.43 40349.9 1911.6

000053

TIRE RRI WET ASPHALT (TRC)

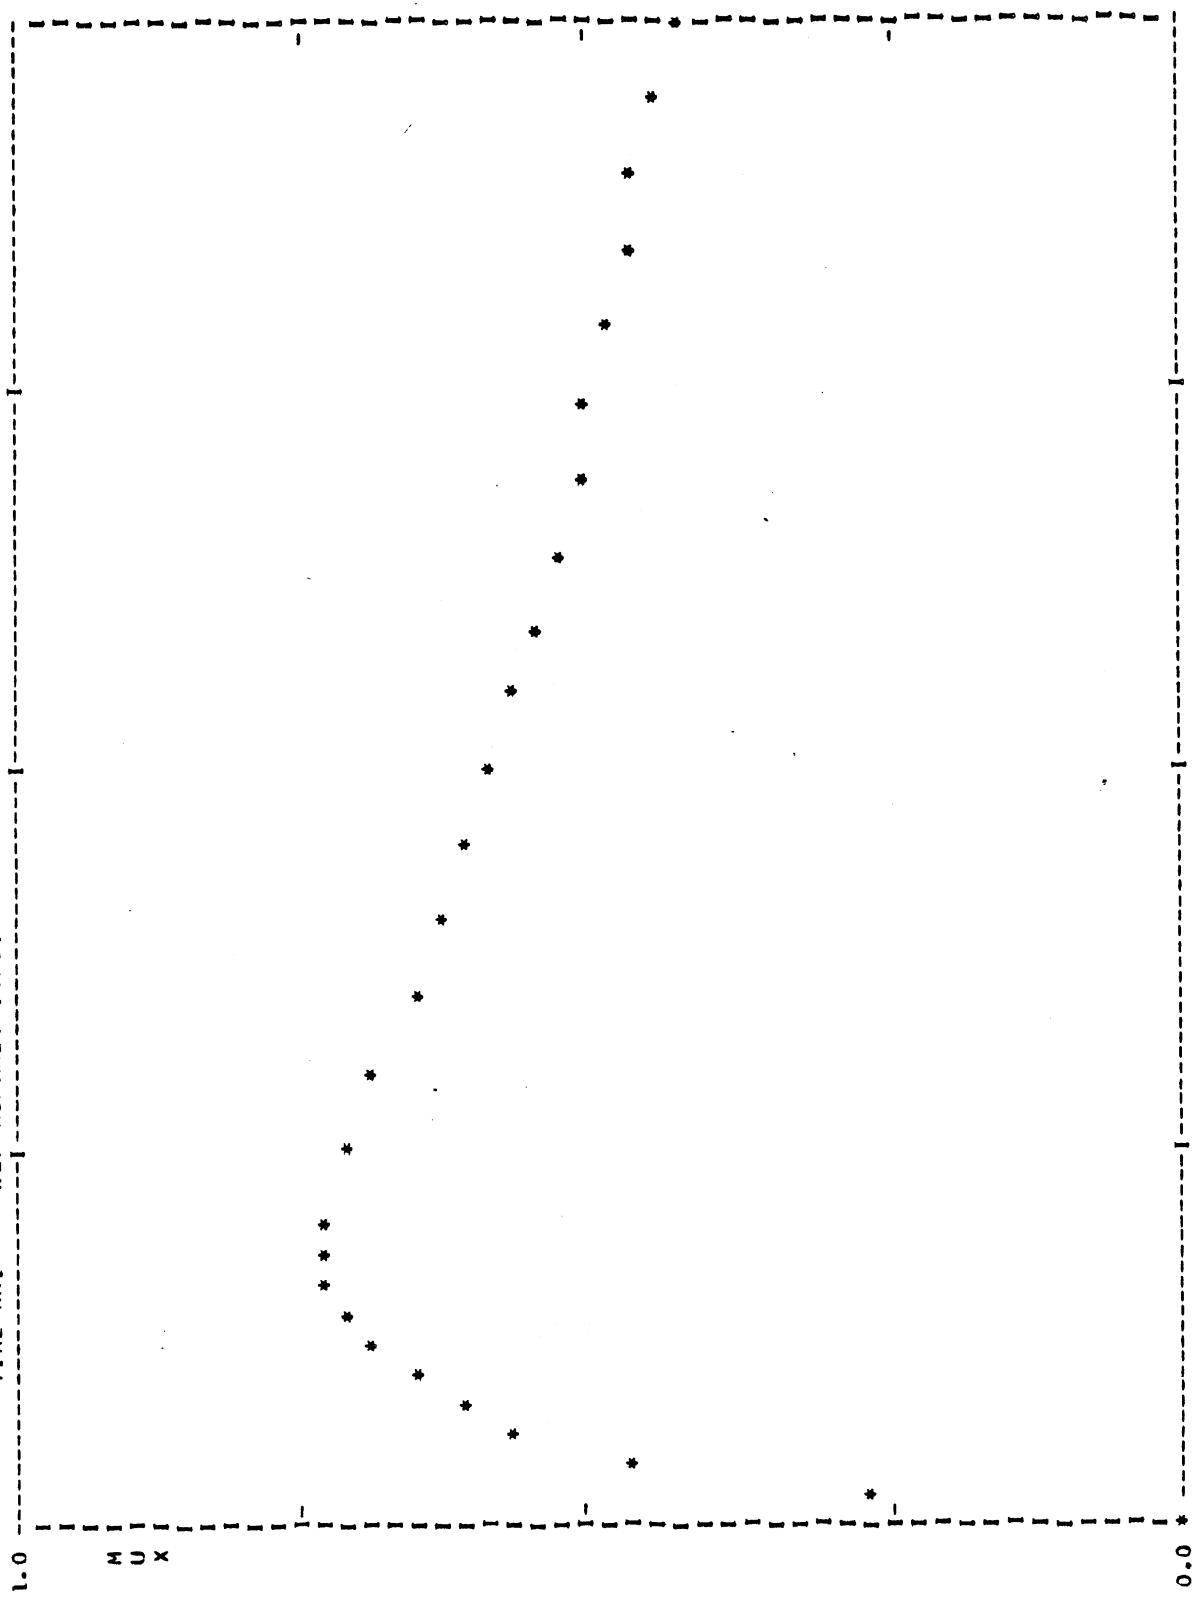

000060

FZ = 4605.0 VEL = 50.0 MUPEAK = 0.43 MULOCK = 0.73 RATIO = 1.72 A-D FILE 31 NWFILE 9 SAMPLE 110

LONGITUDINAL SLIP


MU-PEAK	SLIP-P-EAK
0.802	0.180
0.780	0.180
0.733	0.250
0.705	0.250
0.678	0.140
	0.424

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.739 0.051
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.421 0.045

000061

000062

AVERAGE OF FILE 35 FOR 6 RECORDS.		NEW FILE 10	TEST SAMPLE 111 **
SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.21	22626.5	942.6
0.04	0.30	31667.9	1326.9
0.06	0.35	37304.3	1571.9
0.08	0.39	43498.4	1784.5
0.10	0.40	45957.8	1833.2
0.12	0.41	47889.5	1860.6
0.14	0.41	49703.1	1887.0
0.16	0.42	51325.5	1912.1
0.18	0.42	52728.7	1929.6
0.20	0.42	53812.4	1939.0
0.25	0.43	55899.5	1948.2
0.30	0.43	57996.0	1946.0
0.35	0.43	60092.3	1927.6
0.40	0.42	61946.8	1898.5
0.45	0.42	63389.0	1867.1
0.50	0.41	64641.1	1834.9
0.55	0.41	65680.5	1802.0
0.60	0.40	66587.6	1767.7
0.65	0.39	67480.8	1732.9
0.70	0.38	67541.6	1696.3
0.75	0.38	65643.7	1665.3
0.80	0.37	59991.4	1641.2
0.85	0.36	52178.4	1615.3
0.90	0.35	47020.4	1566.3
0.95	0.34	40137.6	1516.9
1.00	0.31	31354.2	1393.0

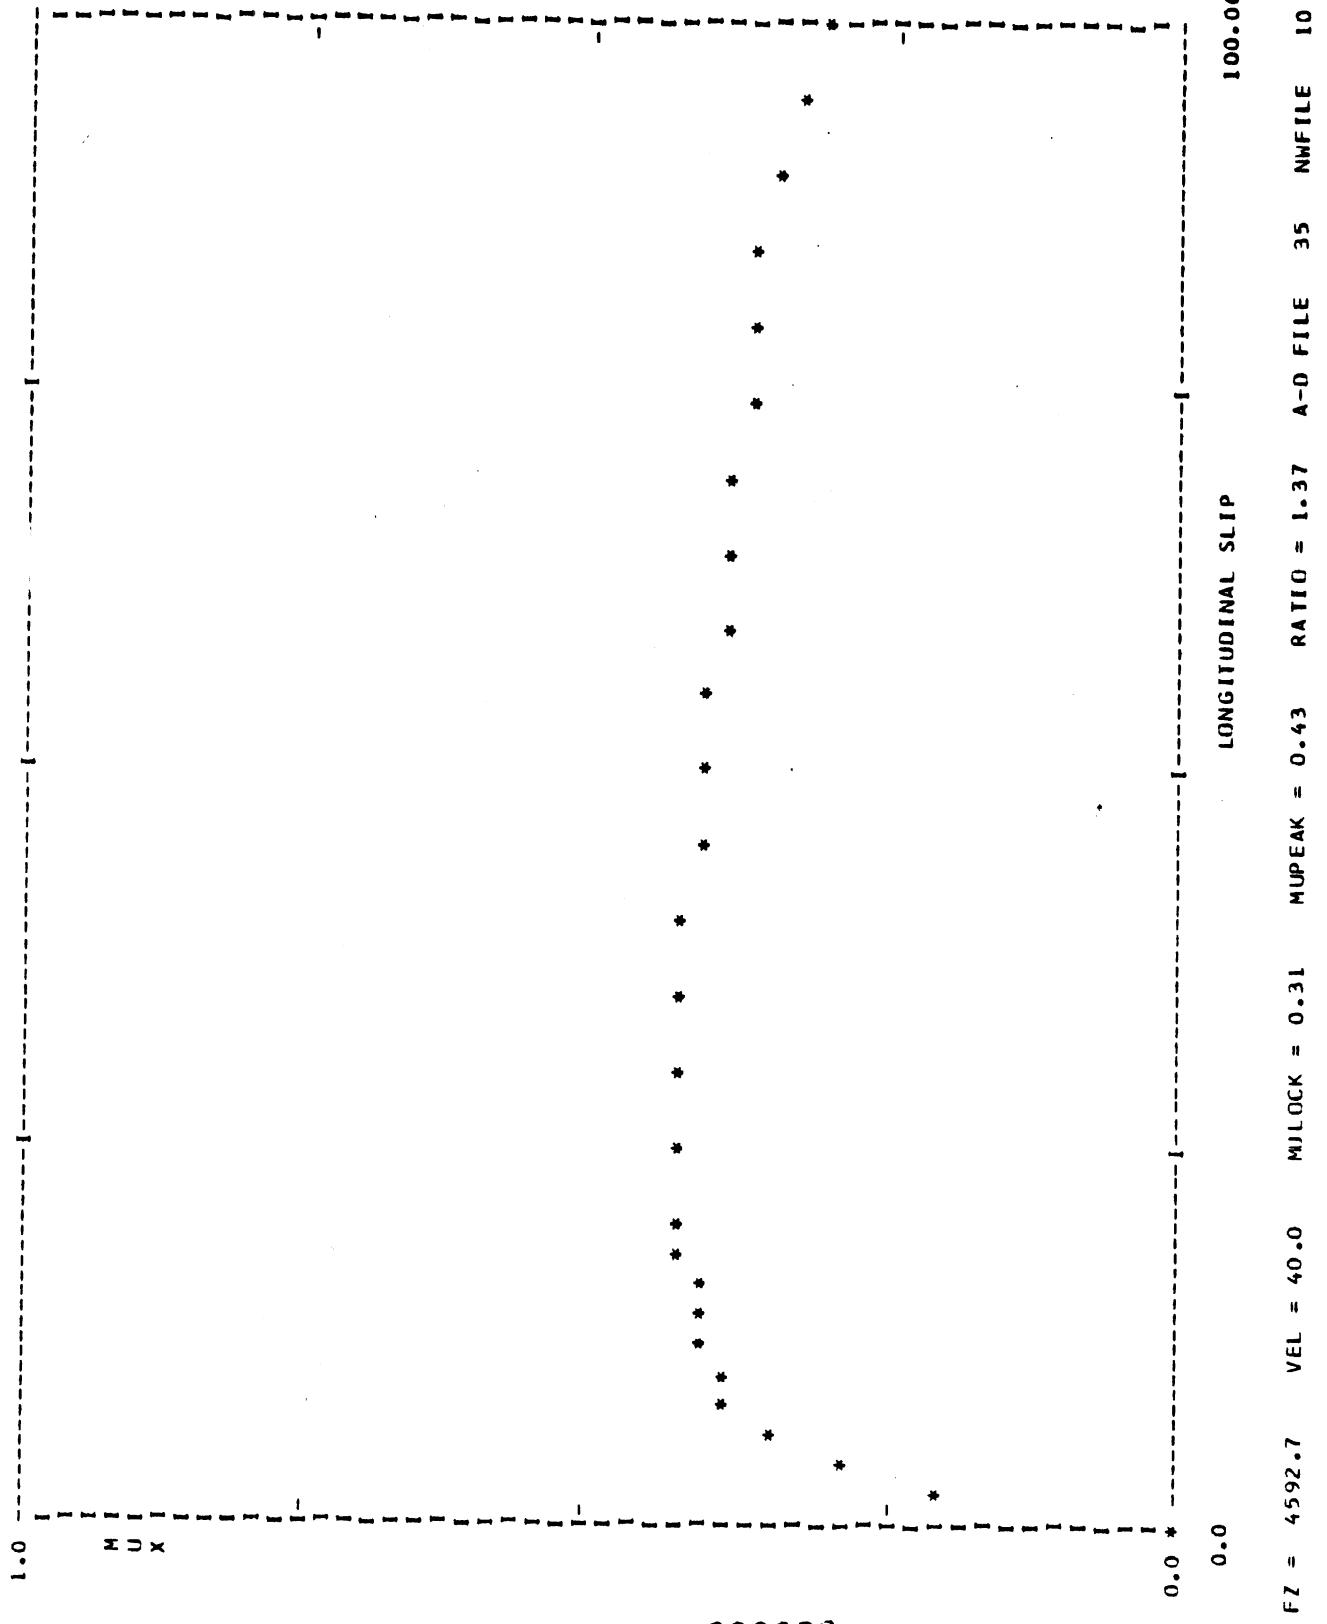

000063

	MU-PEAK	SLIP@PEAK	MU-LOCK
0.511	0.160	0.274	
0.372	0.500	0.300	
0.425	0.450	0.331	
0.493	0.200	0.294	
0.441	0.350	0.298	
0.423	0.500	0.345	


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.444 0.051
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.307 0.026

000064

SLIP	AVERAGE OF FILE	36 FOR 6 RECORDS.	TIRE RRI	WET CONCRETE (TRC)
	MUX	TORQUE	FX	
0.0	0.00	0.0	0.0	0.0
0.02	0.18	21888.1	854.0	
0.04	0.25	29365.0	1131.3	
0.06	0.28	34213.9	1282.4	
0.08	0.31	37699.7	1381.9	
0.10	0.33	40752.5	1468.3	
0.12	0.34	42913.0	1514.2	
0.14	0.35	44747.8	1555.1	
0.16	0.36	46532.3	1594.9	
0.18	0.37	48218.2	1634.2	
0.20	0.37	49769.4	1668.5	
0.25	0.38	52941.3	1719.0	
0.30	0.39	55424.6	1734.3	
0.35	0.38	57339.5	1711.6	
0.40	0.38	58989.4	1678.6	
0.45	0.37	60475.2	1644.5	
0.50	0.36	61831.8	1606.8	
0.55	0.36	63174.0	1577.6	
0.60	0.35	64477.6	1556.9	
0.65	0.35	65639.7	1534.9	
0.70	0.34	66828.1	1509.6	
0.75	0.33	67171.7	1474.4	
0.80	0.32	62325.0	1440.3	
0.85	0.31	52952.1	1414.6	
0.90	0.30	45254.7	1367.7	
0.95	0.29	37429.5	1312.1	
1.00	0.26	27979.2	1200.5	

000065

TIRE RR1 WET CONCRETE (TRC)

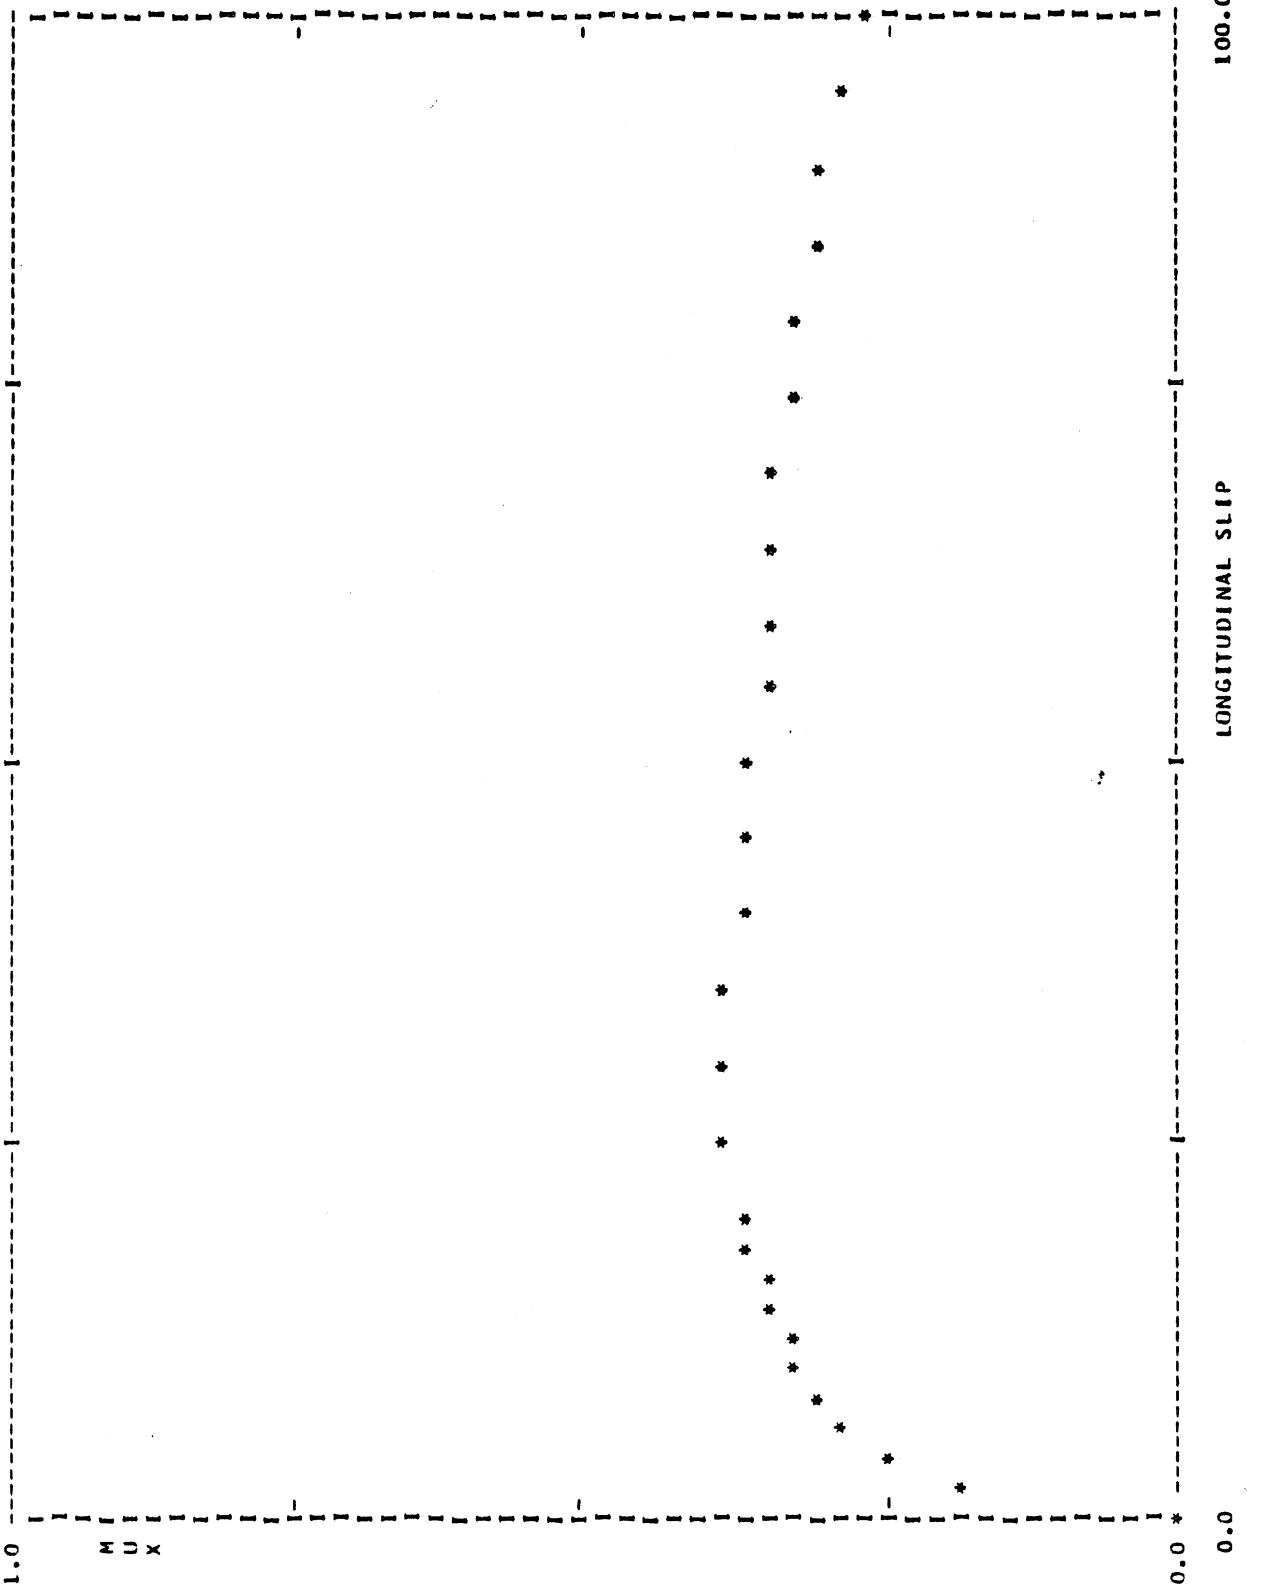

000060

FL = 4603.6 VEL = 50.0 MULOCK = 0.26 MUPEAK = 0.39 RATIO = 1.47 A-D FILE 36 NWFILE 11 SAMPLE 112

MU-PEAK	SLIPPEAK	MU-LCK
0.394	0.350	0.244
0.419	0.250	0.237
0.449	0.200	0.285
0.361	0.700	0.284
0.357	0.250	0.215
0.391	0.450	0.287

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.395 0.035
 MU-LCK AVERAGE VALUE AND STD. DEVIATION : 0.259 0.031

000067

TEST SAMPLE 113 **

NEW FILE 12


** A-D FILE 43

AVERAGE OF FILE 43 FOR 6 RECORDS.

SLIP MUX TORQUE FX

0.0	0.00	0.0	0.0	0.0
0.02	0.17	16930.3	780.5	
0.04	0.30	30681.3	1423.3	
0.06	0.44	44408.2	2072.6	
0.08	0.54	54368.1	2550.1	
0.10	0.61	60990.3	2872.7	
0.12	0.68	66986.3	3152.9	
0.14	0.72	72408.3	3380.6	
0.16	0.74	75675.1	3492.8	
0.18	0.76	77995.5	3573.3	TQAV = 56416.6 LOAD = 4803.4 VEL = 40.0 MPH.
0.20	0.77	80101.4	3627.2	RATIO = 1.34
0.25	0.78	83751.8	3657.7	HUPEAK = 0.78 HULOCK = 0.58
0.30	0.78	86313.8	3619.5	
0.35	0.77	87802.8	3556.4	
0.40	0.75	89094.9	3484.9	
0.45	0.73	90160.5	3417.1	
0.50	0.72	91090.2	3351.0	
0.55	0.70	92013.7	3287.5	
0.60	0.69	92799.6	3227.2	
0.65	0.68	93459.8	3165.1	
0.70	0.67	93085.6	3113.0	
0.75	0.66	89565.9	3064.3	
0.80	0.64	84024.4	3014.5	
0.85	0.63	77323.6	2956.8	
0.90	0.62	71102.3	2884.0	
0.95	0.61	65034.3	2820.1	
1.00	0.58	56416.6	2692.0	

000068

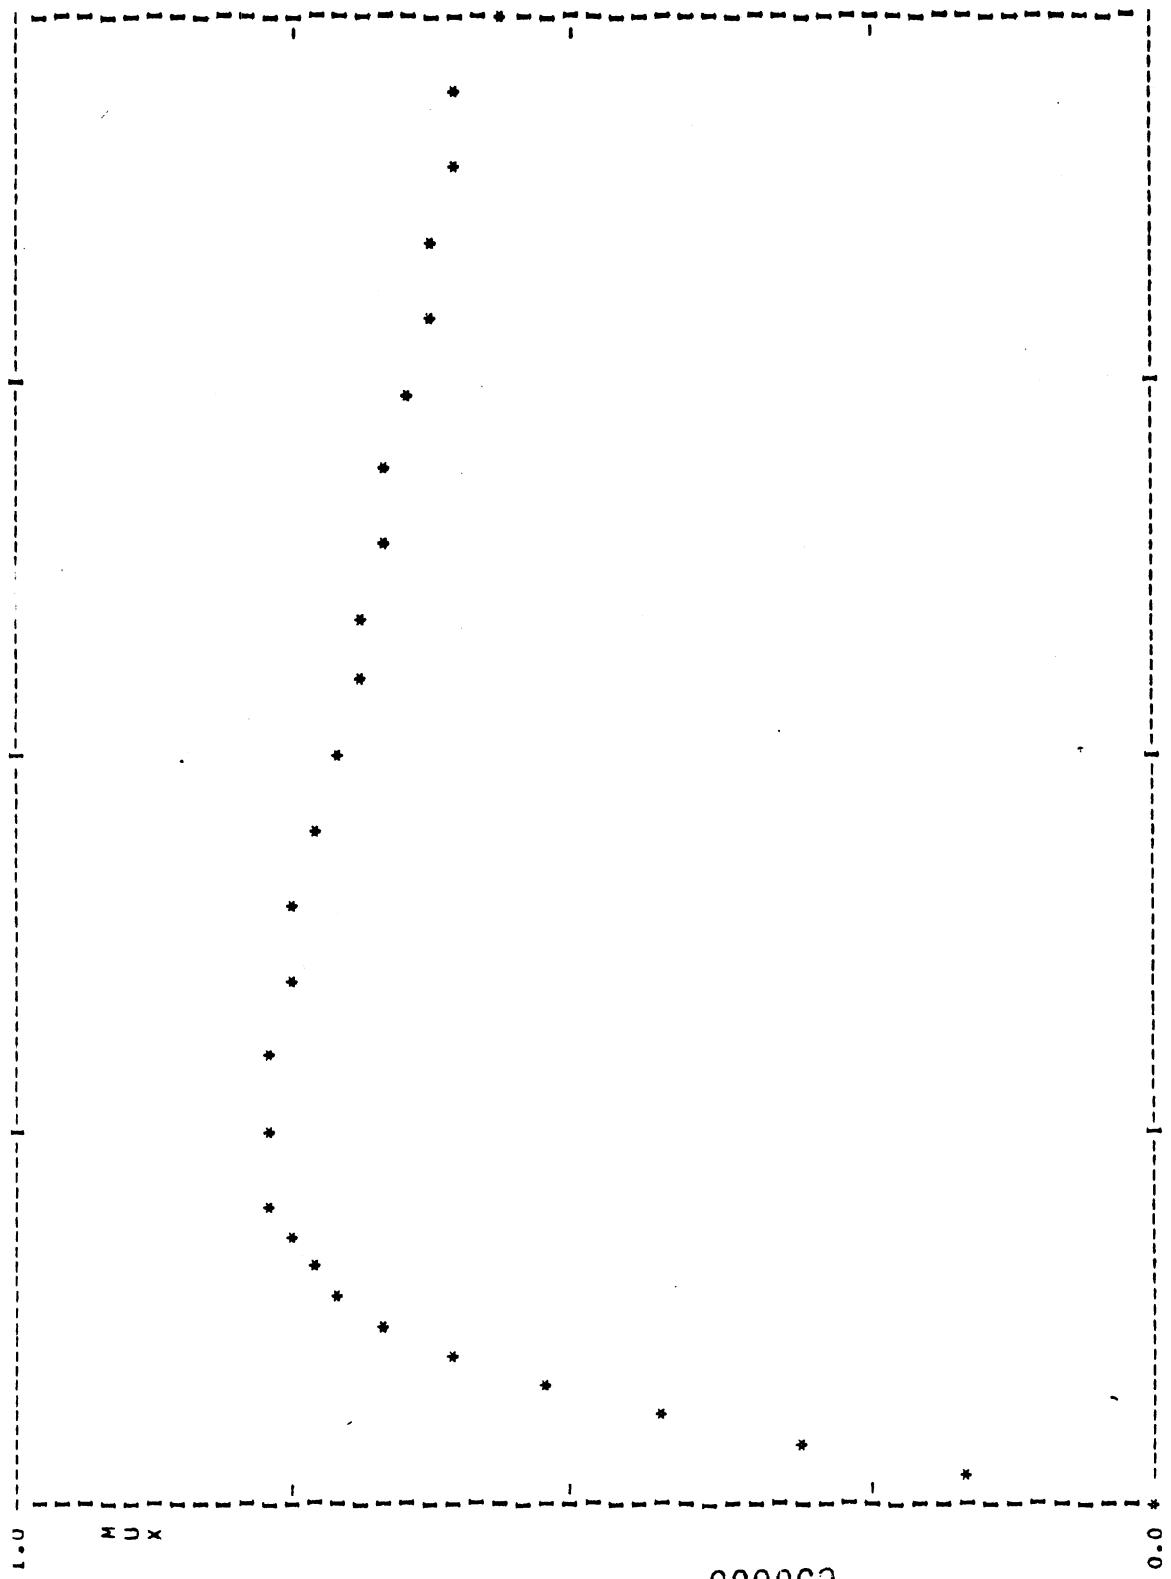

000063

FZ = 4803.4 VEL = 40.0 MULOCK = 0.58 MUPEAK = 0.78 RATIO = 1.34 A-D FILE 43 NWFILE 12 SAMPLE 113


MU-PEAK	SUPERPEAK	MU-LOCK
0.831	0.300	0.625
0.785	0.300	0.583
0.750	0.300	0.570
0.773	0.200	0.547
0.762	0.250	0.540
0.786	0.200	0.603

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.781 0.028
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.578 0.033

000070

SLIP	MUX	TORQUE	FX	FY	TIRE C2	WET ASPHALT (FRC)
0.0	0.00	0.0	0.0	0.0		
0.02	0.18	19422.8	862.4			
0.04	0.31	32305.2	1480.8			
0.06	0.43	43569.2	2012.6			
0.08	0.52	53292.2	2430.6			
0.10	0.57	58864.7	2665.9			
0.12	0.62	63520.4	2872.6			
0.14	0.67	67743.2	3072.2			
0.16	0.69	71903.1	3224.4			
0.18	0.69	74635.6	3265.7	TQAV = 46812.4		
0.20	0.68	76218.0	3257.0			
0.25	0.66	78710.3	3155.7	MUPEAK = 0.69		
0.30	0.65	80579.1	3069.0			
0.35	0.63	82147.5	2983.8			
0.40	0.62	83464.6	2911.4			
0.45	0.61	84738.4	2846.4			
0.50	0.60	85896.0	2792.9			
0.55	0.59	86829.9	2739.7			
0.60	0.58	87672.6	2688.4			
0.65	0.57	88528.4	2634.6			
0.70	0.56	88561.6	2587.6			
0.75	0.55	85715.6	2547.9			
0.80	0.55	79172.3	2516.6			
0.85	0.54	71442.7	2483.2			
0.90	0.53	64514.6	2444.7			
0.95	0.52	58313.3	2419.3			
1.00	0.47	46812.4	2220.5			

000071

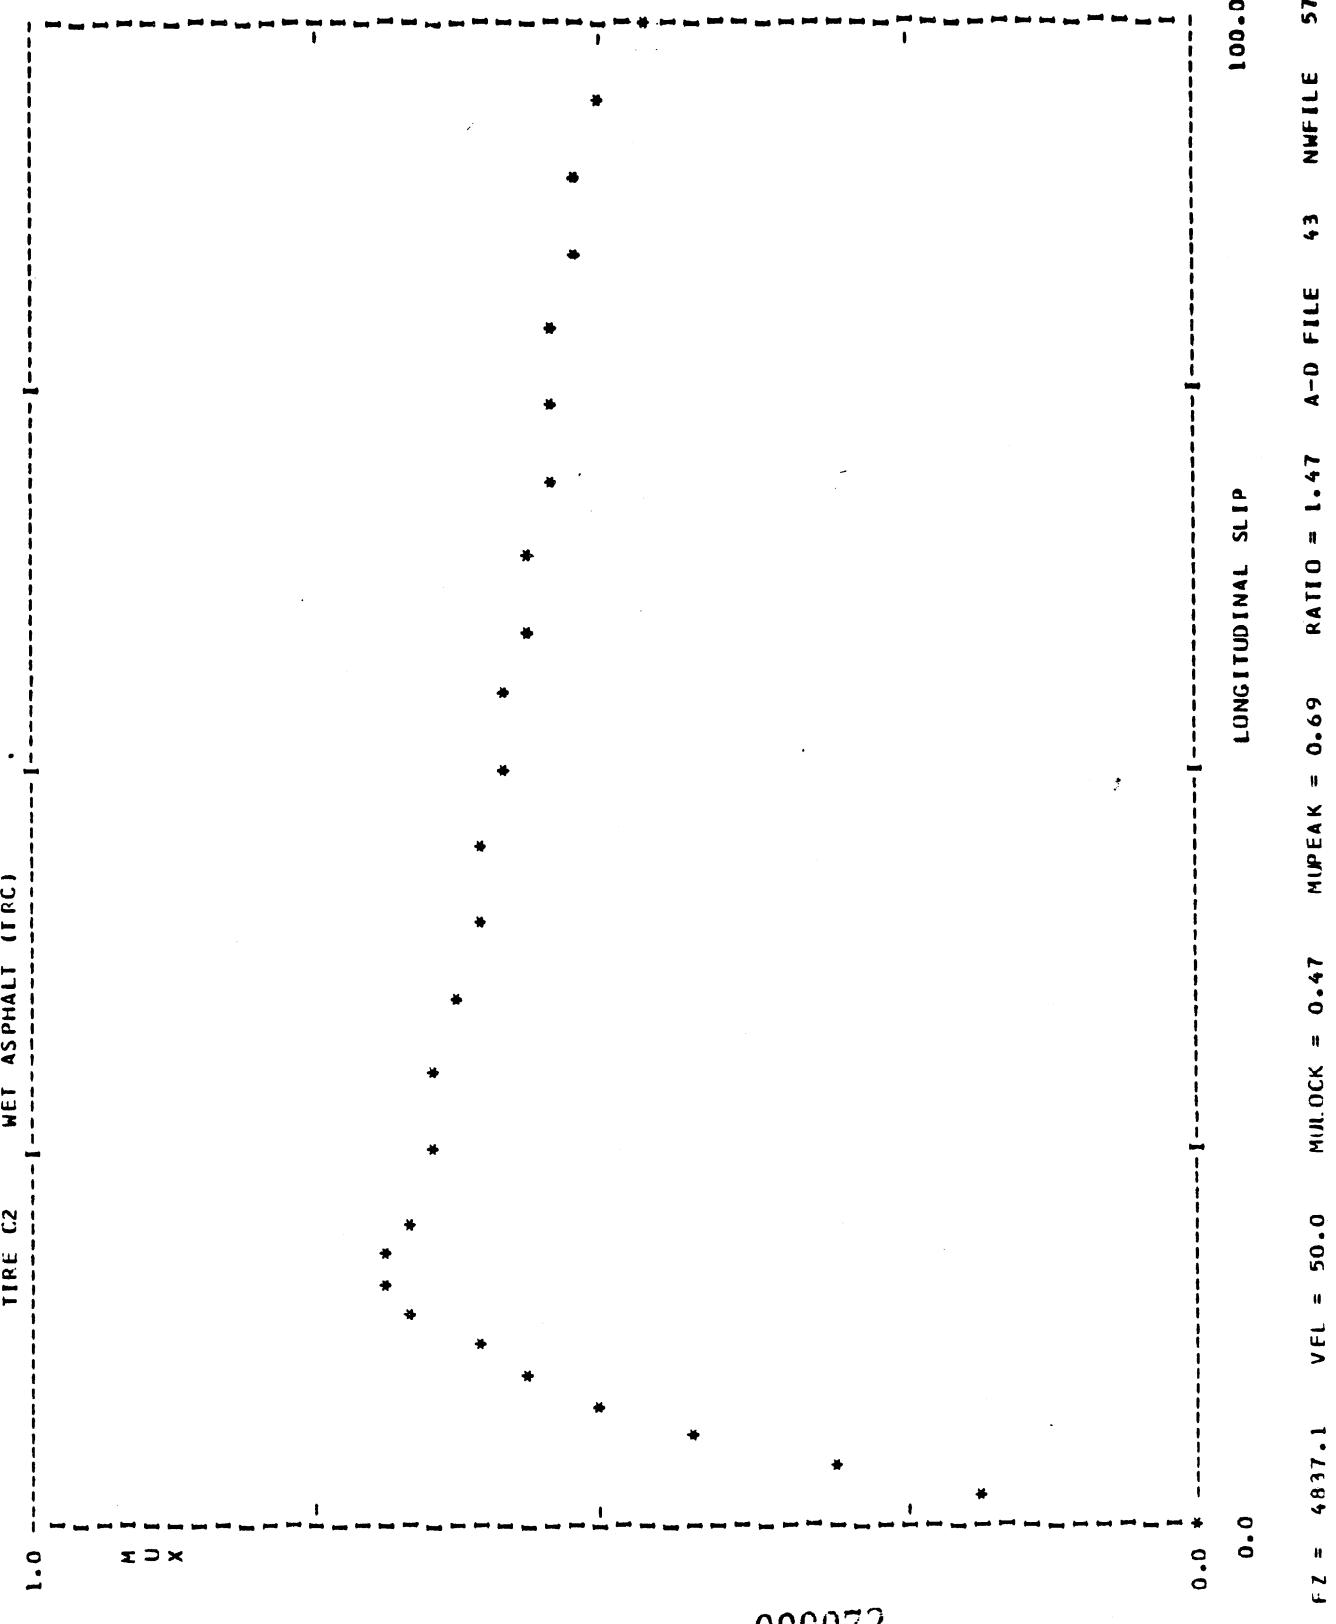

000072


MU-PEAK	SPLIT APPAK	MU-LOCK
0.815	0.200	0.538
0.694	0.200	0.534
0.740	0.160	0.485
0.647	0.140	0.395
0.564	0.200	0.440
0.715	0.160	0.392

MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.696	0.085
MU-LOCK AVERAGE VALUE AND STD. DEVIATION :	0.464	0.065

000073

F400074

** A-D FILE 47		NEW FILE 13		TEST SAMPLE115 **	
AVERAGE OF FILE 47 FOR 6 RECORDS.			TIRE C2	WET CONCRETE (TRC)	
SLIP	MUX	TORQUE	FX		
0.0	0.00	0.0	0.0		
0.02	0.16	17869.9	746.6		
0.04	0.26	27674.6	1217.6		
0.06	0.34	36255.5	1566.4		
0.08	0.37	40563.7	1699.9		
0.10	0.39	43386.3	1775.8		
0.12	0.40	45472.6	1820.9		
0.14	0.41	47312.3	1854.6		
0.16	0.42	48873.0	1887.3		
0.18	0.43	50197.0	1917.1	TQAV = 29312.5	LOAD = 4751.9 VEL = 40.0 MPH.
0.20	0.43	51325.2	1940.9		
0.25	0.44	54026.8	1981.4	MUPEAK = 0.45	MULOCK = 0.28 RATIO = 1.58
0.30	0.45	56291.7	1997.6		
0.35	0.44	58317.3	1991.2		
0.40	0.43	59952.6	1977.5		
0.45	0.43	61385.8	1963.4		
0.50	0.42	62590.2	1942.1		
0.55	0.41	63735.3	1912.2		
0.60	0.40	64883.5	1873.2		
0.65	0.39	65914.9	1829.6		
0.70	0.38	66579.2	1779.6		
0.75	0.37	64466.2	1735.0		
0.80	0.37	58068.9	1689.9		
0.85	0.36	51334.7	1640.0		
0.90	0.34	45248.4	1576.8		
0.95	0.33	39617.4	1526.7		
1.00	0.28	29312.5	1304.0		

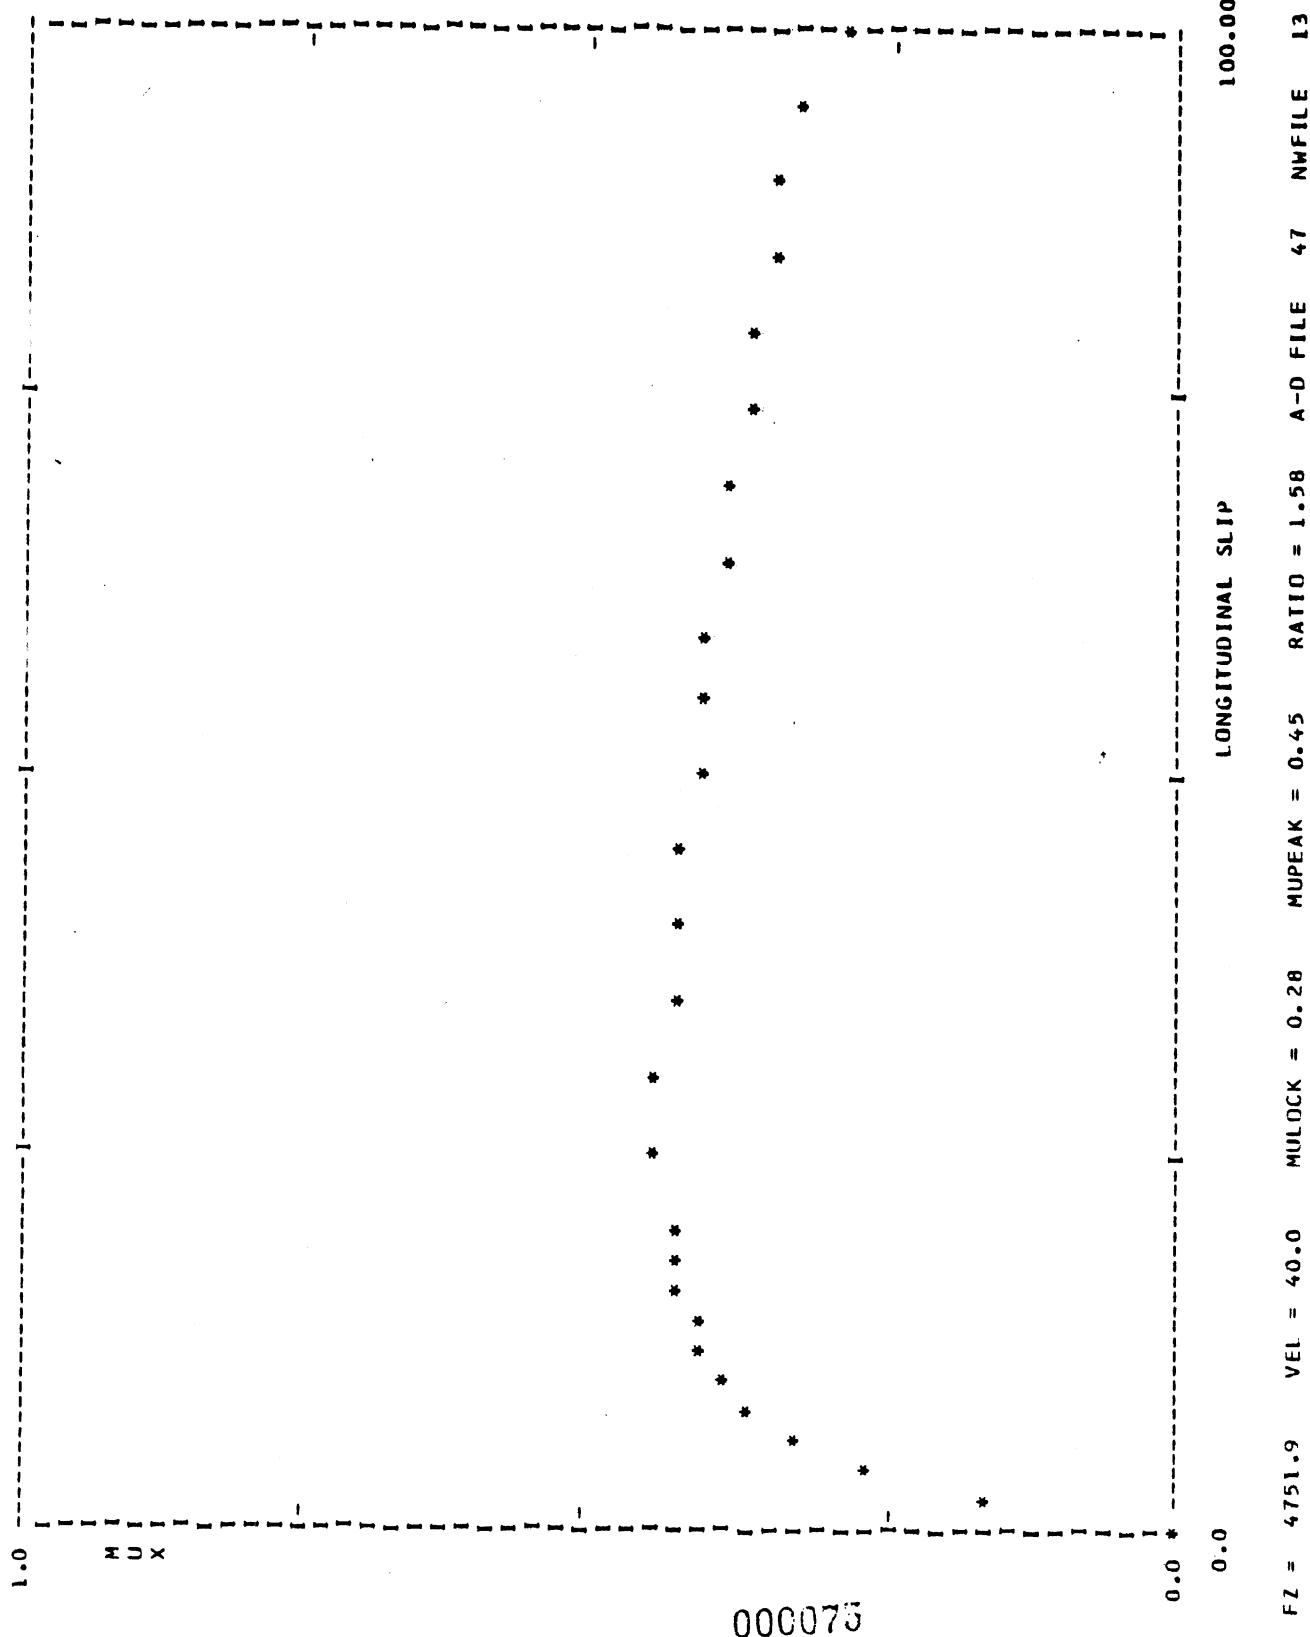

MU-PEAK	SL IP@PEAK	MU-LOCK
0.541	0.250	0.274
0.401	0.180	0.277
0.440	0.350	0.283
0.502	0.200	0.300
0.421	0.300	0.260
0.384	0.300	0.271

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.448 0.061

MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.277 0.014

000073

SLIP	AVERAGE OF FILE 48	MUX	TORQUE	FOR 6 RECORDS.	TIRE C2	WET CONCRETE (TRC)
0.0	0.00	0.0	0.0	0.0	0.0	
0.02	0.16	16110.8	717.9			
0.04	0.23	26097.7	1043.1			
0.06	0.27	31382.1	1223.2			
0.08	0.32	36116.1	1415.7			
0.10	0.34	39651.2	1533.8			
0.12	0.35	42245.5	1606.6			
0.14	0.36	44297.3	1656.0			
0.16	0.36	46034.5	1690.7			
0.18	0.37	47515.4	1716.1	TQAV = 25562.5	LOAD = 4698.6	VEL = 50.0 MPH.
0.20	0.37	48972.3	1731.3			
0.25	0.38	51841.2	1746.5	HUPEAK = 0.38	MULOCK = 0.24	RATIO = 1.58
0.30	0.38	54107.0	1743.4			
0.35	0.38	56156.3	1729.9			
0.40	0.37	58000.0	1712.1			
0.45	0.37	59572.1	1687.0			
0.50	0.37	61012.7	1656.0			
0.55	0.36	62353.9	1620.8			
0.60	0.35	63637.8	1581.7			
0.65	0.34	65024.4	1542.4			
0.70	0.33	65811.6	1497.2			
0.75	0.33	64158.3	1456.7			
0.80	0.32	58923.5	1419.4			
0.85	0.31	50716.9	1383.4			
0.90	0.30	43383.5	1328.8			
0.95	0.28	36244.3	1252.8			
1.00	0.24	25562.5	1071.0			

000077

TIRE C2 WET CONCRETE (TRC)

WET CONCRETE (TRC)

A scatter plot showing the relationship between Time (sec) on the Y-axis and Longitudinal Step on the X-axis. The X-axis ranges from 0.0 to 1.0 with major ticks at 0.0, 0.2, 0.4, 0.6, 0.8, and 1.0. The Y-axis ranges from 0.0 to 1.0 with major ticks at 0.0, 0.2, 0.4, 0.6, 0.8, and 1.0. The data points, represented by asterisks (*), show a clear negative linear correlation. A dashed horizontal line is drawn at approximately Y = 0.95, and a dashed vertical line is drawn at approximately X = 0.55.

Longitudinal Step	Time (sec)
0.00078	0.95
0.00078	0.90
0.00078	0.85
0.00078	0.80
0.00078	0.75
0.00078	0.70
0.00078	0.65
0.00078	0.60
0.00078	0.55
0.00078	0.50
0.00078	0.45
0.00078	0.40
0.00078	0.35
0.00078	0.30
0.00078	0.25
0.00078	0.20
0.00078	0.15
0.00078	0.10
0.00078	0.05
0.00078	0.00

EF = 4698.6 VEN = 50.0 MULOCK = 0.24 MUPEAK = 0.38 RATIO = 1.58 A-D FILE 48 NWFILE 14 SAMPLE 116


MU-PEAK	SLIP PEAK	MU-LOCK
0.339	0.550	0.250
0.365	0.250	0.254
0.425	0.400	0.219
0.341	0.400	0.229
0.415	0.200	0.222
0.405	0.300	0.227

MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.382	0.038
MU-LOCK AVERAGE VALUE AND STD. DEVIATION :	0.233	0.015

000079

00C080

** A-D FILE 55			NEW FILE 15	TEST SAMPLE17 **
AVERAGE OF FILE 55 FOR 4 RECORDS.			TIRE BLI	WET ASPHALT (TRC)
SLIP	MUX	TORQUE	FX	
0.0	0.00	0.0	0.0	
0.02	0.18	14077.5	804.6	
0.04	0.28	25471.4	1342.3	
0.06	0.39	36042.8	1860.5	
0.08	0.46	43522.3	2177.2	
0.10	0.52	49127.6	2427.5	
0.12	0.58	54713.4	2685.6	
0.14	0.62	59208.0	2873.2	
0.16	0.64	62477.5	2977.1	
0.18	0.65	64934.5	3029.1	TQAV = 45250.0 LOAD = 4801.1 VEL = 40.0 MPH.
0.20	0.66	67035.4	3051.7	
0.25	0.66	70759.7	3028.0	MUPEAK = 0.66 MULOCK = 0.50 RATIO = 1.31
0.30	0.65	73269.7	2977.8	
0.35	0.64	74973.4	2924.0	
0.40	0.63	76425.8	2876.7	
0.45	0.63	77792.3	2838.5	
0.50	0.62	78876.8	2802.5	
0.55	0.61	79875.1	2768.2	
0.60	0.60	80930.6	2732.5	
0.65	0.59	81879.5	2695.0	
0.70	0.59	81486.1	2664.3	
0.75	0.58	78580.9	2638.1	
0.80	0.57	71689.4	2614.4	
0.85	0.56	65491.7	2585.3	
0.90	0.55	59544.3	2545.1	
0.95	0.54	53223.5	2488.2	
1.00	0.50	45250.0	2338.5	

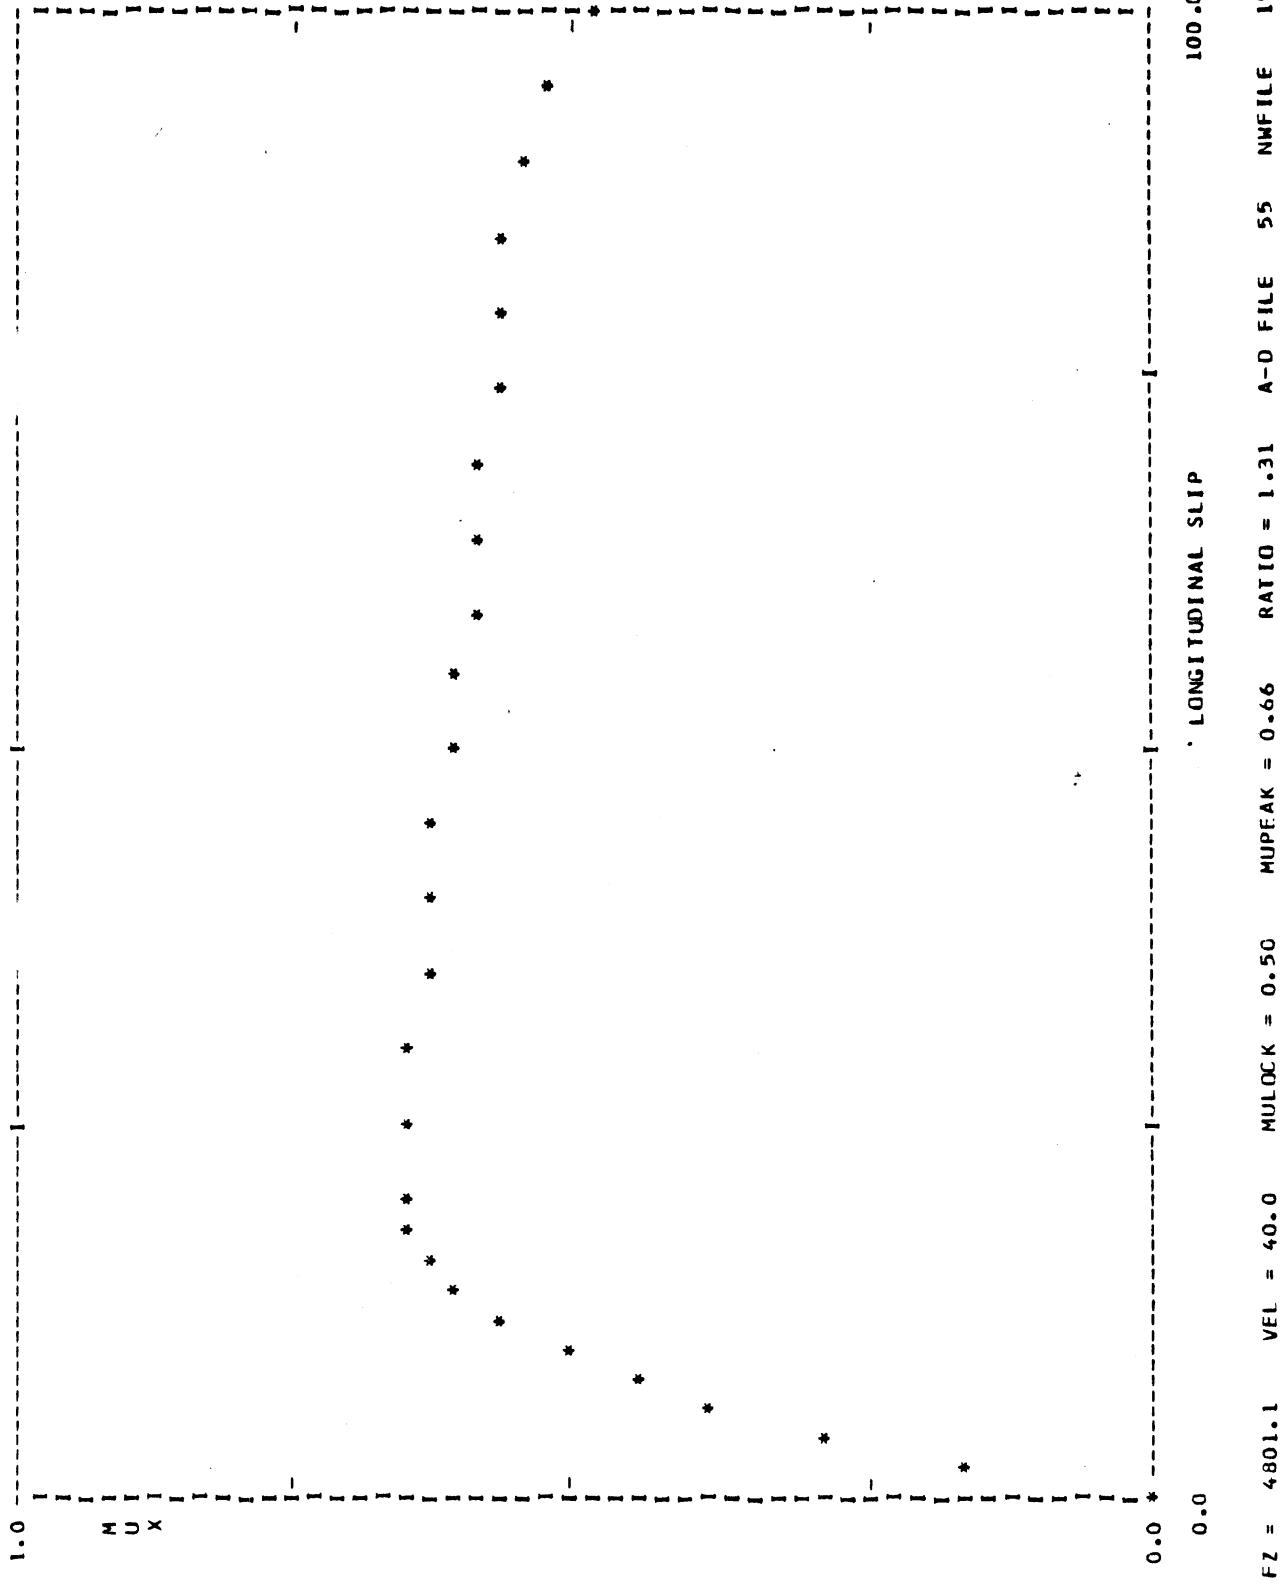

MU-PEAK	SU-PeAK	MU-LCCK
0.692	0.180	0.555
0.697	0.200	0.495
0.667	0.250	0.492
0.571	0.200	0.441


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.657 0.059
MU-LCCK AVERAGE VALUE AND STD. DEVIATION : 0.496 0.047

000082

SLIP	MUX	TORQUE	FX	
0.0	0.00	0.0	0.0	
0.02	0.16	12429.4	726.2	
0.04	0.28	24768.4	1291.8	
0.06	0.37	34231.3	1724.1	
0.08	0.45	42236.8	2089.3	
0.10	0.50	48128.2	2339.6	
0.12	0.54	52641.3	2526.7	
0.14	0.59	56884.2	2699.1	
0.16	0.62	61025.4	2847.3	
0.18	0.63	64039.8	2934.2	
0.20	0.62	66083.5	2936.5	
0.25	0.61	69451.4	2866.0	
0.30	0.60	71898.5	2782.7	
0.35	0.59	73721.3	2707.4	
0.40	0.58	75304.9	2648.8	
0.45	0.57	76570.6	2589.1	
0.50	0.56	77575.0	2524.4	
0.55	0.55	78398.4	2479.0	
0.60	0.54	79289.7	2436.4	
0.65	0.53	80265.7	2395.6	
0.70	0.52	80341.1	2365.4	
0.75	0.51	77596.5	2343.4	
0.80	0.51	70709.2	2330.5	
0.85	0.50	63610.3	2312.8	
0.90	0.50	56329.6	2283.8	
0.95	0.48	48989.5	2228.6	
1.00	0.44	38750.0	2032.5	

000083

TIRE BLI WET ASPHALT (TRCI)

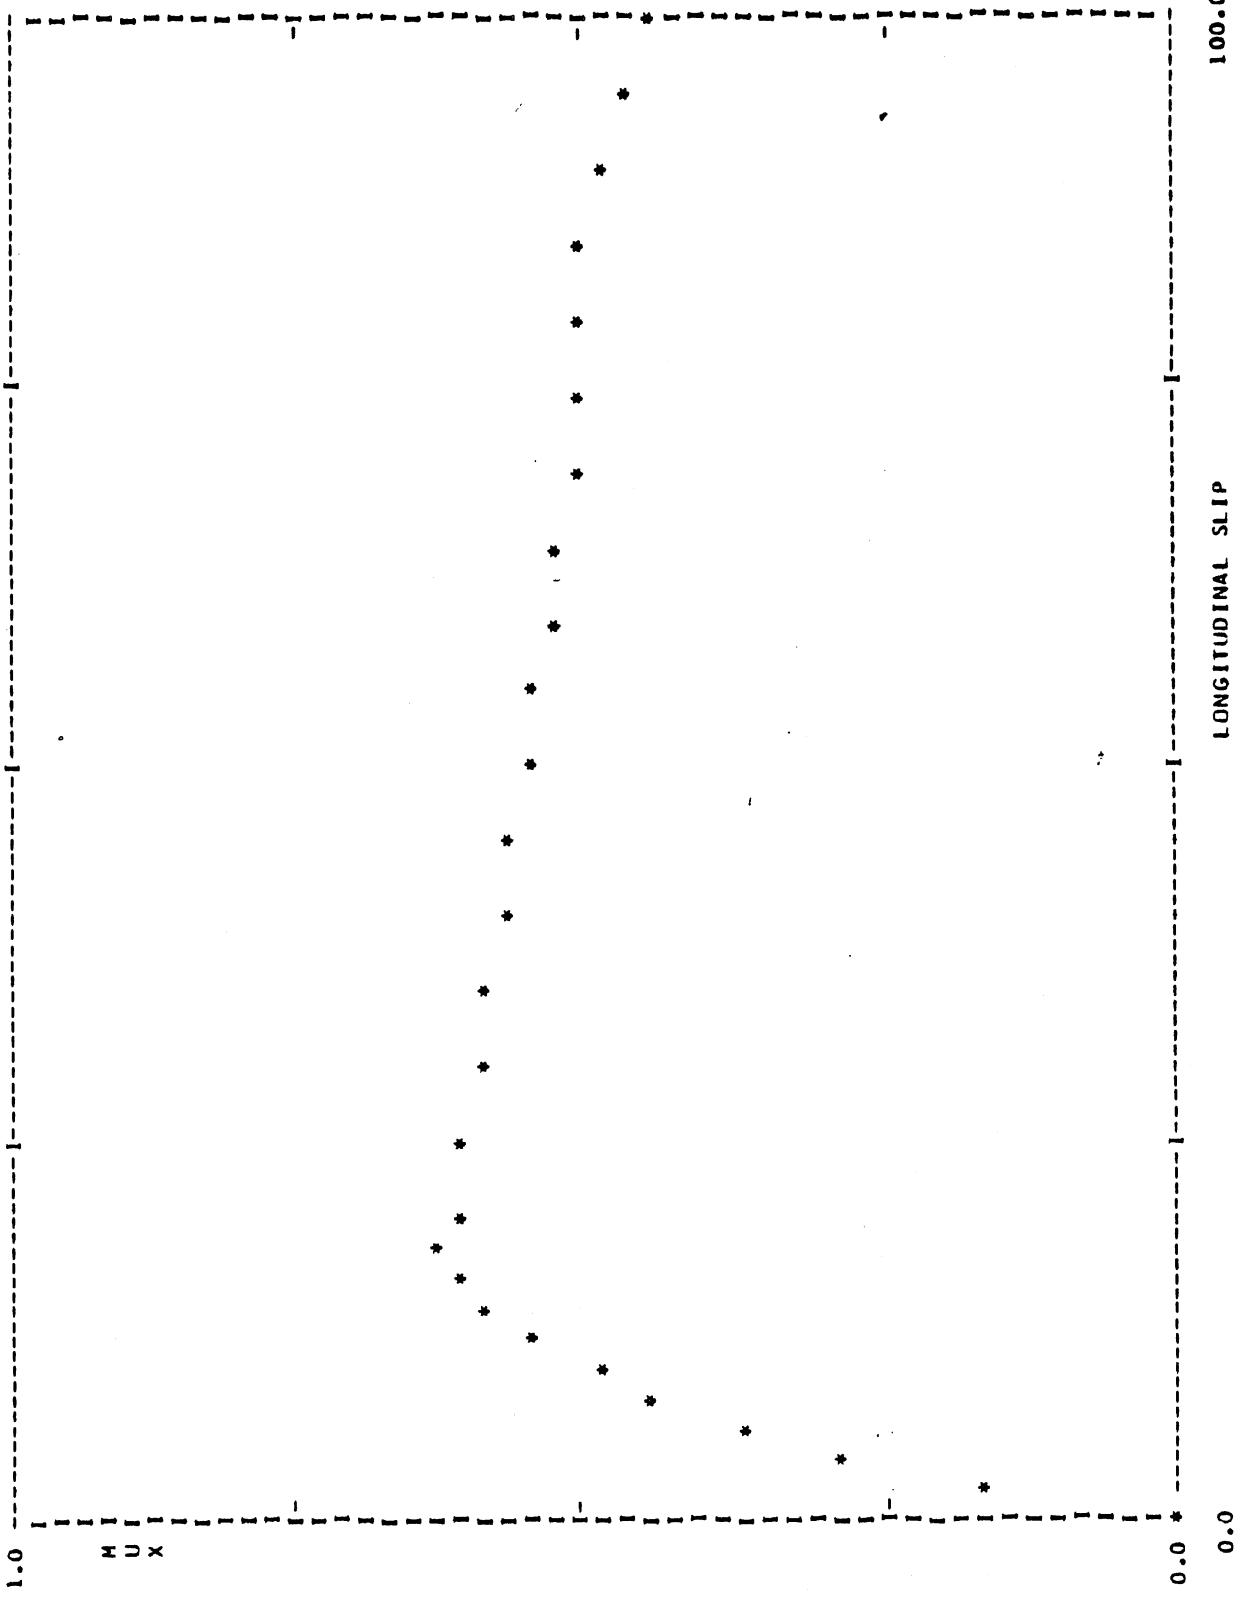

FZ = 4810.2 VEL = 50.0 MULOCK = 0.44 MUPEAK = 0.63 RATIO = 1.41 A-D FILE 56 NWFILE 16 SAMPLE 118

HUX

MU-PEAK	SLIP@PEAK	MU-LOCK
0.677	0.450	0.477
0.636	0.180	0.437
0.571	0.200	0.440
0.654	0.200	0.401

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.635 0.045
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.439 0.031

000085


TEST SAMPLE 119 **

** A-D FILE 60 NEW FILE 17

AV ERAGE OF FILE 60 FUR 6 RECORDS. TIRE BLI WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.14	16069.7	626.5
0.04	0.21	23948.0	986.6
0.06	0.27	30167.1	1223.7
0.08	0.31	35289.0	1420.2
0.10	0.33	38401.1	1521.4
0.12	0.35	41001.1	1603.0
0.14	0.37	43288.1	1667.4
0.16	0.38	45199.2	1716.4
0.18	0.38	46956.2	1749.8
0.20	0.39	48614.6	1770.5
0.25	0.39	51823.5	1782.8
0.30	0.38	54017.4	1764.0
0.35	0.38	55892.0	1745.2
0.40	0.37	57681.1	1724.4
0.45	0.37	59344.5	1702.1
0.50	0.36	60823.0	1677.2
0.55	0.36	62186.2	1650.9
0.60	0.35	63479.0	1622.9
0.65	0.34	64591.2	1581.1
0.70	0.33	64538.0	1536.6
0.75	0.33	61830.2	1493.1
0.80	0.32	55741.8	1453.4
0.85	0.31	48653.9	1412.8
0.90	0.30	42286.8	1356.4
0.95	0.29	36313.3	1314.1
1.00	0.27	28333.3	1217.5

0000086

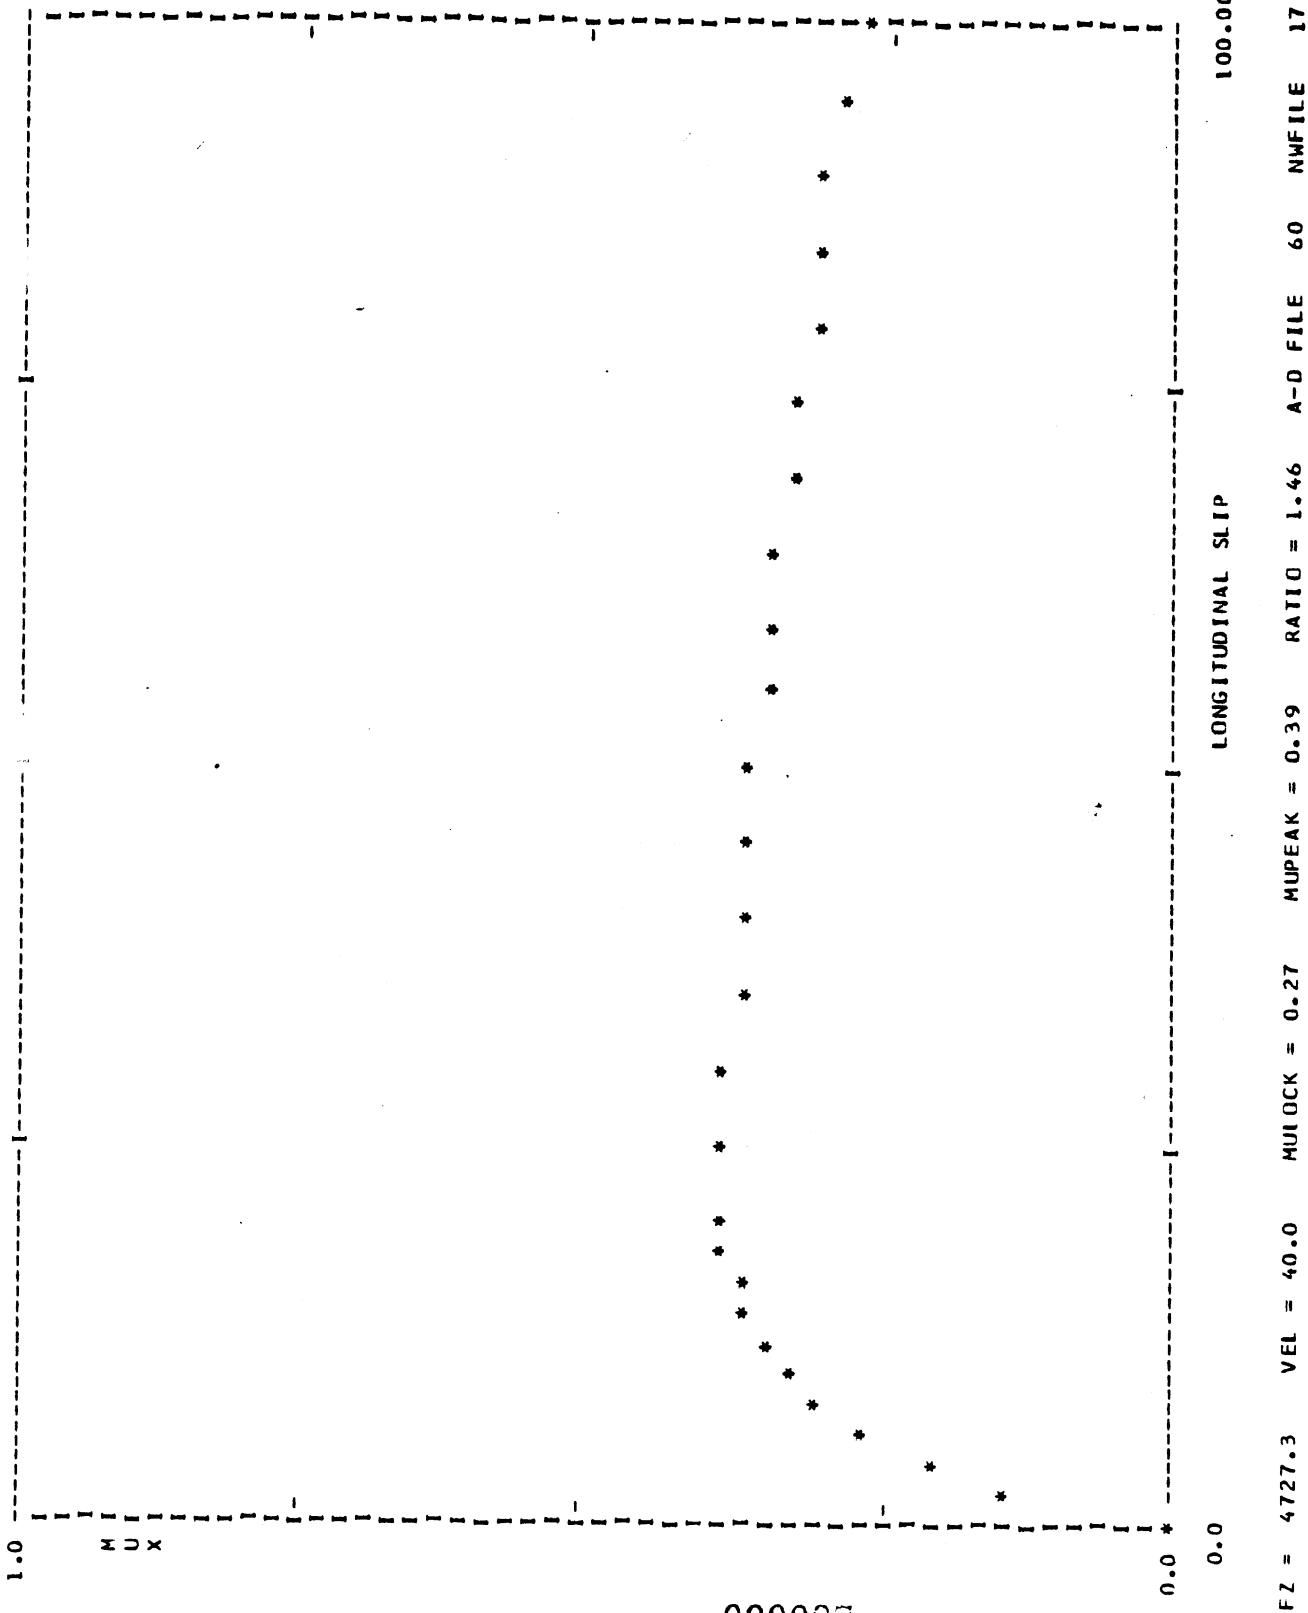


MU-PEAK	SLIP@PEAK	MU-LOCK
0.448	0.160	0.273
0.363	0.250	0.259
0.383	0.300	0.284
0.414	0.200	0.277
0.374	0.180	0.225
0.359	0.300	0.244

MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.390	0.035
MU-LOCK AVERAGE VALUE AND STD. DEVIATION :	0.260	0.023

000088

SLIP	MUX	TORQUE	FX	FY	FZ	WET COFIL RETE (TRC)
0.0	0.00	0.0	0.0	0.0	0.0	
0.02	0.14	16994.3	631.7			
0.04	0.20	23965.9	907.0			
0.06	0.25	29934.3	1139.4			
0.08	0.29	35161.6	1322.5			
0.10	0.31	38393.3	1409.6			
0.12	0.32	40972.5	1470.5			
0.14	0.33	43218.4	1511.5			
0.16	0.34	45219.4	1535.8			
0.18	0.34	46774.0	1545.8			
0.20	0.33	48059.2	1543.4			
0.25	0.33	50661.1	1522.1			
0.30	0.33	52739.5	1498.0			
0.35	0.32	54566.9	1475.7			
0.40	0.32	56220.2	1451.8			
0.45	0.31	57788.7	1426.1			
0.50	0.31	59247.6	1404.9			
0.55	0.31	60745.8	1386.5			
0.60	0.30	62183.2	1367.6			
0.65	0.30	63535.0	1345.1			
0.70	0.29	64455.5	1320.7			
0.75	0.28	63398.6	1292.2			
0.80	0.28	58197.7	1272.1			
0.85	0.28	50023.7	1252.6			
0.90	0.27	42774.7	1215.3			
0.95	0.26	35519.0	1177.2			
1.00	0.24	26437.5	1097.5			

000089

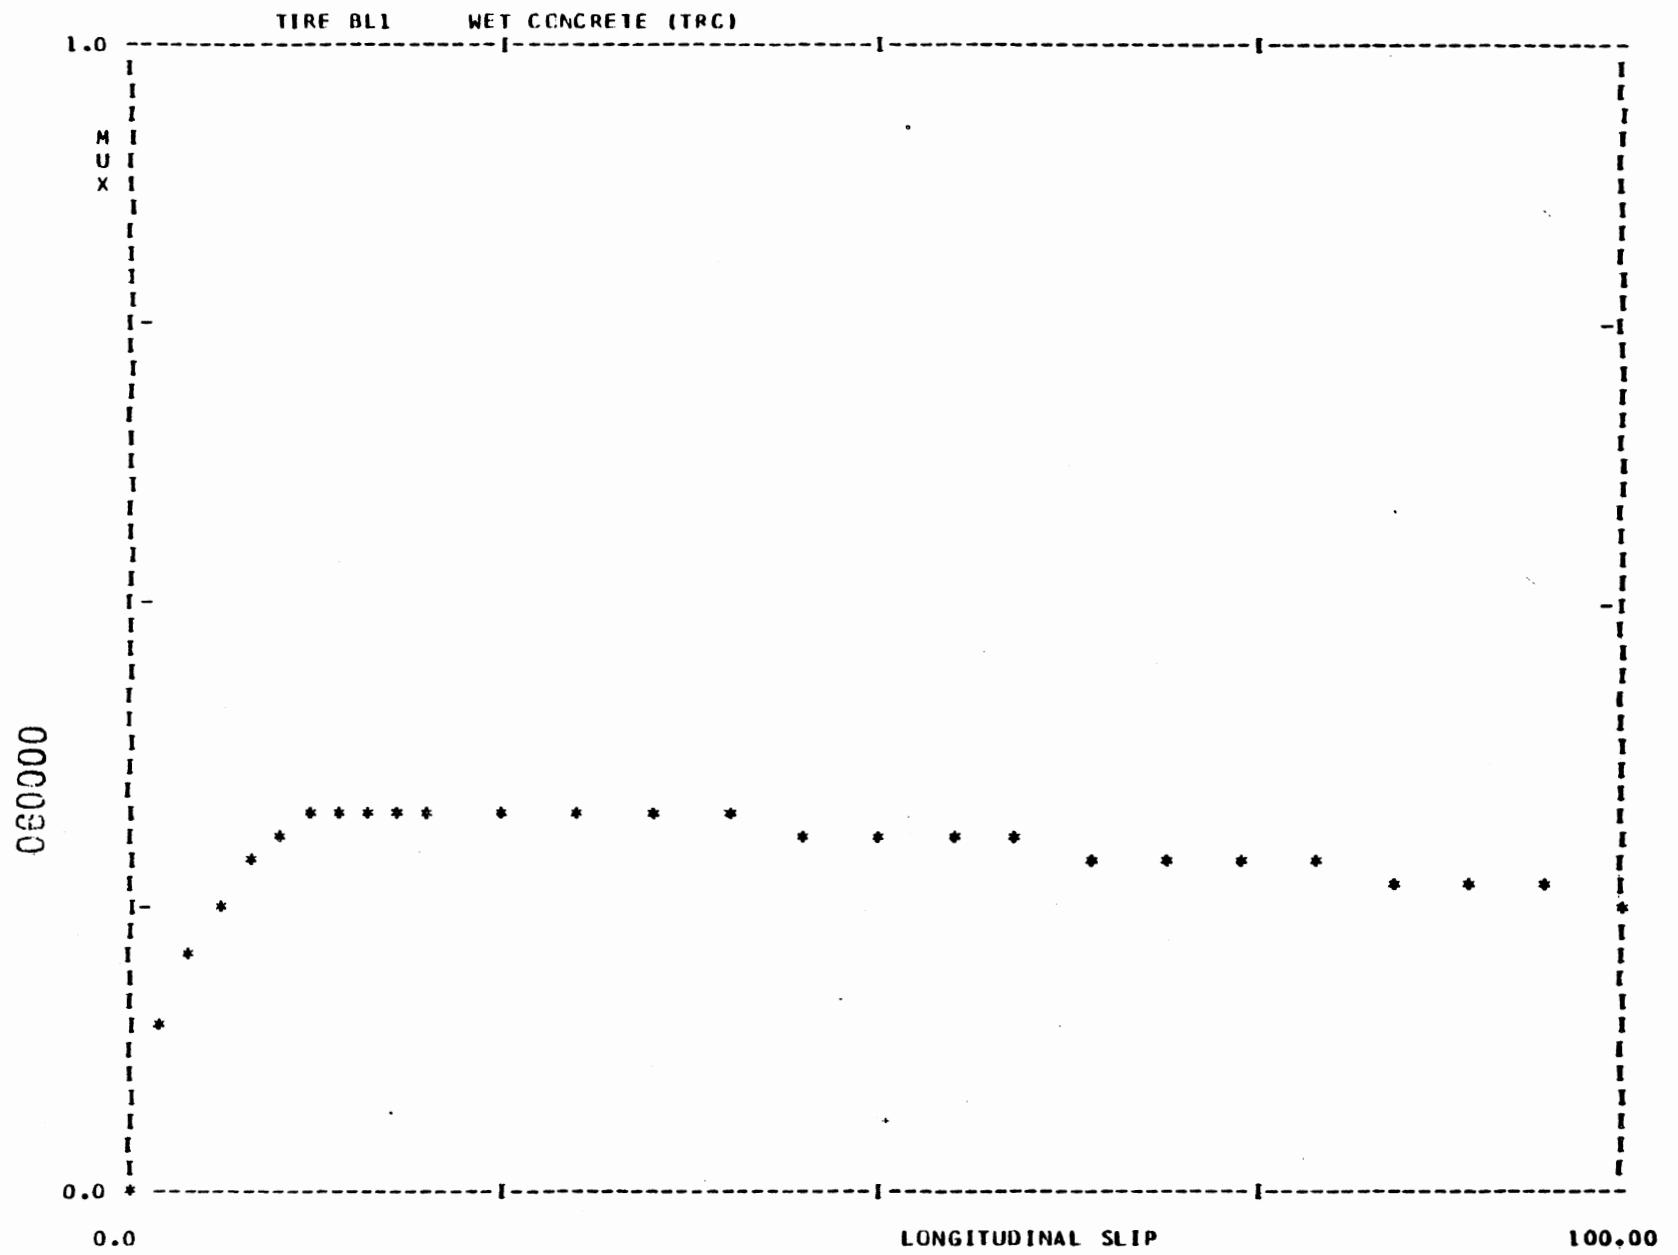

FZ = 4678.4 VEL = 50.0 MULOCK = 0.24 MUPEAK = 0.34 RATIO = 1.40 A-D FILE 61 NWFILE 18 SAMPLE 120

MU-PEAK

0.345	0.160	0.233
0.359	0.180	0.211
0.364	0.140	0.241
0.318	0.600	0.250
0.340	0.250	0.221
0.325	0.400	0.255

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.342 0.018
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.235 0.017


000091

000092

** A-D FILE 70 NEW FILE 19 TEST SAMPLE121 **

AVERAGE OF FILE 70 FOR 6 RECORDS.		TIRE ROLLING RESISTANCE	WET ASPHALT (TRC)
SLIP	MU _X	TORQUE	F _X
0.0	0.00	0.0	0.0
0.02	0.21	22894.0	994.6
0.04	0.35	37709.3	1685.5
0.06	0.47	48405.9	2213.2
0.08	0.58	58181.4	2690.9
0.10	0.65	68187.8	3123.3
0.12	0.69	72527.3	3292.0
0.14	0.72	75571.8	3396.2
0.16	0.74	78151.1	3454.7
0.18	0.75	80375.3	3485.4
0.20	0.75	82171.9	3491.1
0.25	0.76	85441.7	3460.8
0.30	0.75	87998.1	3414.4
0.35	0.75	89848.4	3373.4
0.40	0.73	91147.7	3325.3
0.45	0.72	92108.1	3276.4
0.50	0.71	93007.1	3222.1
0.55	0.69	93842.3	3158.0
0.60	0.67	94708.3	3089.4
0.65	0.65	95541.5	3009.5
0.70	0.63	95640.6	2923.5
0.75	0.61	92374.4	2845.0
0.80	0.59	83313.8	2776.5
0.85	0.57	72308.6	2694.4
0.90	0.55	66845.2	2579.8
0.95	0.53	59491.9	2495.1
1.00	0.49	49874.9	2312.0

TQAV = 49874.9 LOAD = 4782.0 VEL = 40.0 MPH.
MUPEAK = 0.76 MULOCK = 0.49 RATIO = 1.55

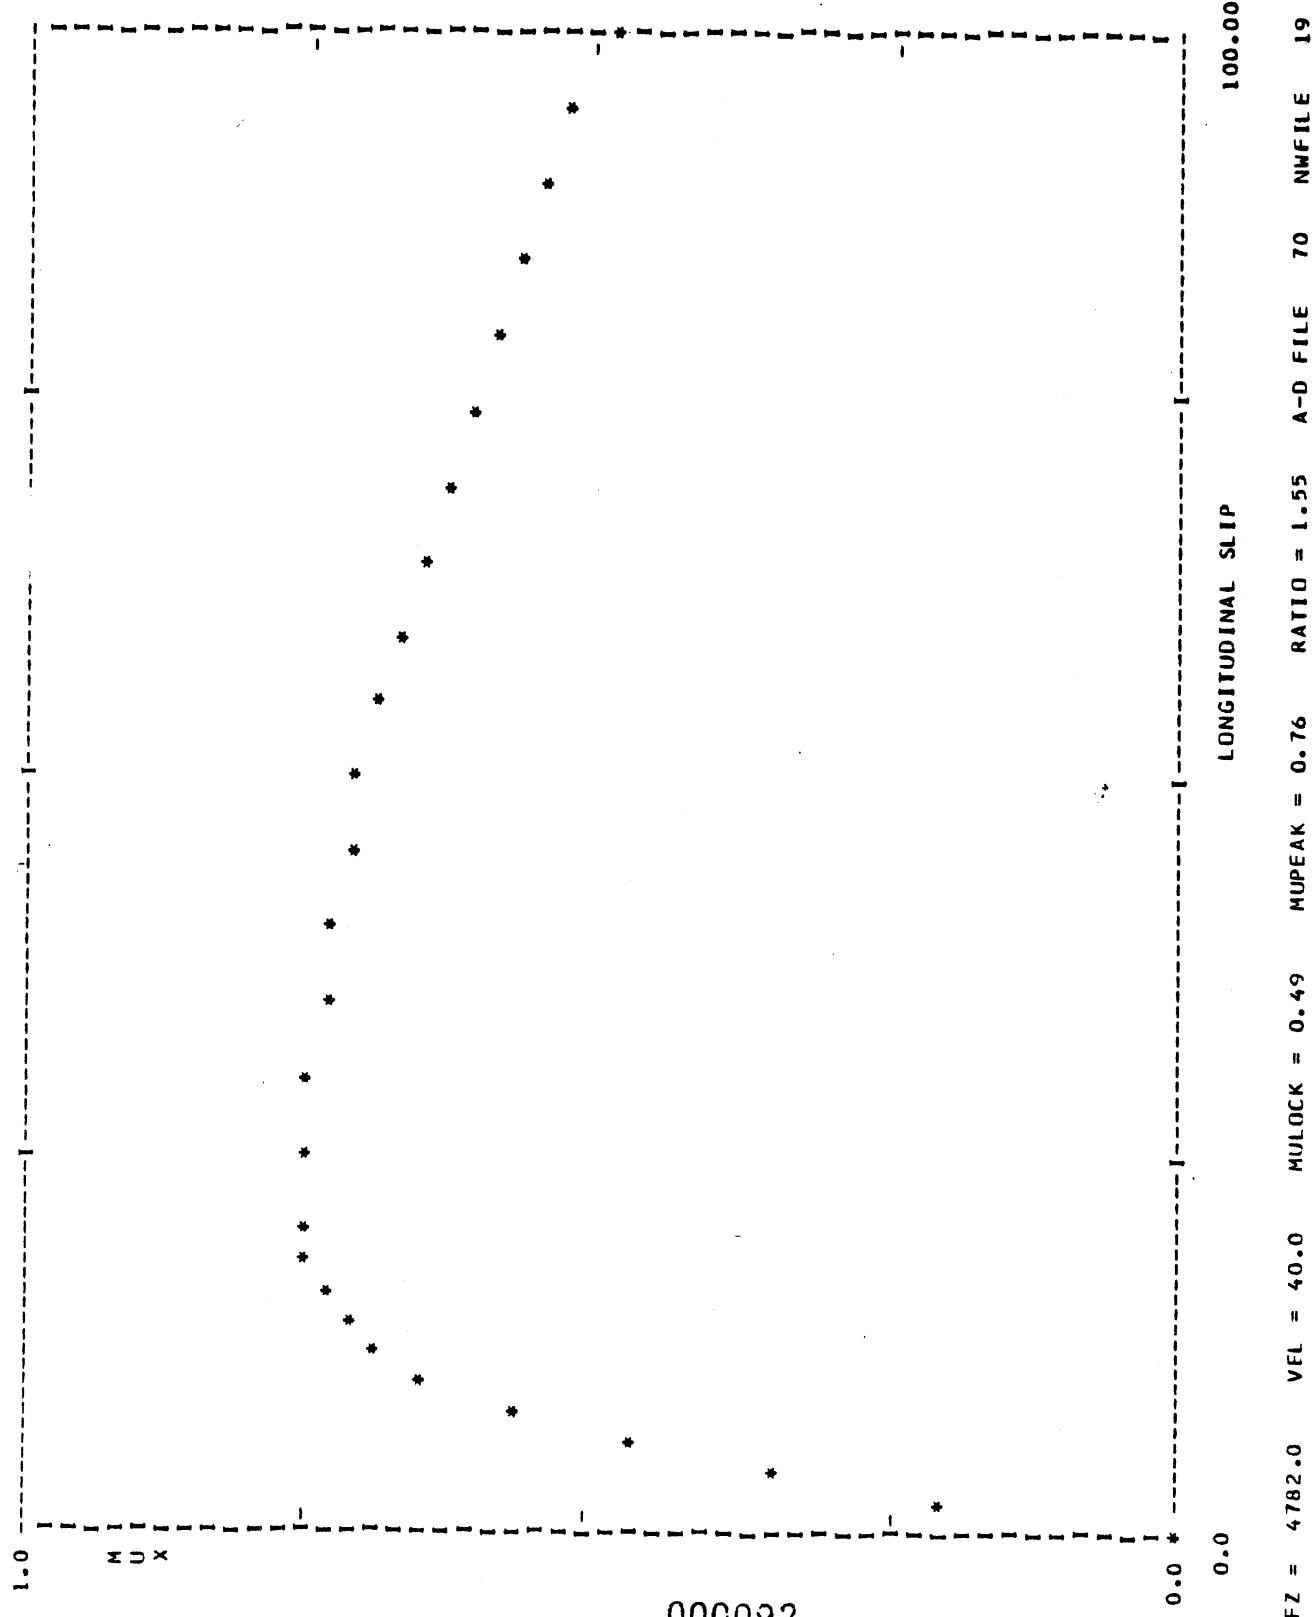

MU-PEAK	SL IP @PEAK	MU-LOCK
0.798	0.250	0.491
0.770	0.200	0.486
0.746	0.300	0.474
0.727	0.350	0.478
0.729	0.350	0.471
0.777	0.200	0.502

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.758 0.028
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.484 0.012

000094


SLIP	AVERAGE OF FILE 71 FOR 7 ROUNDS.	TORQUE	TIRESL	WET ASPHALT (TRC)
	MUX	F _X		
0.0	0.00	0.0	0.0	
0.02	0.22	23994.1	1017.2	
0.04	0.37	39517.5	1740.4	
0.06	0.48	49612.1	2229.0	
0.08	0.56	58216.1	2593.4	
0.10	0.61	64205.2	2835.7	
0.12	0.66	69108.3	3026.6	
0.14	0.69	72455.0	3140.3	
0.16	0.71	75348.1	3224.2	
0.18	0.73	77671.1	3283.1	TQAV = 46249.9 LOAD = 4735.0 VEL = 50.0 MPH.
0.20	0.73	79444.4	3317.0	
0.25	0.73	83137.5	3332.9	MUPEAK = 0.73 MULOCK = 0.46 RATIO = 1.60
0.30	0.70	85678.4	3263.6	
0.35	0.68	87318.1	3167.2	
0.40	0.66	88726.8	3077.5	
0.45	0.64	90020.3	2999.3	
0.50	0.63	91206.3	2937.4	
0.55	0.61	92354.1	2878.7	
0.60	0.60	93298.6	2822.0	
0.65	0.59	94160.3	2761.3	
0.70	0.57	94880.9	2691.7	
0.75	0.56	93032.8	2617.8	
0.80	0.54	85773.6	2548.6	
0.85	0.53	73128.3	2479.8	
0.90	0.51	65642.0	2370.3	
0.95	0.50	56020.8	2293.9	
1.00	0.46	46249.9	2121.0	

000093

330000

1.0 ----- TIRE ROLLING WET ASPHALT (TRC)

$$x \in \mathbb{H}$$

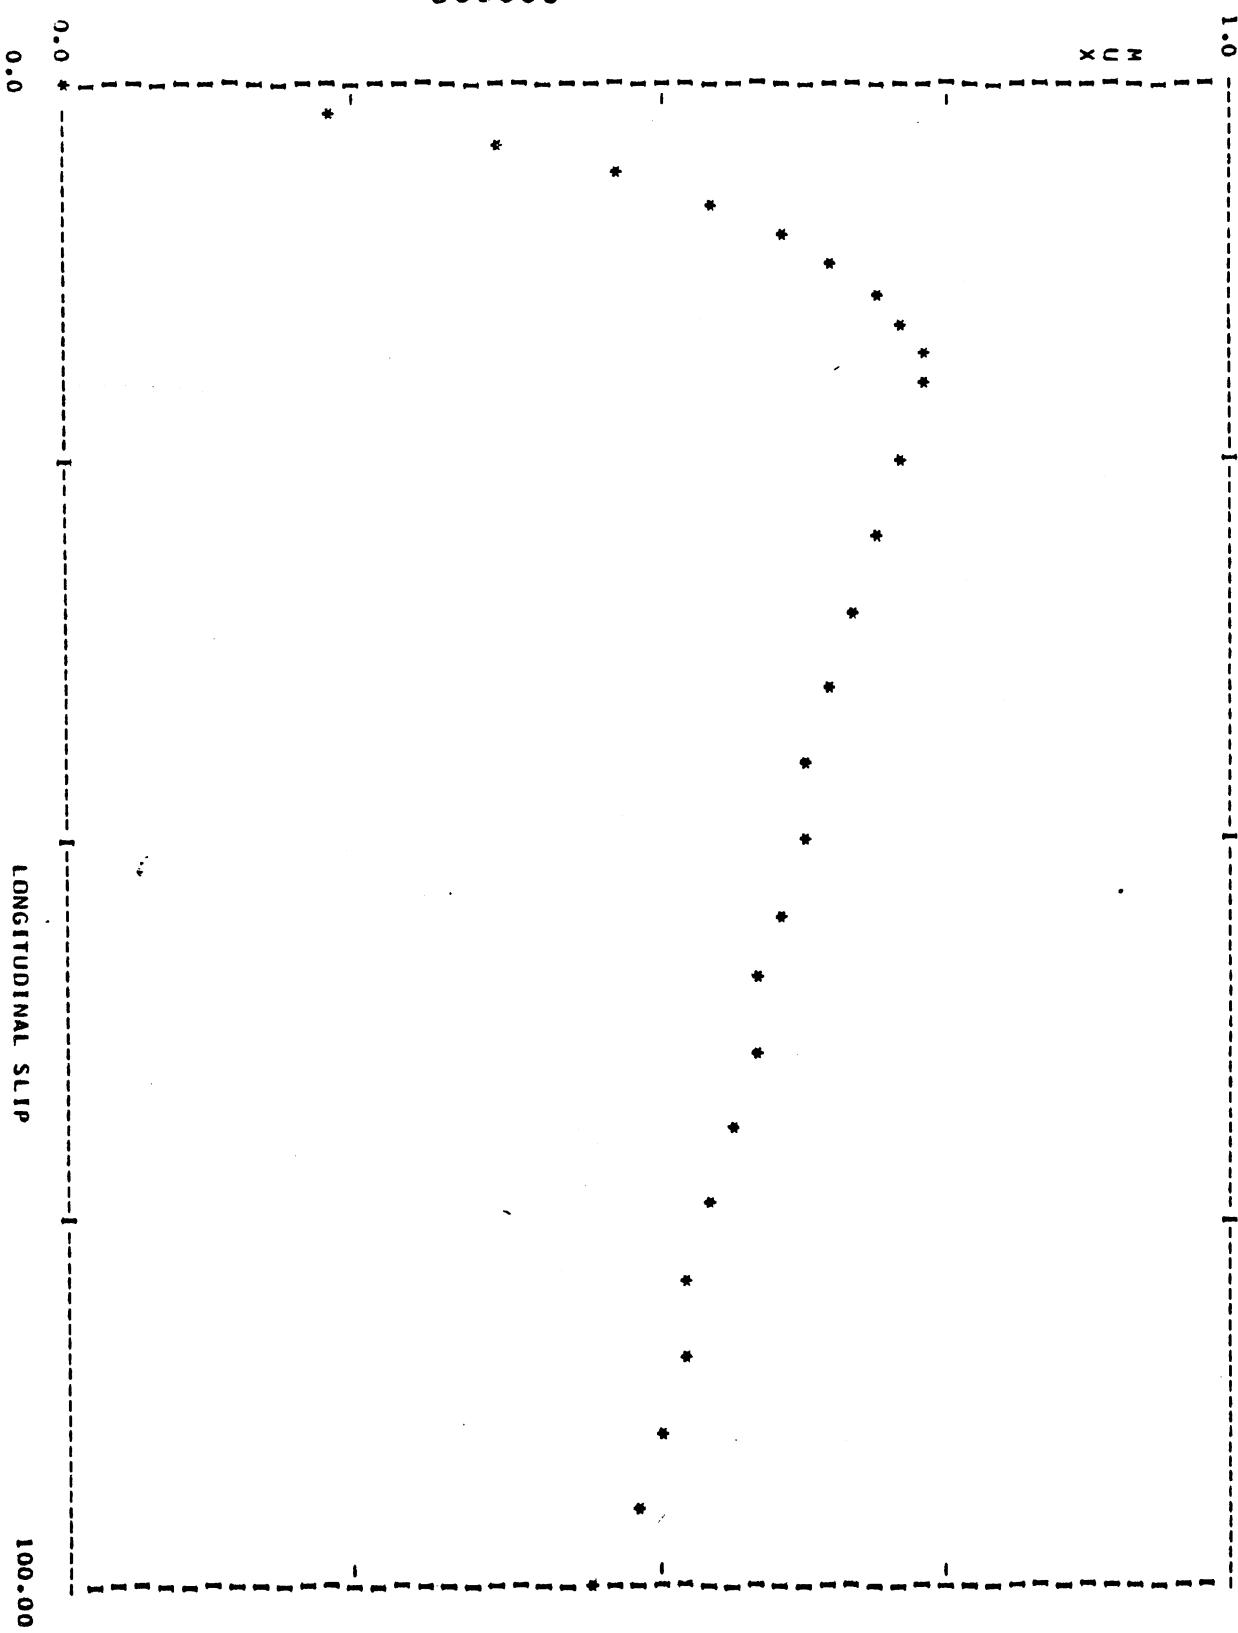

FZ = 4735.0 VEL = 50.0 MULOCK = 0.46 MUPEAK = 0.73 RATIO = 1.60 A-D FILE 71 NWFILE 20 SAMPLE 122

MU-PEAK	ST. IP@PEAK	MU-LOCK
0.814	0.256	0.517
0.756	0.200	0.463
0.760	0.250	0.524
0.739	0.180	0.420
0.707	0.200	0.398
0.741	0.200	0.481
0.612	0.180	0.372

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.733 0.062
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.454 0.059

000097

860000

** A-D FILE 75


NEW FILE 21

TEST SAMPLE123 **

AVERAGE OF FILE 75 FOR 6 RECORDS.

TIRE RL1 WET CONCRETE (TRC)

SL IP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.14	15340.4	673.1
0.04	0.21	23864.6	1006.8
0.06	0.24	28249.0	1131.0
0.08	0.26	31096.2	1205.7
0.10	0.28	33637.7	1262.8
0.12	0.28	35669.7	1290.6
0.14	0.29	37365.7	1311.5
0.16	0.30	38893.6	1330.8
0.18	0.30	40343.2	1345.1
0.20	0.30	41612.4	1357.5
0.25	0.31	44473.5	1379.7
0.30	0.30	46836.6	1378.8
0.35	0.30	48875.5	1362.2
0.40	0.29	50578.1	1345.6
0.45	0.29	52145.1	1328.6
0.50	0.28	53667.1	1313.7
0.55	0.28	55002.9	1300.4
0.60	0.28	56245.2	1288.0
0.65	0.28	57388.6	1273.2
0.70	0.27	58455.2	1255.2
0.75	0.27	57664.2	1233.1
0.80	0.27	53525.3	1221.8
0.85	0.27	44619.3	1225.0
0.90	0.26	38699.8	1216.9
0.95	0.26	32659.5	1200.2
1.00	0.25	24291.7	1132.0

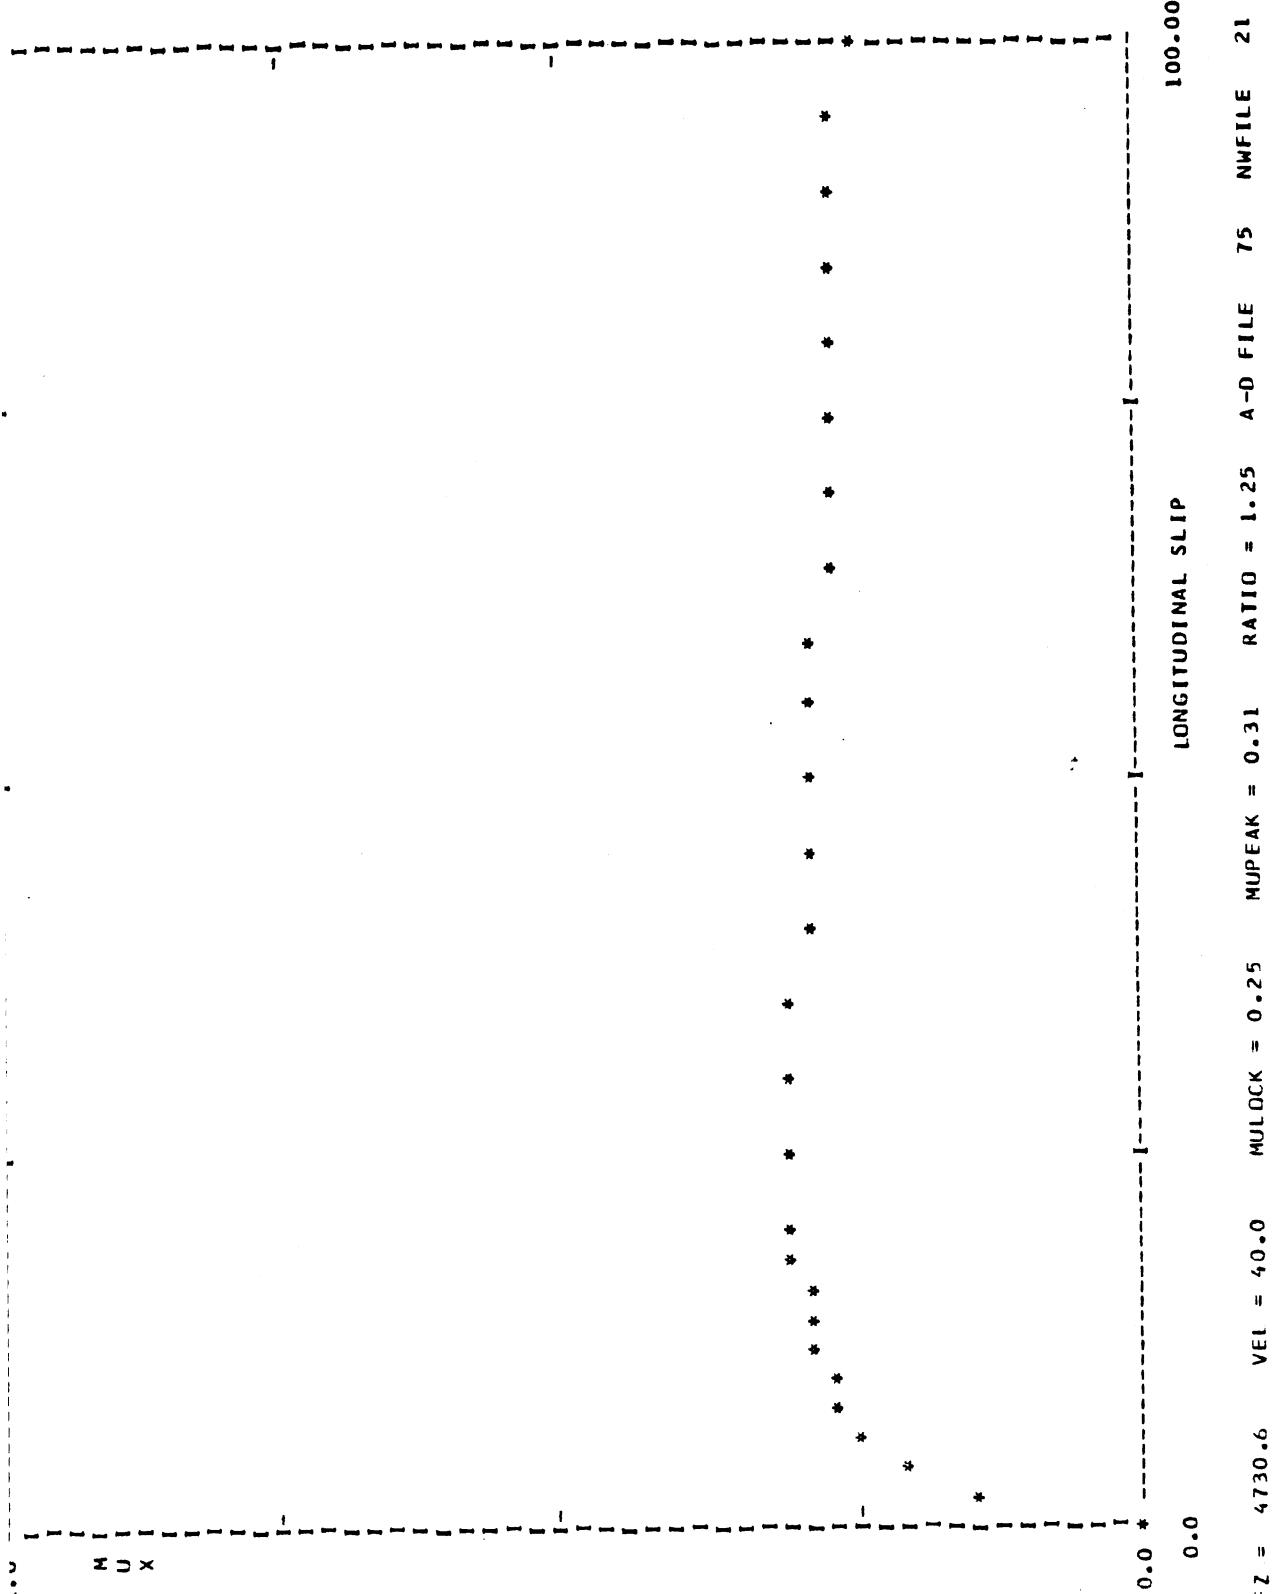

000099

MU-PEAK	SL IP@PEAK	MU-LOCK
0.409	0.160	0.252
0.293	0.250	0.247
0.269	0.300	0.247
0.309	0.250	0.245
0.257	0.250	0.214
0.273	0.250	0.237

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.302 0.056
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.240 0.014


000100

AVERAGE OF FILE 76 FOR 6 RECORDS. TIRE RLL WEIGHT CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.15	17358.0	698.6
0.04	0.20	23674.0	944.3
0.06	0.23	28316.4	1063.3
0.08	0.24	31685.8	1122.4
0.10	0.25	34352.0	1142.2
0.12	0.25	36411.1	1156.2
0.14	0.25	38010.1	1164.2
0.16	0.25	39591.9	1168.6
0.18	0.25	41013.9	1168.7
0.20	0.25	42285.2	1170.0
0.25	0.26	45152.6	1171.3
0.30	0.26	47679.9	1172.5
0.35	0.26	49981.9	1170.8
0.40	0.26	52105.3	1166.4
0.45	0.25	53962.8	1164.9
0.50	0.26	55764.4	1167.6
0.55	0.25	57344.4	1164.9
0.60	0.25	58768.4	1153.6
0.65	0.25	60195.2	1142.2
0.70	0.24	61482.7	1126.7
0.75	0.24	61513.6	1105.9
0.80	0.23	58054.2	1078.7
0.85	0.23	46754.7	1062.1
0.90	0.22	37788.6	1035.2
0.95	0.21	30377.3	970.5
1.00	0.19	20020.8	886.0

000101

TIRE RL1 WET CONCRETE (TRC)

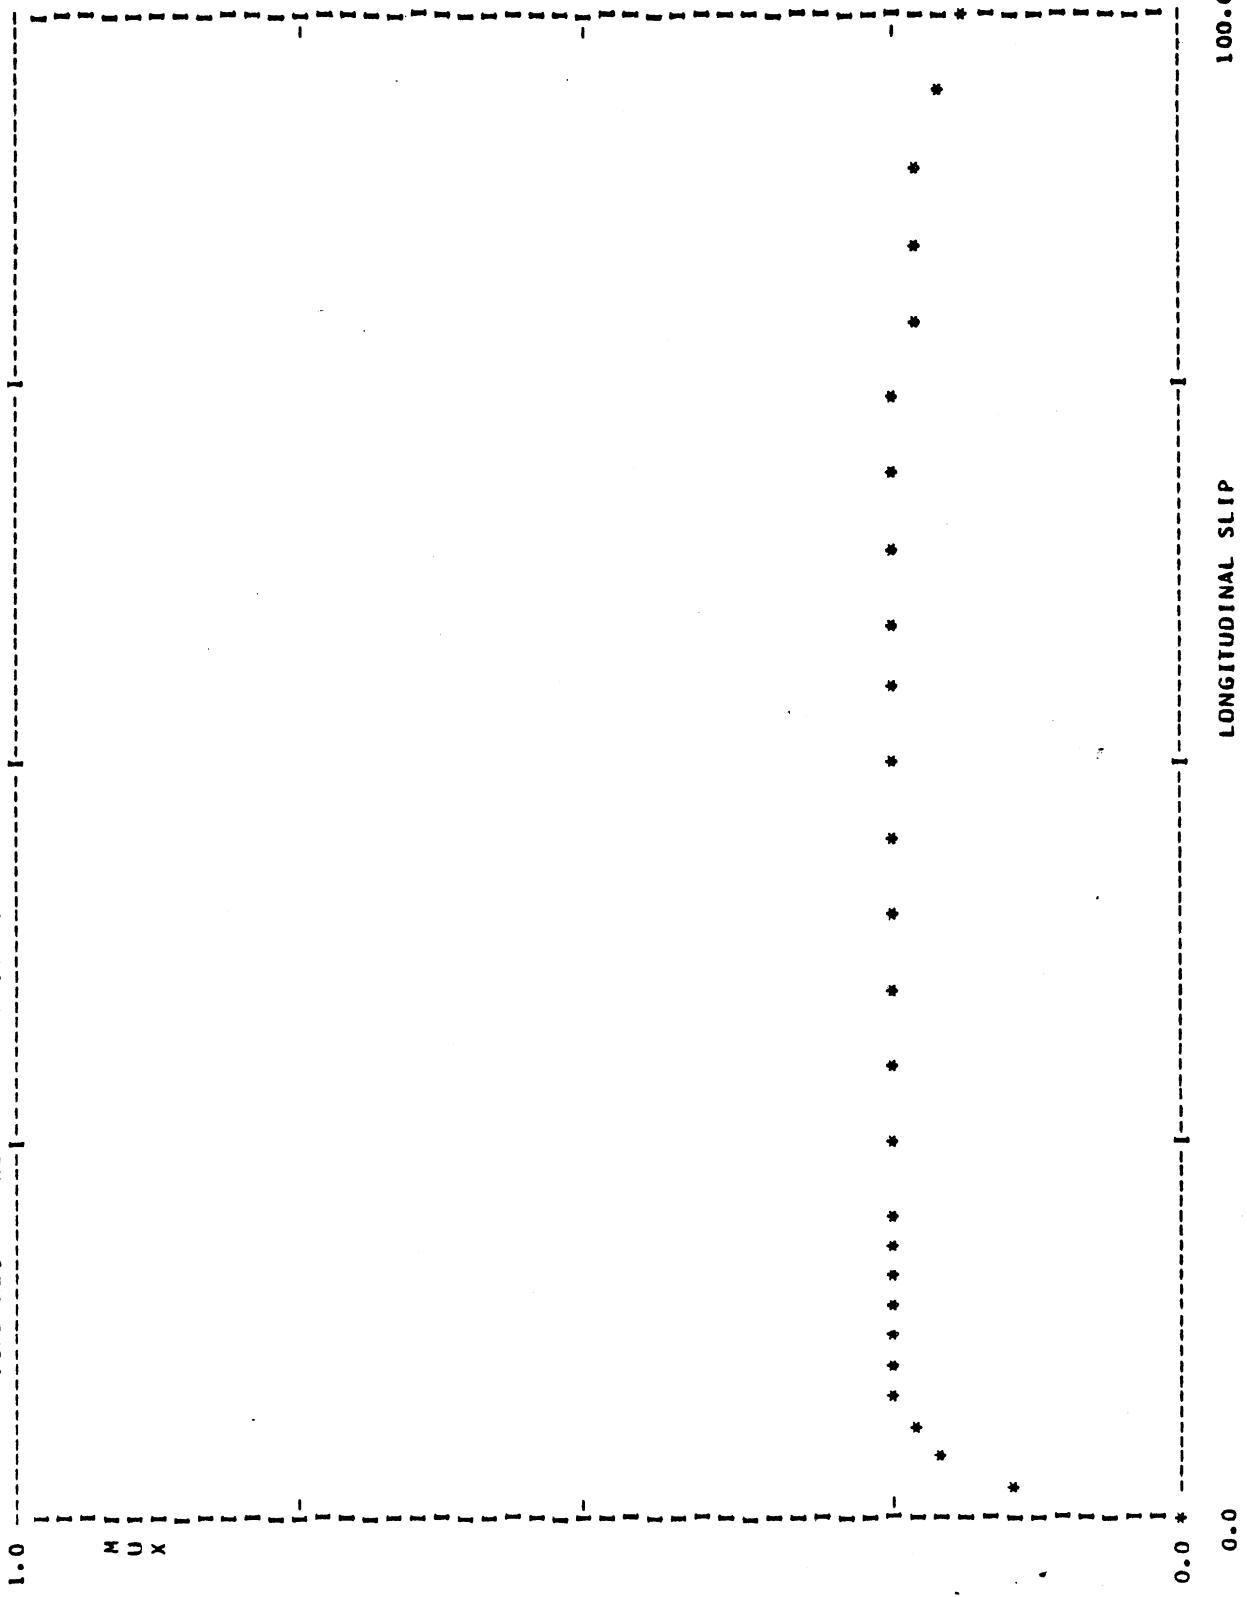

000102

$F_L = 4764.7$ $V_{EL} = 50.0$ $\mu_{BLOCK} = 0.19$ $\mu_{PEAK} = 0.26$ $ratio = 1.34$ A-D FILE 76 NMFILE 22 SAMPLE 124

MU-PEAK	SLIP@PEAK	MU-LOCK
0.307	0.300	0.180
0.246	0.550	0.184
0.286	0.160	0.208
0.221	0.200	0.174
0.270	0.350	0.178
0.238	0.160	0.196

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.261 0.032
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.187 0.013

000103


TEST SAMPLE 125 **

NEW FILE 23

** A-D FILE 83

SLIP	AVERAGE OF FILE 83 FOR 6 RECORDS.	TORQUE	FX	NEW FILE 23 WET ASPHALT (TRC)	TIRE C2
0.0	0.00	0.0	0.0		
0.02	0.18	19037.8	863.0		
0.04	0.31	32681.5	1501.8		
0.06	0.43	44107.7	2025.0		
0.08	0.53	53565.9	2449.5		
0.10	0.61	61453.3	2847.9		
0.12	0.69	67966.9	3188.1		
0.14	0.75	74085.4	3460.1		
0.16	0.77	77916.4	3629.1		
0.18	0.78	80823.8	3703.5	TQAV = 53437.4	LOAD = 4806.5
0.20	0.78	82823.2	3716.3		VEL = 40.0 MPH.
0.25	0.77	86263.6	3654.9	HUPEAK = 0.78	MULOCK = 0.54
0.30	0.75	88721.6	3560.2		RATIO = 1.46
0.35	0.74	90637.8	3471.1		
0.40	0.72	92226.4	3392.5		
0.45	0.71	93324.3	3320.9		
0.50	0.69	94151.6	3256.8		
0.55	0.68	94903.0	3194.6		
0.60	0.66	95577.1	3133.6		
0.65	0.65	95321.3	3075.9		
0.70	0.64	92972.4	3022.1		
0.75	0.63	88061.3	2969.2		
0.80	0.62	81282.4	2915.1		
0.85	0.60	74569.4	2843.5		
0.90	0.59	68214.4	2769.1		
0.95	0.57	61933.9	2688.0		
1.00	0.54	53437.4	2518.0		

00010

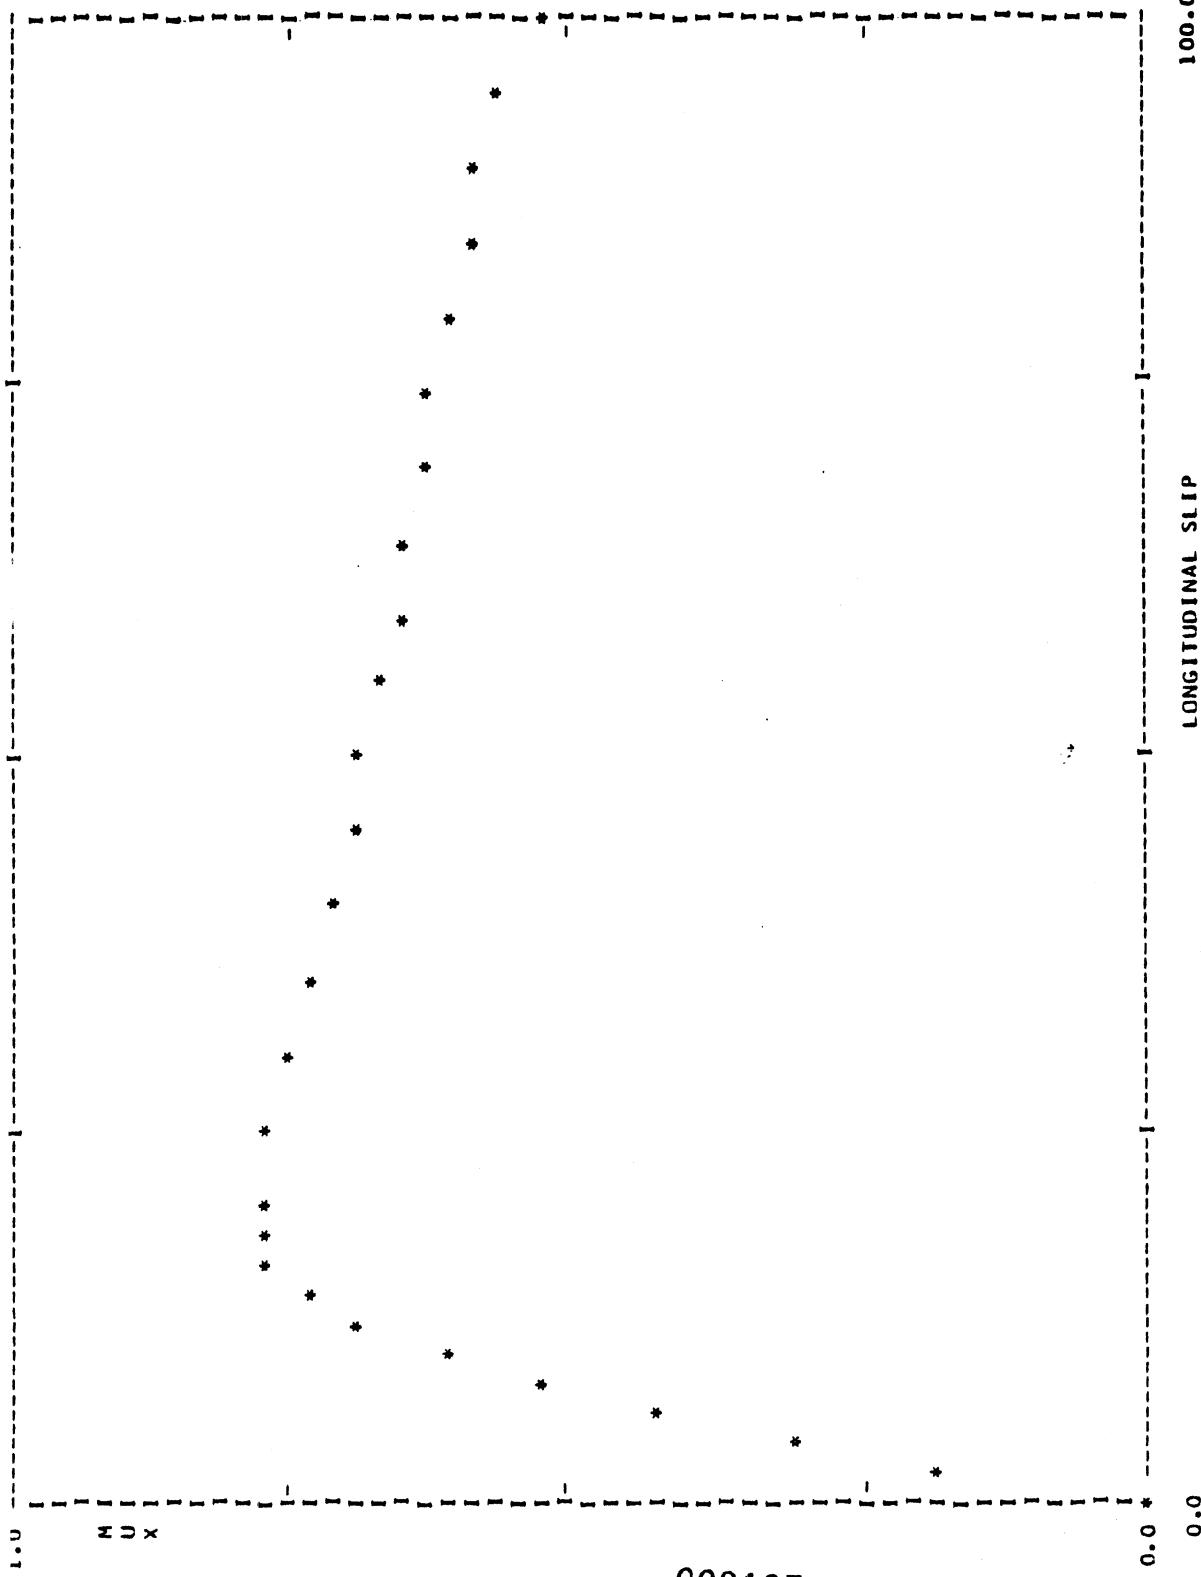

000105

MU-PEAK	SLIPPEAK	MU-LOCK
0.872	0.300	0.602
0.778	0.200	0.499
0.772	0.160	0.540
0.808	0.200	0.542
0.718	0.160	0.476
0.780	0.180	0.521

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.788 0.051

MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.530 0.043

000106

000107


AVERAGE OF FILE 84 FOR 6 RECORDS. TIRE C2 WET ASPHALT (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.18	19448.6	834.0
0.04	0.31	33721.6	1462.6
0.06	0.43	44669.6	2006.7
0.08	0.53	53707.8	2452.5
0.10	0.60	61721.8	2822.5
0.12	0.64	68443.8	3056.4
0.14	0.65	72055.9	3102.2
0.16	0.65	74423.6	3119.9
0.18	0.66	76246.9	3124.3
0.20	0.66	77406.9	3110.4
0.25	0.65	79607.8	3044.2
0.30	0.64	81734.6	2975.2
0.35	0.63	83352.1	2913.6
0.40	0.62	84686.3	2866.0
0.45	0.62	86036.1	2826.1
0.50	0.61	87266.8	2790.3
0.55	0.60	88427.4	2759.6
0.60	0.59	89567.6	2726.4
0.65	0.59	90616.9	2690.7
0.70	0.58	90498.2	2656.2
0.75	0.57	87628.7	2622.5
0.80	0.56	79980.7	2587.9
0.85	0.54	72395.6	2547.1
0.90	0.53	65358.8	2487.6
0.95	0.51	58202.4	2415.6
1.00	0.46	47520.8	2205.0

000108

TIRE C2 WET ASPHALT (TRC)

MU
X

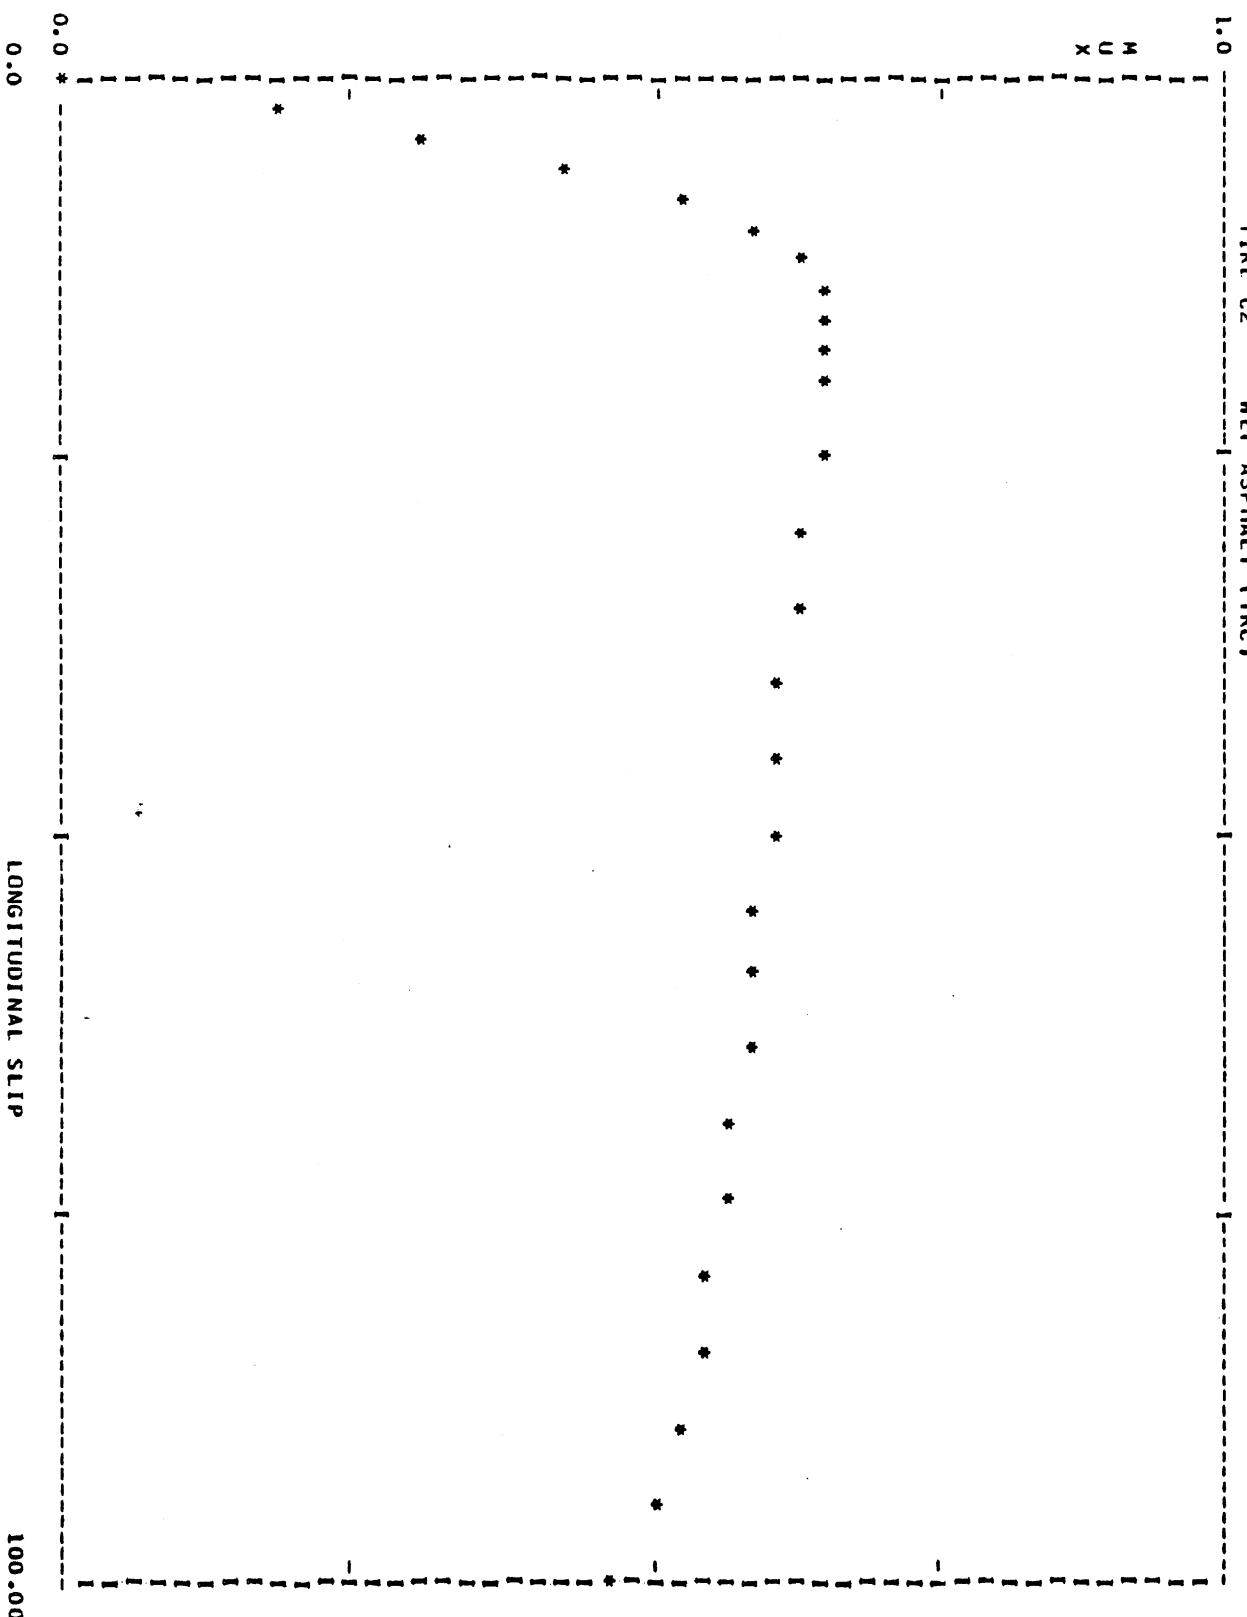

FZ = 4857.5 VEL = 50.0 MULOCK = 0.46 MUPEAK = 0.66 RATIO = 1.42 A-D FILE 84 NMFILE 24 SAMPLE 126

MU-PEAK	SLIP@PEAK	MU-LOCK
0.669	0.160	0.457
0.698	0.120	0.502
0.627	0.300	0.502
0.606	0.200	0.410
0.771	0.200	0.473
0.594	0.120	0.407

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.661 0.067
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.458 0.043

000109

TEST SAMPLE 127 **

NEW FILE 25


** A-D FILE 88

AVVERAGE OF FILE 88 FOR 5 RECORDS.

TIRE C2 WET CONCRETE (TRC.)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.15	16721.5	690.5
0.04	0.25	26213.4	1138.2
0.06	0.31	33566.0	1446.0
0.08	0.33	38138.1	1570.1
0.10	0.34	40750.3	1610.0
0.12	0.35	42701.4	1632.9
0.14	0.36	44396.7	1656.5
0.16	0.36	45988.6	1680.4
0.18	0.37	47365.1	1709.7
0.20	0.38	48644.9	1739.9
0.25	0.40	51460.3	1823.8
0.30	0.41	53877.7	1875.5
0.35	0.41	55972.0	1885.4
0.40	0.41	57730.4	1864.0
0.45	0.40	59335.5	1836.9
0.50	0.40	60860.4	1805.0
0.55	0.39	62358.1	1774.2
0.60	0.38	63754.8	1737.5
0.65	0.37	65080.2	1692.5
0.70	0.36	64958.9	1645.5
0.75	0.35	61228.0	1605.3
0.80	0.35	55015.7	1565.2
0.85	0.34	48534.8	1517.4
0.90	0.32	42610.7	1457.0
0.95	0.31	37068.1	1407.1
1.00	0.27	28125.0	1249.8

000110

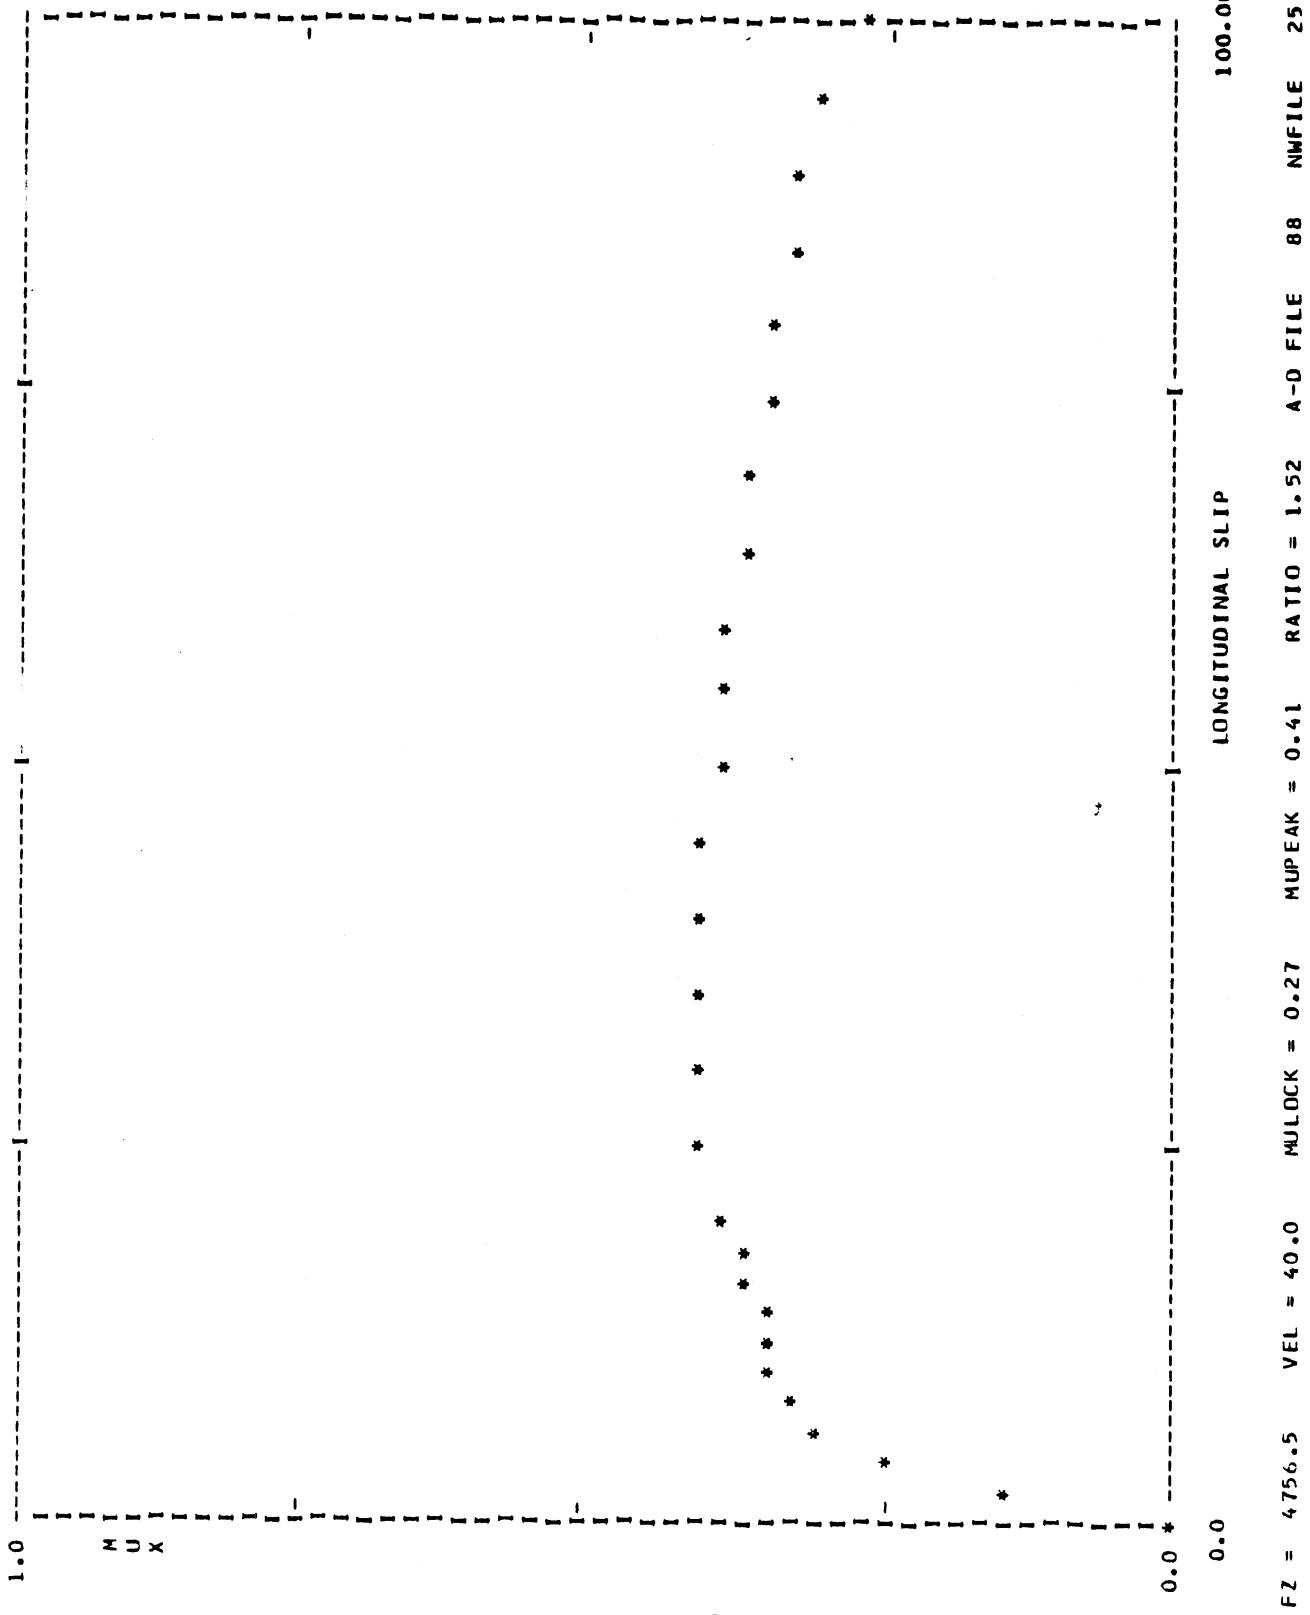

000111

MU-PEAK	SLIP@PEAK	MU-LOCK
0.436	0.350	0.288
0.424	0.250	0.264
0.444	0.300	0.278
0.350	0.500	0.224
0.398	0.350	0.278


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.410 0.038
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.266 0.025

000112

SLIP	AVERAGE OF FILE	89	FOR 6 RECORDS.	TIRE C2	WET CONCRETE (TRC)
MUX			TORQUE	FX	
0.0	0.00	0.0	0.0	0.0	
0.02	0.15	17317.8	691.2		
0.04	0.23	25750.0	1024.9		
0.06	0.28	31677.9	1259.3		
0.08	0.31	36348.8	1428.3		
0.10	0.33	39778.7	1504.2		
0.12	0.34	42435.5	1557.3		
0.14	0.35	44518.8	1603.8		
0.16	0.35	46032.0	1641.4		
0.18	0.36	47364.9	1672.2	TQAV = 23645.	
0.20	0.36	48573.6	1699.3		
0.25	0.37	51572.8	1739.3	HUPEAK = 0.38	
0.30	0.38	54073.5	1751.6		
0.35	0.38	56607.1	1764.3		
0.40	0.38	59025.4	1761.4		
0.45	0.38	61220.7	1747.6		
0.50	0.38	62807.5	1732.6		
0.55	0.37	64169.5	1710.4		
0.60	0.36	65370.4	1677.9		
0.65	0.36	66545.2	1634.2		
0.70	0.34	67371.4	1581.1		
0.75	0.33	65558.5	1531.3		
0.80	0.32	59165.7	1482.0		
0.85	0.31	50584.3	1429.3		
0.90	0.30	42935.1	1357.7		
0.95	0.28	35405.8	1278.0		
1.00	0.22	23645.8	1034.5		

000113

TIRE C2 WET CONCRETE (TRC)

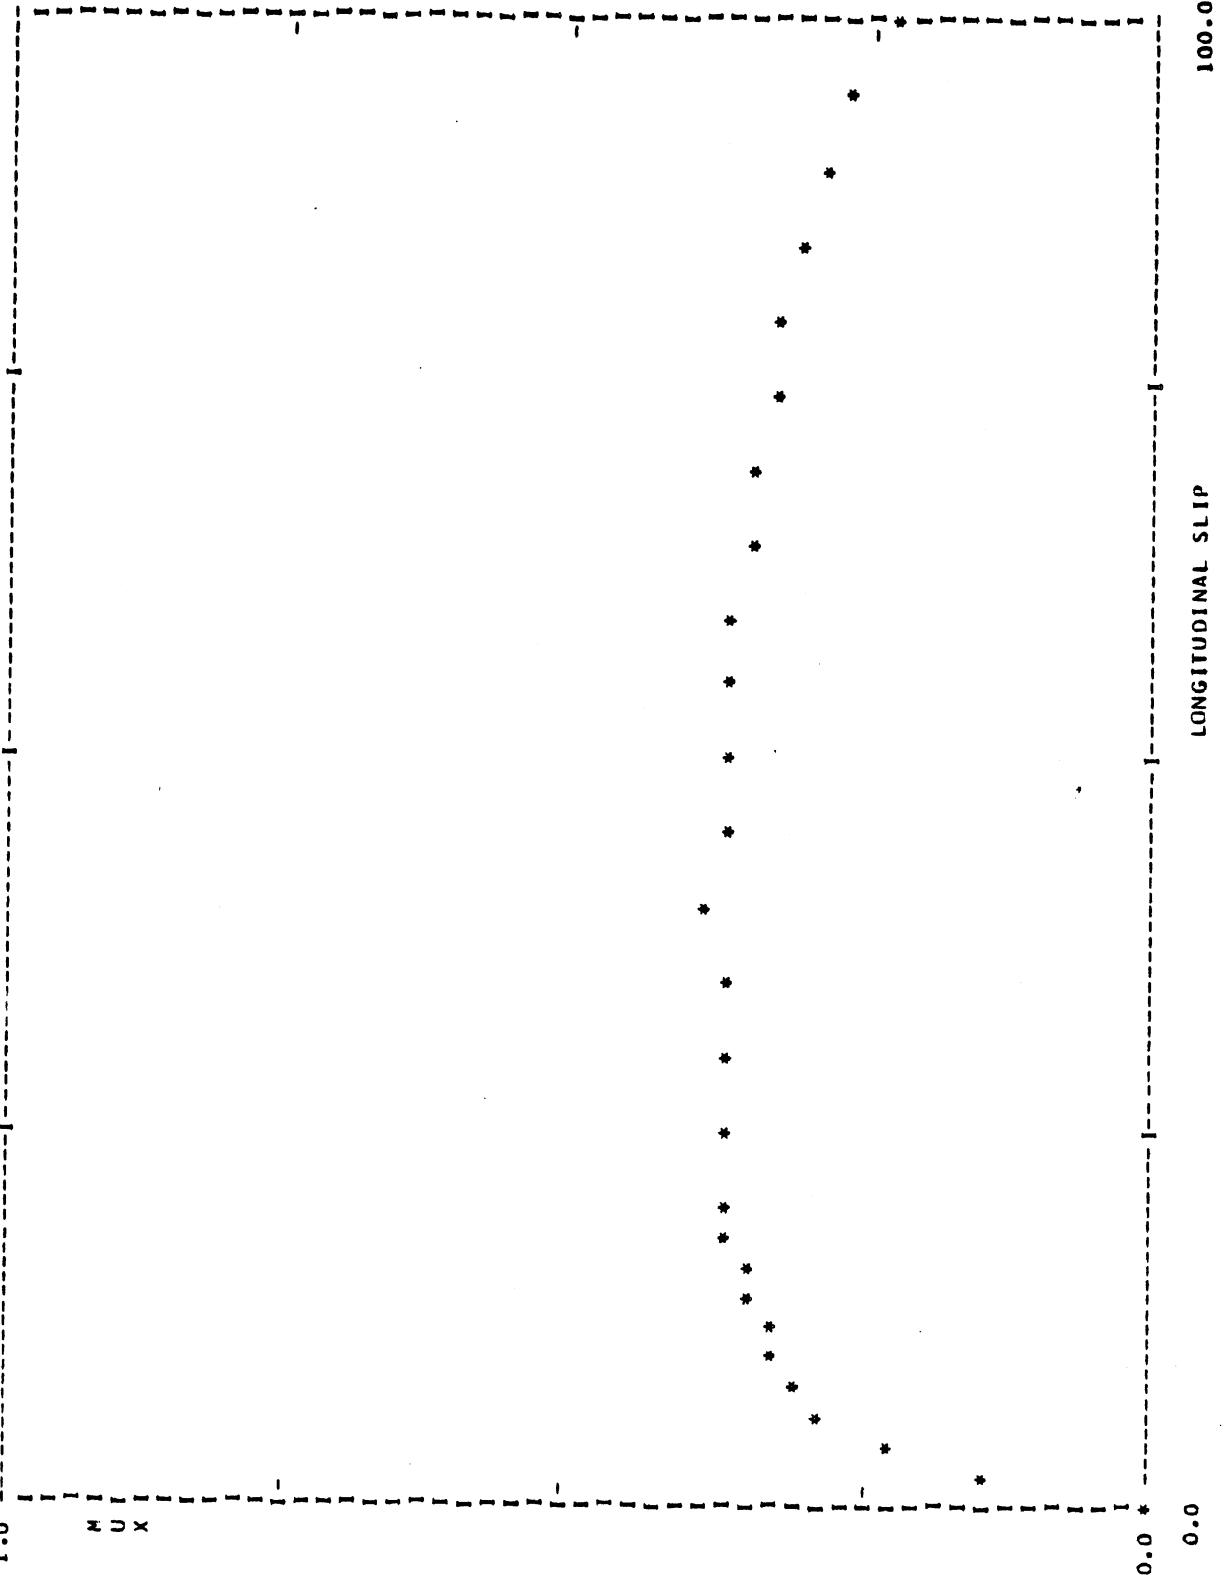

000114

FZ = 4760.5 VEL = 50.0 MULOCK = 0.22 MUPEAK = 0.38 RATIO = 1.71 A-D FILE 89 NWFILE 26 SAMPLE 128

MU-PEAK	SLIP@PEAK	MU-LOCK
0.358	0.400	0.199
0.353	0.250	0.226
0.390	0.550	0.245
0.299	0.400	0.199
0.516	0.400	0.228
0.340	0.250	0.205

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.376 0.075
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.217 0.019

000110

TEST SAMPLE E129 **

NEW FILE 27


** A-D FILE 97 FOR 6 RECORDS.

AVERAGE OF FILE 97

TIRE BR2
WET ASPHALT (TRC)

SLIP	MUX	TORQUE	FX
0.00	0.00	0.0	0.0
0.02	0.20	20937.4	911.7
0.04	0.42	42194.6	1919.8
0.06	0.56	55187.3	2565.8
0.08	0.66	66700.1	3118.0
0.10	0.73	73367.1	3394.2
0.12	0.78	77699.1	3554.7
0.14	0.80	80832.0	3628.2
0.16	0.81	83130.9	3663.6
0.18	0.81	84692.4	3670.0
0.20	0.81	85958.4	3666.7
0.25	0.80	88345.3	3630.3
0.30	0.79	90122.4	3569.5
0.35	0.77	91612.8	3500.1
0.40	0.75	92864.4	3426.3
0.45	0.74	93919.9	3354.1
0.50	0.72	94848.2	3284.1
0.55	0.71	95699.8	3218.6
0.60	0.70	96526.9	3153.2
0.65	0.68	96964.5	3091.0
0.70	0.67	95264.1	3036.4
0.75	0.66	90224.4	2987.8
0.80	0.65	83854.6	2939.2
0.85	0.64	77374.7	2880.2
0.90	0.62	71520.0	2819.8
0.95	0.61	65784.8	2785.3
1.00	0.58	57562.5	2681.0

000116

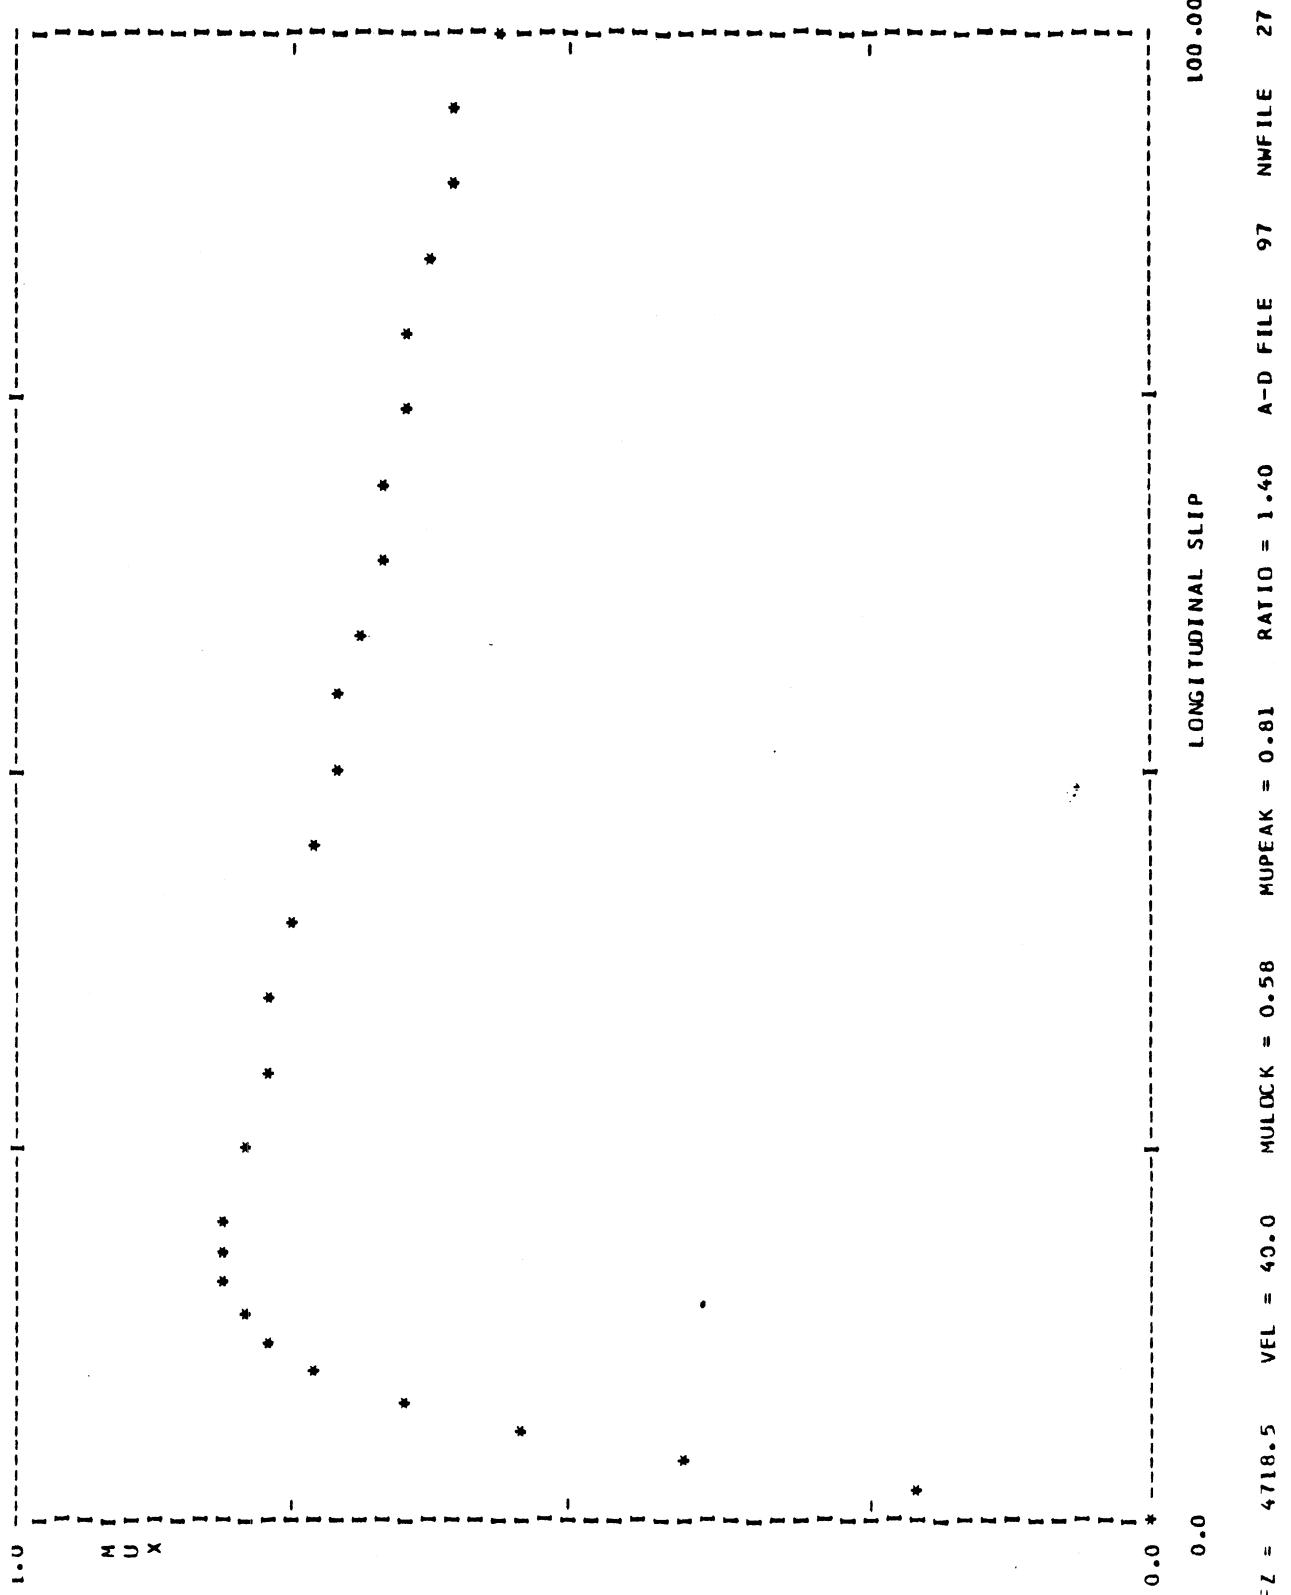

000117

MU-PEAK	SLIP@PEAK	MU-LOCK
0.833	0.250	0.525
0.837	0.160	0.605
0.796	0.120	0.598
0.798	0.250	0.558
0.808	0.180	0.581
0.853	0.160	0.582


MU-PEAK AVERAGE	VALUE AND STD. DEVIATION :	0.821	0.023
MU-LOCK AVERAGE	VALUE AND STD. DEVIATION :	0.575	0.029

000118.

AVERAGE OF FILE 98 FOR 6 RECORDS.			TIRE BR2	WET ASPHALT (TRC)
SLIP	MUX	TORQUE	FX	
0.0	0.30	0.0	0.0	
0.02	0.26	28592.4	1229.7	
0.04	0.41	42277.3	1884.6	
0.06	0.55	55125.5	2504.3	
0.08	0.64	63836.9	2919.0	
0.10	0.69	70145.8	3166.9	
0.12	0.72	73914.3	3287.4	
0.14	0.73	76430.0	3346.8	
0.16	0.73	78590.9	3367.0	
0.18	0.73	80287.2	3361.9	TQAV = 50541.
0.20	0.72	81577.1	3335.5	
0.25	0.70	84005.2	3251.7	MUPEAK = 0.73
0.30	0.69	85781.6	3173.1	
0.35	0.68	87235.3	3111.2	
0.40	0.67	88413.7	3058.1	
0.45	0.66	89558.6	3008.9	
0.50	0.65	90660.4	2961.7	
0.55	0.64	91744.5	2916.4	
0.60	0.63	92839.8	2870.1	
0.65	0.62	93935.9	2815.9	
0.70	0.60	94275.0	2761.4	
0.75	0.59	91374.1	2710.7	
0.80	0.58	84238.4	2666.8	
0.85	0.57	75808.4	2620.0	
0.90	0.56	68576.0	2555.9	
0.95	0.54	61846.4	2507.9	
1.00	0.50	50541.6	2320.5	

000113

TIRE BR2 WET ASPHALT (TRC)

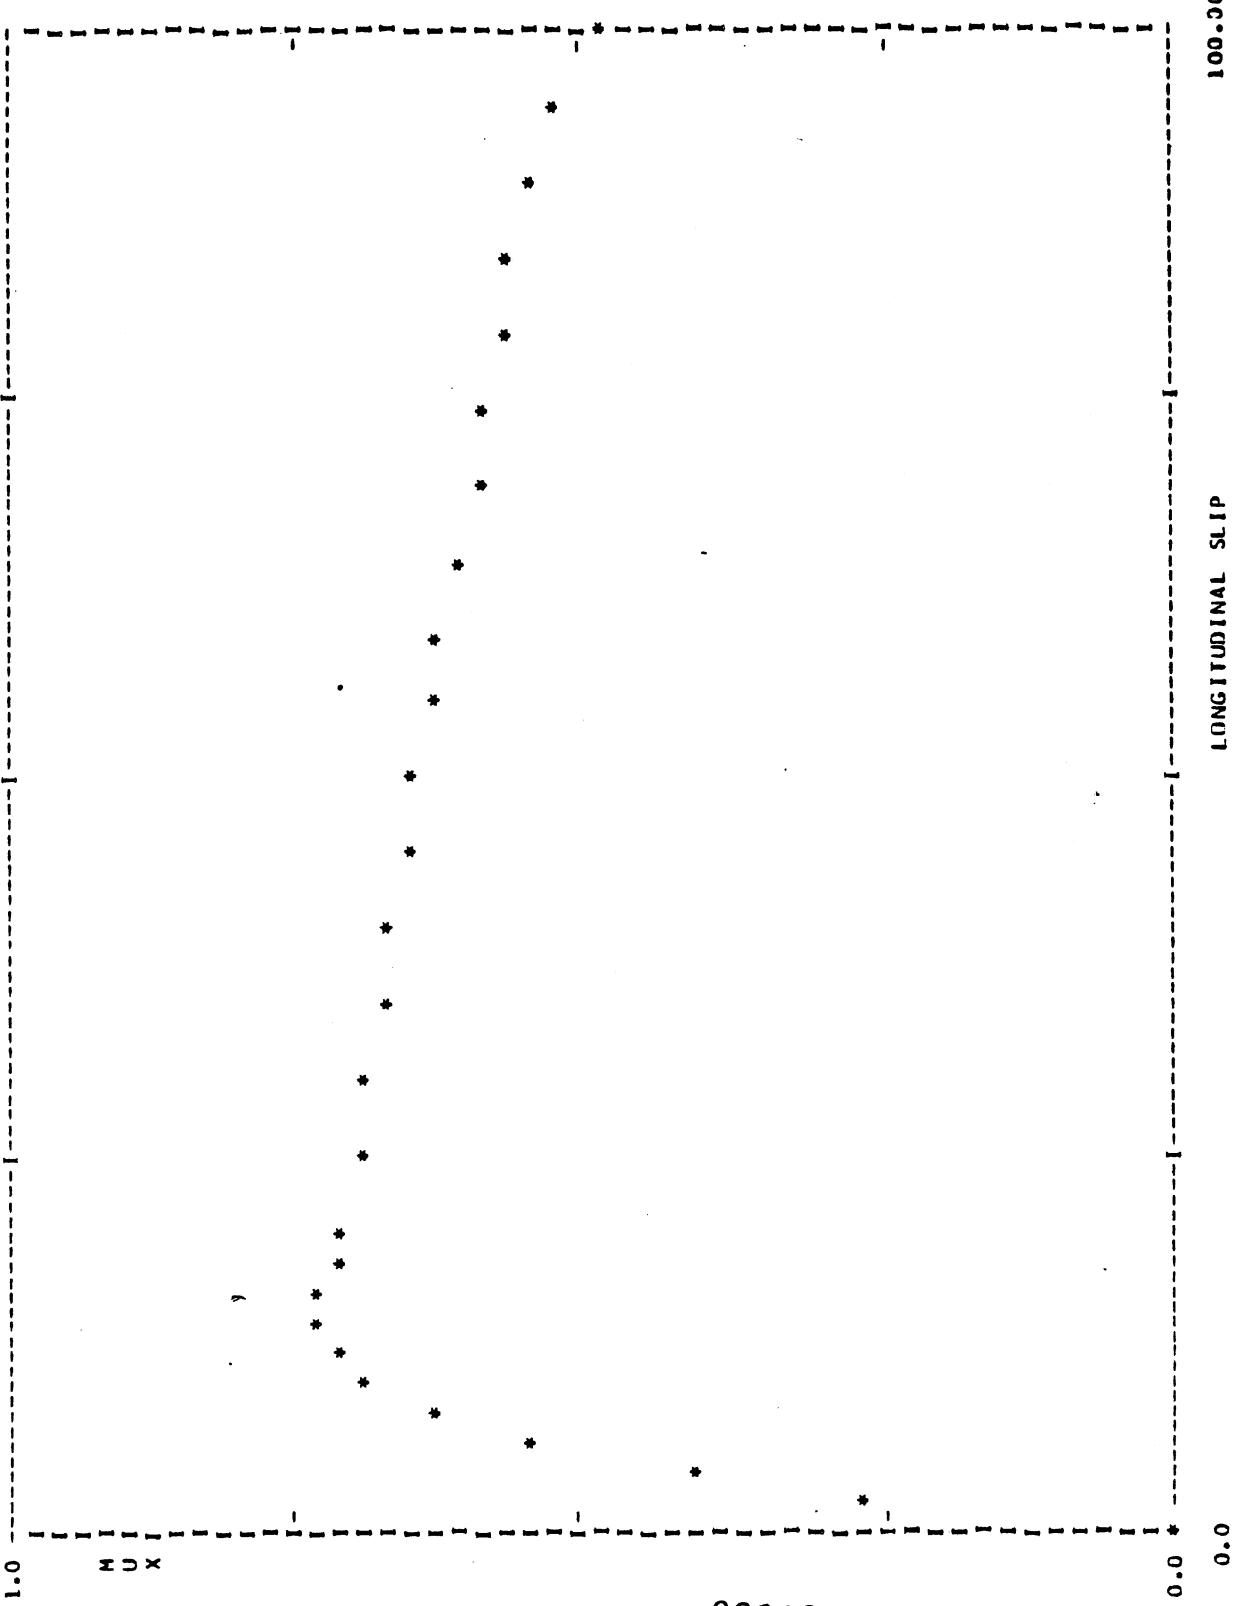

000120

FZ = 4741.3 VEL = 50.0 MUPEAK = 0.50 MULOCK = 0.50 RATIO = 1.46 A-D FILE 98 NMFILE 28 SAMPLE 130

MU-PEAK	MU-LICK
0.759	0.528
0.752	0.475
0.701	0.518
0.667	0.486
0.762	0.488
0.724	0.483

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.727 0.038
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.496 0.021

000121

000122

** A-D FILE 102

NEW FILE 29

TEST SAMPLE 131 **


AVERAGE OF FILE 102 FOR 5 RECORDS.

TIRE BR2 WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.16	17474.1	734.7
0.04	0.27	28352.2	1224.7
0.06	0.31	34276.7	1422.3
0.08	0.32	37459.6	1490.0
0.10	0.33	39917.5	1538.3
0.12	0.35	41819.5	1585.5
0.14	0.35	43482.5	1633.6
0.16	0.36	45273.1	1683.9
0.18	0.37	46877.4	1726.1
0.20	0.38	48281.1	1765.0
0.25	0.38	51262.4	1808.1
0.30	0.38	53731.6	1800.4
0.35	0.38	55736.6	1800.2
0.40	0.38	57441.9	1796.8
0.45	0.38	59025.3	1787.0
0.50	0.37	60442.1	1767.6
0.55	0.37	61922.6	1752.7
0.60	0.37	63305.5	1731.3
0.65	0.36	64590.5	1703.0
0.70	0.36	64993.9	1677.4
0.75	0.35	62439.9	1656.0
0.80	0.35	56457.5	1638.9
0.85	0.34	50572.1	1621.2
0.90	0.34	45153.9	1595.2
0.95	0.33	40234.4	1576.2
1.00	0.30	31575.0	1418.4

TQAV = 31575.0 LOAD = 4804.9 VEL = 40.0 MPH.

MUPEAK = 0.38 MULOCK = 0.30 RATIO = 1.29

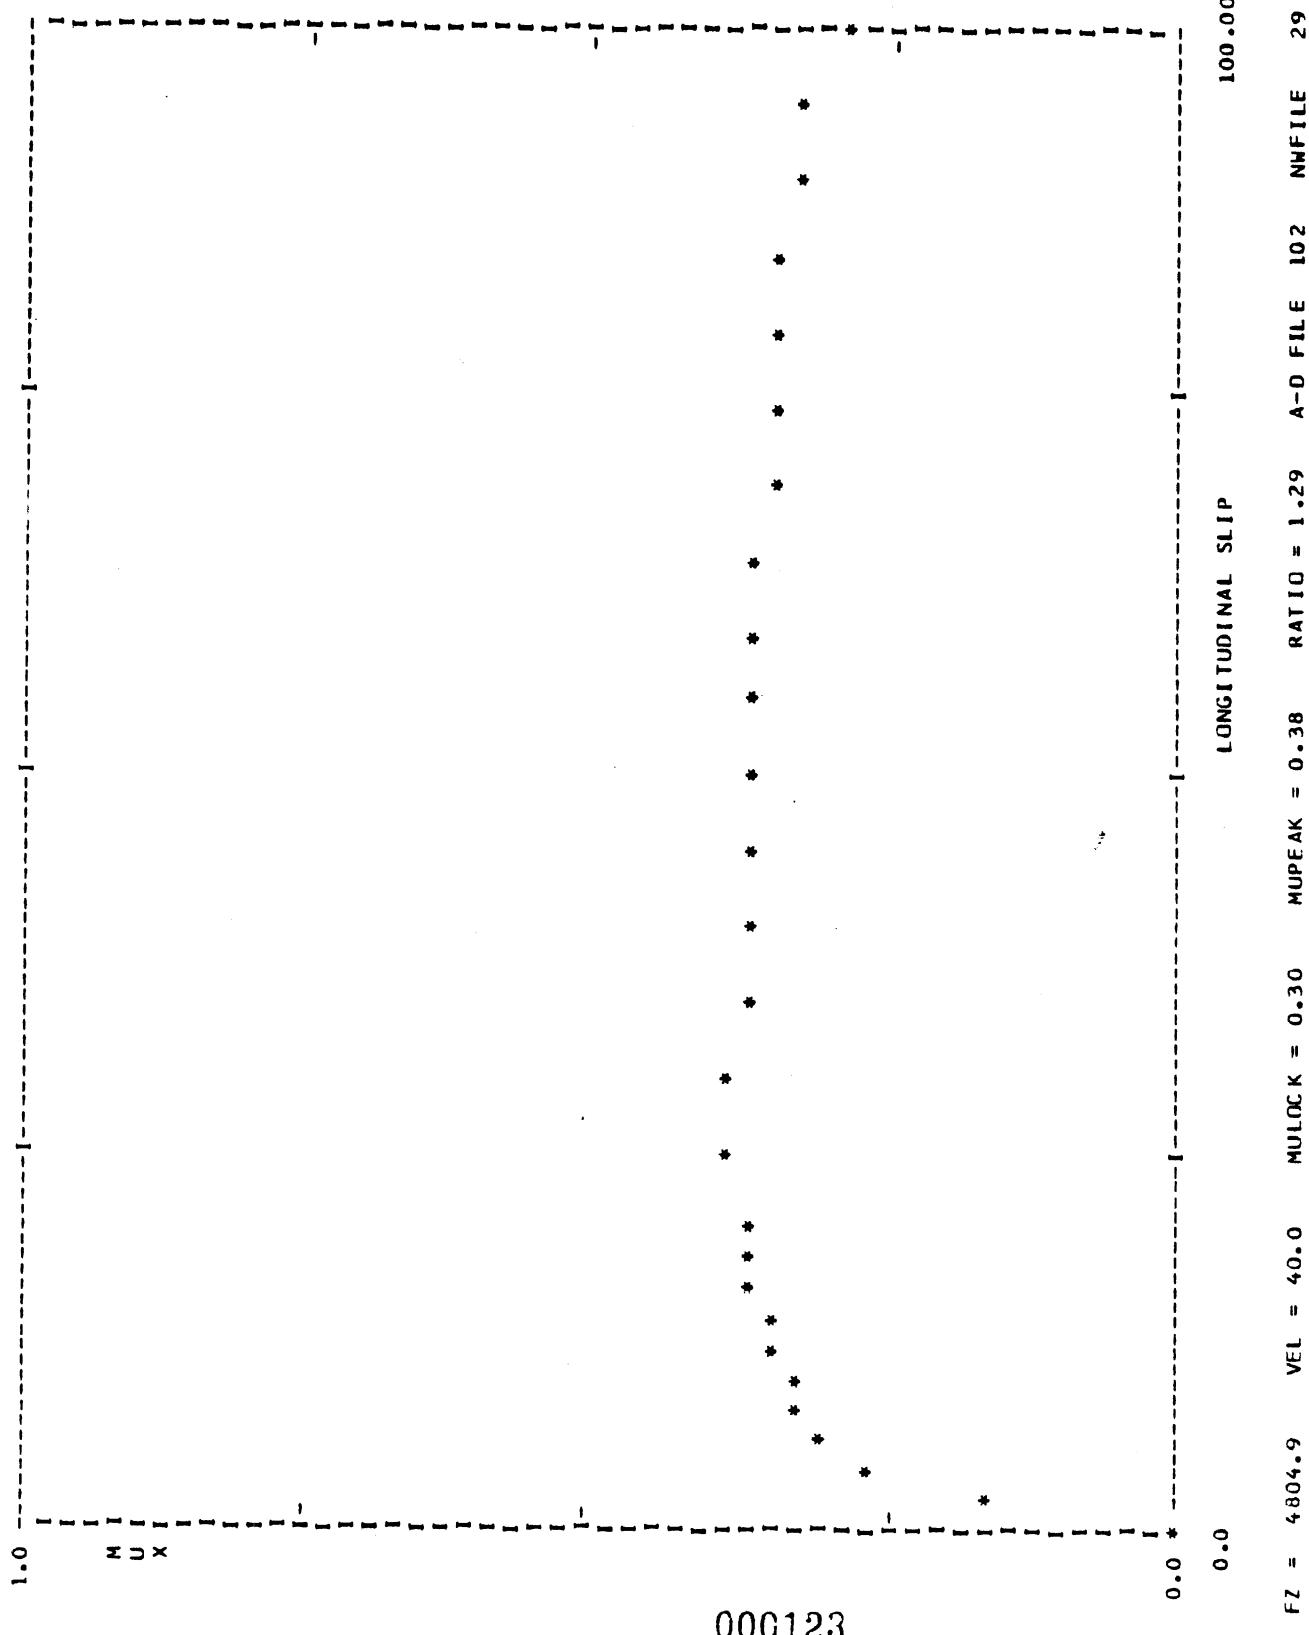

000123

	MU-PEAK	SLIPPEAK	MU-LOCK
0.402	0.200	0.291	
0.364	0.300	0.267	
0.476	0.200	0.316	
0.382	0.450	0.296	
0.328	0.250	0.288	


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.390 0.055
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.292 0.017

000124

AVERAGE OF FILE 103 FOR 4 RECORDS.		TIRE BR2		WET CONCRETE (TRC)	
SL IP	MUX	TORQUE	FX		
0.0	0.00	0.0	0.0	0.0	
0.02	0.16	17725.8	732.0		
0.04	0.24	26327.6	1096.8		
0.06	0.26	31233.3	1220.5		
0.08	0.28	34522.2	1288.9		
0.10	0.29	37096.8	1334.3		
0.12	0.30	39273.4	1367.1		
0.14	0.30	41025.2	1387.9		
0.16	0.31	42676.2	1405.6		
0.18	0.31	44193.5	1417.5	TQAV = 26812.5	LOAD = 4759.5 VEL = 50.0 MPH.
0.20	0.32	45509.2	1429.2		
0.25	0.33	48338.0	1472.3	HUPEAK = 0.34	HULOCK = 0.26 RATIO = 1.31
0.30	0.33	50848.4	1515.2		
0.35	0.34	53209.7	1557.6		
0.40	0.34	55473.8	1579.7		
0.45	0.34	57462.7	1591.8		
0.50	0.34	59149.1	1592.0		
0.55	0.34	60768.6	1587.0		
0.60	0.33	62193.5	1569.4		
0.65	0.33	63616.0	1545.2		
0.70	0.32	64850.4	1510.0		
0.75	0.31	63728.5	1476.1		
0.80	0.31	58705.9	1441.5		
0.85	0.30	50200.0	1405.4		
0.90	0.29	42676.6	1350.5		
0.95	0.28	35877.4	1303.4		
1.00	0.26	26812.5	1200.7		

000125

TIRE BR2 WET CONCRETE (TRC)

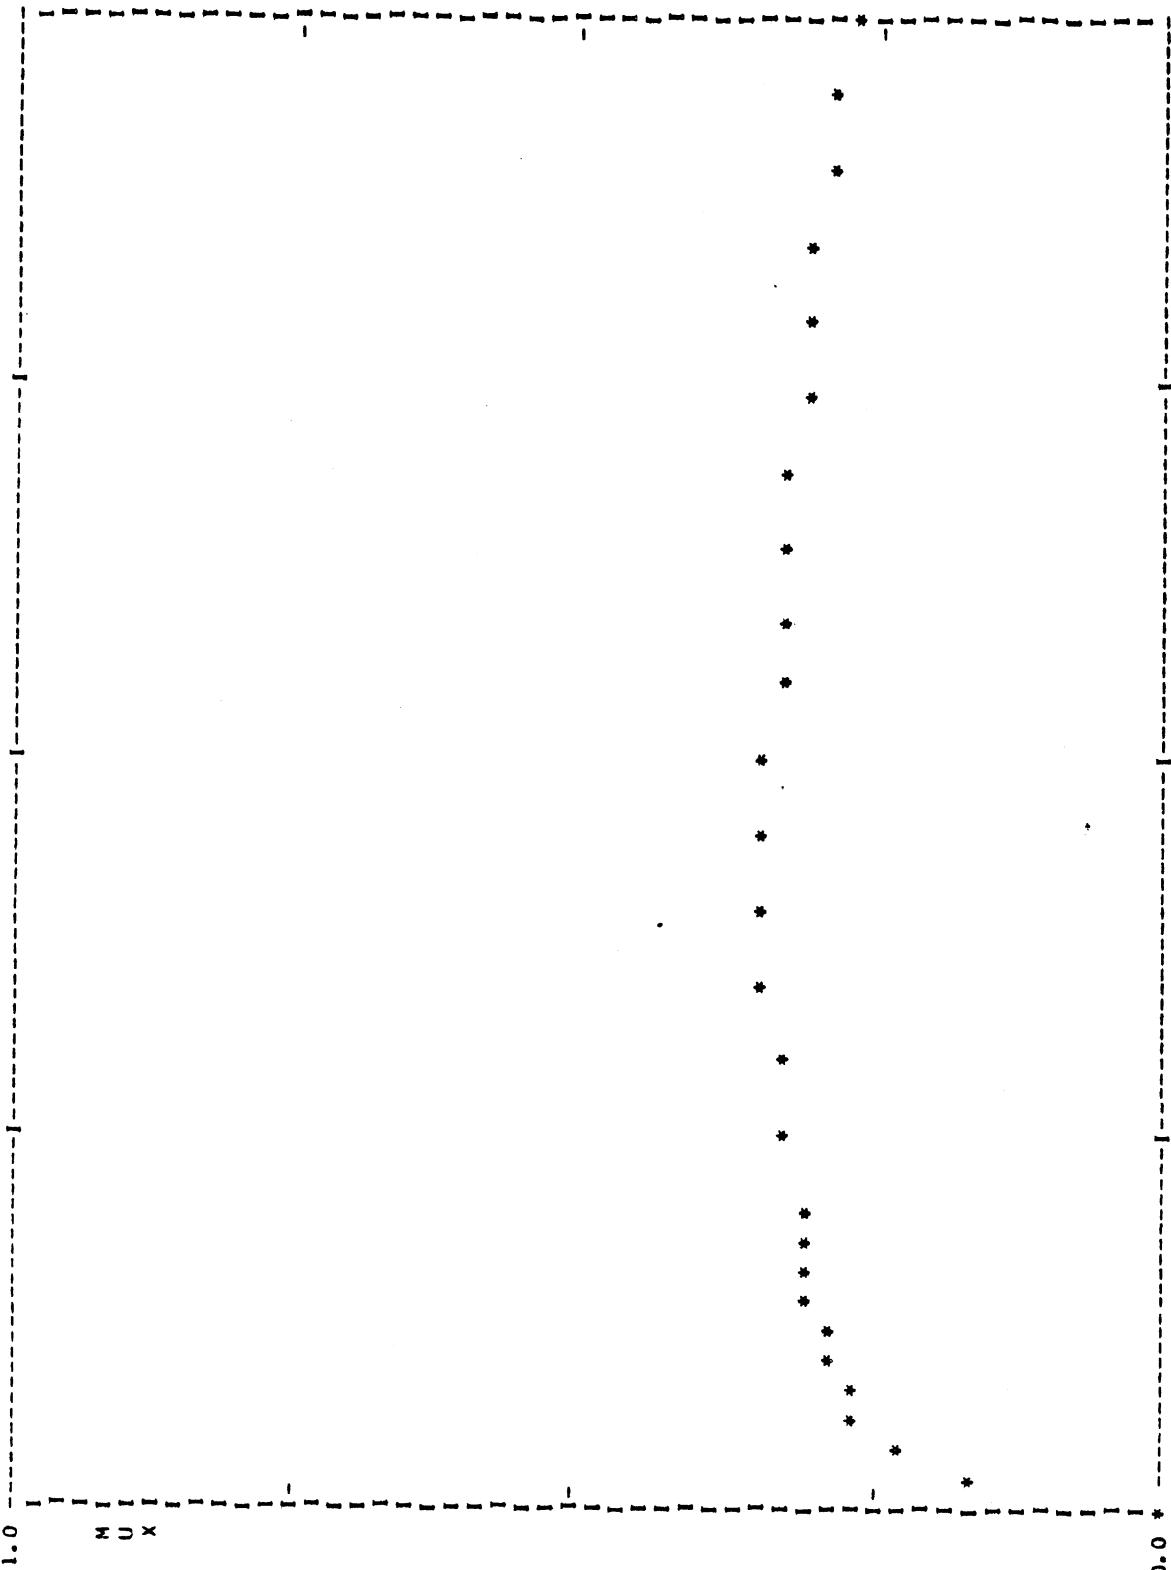

000126

FZ = 4759.5 VEL = 50.0 MULOCK = 0.26 MUPEAK = 0.34 RATIO = 1.31 A-D FILE 103 NMFILE 30 SAMPLE 132

MU-PEAK	SLIP@PEAK	MU-LOCK
0.336	0.350	0.277
0.378	0.160	0.254
0.327	0.350	0.236
0.340	0.600	0.253

MU-PEAK AVERAGE VALUE AND STD. DEVIATION :

MU-LOCK AVERAGE VALUE AND STD. DEVIATION :

0.345

0.022

0.255

0.017

000127

TEST SAMPLE 133 **

** A-D FILE 110


NEW FILE 31

AVERAGE OF FILE 110 FOR 6 RECORDS.

SLIP MU X TORQUE F X

SLIP	MU X	TORQUE	F X
0.0	0.00	0.0	0.0
0.02	0.33	39768.5	1497.8
0.04	0.51	57837.8	2375.5
0.06	0.68	74101.7	3139.5
0.08	0.73	81411.3	3397.2
0.10	0.76	85046.8	3507.2
0.12	0.78	87277.9	3579.6
0.14	0.79	88926.5	3612.6
0.16	0.80	90502.4	3651.1
0.18	0.81	91887.8	3668.1
0.20	0.81	93184.4	3658.8
0.25	0.80	95953.7	3599.2
0.30	0.78	98030.9	3518.5
0.35	0.76	99391.4	3432.7
0.40	0.74	100267.2	3344.2
0.45	0.72	100806.4	3256.0
0.50	0.71	101249.1	3172.0
0.55	0.69	101599.7	3088.8
0.60	0.67	101892.9	3005.3
0.65	0.65	101910.7	2922.8
0.70	0.63	100231.3	2848.7
0.75	0.62	95690.4	2782.1
0.80	0.60	86861.6	2723.8
0.85	0.59	79210.4	2655.5
0.90	0.57	73502.9	2573.7
0.95	0.55	67157.4	2511.4
1.00	0.50	56833.3	2325.0

000128

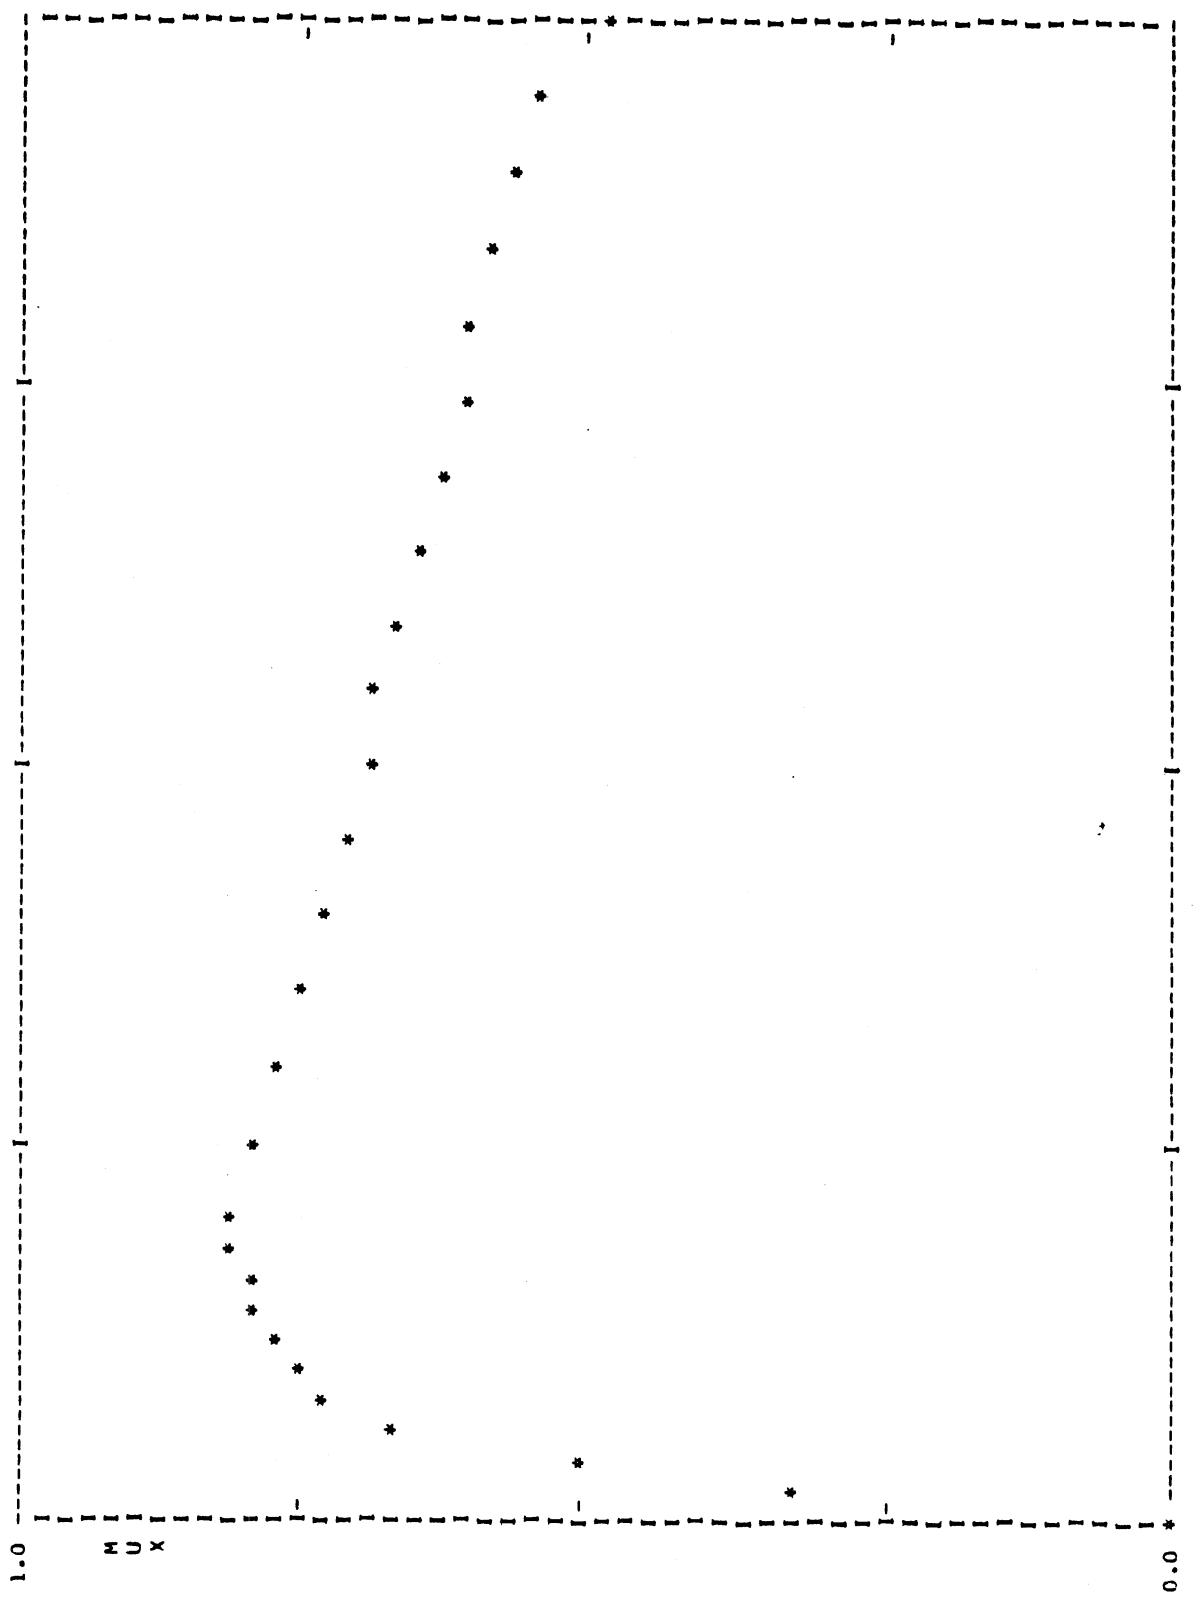

000129

FZ = 4738.0 VEL = 40.0 MUPEAK = 0.50 MULOCK = 0.81 RATIO = 1.62 A-D FILE 110 NWFILE 31 SAMPLE 133

MU-PEAK	SL. IP @PEAK	MU-LOCK
0.818	0.180	0.506
0.802	0.200	0.538
0.790	0.200	0.465
0.816	0.180	0.452
0.810	0.120	0.495
0.807	0.180	0.517


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.807 0.010
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.496 0.032

000130

AV ERAGE OF FILE 111		FOR 5 RECORDS.		TIRE RR2	WET ASPHALT (TRC)
SLIP	MUX	TORQUE	FX		
0.0	0.00	0.0	0.0		
0.02	0.29	42569.1	1348.9		
0.04	0.49	61929.1	2298.2		
0.06	0.62	75588.3	2914.2		
0.08	0.68	82367.8	3166.6		
0.10	0.71	86762.4	3320.5		
0.12	0.73	90109.1	3399.5		
0.14	0.74	91926.9	3426.3		
0.16	0.75	93635.7	3427.9		
0.18	0.74	94989.4	3404.2	TQAV = 57074.	
0.20	0.74	96000.1	3376.6		
0.25	0.73	97814.1	3316.2	MUPEAK = 0.75	
0.30	0.71	99617.1	3259.1		
0.35	0.69	101231.9	3197.5		
0.40	0.67	102434.6	3121.6		
0.45	0.65	103292.9	3036.1		
0.50	0.62	104020.7	2946.4		
0.55	0.61	104773.6	2858.0		
0.60	0.59	105492.1	2772.5		
0.65	0.57	106108.3	2690.3		
0.70	0.55	105817.4	2610.4		
0.75	0.54	102933.2	2539.7		
0.80	0.53	92947.7	2488.2		
0.85	0.51	82987.1	2425.2		
0.90	0.50	76455.8	2341.1		
0.95	0.48	68552.8	2265.3		
1.00	0.44	57074.9	2050.2		

000131

TIRE RR2 WET ASPHALT (TRC)

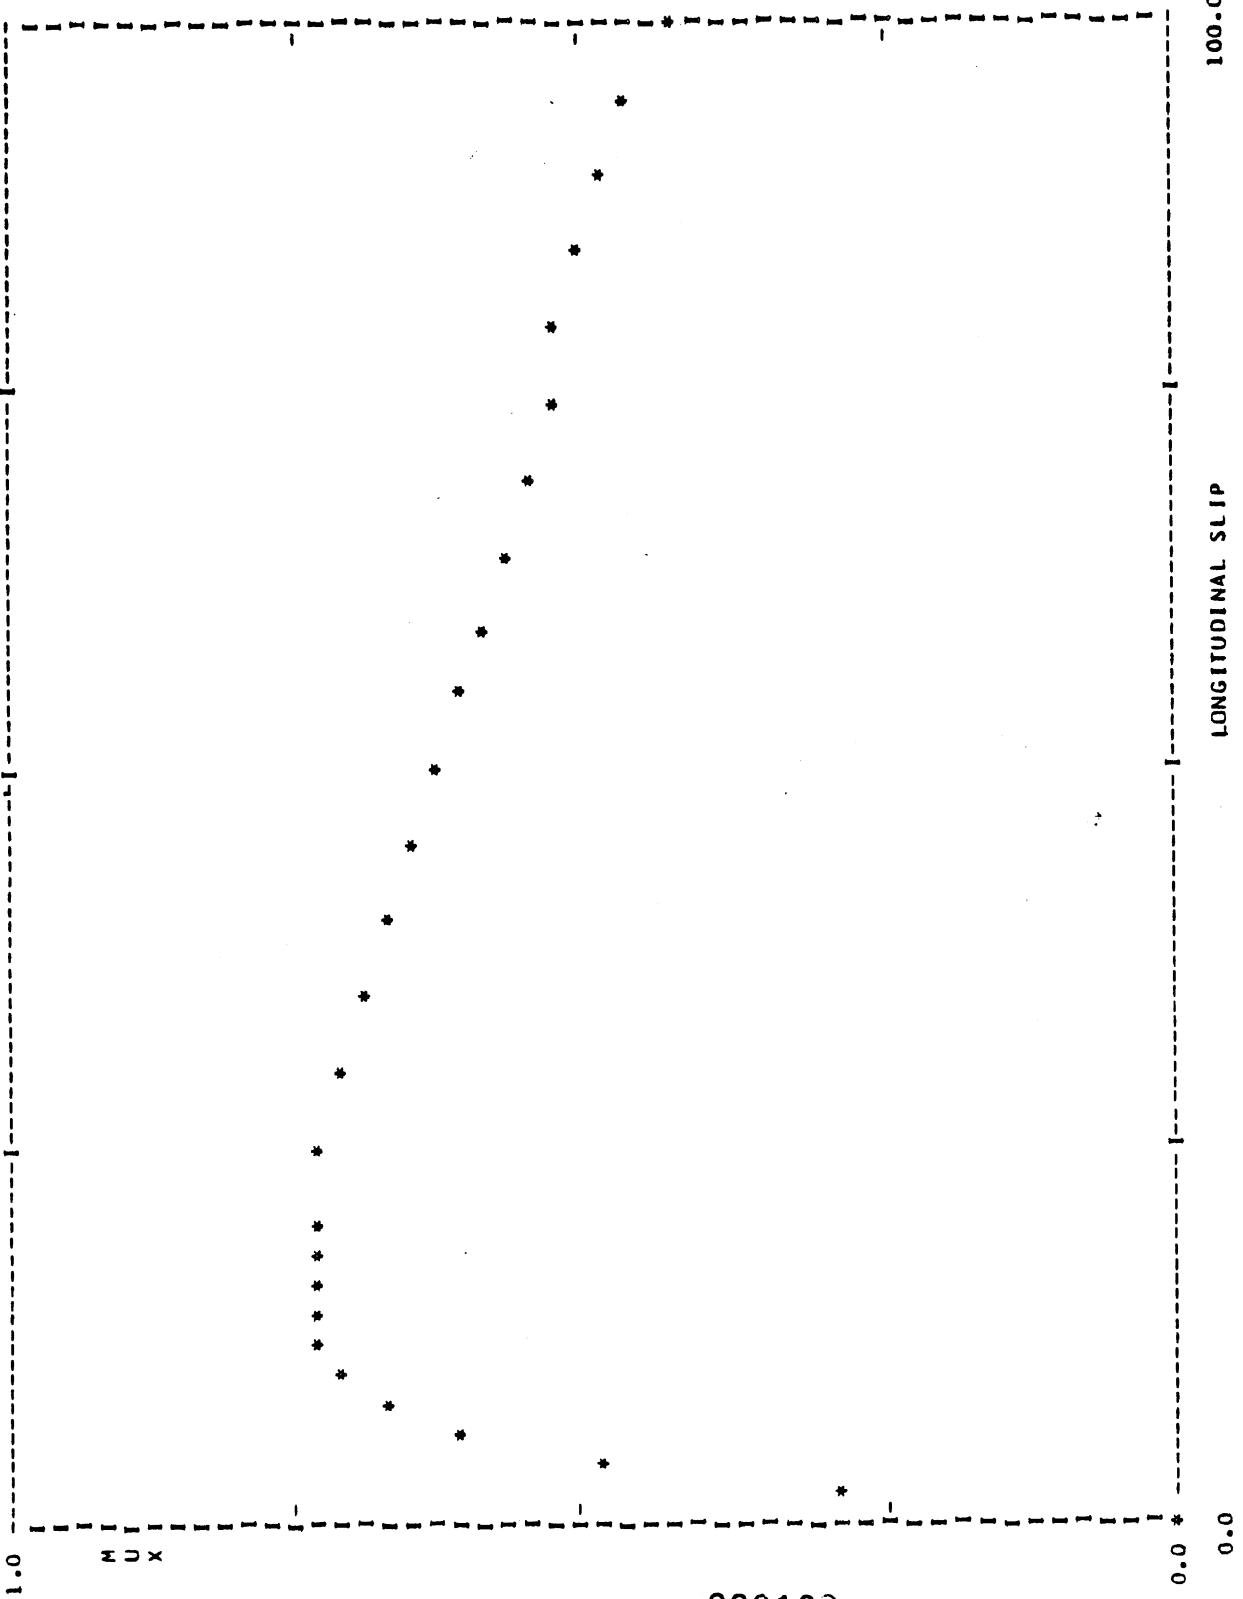

000132

F_L = 4727.3 V_{EL} = 50.0 MULOCK = 0.44 MUEAK = 0.75 RATIO = 1.71 A-D FILE L11 NWFILE 32 SAMPLE 134

MU-PEAK	SLIPPEAK	MU-LOCK
0.806	0.160	0.418
0.747	0.180	0.452
0.720	0.200	0.468
0.716	0.120	0.423
0.748	0.130	0.394

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.747 0.036
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.431 0.029

000133

TEST SAMPLE135 *6

NEW FILE 33


** A-D FILE 115

AVERAGE OF FILE 115 FOR 6 RECORDS.

TIRE RR2 WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.21	33118.2	968.9
0.04	0.29	41863.4	1369.9
0.06	0.34	47783.8	1608.9
0.08	0.37	52051.5	1746.5
0.10	0.38	54752.8	1804.2
0.12	0.39	56745.5	1825.5
0.14	0.39	58384.5	1837.3
0.16	0.40	59776.7	1841.0
0.18	0.40	61097.7	1846.7
0.20	0.40	62267.2	1856.0
0.25	0.41	64771.1	1877.4
0.30	0.42	67007.4	1889.8
0.35	0.42	69016.9	1892.5
0.40	0.42	70693.9	1882.9
0.45	0.41	72305.5	1857.9
0.50	0.40	73720.3	1827.0
0.55	0.39	75032.1	1793.8
0.60	0.38	76197.3	1759.7
0.65	0.38	77339.4	1722.3
0.70	0.36	77873.7	1678.3
0.75	0.35	75212.2	1636.6
0.80	0.35	68792.6	1603.9
0.85	0.34	60447.3	1570.8
0.90	0.33	55522.0	1514.3
0.95	0.32	48808.6	1458.9
1.00	0.29	39624.9	1312.5

000134

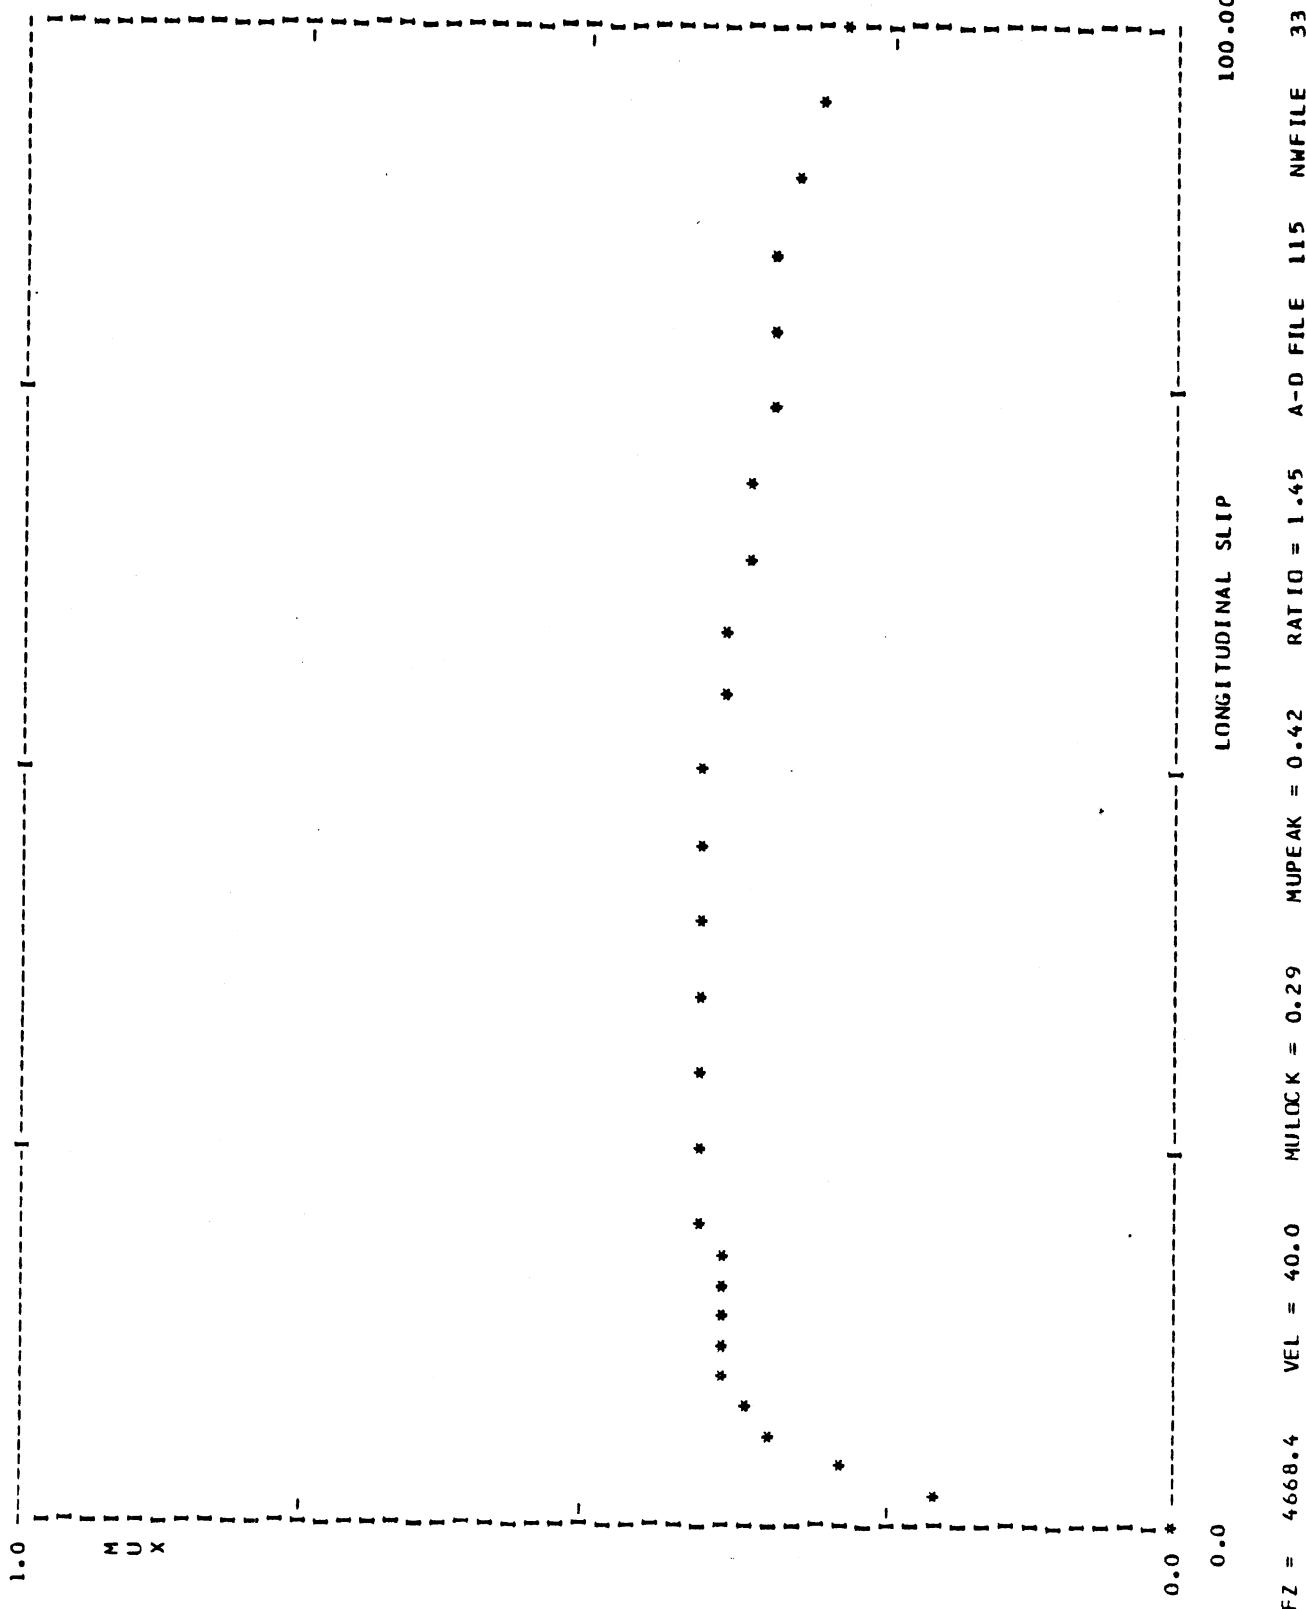

000135

FZ = 4668.4 VEL = 40.0 MULOCK = 0.29 MUPEAK = 0.42 RATIO = 1.45 A-D FILE 115 NWFILE 33 SAMPLE 135

MU-PEAK	SLIP@PEAK	MU-LOCK
0.424	0.250	0.306
0.408	0.400	0.238
0.448	0.300	0.302
0.467	0.400	0.290
0.352	0.250	0.252
0.399	0.300	0.306


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.416 0.040
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.282 0.030

000136

SLIP	MUX	TORQUE	FX	TIRE RR2	WET CONCRETE (TRC)
0.0	0.00	0.0	0.0	0.0	
0.02	0.19	32286.3	863.7		
0.04	0.27	41193.8	1263.4		
0.06	0.30	46236.6	1402.4		
0.08	0.32	49598.4	1484.3		
0.10	0.34	52028.3	1550.4		
0.12	0.35	54077.5	1607.5		
0.14	0.36	56165.5	1650.4		
0.16	0.36	58019.5	1678.1		
0.18	0.36	59701.8	1685.8	TQAV = 366666.6	LOAD = 4700.8 VEL = 50.0 MPH.
0.20	0.36	61033.3	1683.0	MUPEAK = 0.37	MULOCK = 0.24 RATIO = 1.49
0.25	0.37	63779.7	1675.0		
0.30	0.37	65993.5	1664.4		
0.35	0.36	67795.4	1655.7		
0.40	0.36	69456.8	1656.6		
0.45	0.36	71075.9	1656.8		
0.50	0.36	72633.6	1644.5		
0.55	0.36	74104.3	1617.0		
0.60	0.35	75567.9	1587.6		
0.65	0.34	76970.3	1552.5		
0.70	0.33	78214.1	1508.6		
0.75	0.32	77840.3	1454.7		
0.80	0.31	71742.6	1407.2		
0.85	0.30	61918.8	1369.8		
0.90	0.29	54607.5	1308.0		
0.95	0.27	46263.7	1247.4		
1.00	0.24	366666.6	1118.0		

000137

TIRE RR2 WET CONCRETE (TRC)

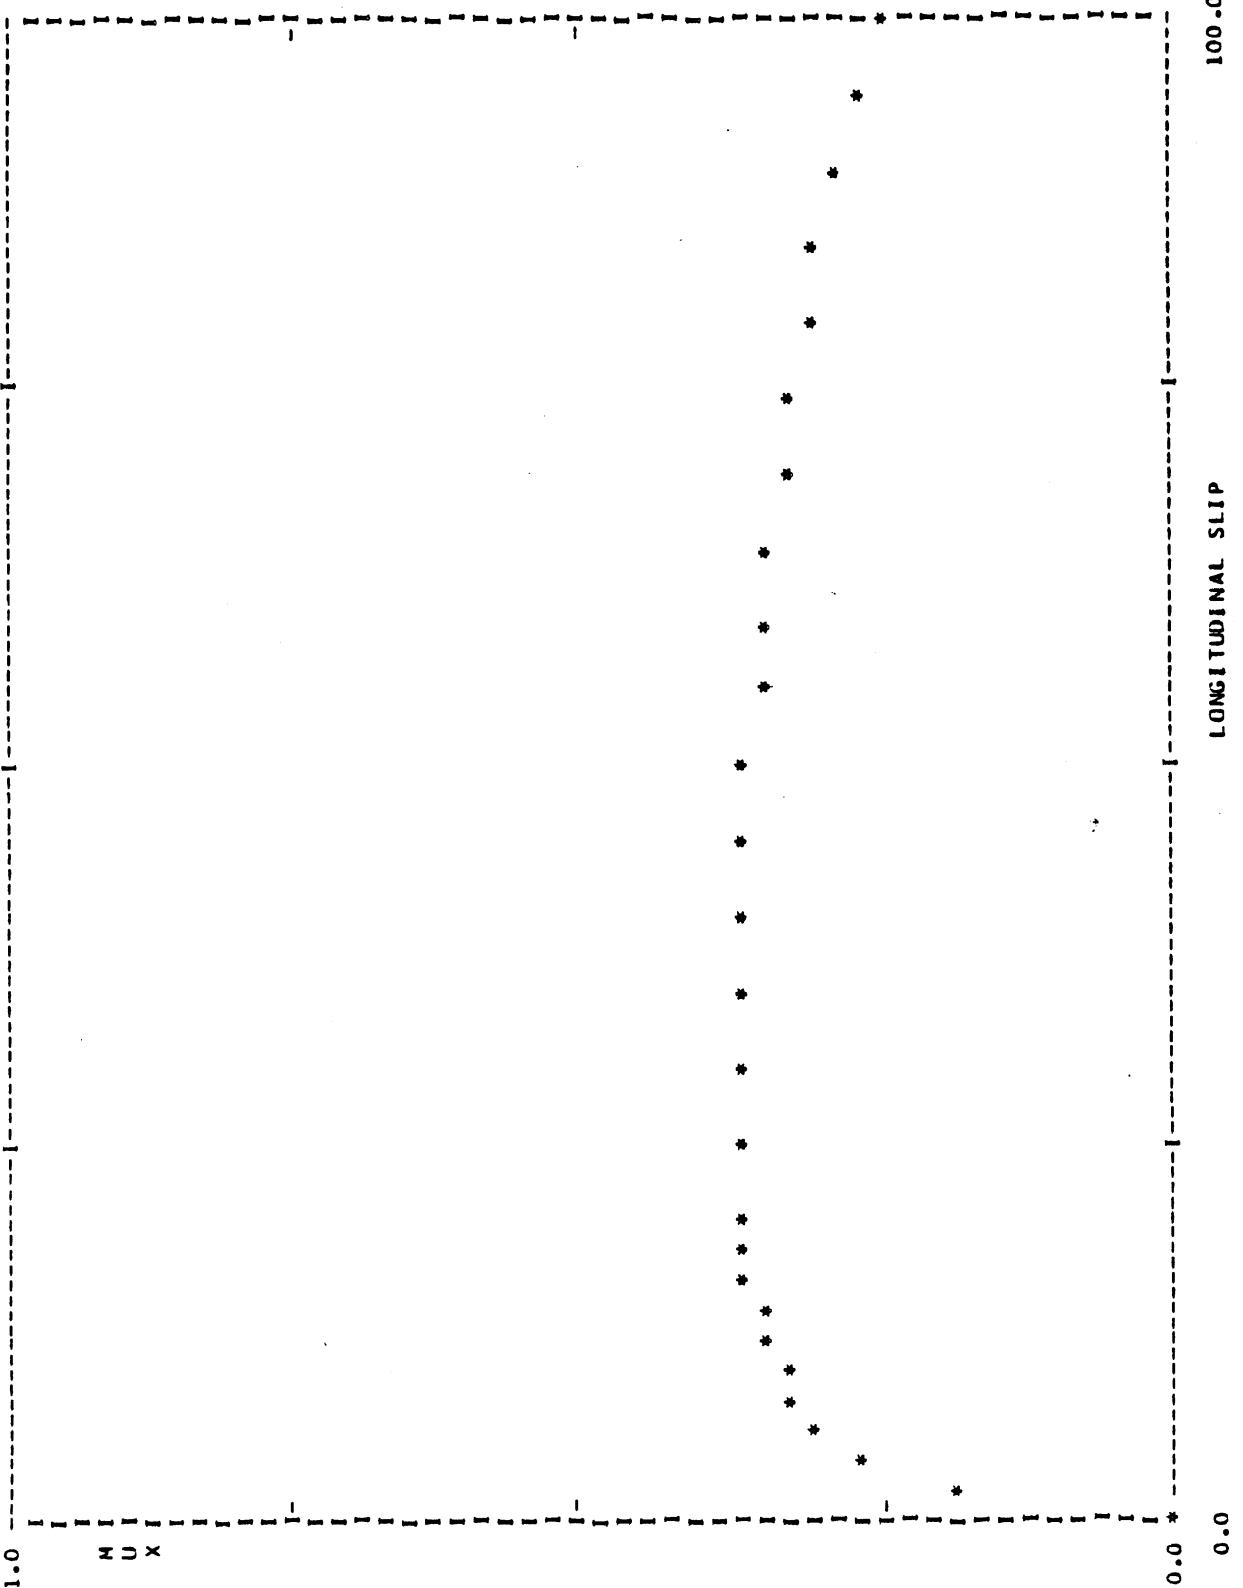

000138

FZ = 4700.8 VFL = 50.0 MULOCK = 0.24 MUPEAK = 0.37 RATIO = 1.49 A-D FILE 116 NMFILE 34 SAMPLE 136

MU-PEAK	SLIPPERY	MU-LOCK
0.360	0.140	0.222
0.375	0.160	0.222
0.409	0.200	0.235
0.340	0.250	0.244
0.377	0.140	0.254
0.367	0.300	0.259

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.371 0.023
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.239 0.016

000139

41000

** A-D FILE 125


NEW FILE 35

TEST SAMPLE 137 **

AVERAGE OF FILE 125 FOR 5 RECORDS.

TIRE C1 WET ASPHALT (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.21	23613.8	1047.0
0.04	0.35	37880.6	1721.3
0.06	0.45	47562.9	2211.7
0.08	0.54	56217.6	2649.4
0.10	0.60	64118.6	2967.1
0.12	0.64	68168.3	3134.7
0.14	0.69	73663.1	3374.1
0.16	0.71	76318.6	3458.2
0.18	0.73	78892.3	3543.1
0.20	0.74	80948.5	3567.6
0.25	0.73	83803.9	3527.2
0.30	0.72	85742.3	3468.2
0.35	0.71	87248.9	3411.2
0.40	0.70	88384.1	3353.8
0.45	0.69	89334.6	3292.3
0.50	0.68	90249.9	3225.2
0.55	0.67	91144.8	3154.9
0.60	0.65	91956.1	3082.6
0.65	0.64	92296.3	3012.9
0.70	0.62	90851.8	2948.9
0.75	0.61	86501.4	2888.4
0.80	0.60	80146.9	2828.1
0.85	0.59	74030.3	2764.3
0.90	0.57	68251.9	2696.4
0.95	0.55	62557.0	2626.8
1.00	0.51	53574.9	2459.4

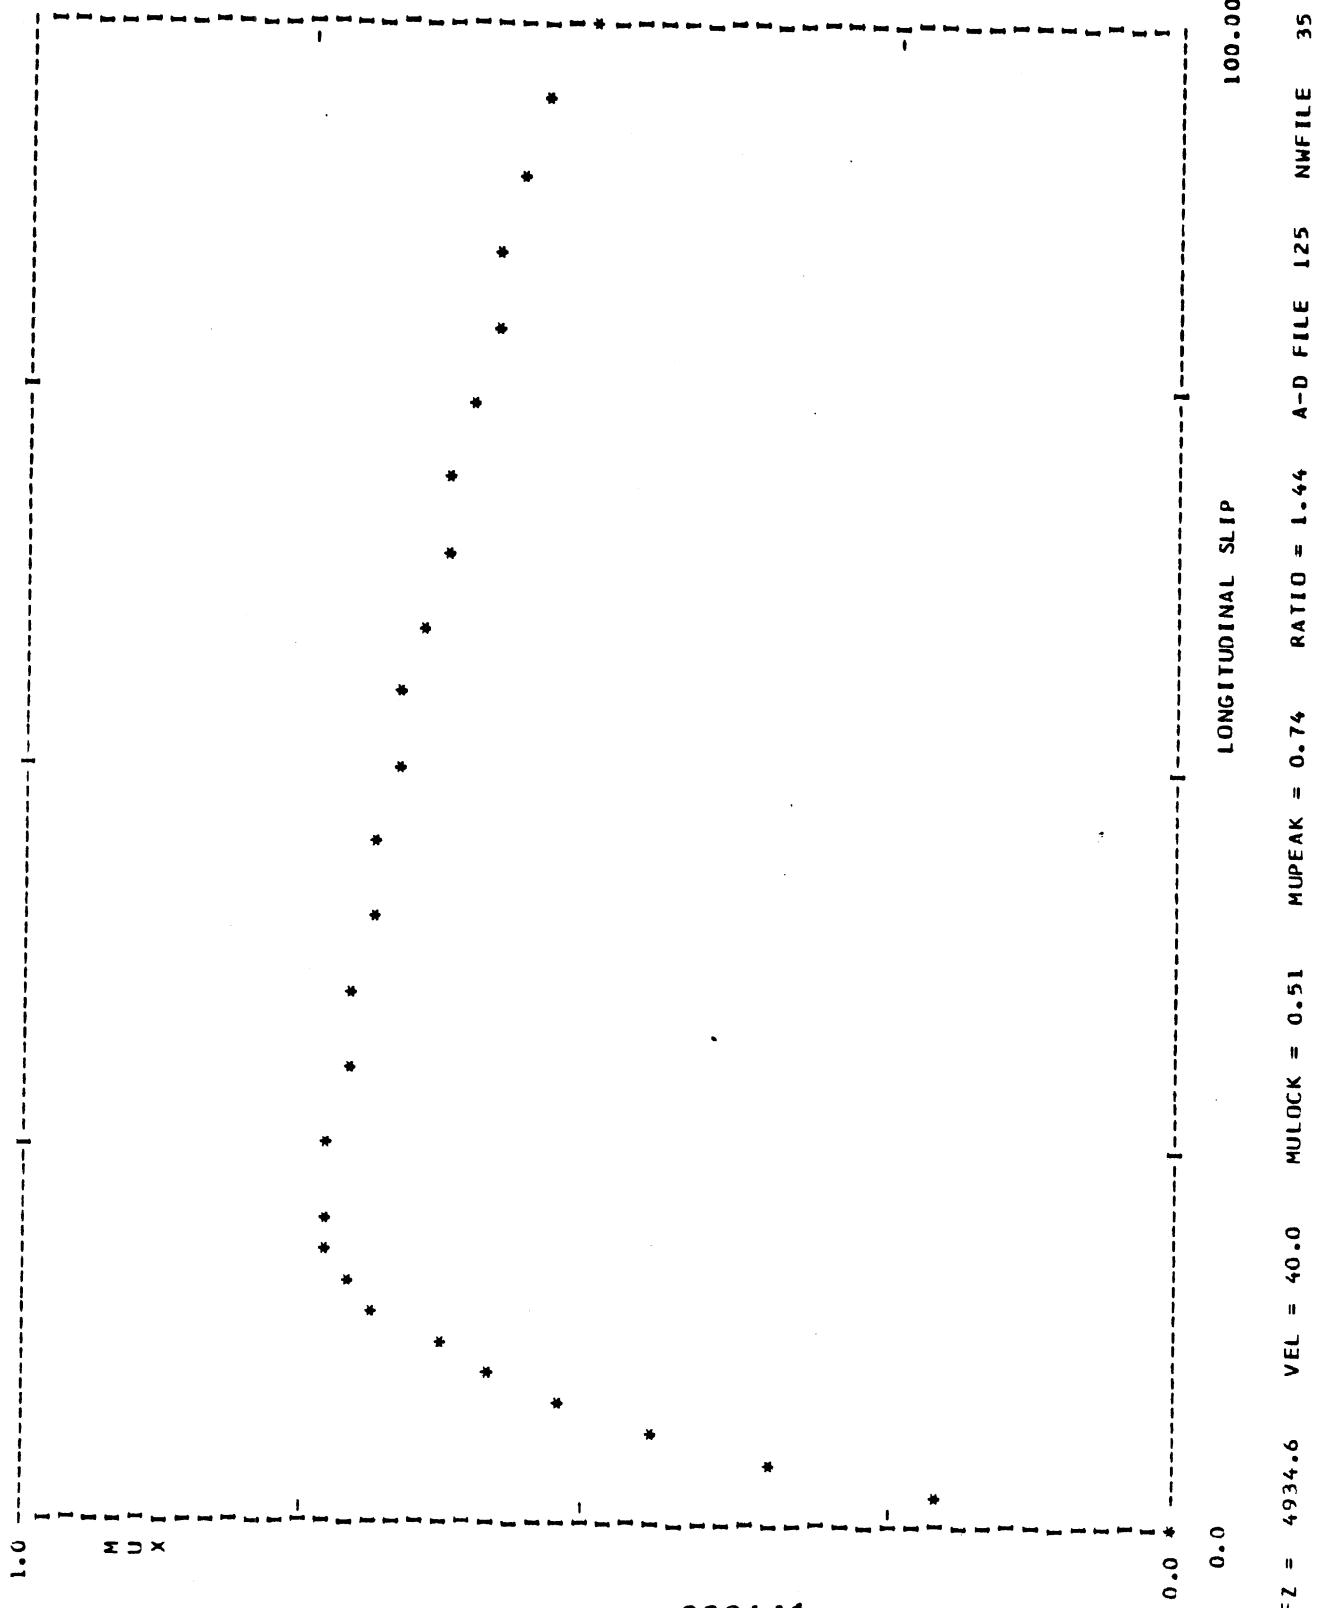

000141

MU-PEAK	SLIPAPEAK	MU-LCCK
0.748	0.200	0.481
0.710	0.200	0.517
0.724	0.180	0.536
0.752	0.200	0.445
0.734	0.180	0.555


MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.734	0.018
MU-LCCK AVERAGE VALUE AND STD. DEVIATION :	0.507	0.044

000142

SLIP	AVERAGE OF FILE 126 FOR 4 RECORDS.	TIRE CL	WET ASPHALT (TRC)
	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.19	21556.5	940.5
0.04	0.31	33546.0	1510.0
0.06	0.44	47272.0	2156.0
0.08	0.50	54892.2	2516.8
0.10	0.55	60445.7	2736.3
0.12	0.58	64178.5	2846.2
0.14	0.60	67395.6	2925.0
0.16	0.61	69248.7	2961.3
0.18	0.61	70876.4	2980.8
0.20	0.61	72309.2	2971.6
0.25	0.61	75236.2	2948.9
0.30	0.61	77197.5	2930.1
0.35	0.60	78536.3	2892.5
0.40	0.60	79092.4	2854.6
0.45	0.59	79092.6	2839.2
0.50	0.58	78892.7	2807.6
0.55	0.57	79269.7	2747.3
0.60	0.56	79730.7	2687.5
0.65	0.55	80257.9	2628.5
0.70	0.55	79876.8	2581.7
0.75	0.54	78001.4	2541.7
0.80	0.54	73972.0	2509.0
0.85	0.53	68155.9	2486.1
0.90	0.53	63273.6	2465.4
0.95	0.52	58761.4	2457.0
1.00	0.46	49906.2	2276.2

000143

TIRE CI WET ASPHALT (TRC)

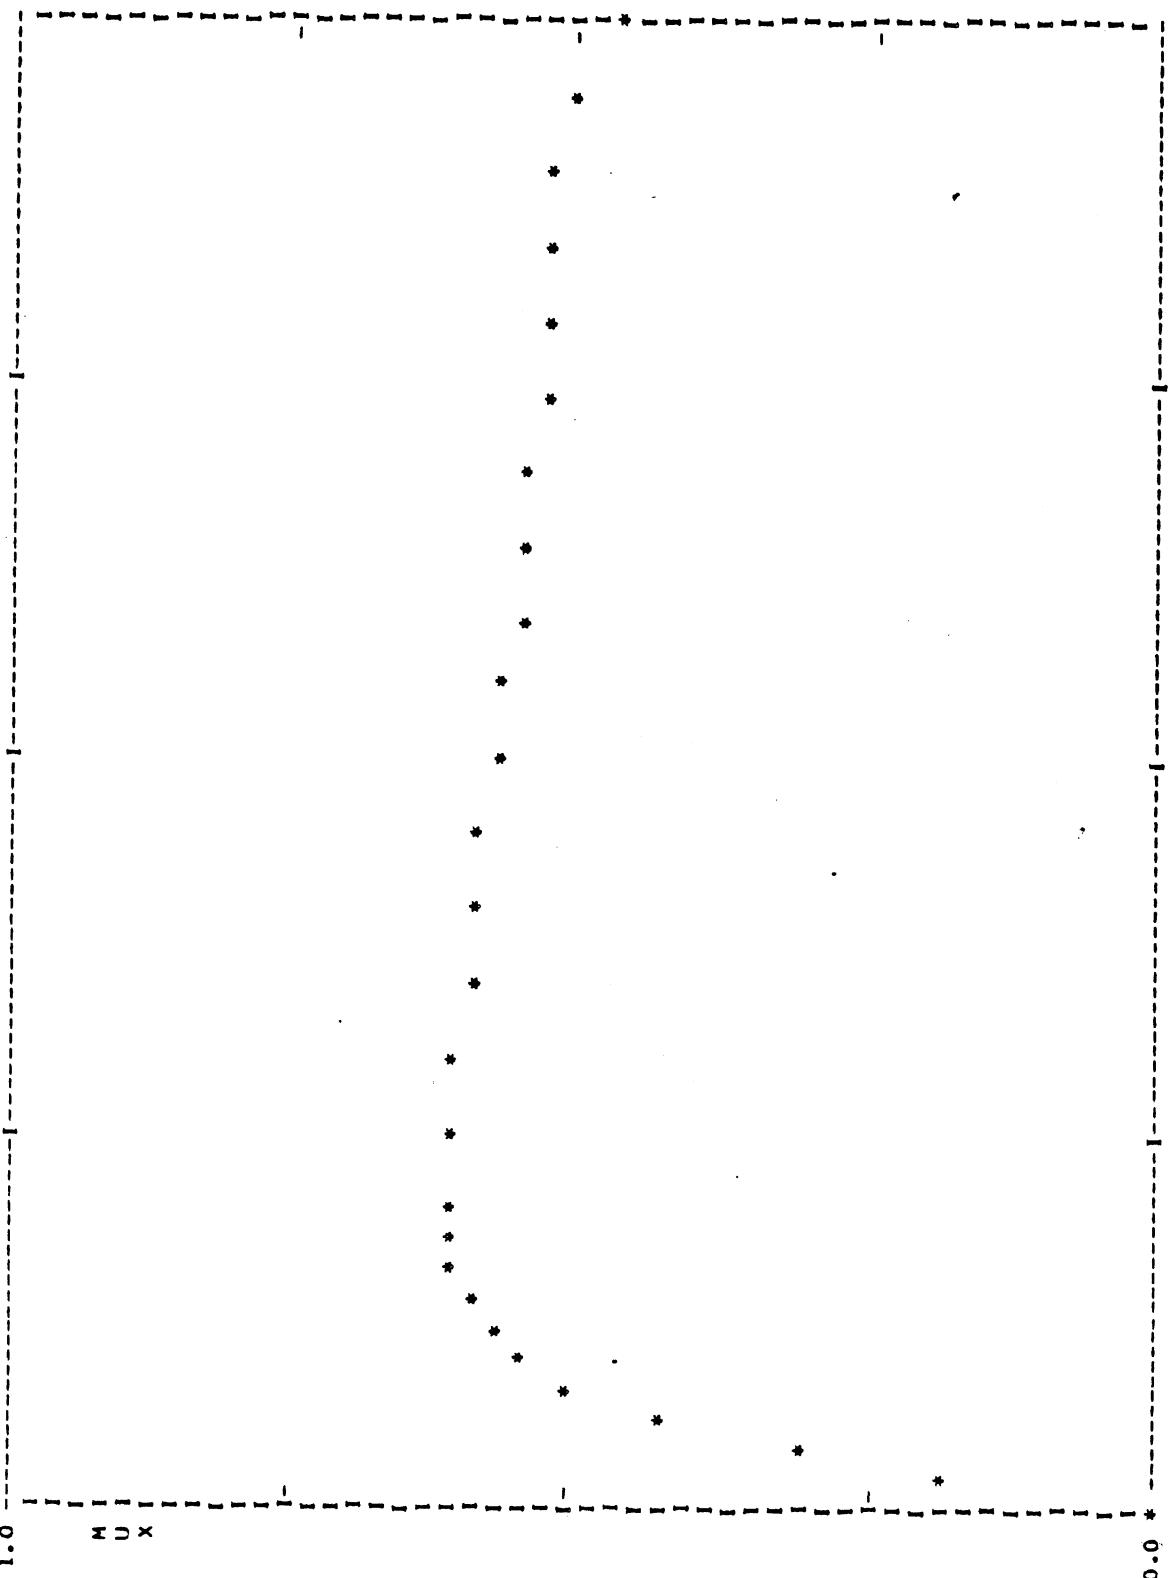

000144

FZ = 4987.8 VEL = 50.0 MULOCK = 0.46 MUPEAK = 0.61 RATIO = 1.32 A-D FILE 126 NWFILE 36 SAMPLE 138

MU-PEAK	SL. IP @ PEAK	MU-L CCK
0.586	0.450	0.519
0.607	0.300	0.450
0.622	0.250	0.454
0.667	0.160	0.415

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.621 0.034
MU-LLOCK AVERAGE VALUE AND STD. DEVIATION : 0.459 0.043

000145

TEST SAMPLE 139 **

NEW FILE 37


** A-D FILE 130

AVERAGE OF FILE 130 FOR 6 RECORDS.

TIRE C1
WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.15	15328.1	649.6
0.04	0.23	23839.8	1039.9
0.06	0.30	30586.2	1299.4
0.08	0.33	35181.7	1477.0
0.10	0.36	38781.5	1618.8
0.12	0.38	41420.7	1680.6
0.14	0.39	43370.8	1718.1
0.16	0.39	45014.4	1739.9
0.18	0.39	46397.6	1744.9
0.20	0.40	47593.1	1746.8
0.25	0.40	50095.4	1768.0
0.30	0.41	52696.1	1774.8
0.35	0.41	54748.6	1775.0
0.40	0.41	56526.8	1773.5
0.45	0.41	58082.3	1760.0
0.50	0.40	59404.7	1730.0
0.55	0.39	60565.5	1696.4
0.60	0.38	61631.8	1660.3
0.65	0.38	62668.8	1617.3
0.70	0.36	62730.9	1567.4
0.75	0.35	59932.7	1520.3
0.80	0.34	54327.5	1469.6
0.85	0.33	47298.9	1411.7
0.90	0.31	40894.5	1341.4
0.95	0.30	34829.6	1277.1
1.00	0.25	24916.7	1094.5

000146

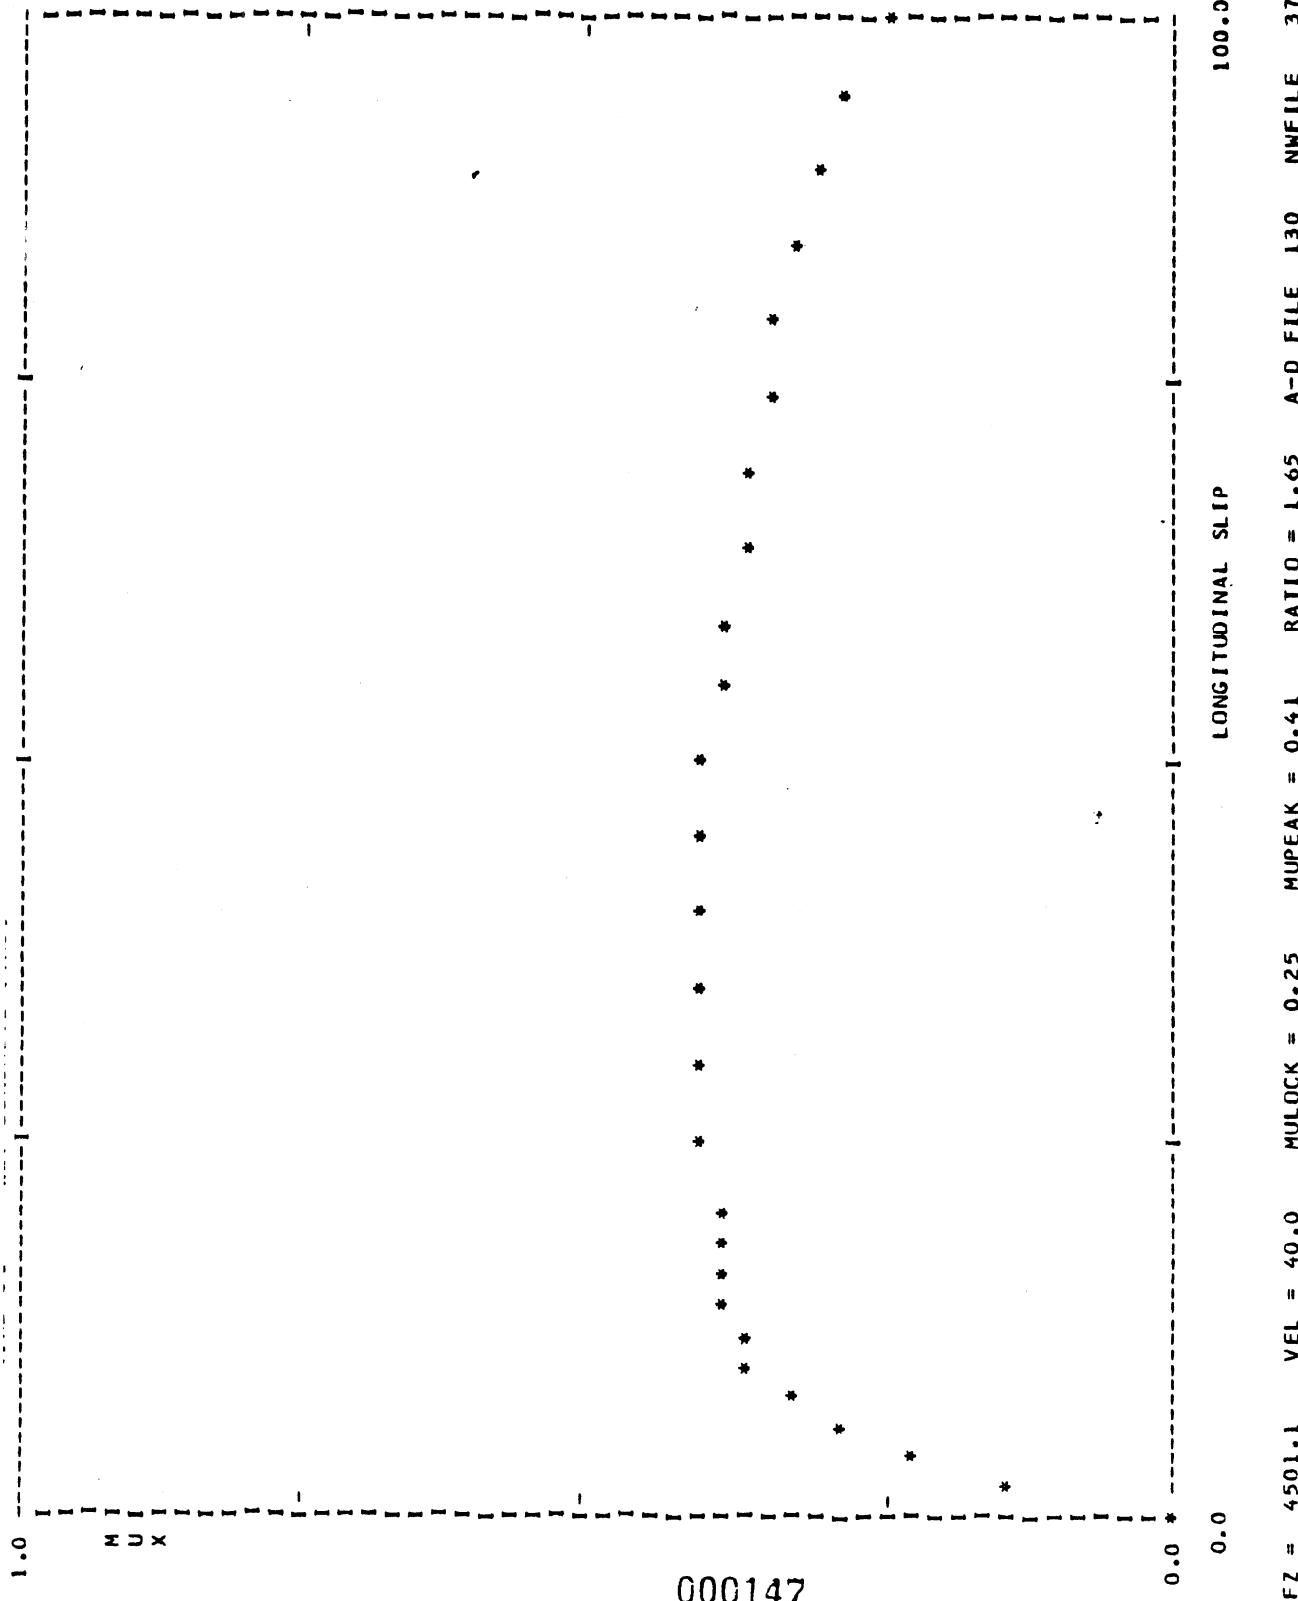

FZ = 4501.1 VEL = 40.0 MULOCK = 0.25 MUPEAK = 0.41 RATIO = 1.65 A-D FILE 130 NWFILE 37 SAMPLE 139


MU-PEAK	SLIP @PFAK	MU-LOCK
0.449	0.300	0.221
0.367	0.500	0.244
0.459	0.400	0.291
0.466	0.300	0.271
0.365	0.200	0.197
0.385	0.450	0.242

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.415 0.048
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.244 0.034

000148

SLIP	AVERAGE OF FILE 131 FOR 6 RECORDS.			TIRE CL			WET CONCRETE (TRC)				
	MUX	TORQUE	FX	MUX	TORQUE	FX	MUX	TORQUE	FX		
0.0	0.00	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0		
0.02	0.18	19198.4	768.5	0.04	24649.8	990.1	0.06	28346.0	1088.8		
0.08	0.29	31417.1	1189.5	0.10	35180.1	1316.1	0.12	37514.7	1356.1		
0.14	0.32	39163.2	1358.6	0.16	40480.4	1364.2	0.18	41715.5	1372.1		
0.20	0.33	42965.4	1382.6	0.25	0.34	45774.6	1407.3	0.30	0.34	48487.9	1428.5
0.35	0.35	50787.8	1449.9	0.40	0.35	52673.8	1454.8	0.45	0.35	54451.3	1453.1
0.50	0.35	55927.0	1443.0	0.55	0.35	57286.3	1424.4	0.60	0.34	58542.7	1390.1
0.65	0.33	59733.6	1351.6	0.70	0.32	60735.1	1301.6	0.75	0.31	59574.3	1248.3
0.80	0.29	53599.6	1197.7	0.85	0.28	45321.6	1151.8	0.90	0.27	38250.2	1096.7
0.95	0.25	31552.8	1035.5	1.00	0.20	20333.3	839.5				

000149

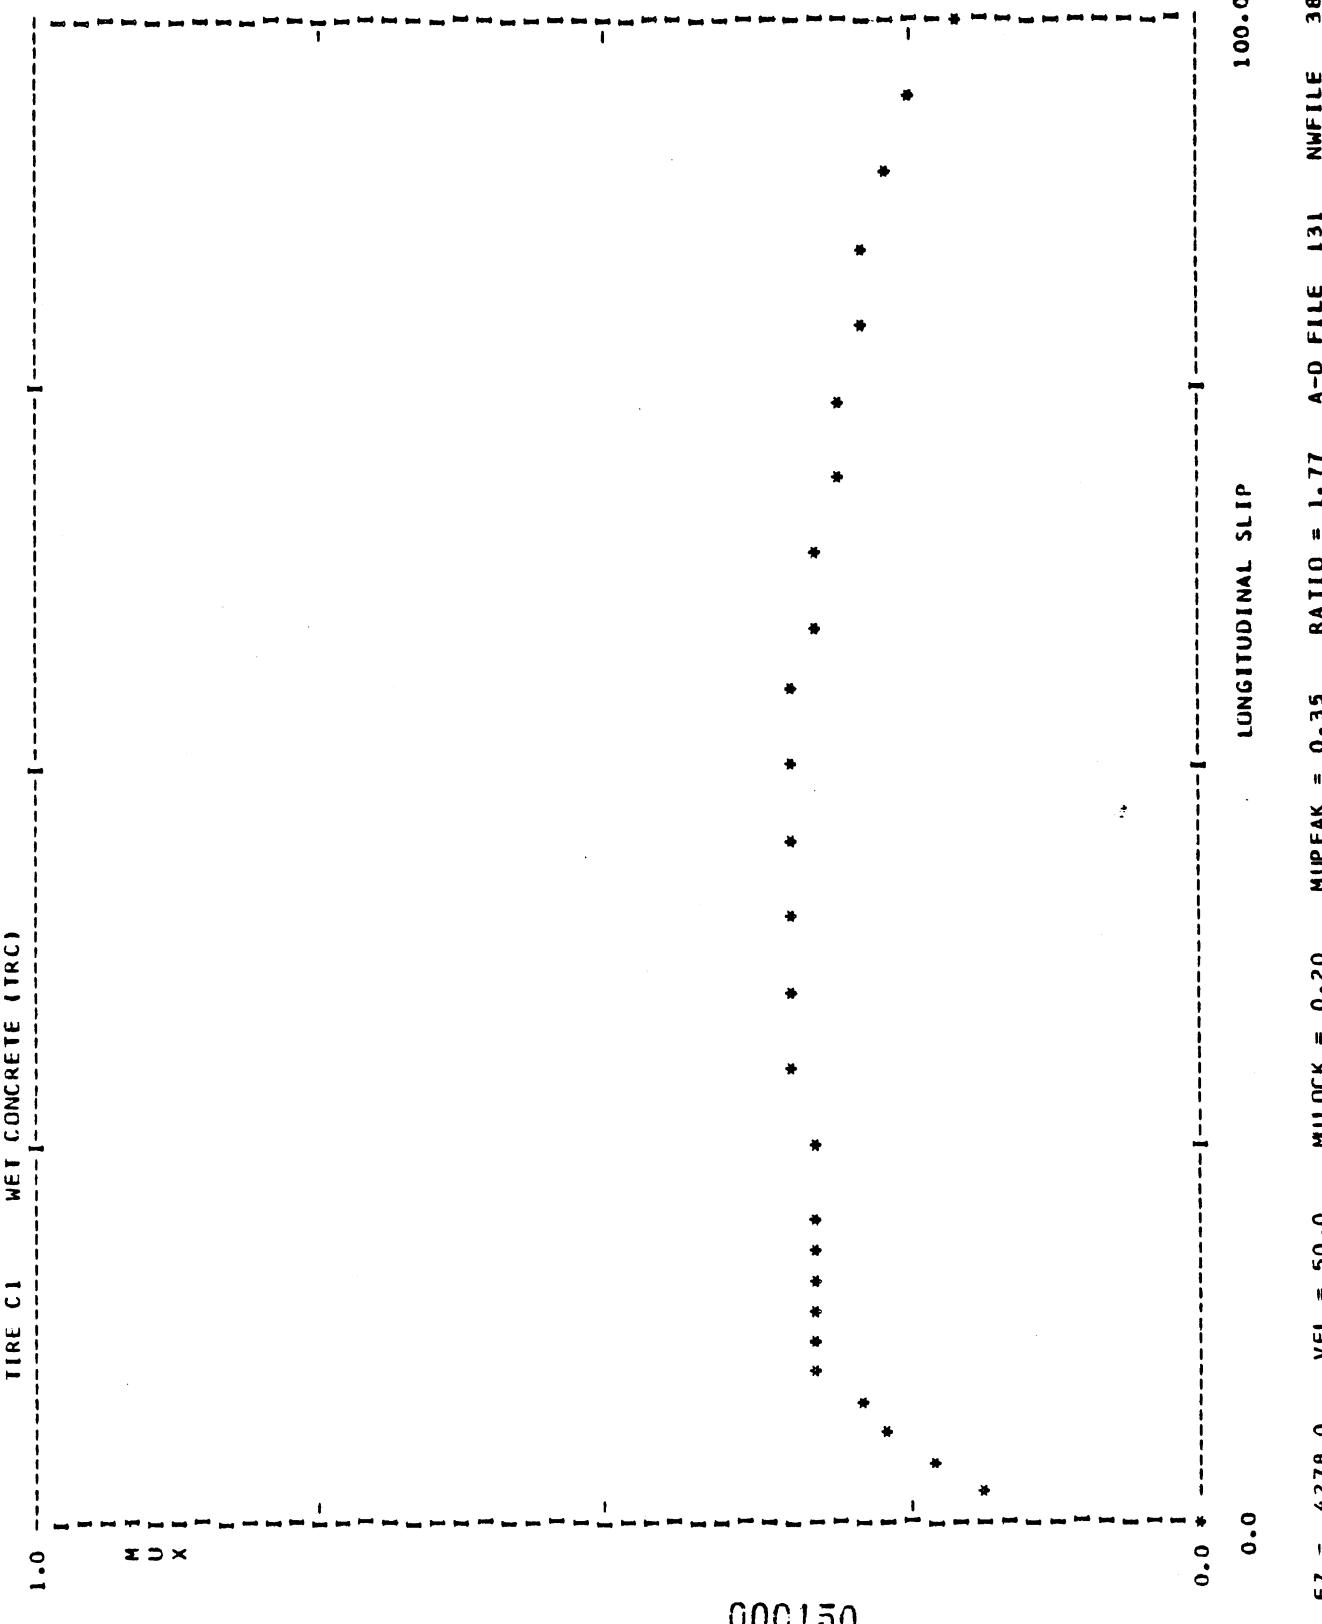

000150

MU-PEAK	SLIP-PEAK	MU-LOCK
0.345	0.400	0.206
0.349	0.120	0.219
0.403	0.350	0.176
0.336	0.400	0.180
0.349	0.600	0.204
0.332	0.100	0.180

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.352 0.026
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.194 0.018

000151

TEST SAMPLE 141 **

NEW FILE 39


** A-D FILE 139

AVERAGE OF FILE 139 FOR 6 RECORDS.

WET ASPHALT (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.17	19002.7	804.7
0.04	0.29	31673.6	1395.6
0.06	0.40	42555.0	1895.9
0.08	0.47	49707.0	2226.3
0.10	0.53	56031.9	2510.7
0.12	0.58	60854.2	2741.7
0.14	0.62	65729.6	2928.9
0.16	0.65	69417.1	3048.5
0.18	0.67	71631.7	3119.4
0.20	0.68	73529.4	3177.2
0.25	0.69	77590.7	3246.5
0.30	0.68	80282.6	3207.5
0.35	0.67	81917.4	3141.7
0.40	0.65	82771.1	3070.4
0.45	0.64	83332.3	3001.6
0.50	0.63	83705.9	2937.8
0.55	0.62	84284.9	2883.9
0.60	0.61	84957.5	2841.2
0.65	0.60	85723.0	2802.6
0.70	0.60	86052.7	2767.3
0.75	0.59	86404.1	2734.6
0.80	0.59	860405.4	2700.1
0.85	0.58	74714.6	2665.7
0.90	0.57	68269.3	2619.1
0.95	0.56	61914.7	2569.5
1.00	0.52	52437.4	2429.0

000152

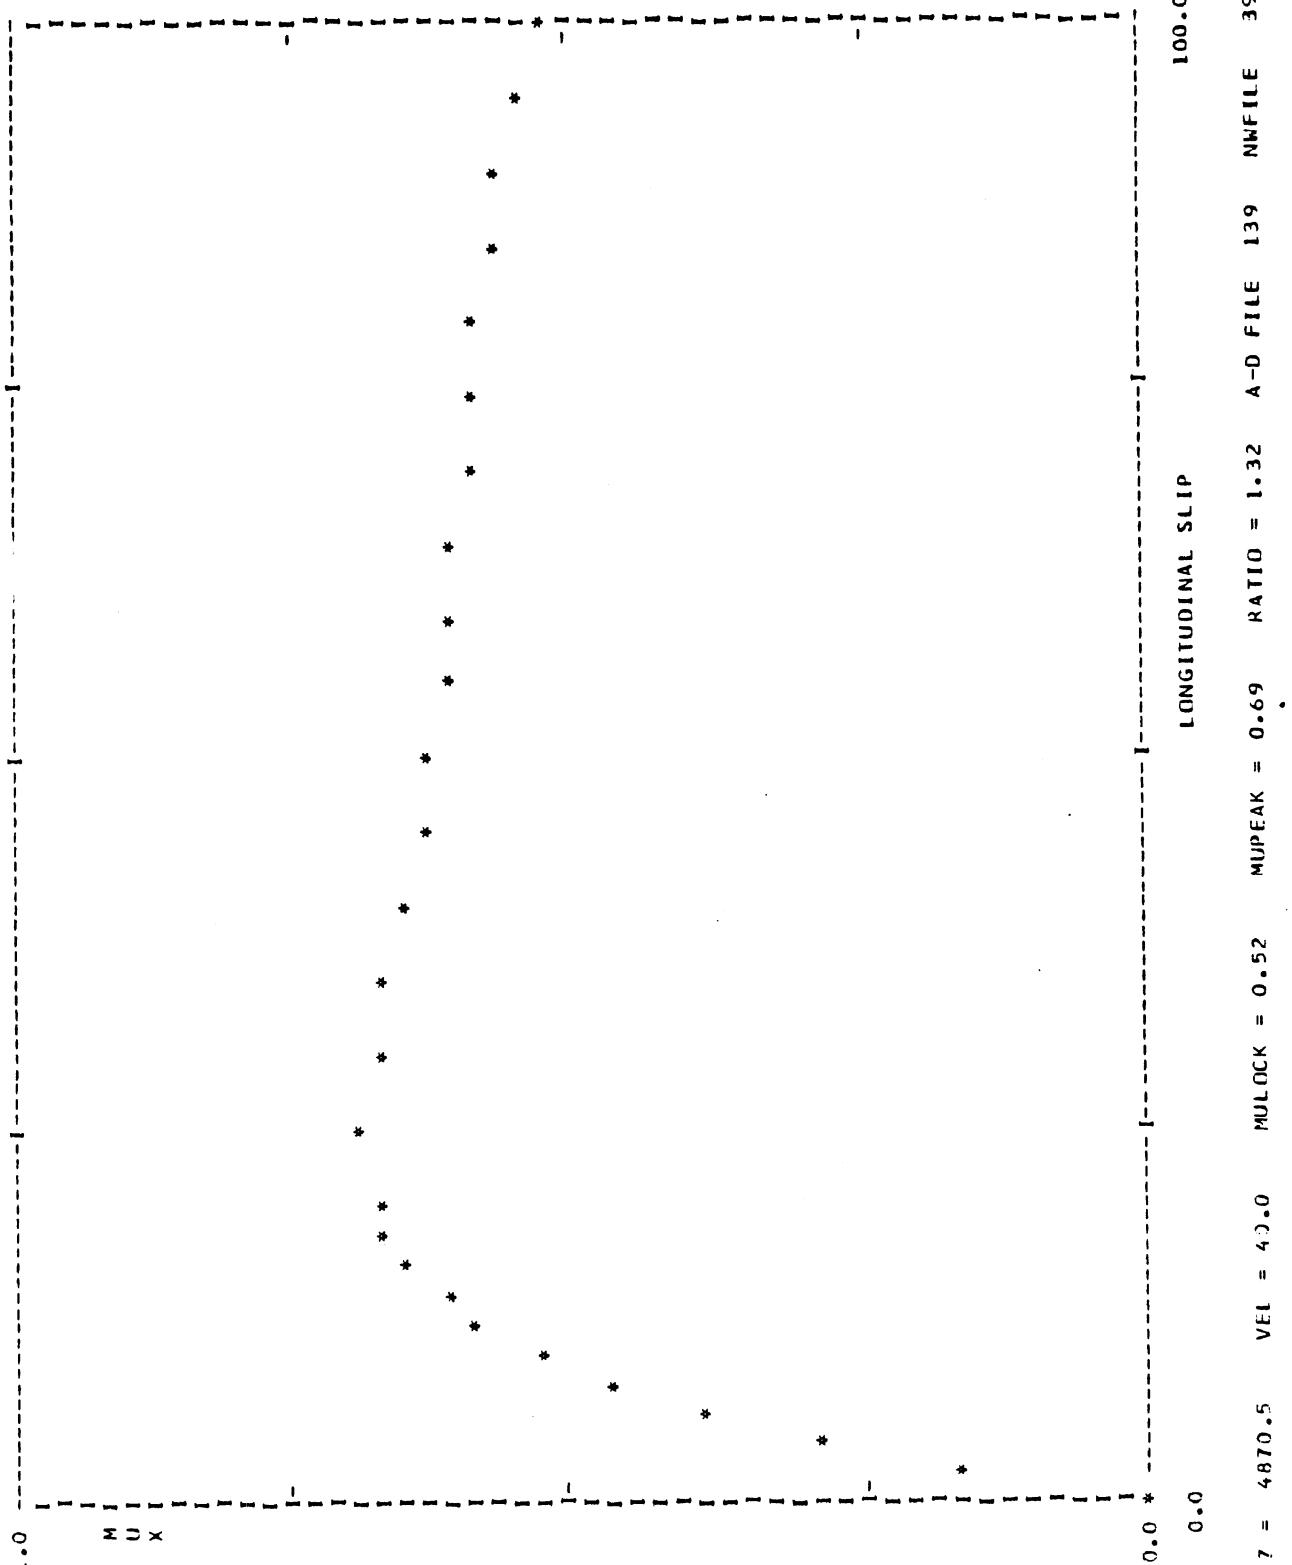

000153

MU-PEAK	SLIP PEAK
0.751	0.253
0.717	0.250
0.664	0.200
0.685	0.250
0.656	0.200
0.666	0.250


MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.689	0.038
MU-LOCK AVERAGE VALUE AND STD. DEVIATION :	0.518	0.033

000154

SLIP	AVERAGE OF FILE 140 FOR 6 RECORDS.	TORQUE	FOR 6 RECORDS.	LIFT 812	WEET ASPHALT (TRC)
0.0	0.00	0.0	0.0	0.0	
0.02	0.19	22345.3		905.2	
0.04	0.29	32020.5		1353.9	
0.06	0.39	42324.0		1837.1	
0.08	0.47	51117.0		2240.8	
0.10	0.52	56361.4		2451.5	
0.12	0.55	60658.6		2616.5	
0.14	0.58	64360.3		2736.6	
0.16	0.60	67176.3		2835.2	
0.18	0.62	69620.1		2920.8	
0.20	0.62	71816.5		2976.0	
0.25	0.62	75262.9		2973.7	
0.30	0.62	77391.1		2928.7	
0.35	0.61	79136.9		2879.6	
0.40	0.60	80698.9		2820.5	
0.45	0.59	81971.6		2760.8	
0.50	0.58	83080.4		2698.1	
0.55	0.57	84087.2		2638.3	
0.60	0.56	85078.4		2583.3	
0.65	0.55	85961.8		2536.5	
0.70	0.54	86823.8		2487.8	
0.75	0.53	86398.9		2452.3	
0.80	0.53	81192.0		2430.5	
0.85	0.52	73729.4		2411.2	
0.90	0.52	66094.5		2382.7	
0.95	0.51	59338.3		2355.7	
1.00	0.45	46979.1		2138.5	

000155

IRF H12 WE1 ASPHALT (TRC)

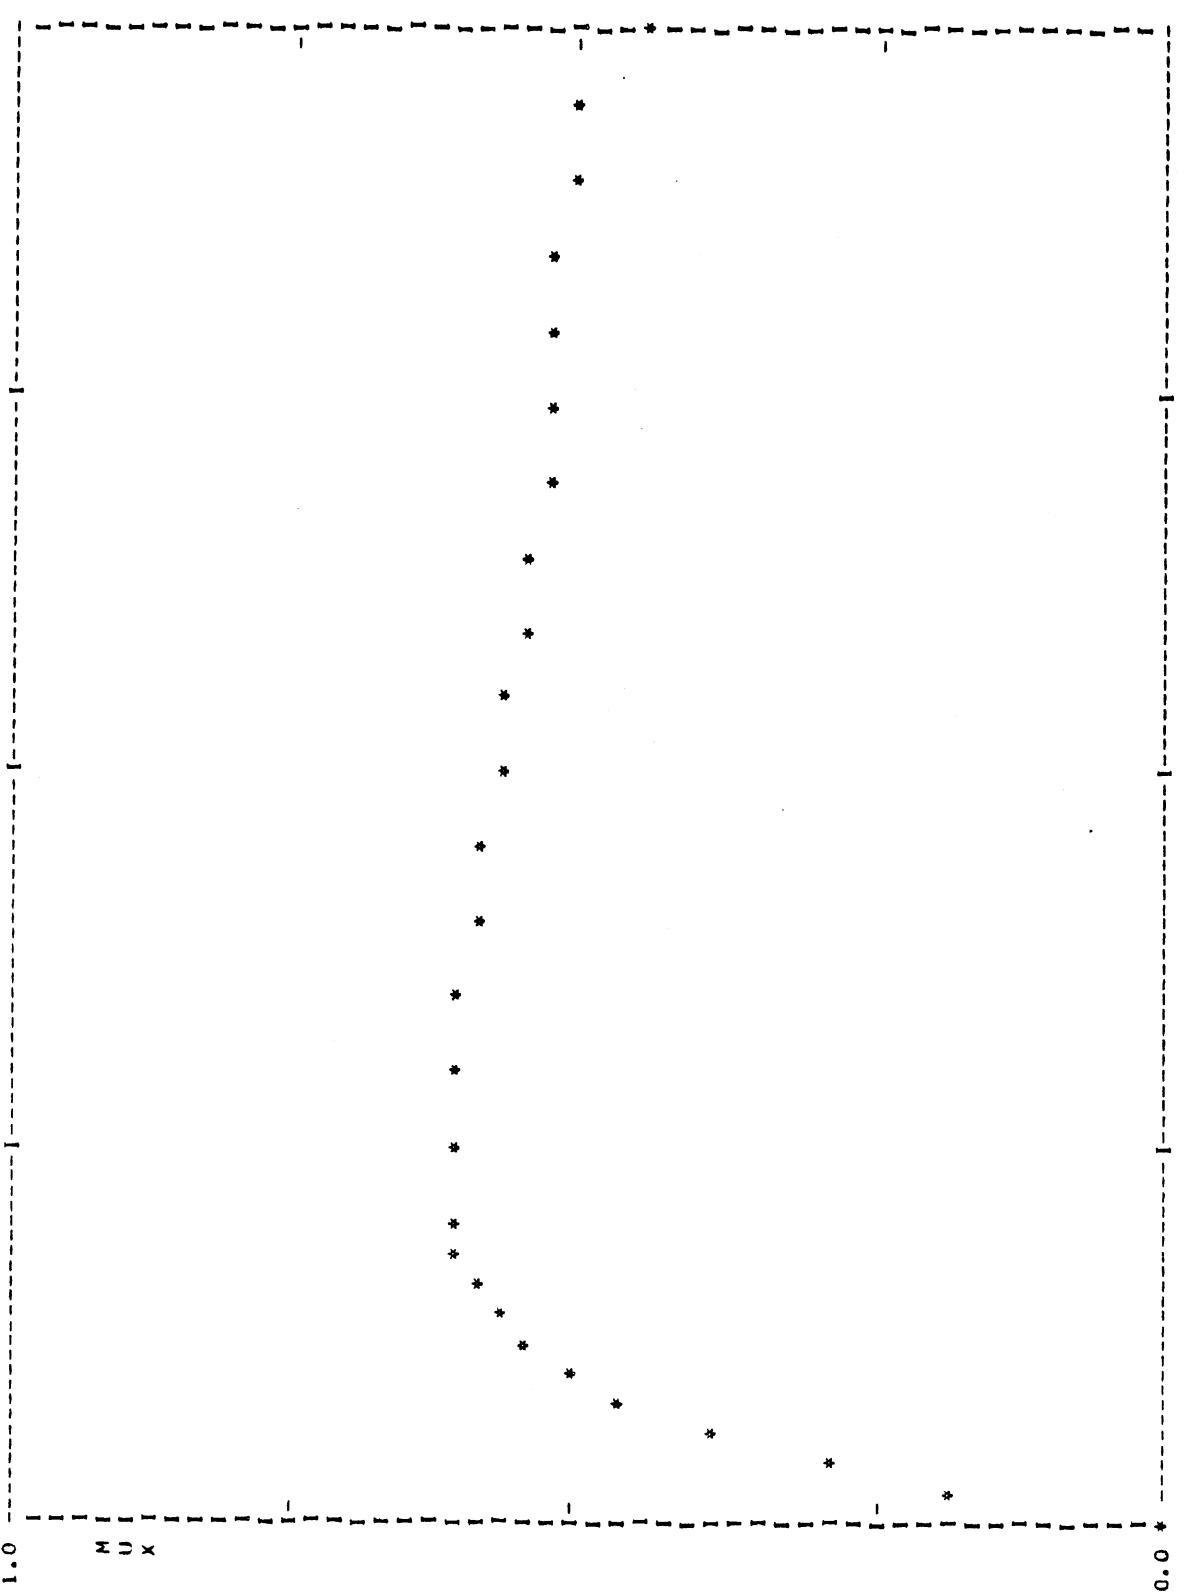

000156

FL = 4824.4 VEL = 50.0 MULOCK = 0.45 MUPEAK = 0.62 RATIO = 1.38 A-D FILE 140 NMFILE 40 SAMPLE 402

100.00

LONGITUDINAL SLIP

0.0

MU-PEAK	SLIP@PEAK	MU-LUCK
0.686	0.200	0.474
0.677	0.200	0.415
0.614	0.300	0.469
0.592	0.300	0.458
0.642	0.350	0.441
0.564	0.250	0.426

MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.629	0.048
MU-LUCK AVERAGE VALUE AND STD. DEVIATION :	0.447	0.024

000157

COOLING

** A-D FILE 144

NEW FILE 41


TEST SAMPLE143 **

AVERAGE OF FILE 144 FOR 6 RECORDS.

TIRE B12

WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.30	0.0	0.0
0.02	0.16	16536.8	722.2
0.04	0.24	24937.0	1119.1
0.06	0.29	30843.8	1364.3
0.08	0.33	35259.2	1534.7
0.10	0.35	38590.8	1622.4
0.12	0.35	41017.6	1661.1
0.14	0.36	42690.3	1687.7
0.16	0.37	44037.0	1705.7
0.18	0.37	45347.8	1722.1
0.20	0.38	46609.2	1739.3
0.25	0.38	49054.6	1779.0
0.30	0.39	51163.4	1801.9
0.35	0.38	53340.1	1797.5
0.40	0.38	55229.5	1778.1
0.45	0.37	56807.9	1745.1
0.50	0.36	58177.2	1699.5
0.55	0.35	59416.3	1654.6
0.60	0.34	60442.1	1609.4
0.65	0.33	61402.7	1563.7
0.70	0.33	61622.5	1519.8
0.75	0.32	59000.6	1480.6
0.80	0.31	53941.5	1447.0
0.85	0.30	47056.1	1417.8
0.90	0.29	40767.9	1373.1
0.95	0.28	34523.1	1321.8
1.00	0.25	24916.7	1164.5

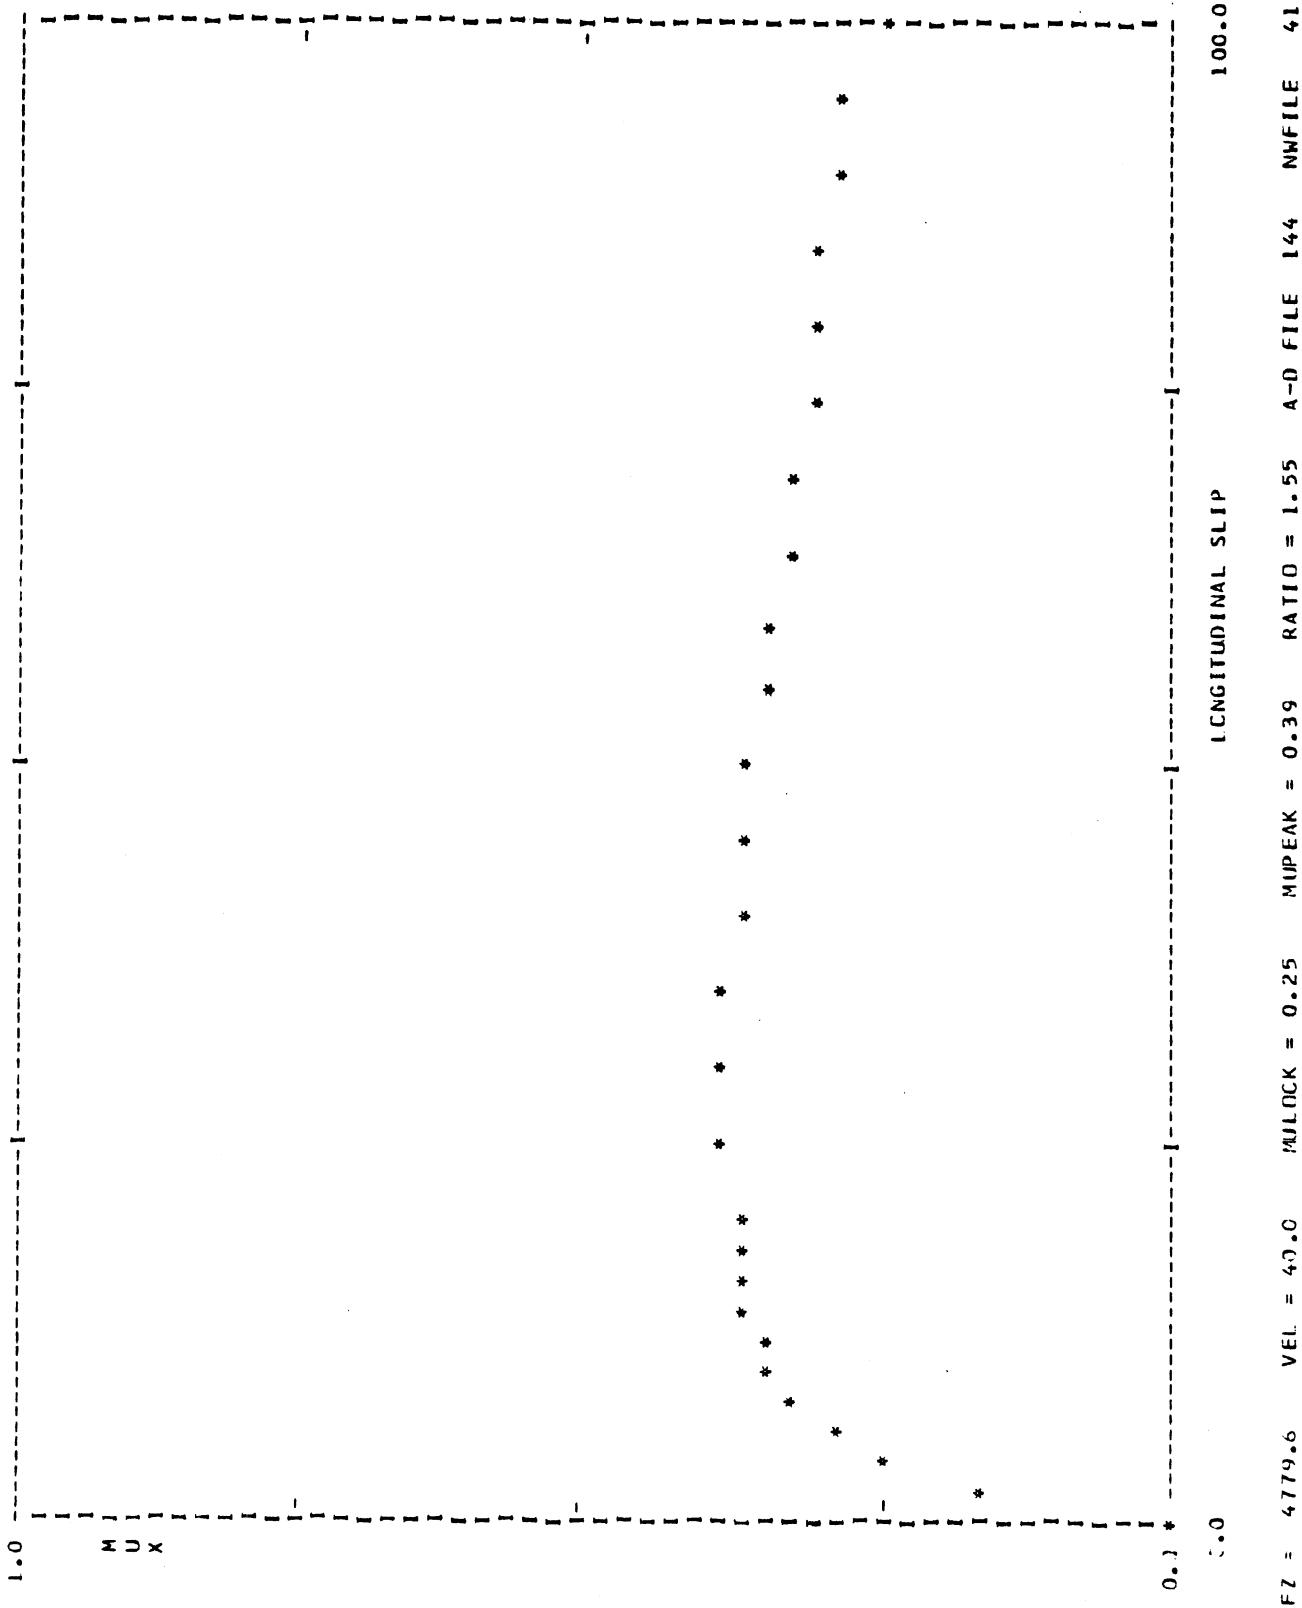

000159

MU-PEAK	SLIPPERY	MU-LUCK
0.411	0.350	0.240
0.397	0.300	0.241
0.380	0.300	0.274
0.434	0.200	0.250
0.361	0.450	0.205
0.338	0.200	0.254


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.387 0.035
 MU-LUCK AVERAGE VALUE AND STD. DEVIATION : 0.244 0.023

09160

SLIP	AVERAGE OF FILE 145 FOR 6 RECORDS.			TIRE B12	WEI CONCRETE (TRC)
	MUX	TORQUE	FX		
0.0	0.00	0.0	0.0		
0.02	0.15	16714.0	689.2		
0.04	0.21	23470.1	999.6		
0.06	0.26	28679.9	1190.1		
0.08	0.29	32719.5	1339.2		
0.10	0.30	36183.4	1419.4		
0.12	0.31	38394.3	1455.8		
0.14	0.32	40275.1	1485.4		
0.16	0.32	41928.4	1502.8		
0.18	0.33	43516.3	1515.5		
0.20	0.33	44876.8	1528.0		
0.25	0.34	47570.0	1549.8		
0.30	0.34	49950.9	1549.3		
0.35	0.33	51986.9	1531.6		
0.40	0.33	53892.0	1505.8		
0.45	0.32	55558.7	1480.4		
0.50	0.31	57173.8	1452.4		
0.55	0.31	58573.3	1422.0		
0.60	0.30	59692.3	1391.2		
0.65	0.29	60763.3	1358.8		
0.70	0.29	61742.4	1321.6		
0.75	0.28	60916.1	1283.0		
0.80	0.27	55845.9	1249.6		
0.85	0.27	47235.3	1220.9		
0.90	0.26	39636.5	1179.0		
0.95	0.25	32286.1	1137.0		
1.00	0.23	23145.8	1051.0		

000161

TURF B12 WET CONCRETE (TRC)

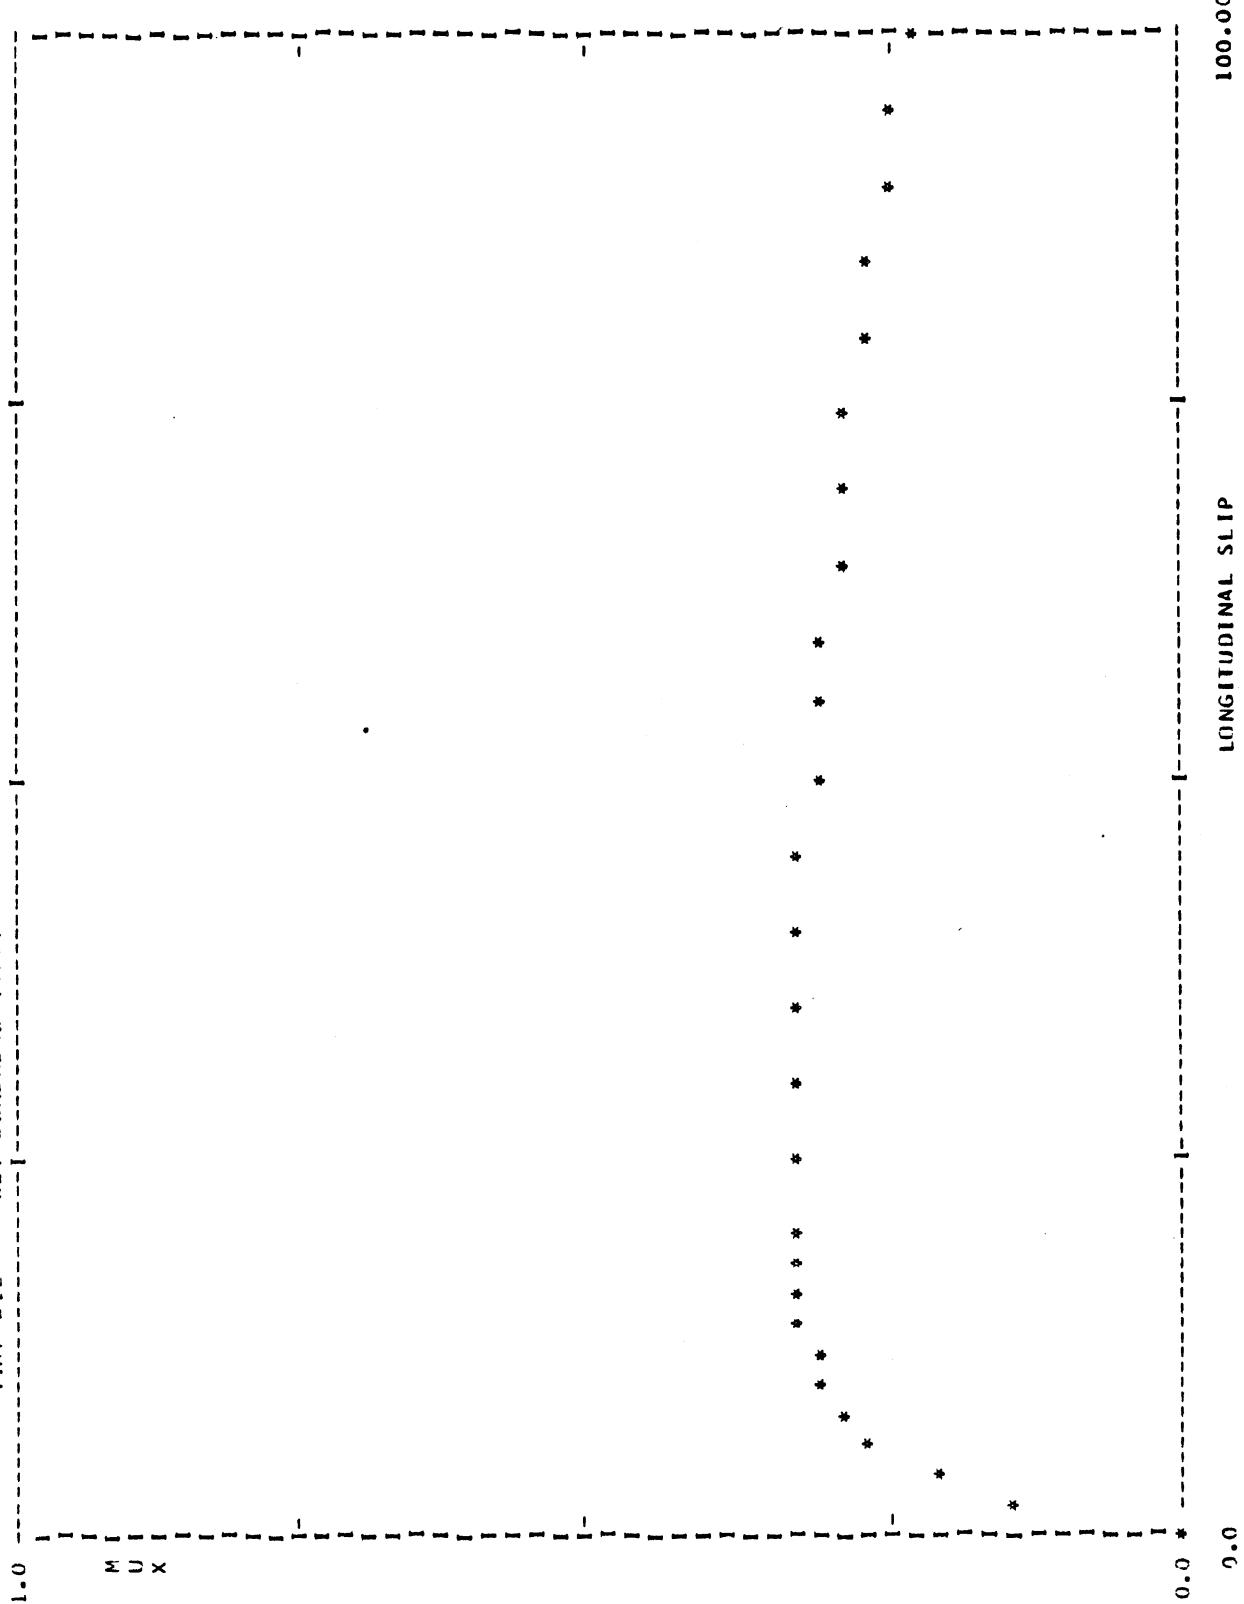

000182

FZ = 4700.1 VEL = 57.0 MULOCK = 0.23 MUPEAK = 0.34 RATIO = 1.49 A-D FILE 145 NMFILE 42 SAMPLE 144

MU-PEAK	SPLIT-P-EAK	MU-LOCK
0.325	0.253	0.217
0.312	0.200	0.207
0.373	0.500	0.229
0.322	0.300	0.226
0.338	0.250	0.222
0.336	0.250	0.225

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.334 0.021
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.221 0.008

000163

F0019

** A-D FILE 152

AVERAGE OF FILE 152 FOR 6 RECORDS.

NEW FILE 43


TEST SAMPLE 145 **

TIRE RL2 WET ASPHALT (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.23	22863.6	1041.3
0.04	0.37	37002.8	1706.4
0.06	0.48	48648.5	2237.5
0.08	0.58	58159.9	2695.6
0.10	0.66	65854.7	3060.1
0.12	0.69	70317.3	3219.5
0.14	0.71	73060.8	3326.5
0.16	0.73	75090.4	3400.7
0.18	0.74	77285.7	3445.6
0.20	0.74	78909.6	3456.2
0.25	0.74	81658.4	3434.9
0.30	0.73	83732.4	3376.0
0.35	0.71	85428.2	3306.4
0.40	0.70	86846.1	3230.9
0.45	0.69	88055.8	3162.3
0.50	0.68	88993.4	3099.6
0.55	0.66	89811.8	3040.9
0.60	0.65	90487.6	2985.5
0.65	0.64	91073.6	2932.7
0.70	0.63	91517.1	2880.0
0.75	0.62	90523.8	2827.8
0.80	0.61	85350.1	2785.1
0.85	0.60	75903.8	2749.6
0.90	0.58	68641.9	2684.8
0.95	0.57	60974.4	2628.2
1.00	0.53	51895.8	2453.0

TQAV = 51895.8 LOAD = 4713.8 VEL = 40.0 MPH.

MUPEAK = 0.74 MULOCK = 0.53 RATIO = 1.40

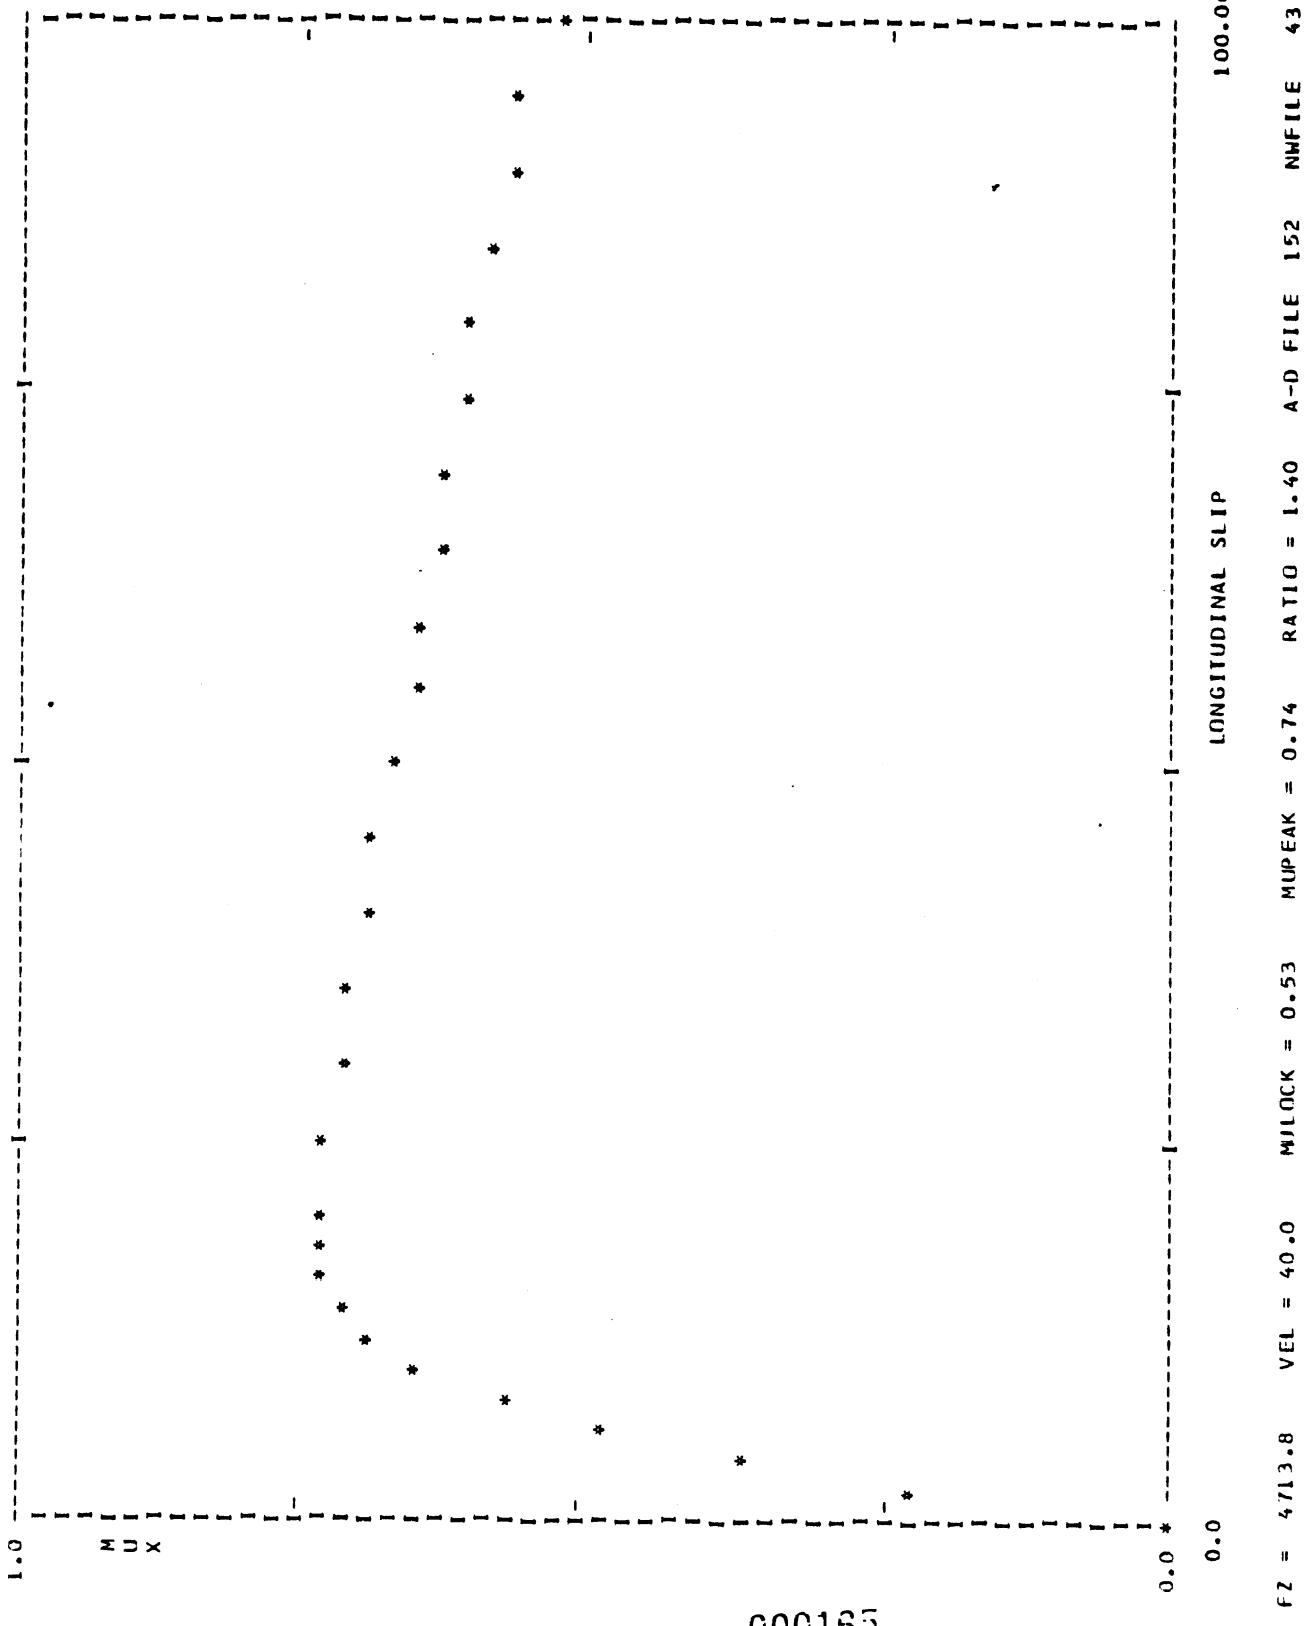

MU-PEAK	SLIP@PEAK	MU-LOCK
0.746	0.200	0.505
0.749	0.250	0.494
0.716	0.250	0.491
0.734	0.180	0.557
0.741	0.200	0.558
0.750	0.180	0.553


MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.739	0.013
MU-LOCK AVERAGE VALUE AND STD. DEVIATION :	0.526	0.033

000166

AVERAGE OF FILE 153 FOR 6 RECORDS.		TIRE RL2		WET ASPHALT (TRC)	
SLIP	MUX	TORQUE	FX		
0.0	0.00	0.0	0.0	0.0	
0.02	0.23	21029.8	1080.1		
0.04	0.37	33915.1	1716.1		
0.06	0.49	44488.6	2262.7		
0.08	0.57	53534.8	2666.9		
0.10	0.62	58620.8	2929.3		
0.12	0.66	62952.0	3103.0		
0.14	0.69	65958.6	3192.2		
0.16	0.70	68767.2	3236.7		
0.18	0.70	70710.1	3247.2	TQAV = 45104.1	LOAD = 4742.6 VEL = 50.0 MPH.
0.20	0.70	71674.7	3242.8		
0.25	0.70	73976.0	3192.2	MUPEAK = 0.70	MULOCK = 0.50 RATIO = 1.41
0.30	0.68	76270.6	3129.5		
0.35	0.67	77904.8	3077.2		
0.40	0.66	79166.8	3029.3		
0.45	0.65	80096.8	2984.3		
0.50	0.64	80914.3	2942.3		
0.55	0.62	81686.2	2898.6		
0.60	0.61	82234.9	2847.2		
0.65	0.60	82818.0	2797.8		
0.70	0.59	83365.6	2750.7		
0.75	0.58	83689.1	2697.9		
0.80	0.57	81632.0	2647.1		
0.85	0.56	73551.0	2617.3		
0.90	0.55	63119.9	2579.1		
0.95	0.54	56027.6	2522.5		
1.00	0.50	45104.1	2330.0		

000167

TIRE PL2 WET ASPHALT (TRC)

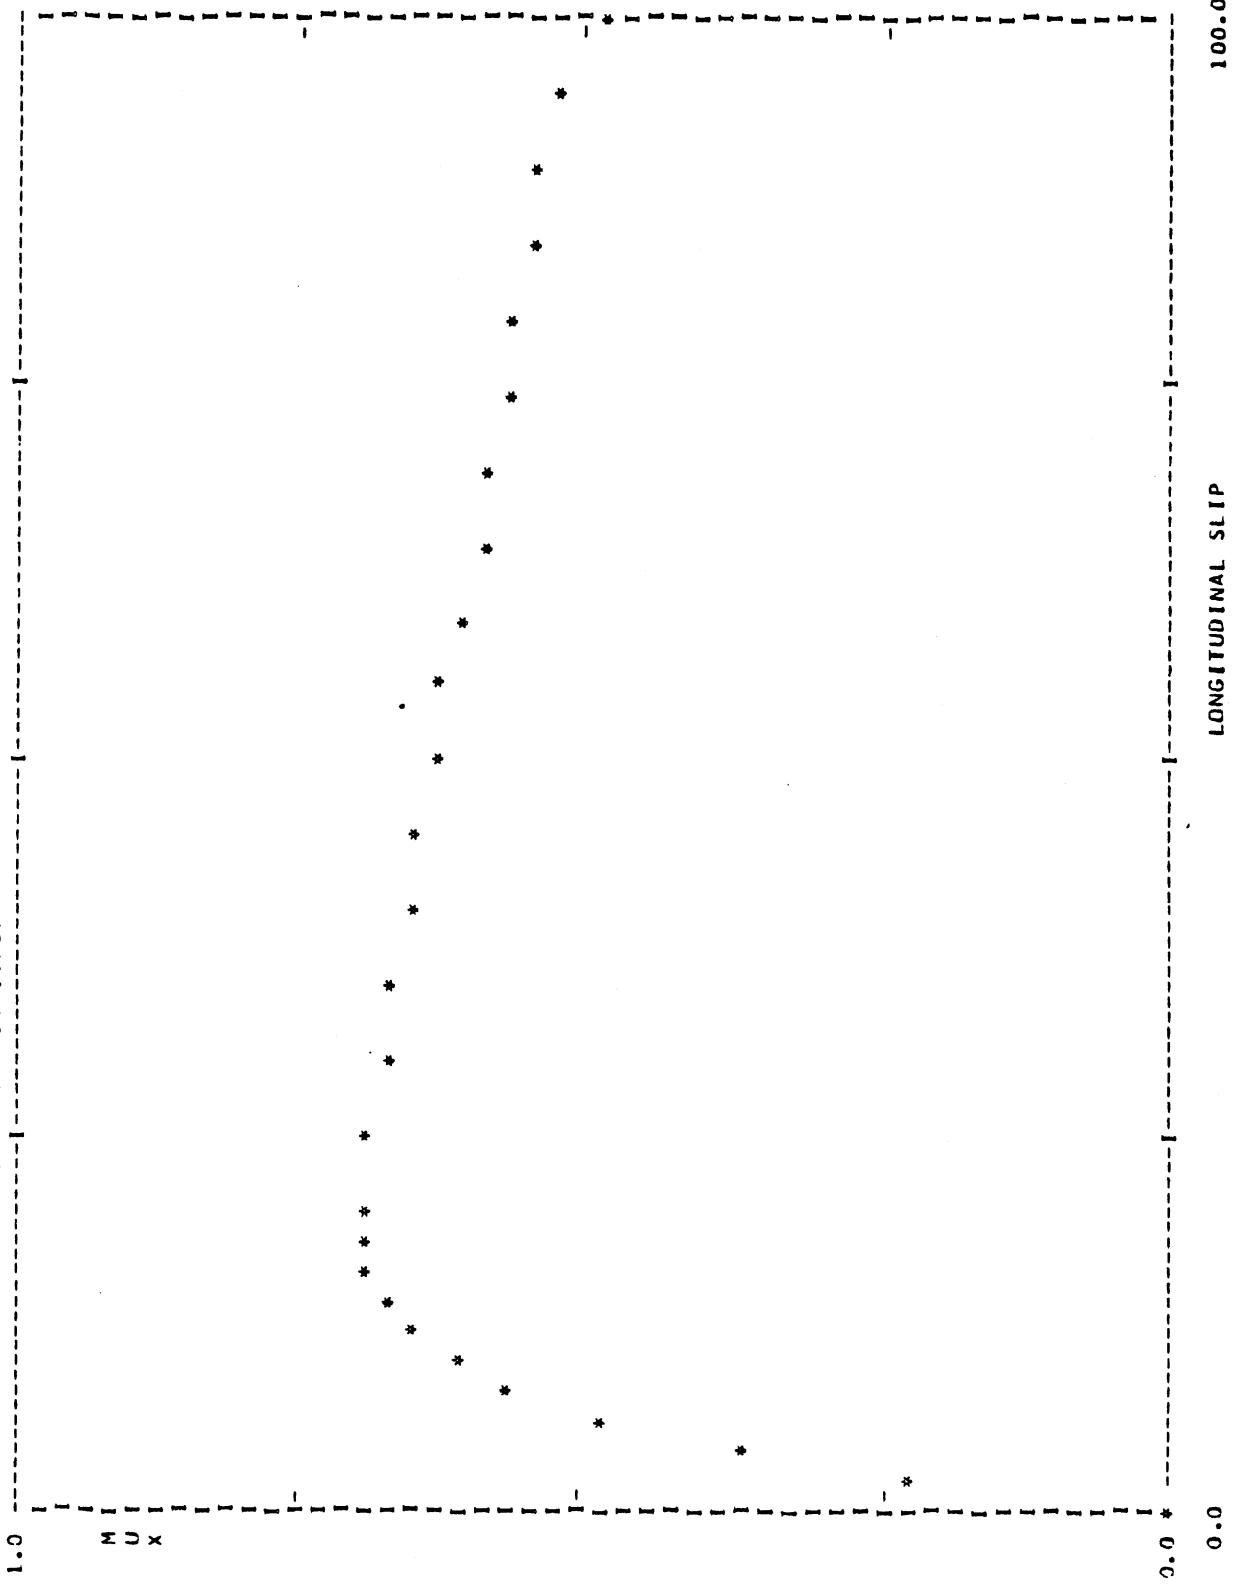

000168

FZ = 4742.6 VEL = 50.0 MUPEAK = 0.50 MULOCK = 0.50 RATIO = 1.41 A-D FILE 153 NMFILE 44 SAMPLE 146

100.00

LONGITUDINAL SLIP

MU-PEAK	SLIP-Peak	MU-LOCK
0.690	0.200	0.493
0.719	0.160	0.427
0.702	0.200	0.510
0.706	0.250	0.513
0.686	0.160	0.503
0.713	0.180	0.516

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.702 0.013
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.494 0.034

000169

** A-D FILE 157 TEST SAMPLE 147 **

SLIP	AVERAGE OF FILE 157 FOR 6 RECORDS.			NEW FILE 45 TIRE RL2 WET CONCRETE (TRC)		
	MUX	TORQUE	FX	MUX	TQAV = -65041.6	LOAD = 4778.4 VEL = 40.0 MPH.
0.0	0.00	0.0	0.0	0.0	-79081.0	858.5
0.02	0.19	-70931.1	1230.7			
0.04	0.27	-62411.6	1461.6			
0.06	0.31	-56893.2	1567.8			
0.08	0.33	-52575.0	1609.0			
0.10	0.34	-48837.4	1635.1			
0.12	0.35	-46442.4	1642.7			
0.14	0.35	-44287.6	1647.3			
0.16	0.35	-42714.7	1647.8			
0.18	0.35	-41268.9	1641.5			
0.20	0.35	-38876.4	1639.2			
0.25	0.35	-37589.4	1641.1			
0.30	0.35	-36139.9	1628.1			
0.35	0.35	-34837.8	1613.8			
0.40	0.35	-34020.4	1604.5			
0.45	0.35	-33541.1	1592.2			
0.50	0.34	-33399.7	1576.5			
0.55	0.34	-33213.7	1559.5			
0.60	0.34	-32953.5	1541.2			
0.65	0.33	-32440.0	1521.4			
0.70	0.33	-32926.3	1494.5			
0.75	0.32	-36019.9	1464.1			
0.80	0.31	-44855.3	1448.3			
0.85	0.31	-53212.4	1417.5			
0.90	0.30	-60437.5	1368.5			
0.95	0.29	-65041.6	1263.0			
1.00	0.27					

000170

1.0

N U X

000171

0.0 *
C.C

FZ = 4778.4 VEL = 40.0 MULNCK = 0.21 MUPEAK = 0.35 RATIO = 1.30 A-D FILE 157 NWFILE 45 SAMPLE 147

100.00
LONGITUDINAL SLIP

MU-PEAK	SLIP PEAK	MU-LOCK
0.371	0.300	0.268
0.347	0.300	0.249
0.371	0.350	0.270
0.416	0.120	0.243
0.316	0.160	0.298
0.350	0.450	0.282

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.362 0.033
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.268 0.020

000172

SLIP	AVERAGE OF FILE 158	FNR	RECORDS	TURQUE	FX	WET CONCRETE (TRC)
	MIX					
0.0	0.00			0.0	0.0	
0.02	0.16			-66891.6	722.3	
0.04	0.24			-57360.3	1098.9	
0.06	0.29			-48820.9	1294.6	
0.08	0.31			-44147.8	1426.2	
0.10	0.32			-40895.2	1504.3	
0.12	0.33			-36410.1	1563.4	
0.14	0.32			-33190.3	1556.9	
0.16	0.32			-30354.7	1536.6	
0.18	0.32			-28248.8	1517.3	
0.20	0.32			-26693.4	1497.6	
0.25	0.31			-24656.9	1448.2	HUPEAK = 0.33 MULOCK = 0.23 RATIO = 1.41
0.30	0.31			-22527.1	1412.0	
0.35	0.32			-21156.9	1410.6	
0.40	0.32			-20813.4	1419.7	
0.45	0.32			-20507.7	1428.0	
0.50	0.32			-19942.5	1450.2	
0.55	0.32			-19510.7	1470.5	
0.60	0.32			-19101.2	1477.3	
0.65	0.31			-17389.5	1448.1	
0.70	0.30			-15263.1	1411.7	
0.75	0.29			-13941.0	1368.9	
0.80	0.28			-14780.3	1326.3	
0.85	0.28			-23912.2	1296.7	
0.90	0.28			-33900.9	1265.1	
0.95	0.26			-41085.2	1192.9	
1.00	0.23			-57875.0	1093.5	

000173

TIRF RL2

WET CONCRETE (TRC)

1.0
0.0

M U X

000174

100.00
0.0

LONGITUDINAL SLIP

FZ = 4736.7 VEL = 50.0 MULOCK = 0.23 MUPEAK = 0.33 RATIO = 1.41 A-D FILE 158 NMFILE 46 SAMPLE 148

MU-PEAK	S. I. IPMPEAK	MU-LOCK
0.320	0.120	0.225
0.339	0.600	0.229

MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.330	0.013
MU-LOCK AVERAGE VALUE AND STD. DEVIATION :	0.227	0.003

000175

TEST SAMPLE 148 **

NEW FILE 47


** A-D FILE 159

AVERAGE OF FILE 159 FOR 4 RECORDS.

TIRE RL2 WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.16	-58754.6	695.9
0.04	0.25	-48722.3	1161.6
0.06	0.28	-43509.9	1300.5
0.08	0.30	-41438.2	1395.7
0.10	0.32	-39259.2	1449.1
0.12	0.32	-37655.7	1482.5
0.14	0.33	-36329.6	1515.5
0.16	0.34	-35118.1	1543.6
0.18	0.34	-33842.2	1561.3
0.20	0.34	-32302.3	1575.3
0.25	0.34	-27735.1	1597.4
0.30	0.34	-23748.2	1591.5
0.35	0.33	-20911.8	1567.4
0.40	0.32	-19319.4	1527.5
0.45	0.31	-18548.1	1471.1
0.50	0.30	-17448.5	1426.4
0.55	0.30	-16321.1	1403.3
0.60	0.30	-15200.4	1390.7
0.65	0.30	-14172.3	1386.2
0.70	0.30	-13355.8	1377.1
0.75	0.30	-13095.6	1363.8
0.80	0.29	-15255.3	1349.5
0.85	0.29	-24056.9	1346.0
0.90	0.29	-34091.6	1325.8
0.95	0.28	-40660.1	1277.2
1.00	0.25	-49156.2	1166.2

000176

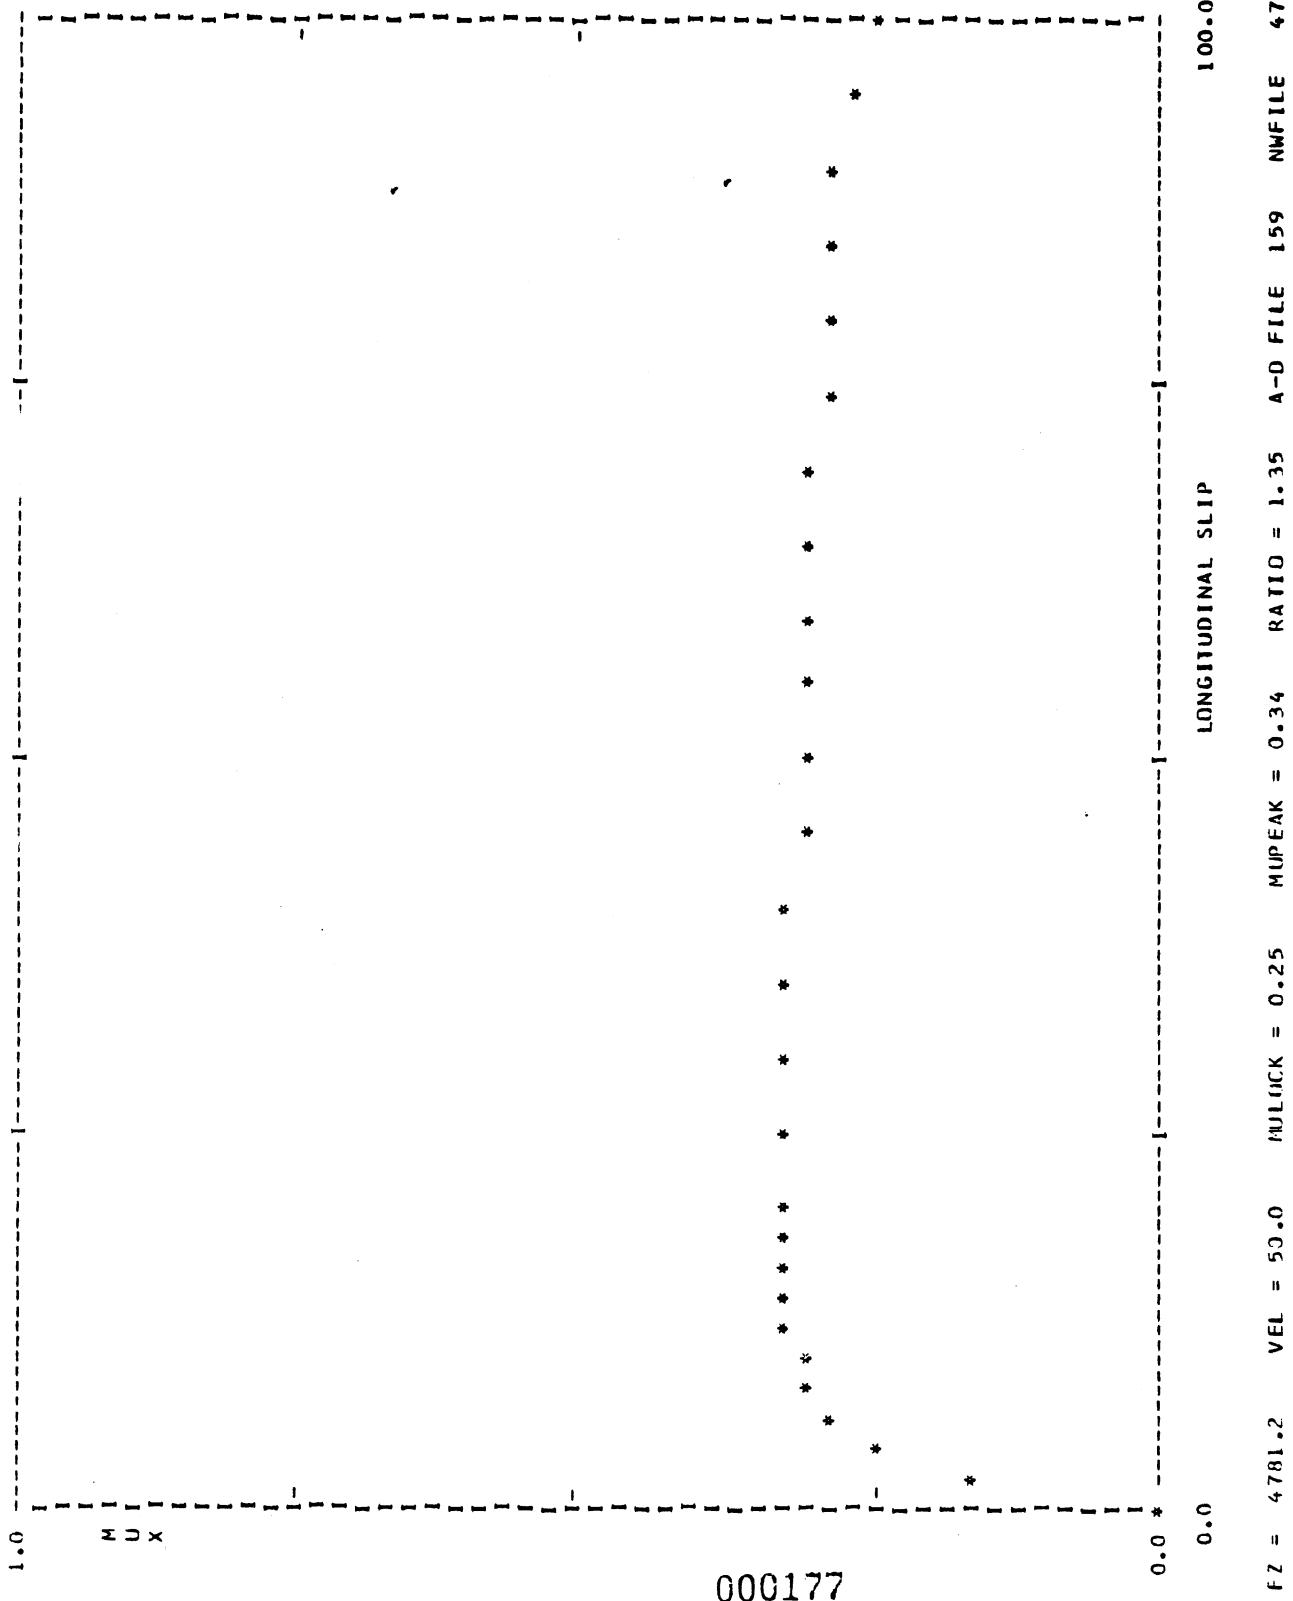

MU-PEAK	SLIP-PEAK
0.378	0.160
0.302	0.360
0.352	0.200
0.357	0.300


MU-PEAK AVERAGE VALUE AND STD. DEVIATION :	0.347	0.032
MU-LOCK AVERAGE VALUE AND STD. DEVIATION :	0.246	0.012

000178

SLIP	AVERAGE OF FILTER 166	FOR RECORDS.	TIRE C1	WET ASPHALT (TRC)
	MUX	TORQUE	Fx	
0.0	0.00	0.0	0.0	0.0
0.02	0.23	56338.4	1048.4	
0.04	0.36	66208.3	1645.5	
0.06	0.47	75425.3	2184.2	
0.08	0.56	83572.6	2570.1	
0.10	0.65	91724.2	3029.7	
0.12	0.72	97234.3	3290.6	
0.14	0.76	98722.8	3467.1	
0.16	0.80	101457.8	3592.1	
0.18	0.81	106552.6	3652.0	
0.20	0.81	108533.8	3645.7	
0.25	0.81	112991.6	3625.0	
0.30	0.78	113266.7	3489.3	
0.35	0.75	114733.3	3355.5	
0.40	0.73	114383.3	3262.1	
0.45	0.71	114155.9	3180.4	
0.50	0.70	113549.3	3118.5	
0.55	0.69	113061.2	3062.6	
0.60	0.68	113061.1	3016.6	
0.65	0.67	112907.8	2978.3	
0.70	0.66	112275.6	2941.5	
0.75	0.65	109929.9	2908.1	
0.80	0.64	104621.6	2877.3	
0.85	0.63	99325.8	2838.7	
0.90	0.61	94816.2	2775.5	
0.95	0.59	91417.0	2697.7	
1.00	0.55	83895.8	2515.5	

000179

TIRE C1 WET ASPHALT (TRC)

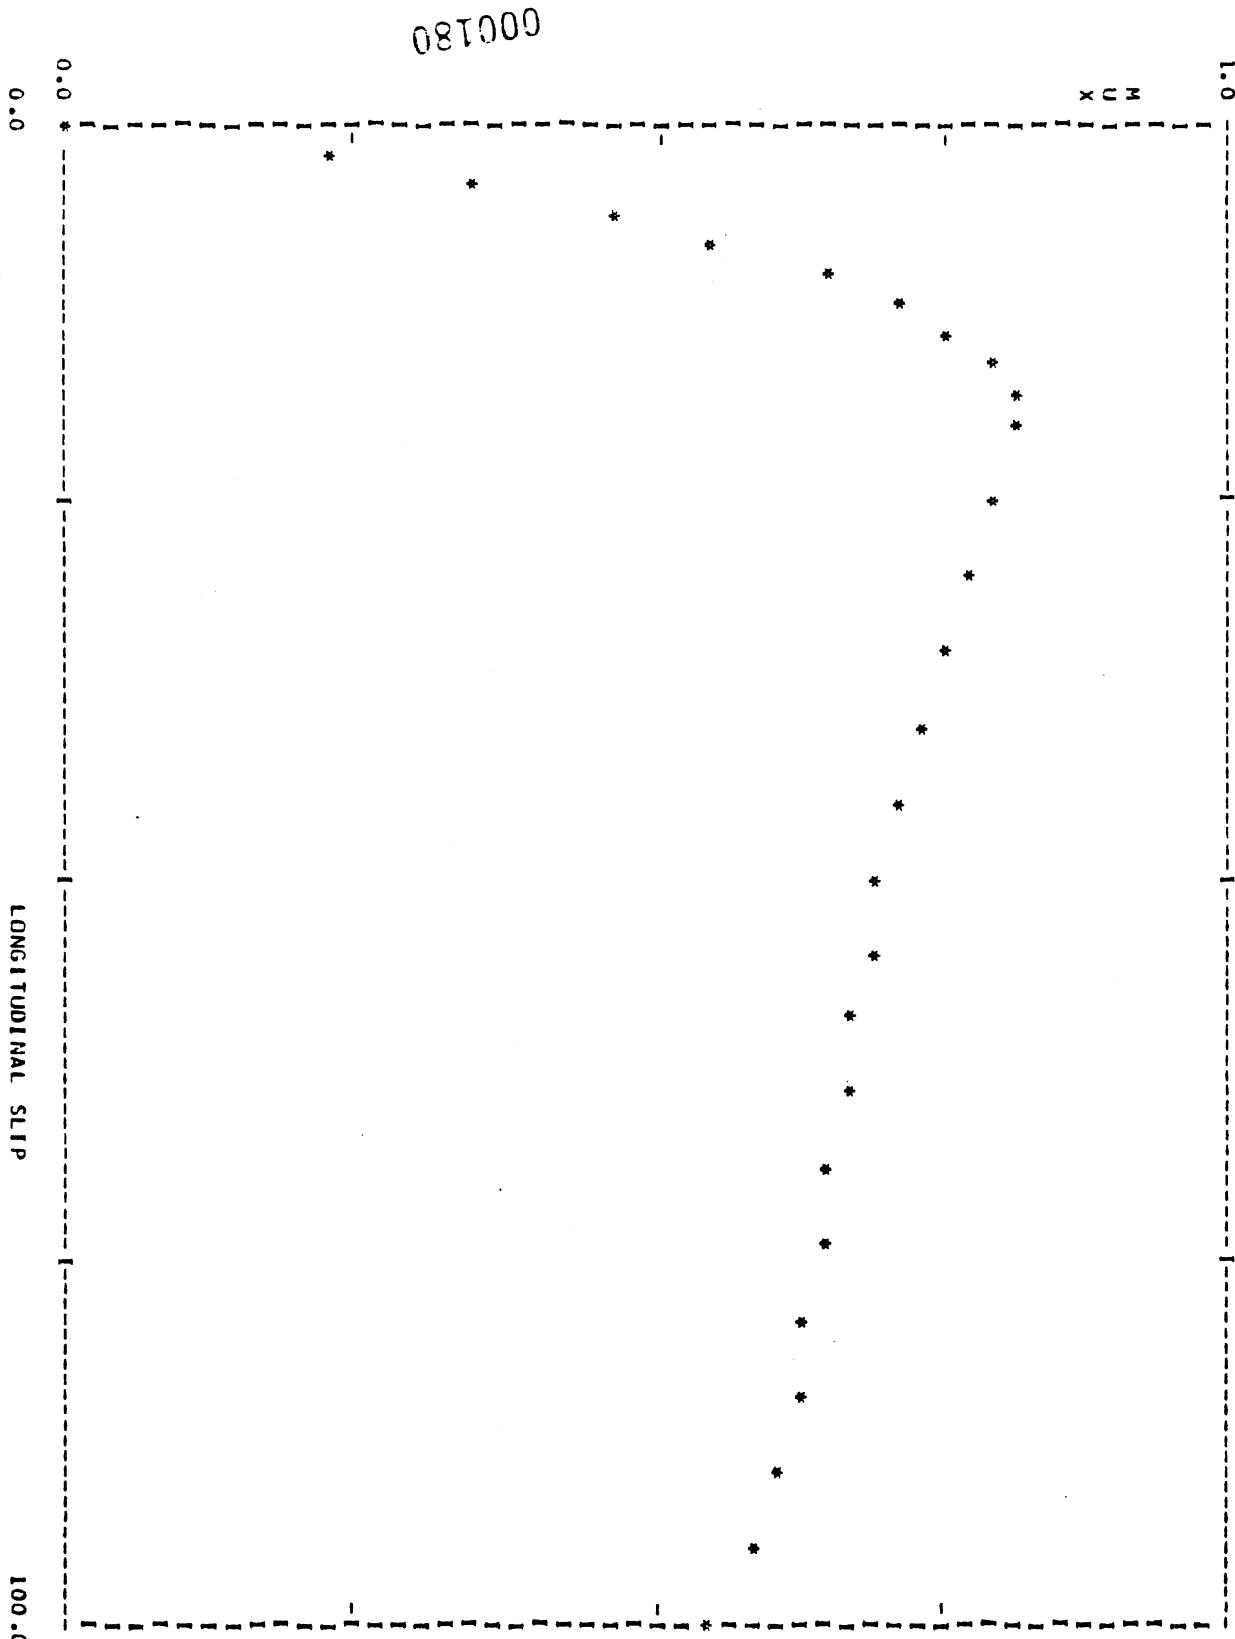

FZ = 4667.3

VEL = 40.0

MULOCK = 0.55

MUPEAK = 0.81

RATIO = 1.47 A-D FILE 166 NWFILE 48 SAMPLE 149

	MU-PEAK	SLIP&PFACK	MU-LOCK
0.875	0.200	0.532	
0.845	0.160	0.493	
0.900	0.250	0.625	
0.766	0.200	0.555	
0.782	0.160	0.546	
0.774	0.180	0.524	

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.823 0.057
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.546 0.044

000181

TEST SAMPLE 150 **

** A-D FILE 167


NEW FILE 49

AVERAGE OF FILE 167 FOR 6 RECORDS.

TIRF C1 WET ASPHALT (TRC)

SLIP	MU _X	TORQUE	F _X
0.0	0.00	0.0	0.0
0.02	0.19	55394.8	859.1
0.04	0.34	74970.7	1562.4
0.06	0.44	84431.1	2052.0
0.08	0.54	92938.0	2521.1
0.10	0.60	91222.6	2843.8
0.12	0.64	91806.4	3002.1
0.14	0.67	95392.6	3118.2
0.16	0.67	97163.9	3109.3
0.18	0.67	98429.9	3090.6
0.20	0.67	98593.3	3081.2
0.25	0.67	98903.6	3056.0
0.30	0.66	100580.7	3030.3
0.35	0.65	101619.8	2984.4
0.40	0.63	101926.4	2910.0
0.45	0.61	102405.0	2830.1
0.50	0.60	103367.3	2756.0
0.55	0.58	104557.8	2686.8
0.60	0.57	106273.7	2622.2
0.65	0.56	108283.1	2558.7
0.70	0.55	109382.9	2504.0
0.75	0.55	107756.8	2469.8
0.80	0.54	102075.4	2441.2
0.85	0.54	95838.6	2416.3
0.90	0.53	90437.3	2384.9
0.95	0.52	84227.0	2355.2
1.00	0.45	75624.9	2091.0

000182

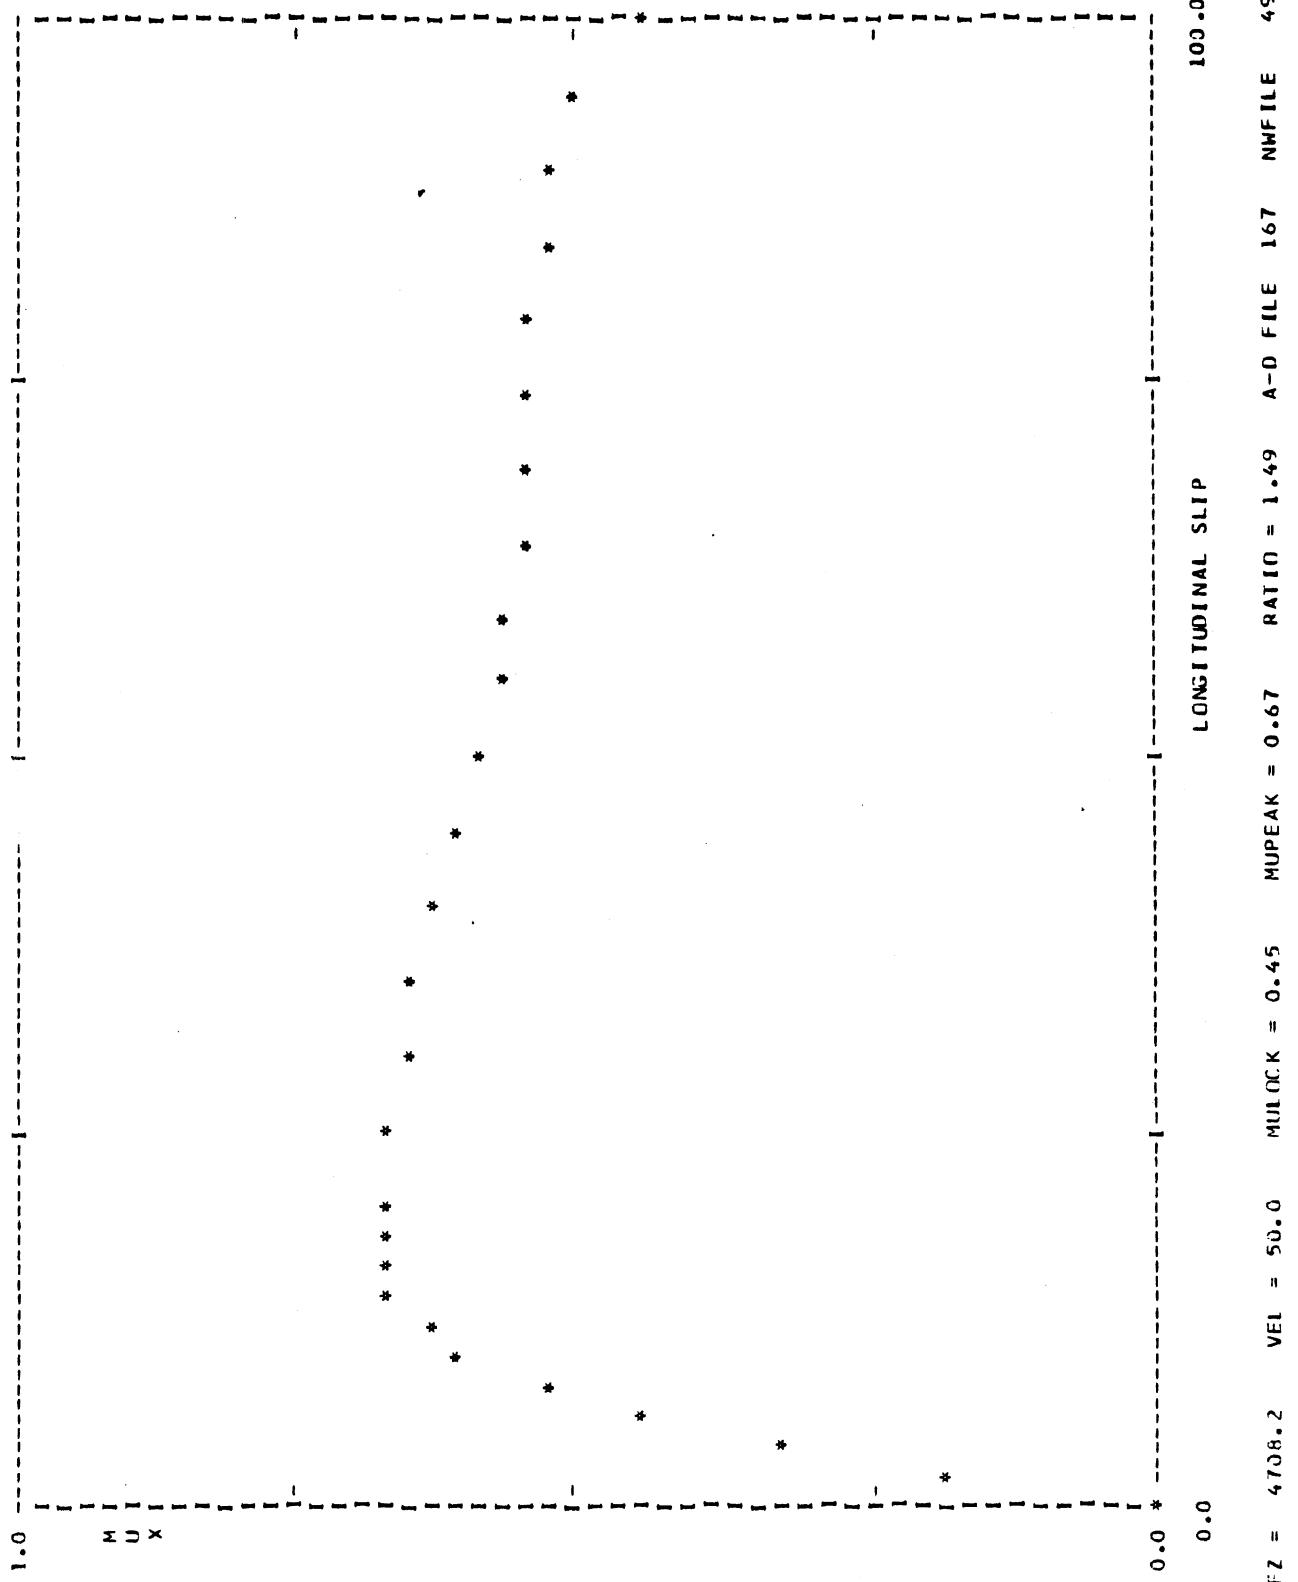

000183

F2 = 4706.2 VEL = 50.0 MUPEAK = 0.45 MUNCK = 0.67 RATIO = 1.49 A-D FILE 167 NMFILE 49 SAMPLE 150

MU-PEAK	SLIPPERY	MU-LCCK
0.686	0.140	0.395
0.692	0.300	0.440
0.710	0.160	0.468
0.645	0.250	0.409
0.683	0.200	0.451
0.650	0.250	0.502

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.678 0.025
 MU-LCCK AVERAGE VALUE AND STD. DEVIATION : 0.444 0.039


000184

000180

AVERAGE OF FILE 171 FOR 6 RECORDS. TIRE C1 WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.16	8169.8	737.0
0.04	0.25	18012.5	1150.8
0.06	0.32	27213.7	1476.6
0.08	0.36	33075.3	1644.6
0.10	0.39	33979.0	1752.6
0.12	0.40	36149.2	1816.8
0.14	0.40	36383.3	1840.2
0.16	0.41	36905.8	1857.7
0.18	0.41	37565.0	1873.7
0.20	0.41	38290.2	1886.6
0.25	0.41	40623.2	1900.3
0.30	0.41	43828.2	1900.5
0.35	0.41	45950.9	1884.3
0.40	0.40	47654.5	1856.6
0.45	0.39	49613.3	1822.4
0.50	0.39	51357.4	1800.8
0.55	0.39	53005.3	1782.1
0.60	0.38	54846.6	1757.1
0.65	0.37	56985.4	1719.8
0.70	0.36	57820.8	1674.3
0.75	0.35	55043.9	1632.4
0.80	0.34	50105.8	1589.7
0.85	0.33	43883.5	1540.9
0.90	0.32	36988.8	1475.7
0.95	0.31	27730.5	1411.9
1.00	0.27	20458.3	1234.0

TIRE C1 WFL CONCRETE (TRC)

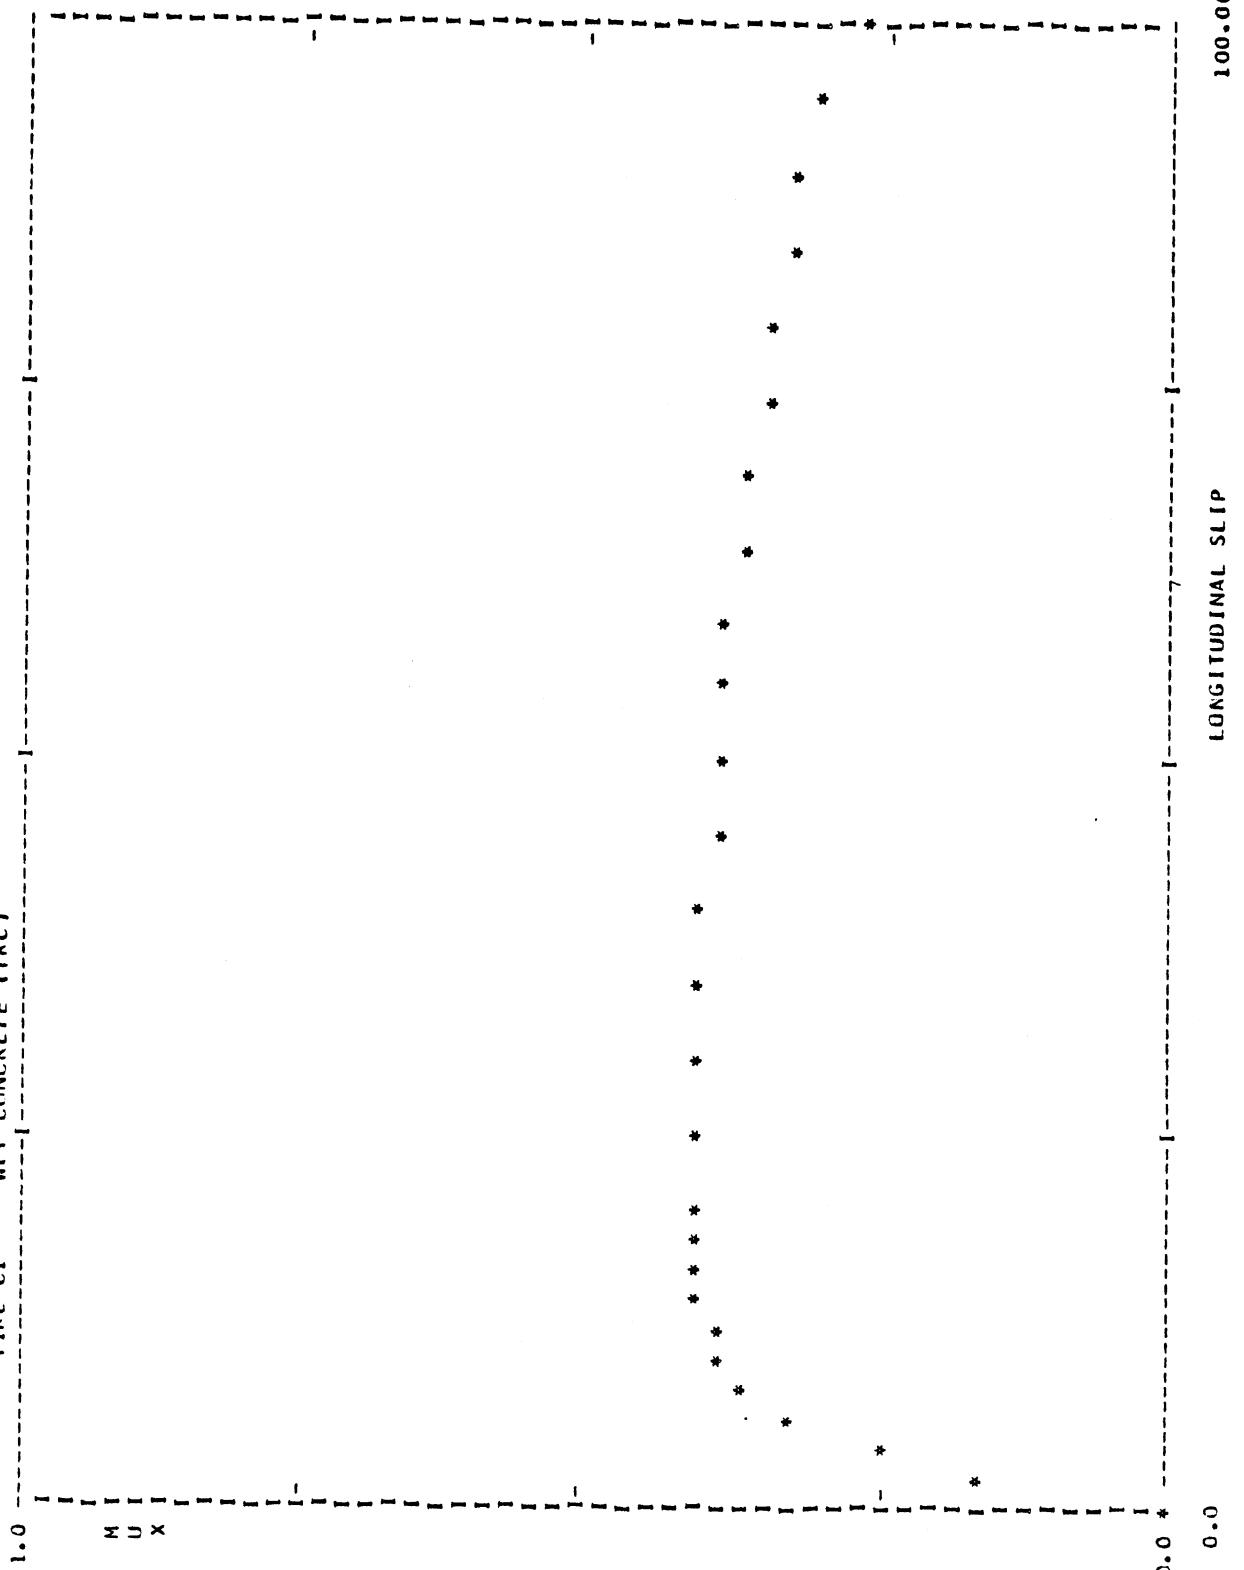

000186

FZ = 4744.2 VEL = 40.0 MULOCK = 0.27 MUPEAK = 0.41 RATIO = 1.53 A-D FILE 171 NWFILE 50 SAMPLE 151

MU-PEAK	SLIP@PEAK	MU-LOCK
0.415	0.350	0.234
0.401	0.320	0.261
0.462	0.160	0.292
0.503	0.300	0.241
0.345	0.200	0.254
0.421	0.550	0.312

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.425 0.054
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.266 0.030

000187

00010000

** A-D FILE 172


NEW FILE 51

TEST SAMPLE152 **

AVERAGE OF FILE 172 FOR 6 RECORDS.

TIRE C1 WET CONCRETE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.16	10577.7	716.7
0.04	0.25	23254.7	1147.0
0.06	0.29	26913.4	1300.7
0.08	0.30	31252.7	1375.7
0.10	0.31	32884.9	1432.4
0.12	0.32	34026.6	1478.5
0.14	0.33	35929.2	1525.1
0.16	0.34	38049.2	1564.9
0.18	0.35	39383.1	1584.1
0.20	0.35	39228.7	1596.3
0.25	0.35	38129.0	1602.0
0.30	0.35	38139.0	1579.6
0.35	0.35	38283.7	1548.3
0.40	0.34	40134.0	1521.3
0.45	0.34	41722.6	1501.3
0.50	0.33	42747.8	1480.6
0.55	0.33	43588.7	1459.5
0.60	0.32	44369.1	1437.5
0.65	0.31	45114.1	1416.9
0.70	0.31	46128.3	1387.2
0.75	0.30	45182.5	1350.8
0.80	0.29	41238.8	1312.7
0.85	0.28	33865.3	1272.2
0.90	0.26	27186.9	1209.1
0.95	0.25	20457.3	1138.6
1.00	0.21	14812.5	980.5

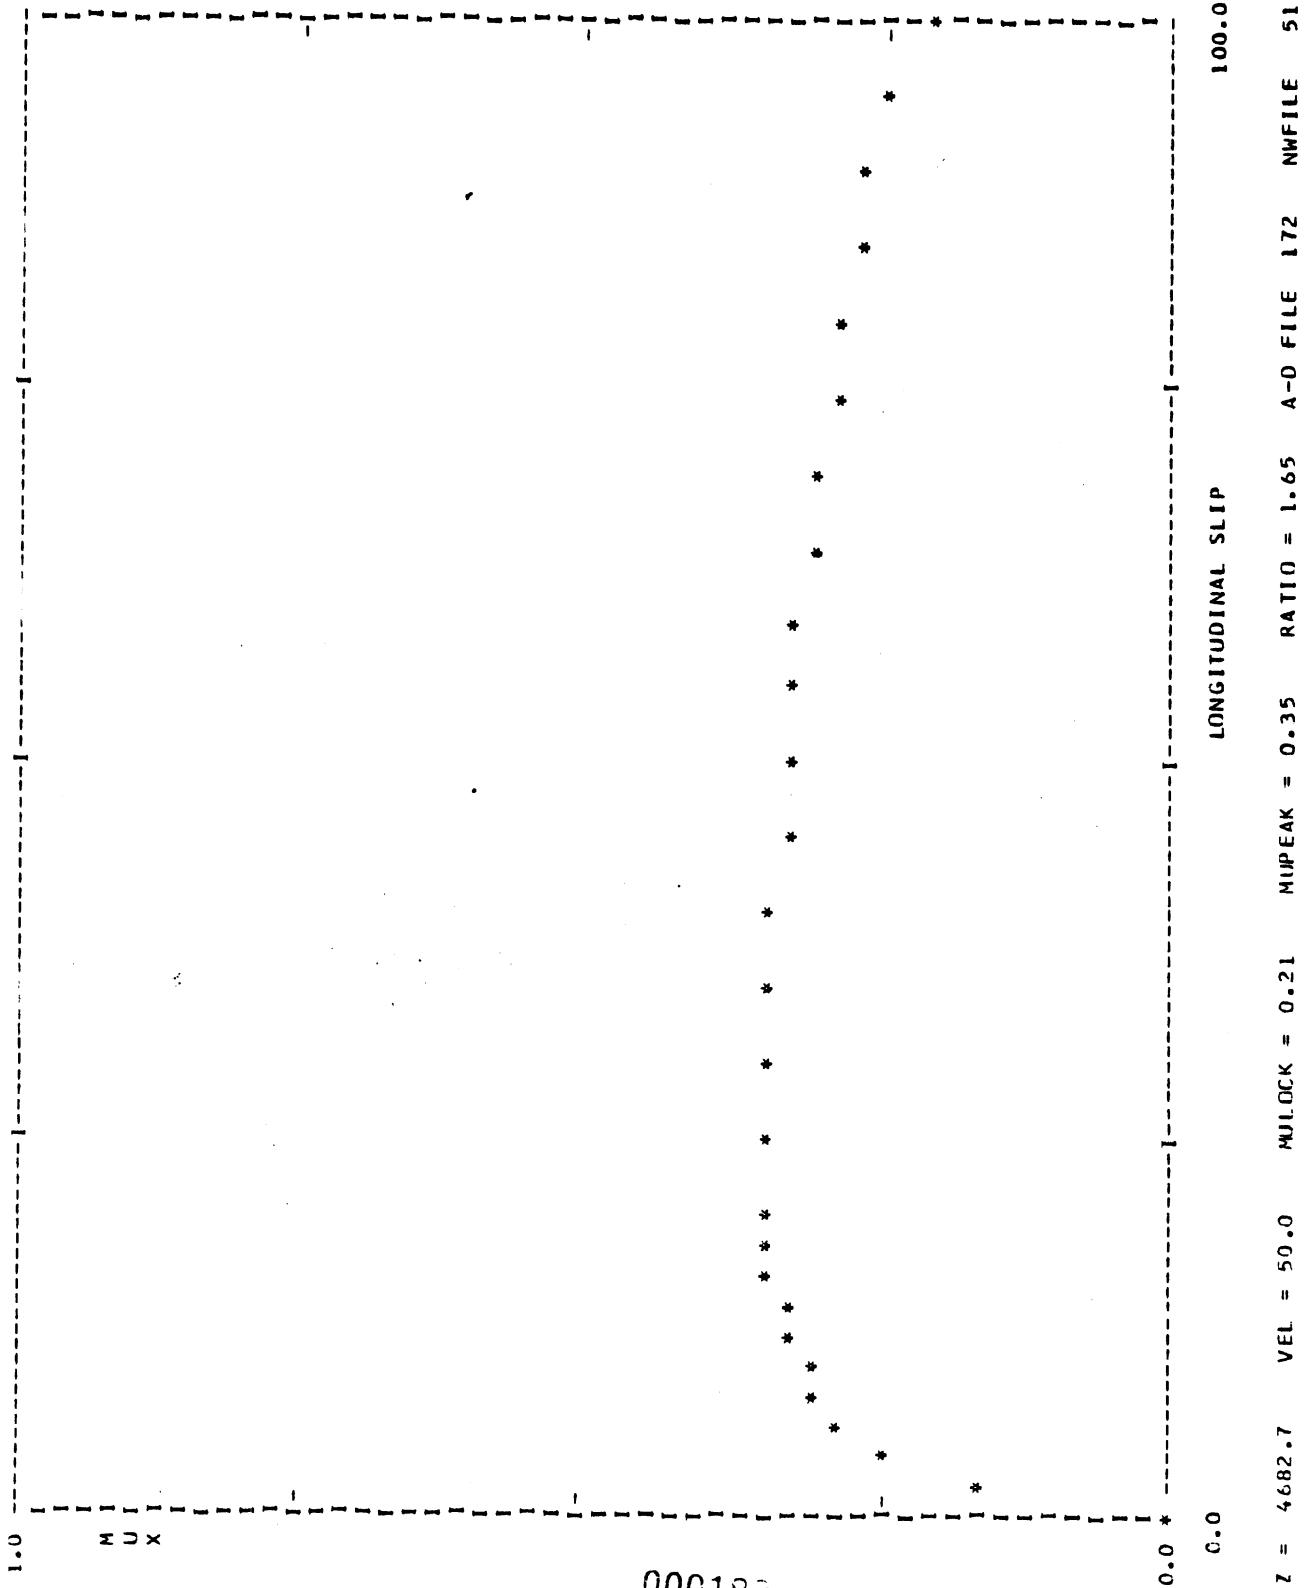


MU-PEAK	SLIPPERY	MU-LOCK
0.327	0.250	0.219
0.349	0.200	0.202
0.428	0.350	0.225
0.334	0.300	0.201
0.330	0.180	0.204
0.345	0.450	0.204

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.352 0.038
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.209 0.010

000190

SLIP	AVERAGE OF FILE 179 FOR 7 RECORDS.			TIRE NHTSA WET JENNITE (TRC)		
	MUX	TORQUE	FX	MUX	LOAD = 4743.4	VEL = 20 MPH.
0.0	0.00	0.0	0.0	0.0		
0.02	0.18	22600.5	808.0			
0.04	0.27	38406.9	1252.8			
0.06	0.33	39896.1	1499.7			
0.08	0.36	41146.3	1677.4			
0.10	0.39	43649.9	1769.4			
0.12	0.40	44890.6	1862.7			
0.14	0.43	45972.6	1871.8			
0.16	0.41	47134.3	1878.0			
0.18	0.40	47841.7	1873.4			
0.20	0.40	48682.4	1858.9			
0.25	0.39	49921.4	1807.6			
0.30	0.38	50427.9	1752.8			
0.35	0.37	50722.1	1699.6			
0.40	0.36	51096.1	1646.5			
0.45	0.34	51541.6	1594.3			
0.50	0.33	52106.5	1539.7			
0.55	0.32	51938.8	1488.0			
0.60	0.31	51399.4	1437.3			
0.65	0.30	49203.0	1389.1			
0.70	0.29	46348.8	1341.8			
0.75	0.28	42834.5	1298.1			
0.80	0.27	39790.6	1249.5			
0.85	0.26	36435.8	1193.9			
0.90	0.24	33804.7	1142.1			
0.95	0.23	32162.6	1090.6			
1.00	0.21	30589.3	972.4			

000191

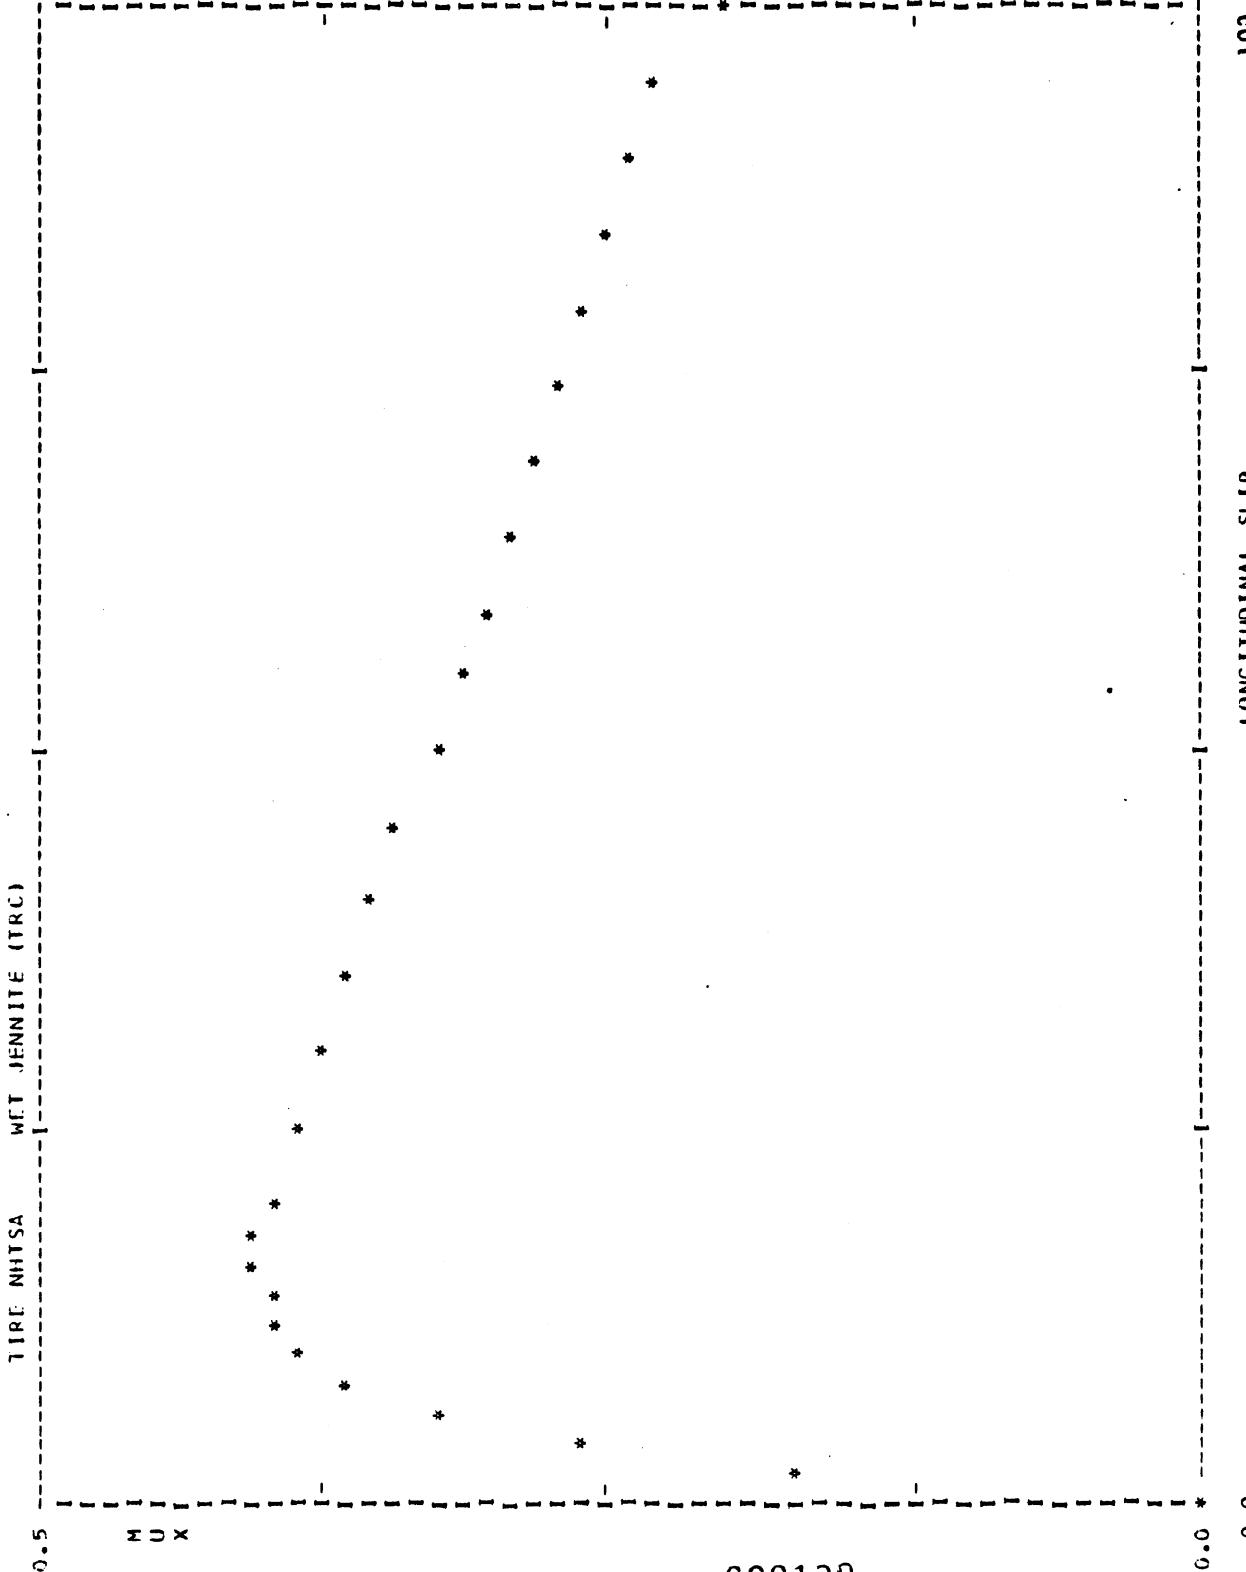

000192

	MU-PEAK	SPLIT-PEAK	MU-LOCK
0.445	0.140	0.238	
0.452	0.200	0.211	
0.393	0.140	0.207	
0.436	0.120	0.192	
0.308	0.100	0.154	
0.405	0.200	0.248	
0.416	0.120	0.186	

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.408 0.049
MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.205 0.032

000193

861000


** A-D FILE 180 NEW FILE 53 TEST SAMPLE156 **

AVERAGE OF FILE 180 FOR 7 RECORDS. TIRE NHTSA WET JENNITE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.18	12352.8	814.9
0.04	0.25	14610.4	1126.9
0.06	0.29	23452.5	1316.4
0.08	0.30	28164.9	1389.5
0.10	0.31	32480.9	1435.0
0.12	0.31	34785.3	1430.8
0.14	0.31	36164.2	1414.1
0.16	0.31	37149.2	1393.6
0.18	0.30	37951.8	1370.8
0.20	0.30	38761.1	1351.5
0.25	0.29	40304.1	1295.5
0.30	0.28	41013.8	1249.5
0.35	0.27	41481.6	1208.8
0.40	0.26	41971.0	1168.4
0.45	0.25	42664.5	1130.7
0.50	0.25	43417.4	1094.1
0.55	0.24	44016.0	1057.3
0.60	0.23	44300.9	1019.4
0.65	0.22	42747.7	981.3
0.70	0.21	39394.4	945.8
0.75	0.21	34855.8	913.5
0.80	0.20	30219.9	883.1
0.85	0.19	26024.7	846.2
0.90	0.18	21939.1	800.9
0.95	0.17	16858.2	764.3
1.00	0.15	-1142.9	678.4

TQAV = -1142.9 LOAD = 4726.2 VEL = ~~40~~ MPH.

MUPEAK = 0.31 MULOCK = 0.15 RATIO = 2.09

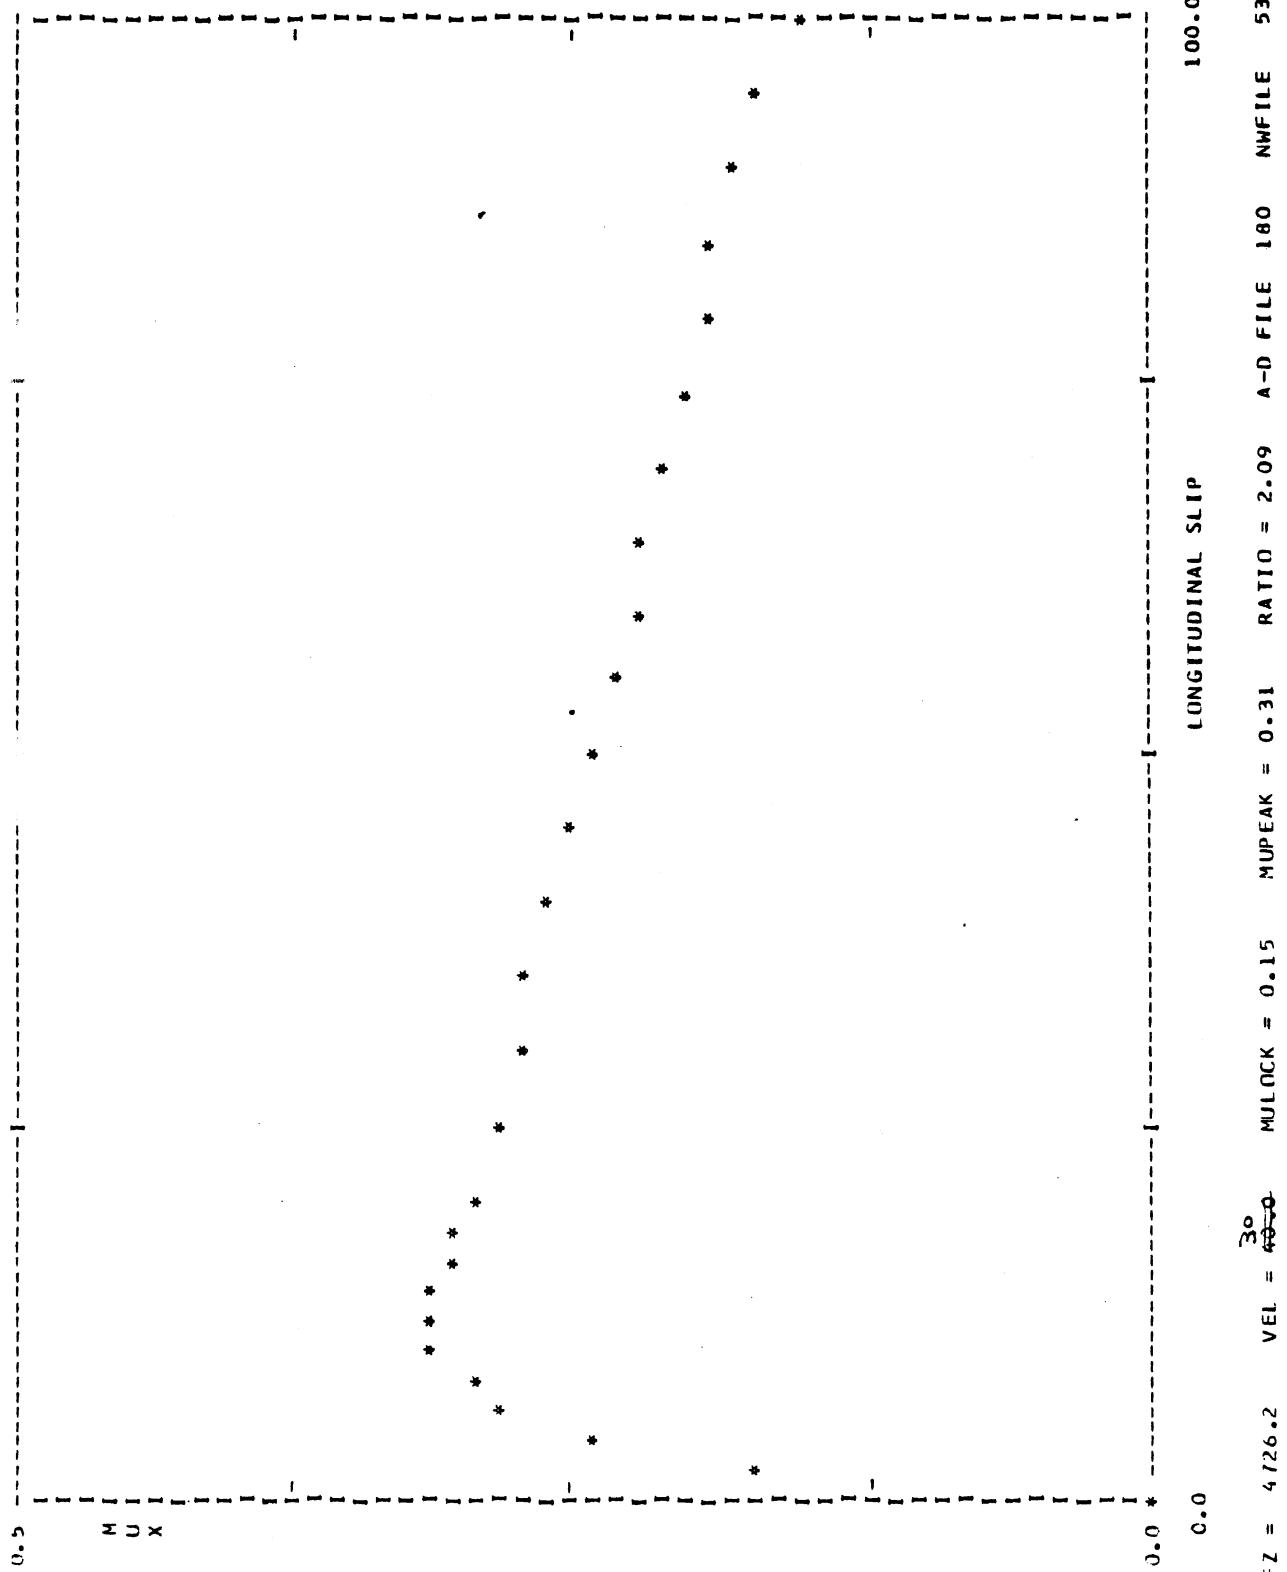

000195

FZ = 4126.2 VEL = ~~30~~ MULOCK = 0.15 MUPEAK = 0.31 RATIO = 2.09 A-D FILE 180 NWFILE 53 SAMPLE 156

MU-PEAK	SLIPPEAK	MU-LOCK
0.369	0.140	0.180
0.270	0.080	0.140
0.335	0.140	0.147
0.314	0.120	0.146
0.379	0.080	0.161
0.240	0.060	0.129
0.295	0.140	0.114


MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.315 0.051
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.145 0.021

000196

SLIP	AVERAGE OF FILE 181 FOR 7 RECORDS.			TIRE PRESSURE			WET JENNITE (TRC)		
	MUX	TOPQUE	FX	MUPEAK	LOAD	VEL	QAV	LOAD	RATIO
0.0	0.60	0.0	0.0	-89356.4	1076.2				
0.02	0.17	-78469.8	1640.2						
0.04	0.26	-71000.1	1865.7						
0.06	0.30	-73088.4	2099.5						
0.08	0.34	-76147.7	2188.3						
0.10	0.35	-75850.2	2221.0						
0.12	0.36	-72590.4	2215.8						
0.14	0.36	-74111.0	2229.3						
0.16	0.36	-71235.0	2185.5						
0.18	0.36	-69135.6	2157.2						
0.20	0.35	-65414.4	2079.4						
0.25	0.34	-62133.3	2005.8						
0.30	0.33	-59778.0	1932.1						
0.35	0.32	-57521.1	1864.6						
0.40	0.31	-55488.0	1798.6						
0.45	0.30	-53907.8	1735.8						
0.50	0.29	-53635.2	1673.4						
0.55	0.28	-53667.4	1615.6						
0.60	0.27	-55714.2	1562.5						
0.65	0.26	-59733.1	1512.5						
0.70	0.26	-63756.3	1463.0						
0.75	0.25	-67582.3	1408.5						
0.80	0.24	-71352.0	1347.3						
0.85	0.23	-74804.3	1294.0						
0.90	0.22	-75382.3	1244.1						
0.95	0.21	-79964.2	1174.7						
1.00	0.20								

000197

TIRE NH TSA WFT JENNITE (TRC)

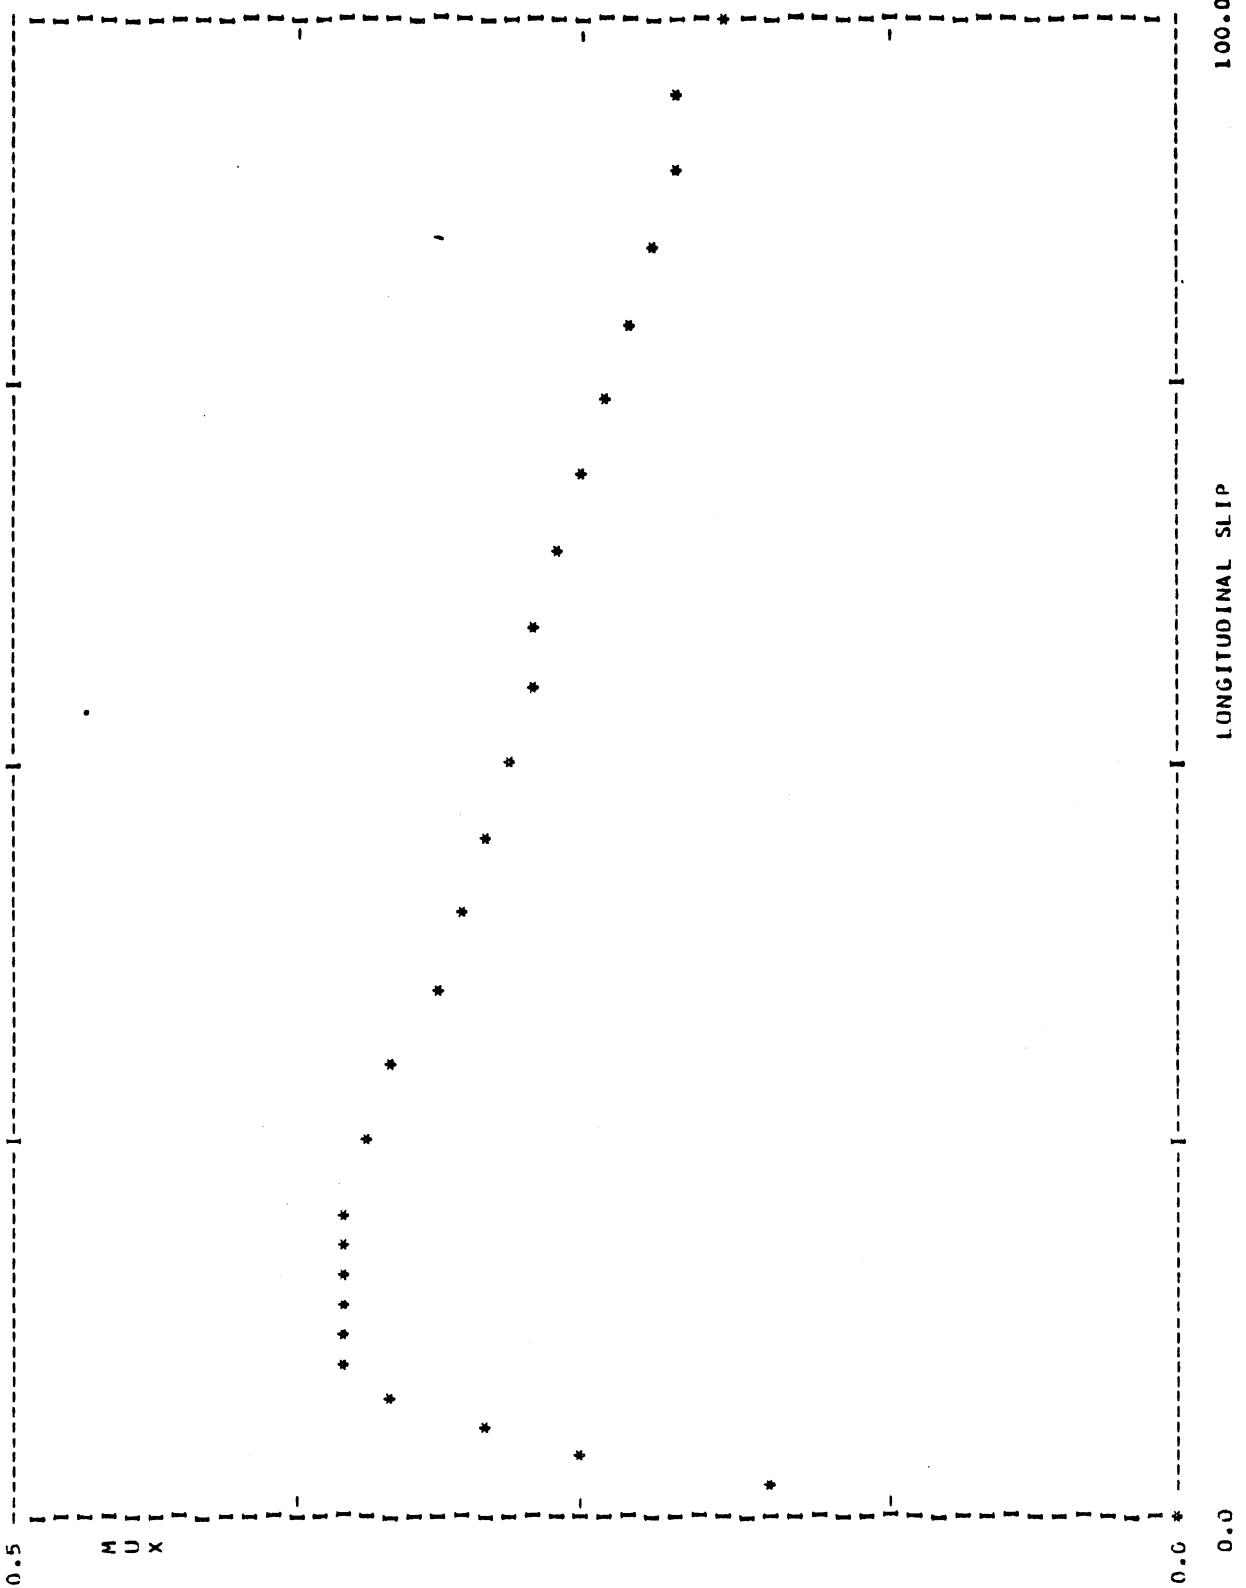

00019c

FZ = 6197.1 VFL = $\frac{2.0}{36.0}$ MULOCK = 0.20 MUPEAK = 0.36 RATIO = 1.83 A-D FILE 181 NWFILE 54 SAMPLE 157

100.00

LONGITUDINAL SLIP

0.0

MU-PEAK

MU-LOCK

0.392

0.120

0.456

0.160

0.309

0.120

0.389

0.140

0.296

0.160

0.313

0.180

0.355

0.140

0.355

0.174

MU-PEAK AVERAGE VALUE AND STD. DEVIATION :
0.358 0.058

MU-LOCK AVERAGE VALUE AND STD. DEVIATION :
0.193 0.030

000199

000200

** A-D FILE 182

NEW FILE 55


TEST SAMPLE158 **

AVERAGE OF FILE 182 FOR 8 RECORDS.

TIRE NHTSA WET JENNITE (TRC)

SLIP	MUX	TORQUE	FX
0.0	0.00	0.0	0.0
0.02	0.14	-87046.1	850.9
0.04	0.23	-61624.5	1364.4
0.06	0.29	-55750.0	1754.4
0.08	0.30	-56453.0	1834.6
0.10	0.30	-54289.7	1858.3
0.12	0.30	-52424.5	1868.3
0.14	0.30	-51993.0	1865.2
0.16	0.30	-50375.7	1846.9
0.18	0.30	-48247.8	1826.1
0.20	0.29	-46631.9	1801.5
0.25	0.28	-45117.2	1734.4
0.30	0.27	-44959.9	1666.0
0.35	0.26	-44924.1	1600.9
0.40	0.25	-44611.4	1533.4
0.45	0.24	-44547.8	1470.9
0.50	0.23	-44782.4	1409.1
0.55	0.23	-45420.2	1351.6
0.60	0.22	-47500.4	1298.4
0.65	0.21	-51632.2	1249.1
0.70	0.20	-57289.9	1203.6
0.75	0.20	-63714.0	1161.8
0.80	0.19	-70207.8	1120.6
0.85	0.18	-76706.4	1073.5
0.90	0.17	-82789.2	1022.9
0.95	0.17	-86090.1	983.6
1.00	0.14	-87234.3	833.6


TQAV = -87234.3 LOAD = 6207.1 VEL = ~~4000~~³⁰ MPH.
 MUPEAK = 0.30 MULOCK = 0.14 RATIO = 2.19

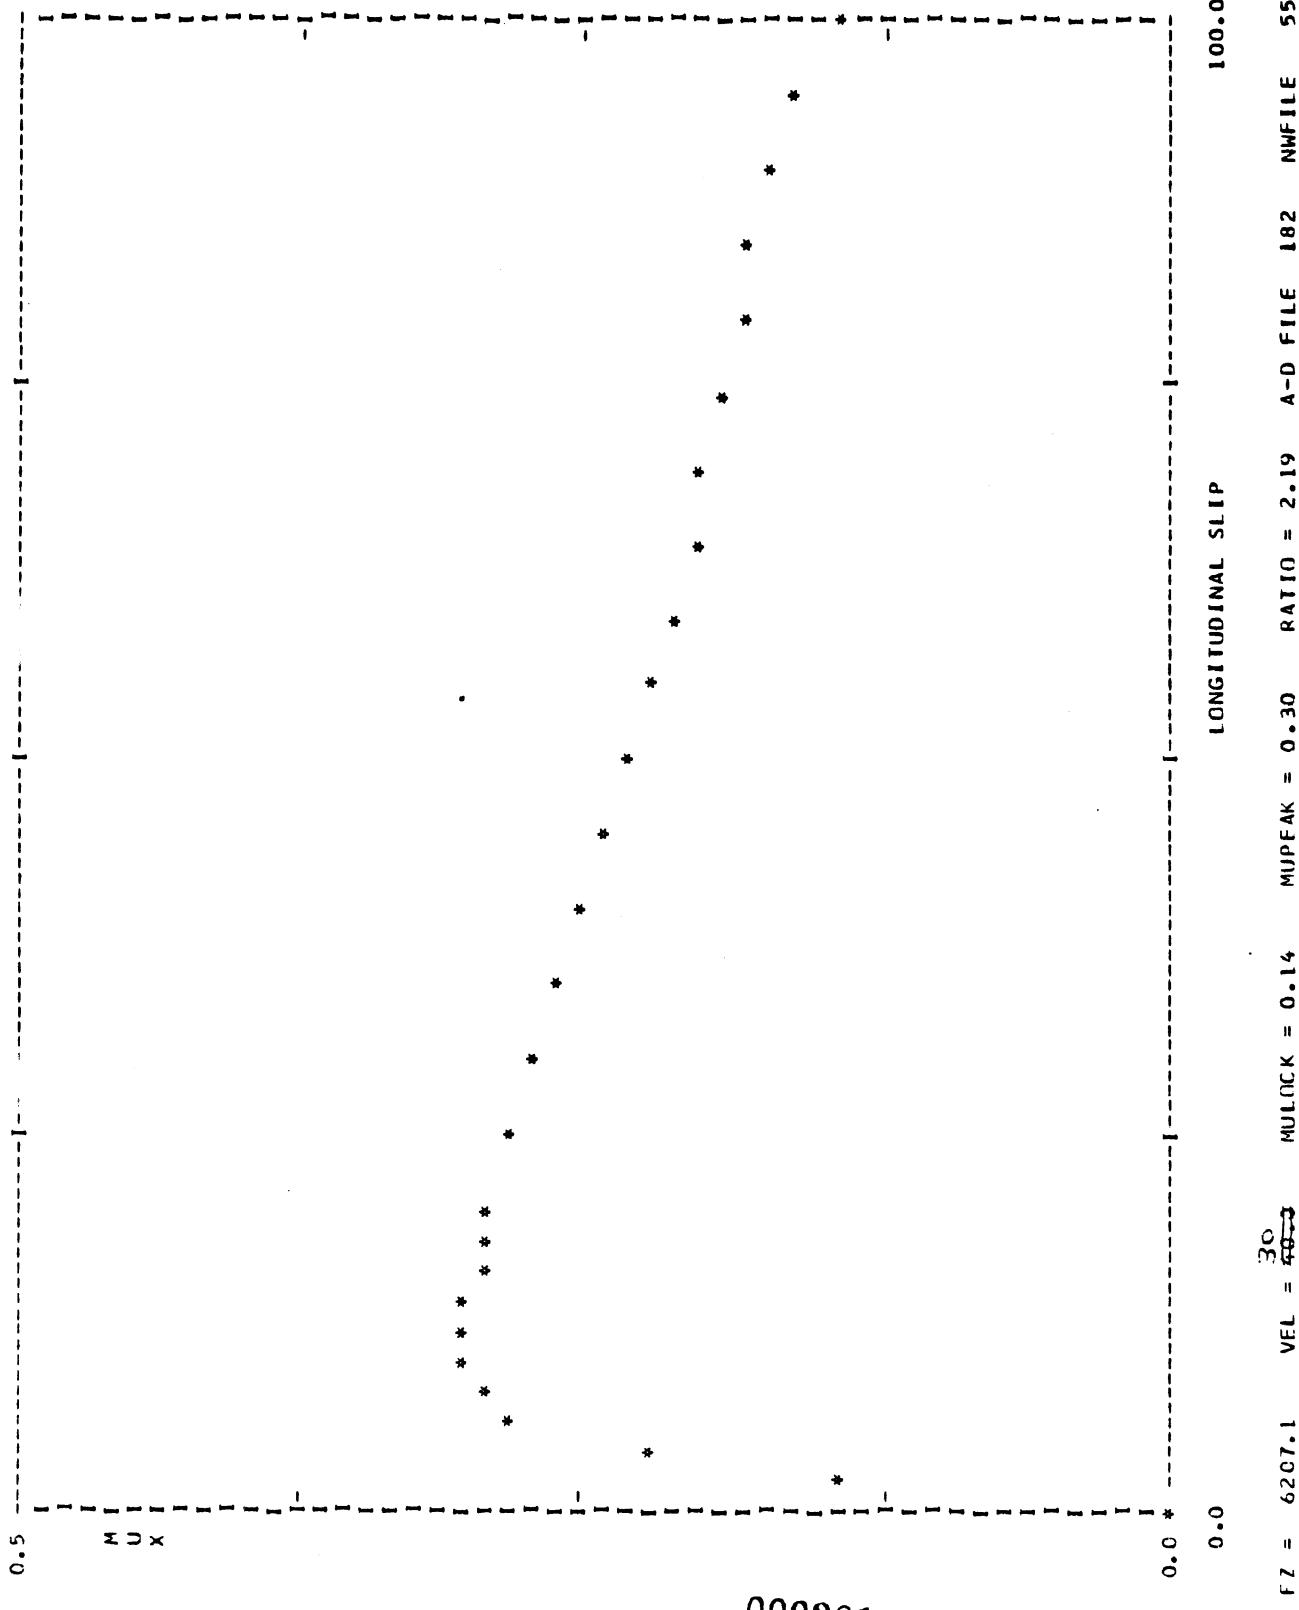

FZ = 6207.1 VEL = 30 MULTICK = 0.14 MUPFAK = 0.30 RATIO = 2.19 A-D FILE 182 NMFILE 55 SAMPLE 158

	MU-PEAK	SLIP@PEAK	MU-LOCK
(0.300	0.120	0.147
)	0.318	0.120	0.117
(0.291	0.080	0.136
)	0.294	0.080	0.127
(0.324	0.250	0.147
)	0.330	0.140	0.140
(0.353	0.120	0.135
)	0.260	0.060	0.124

MU-PEAK AVERAGE VALUE AND STD. DEVIATION : 0.309 0.029
 MU-LOCK AVERAGE VALUE AND STD. DEVIATION : 0.134 0.011

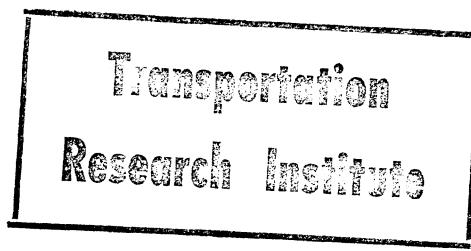

000202